

The Pseudogap Challenge: Understanding the ab-plane AC Conductivity below T_c Andrew Iyengar¹, Jelena Stajic¹, Ying-Jer Kao², K. Levin¹¹ James Franck Institute and Department of Physics,
University of Chicago, Chicago, Illinois 60637 and² Department of Physics, University of Waterloo, Waterloo, ON, N2L3G1, Canada
(Dated: March 22, 2024)

We establish that the cuprate pseudogap plays a crucial role in the ab-plane optical conductivity $\sigma_1(\omega; T)$ for temperatures $T < T_c$. The pseudogap signatures in $\sigma_1(\omega; T)$ associated with competing proposals of a "hidden order" and "superconducting" origin for the $d_{x^2-y^2}$ pseudogap are found to differ in their qualitative $\omega; T$ dependences. For the latter case, as T increases from 0, excess low ω weight appears; moreover, a much wider range of ω contributes to form the condensate. We discuss these theories in light of current experiments.

While a major fraction of the cuprate phase diagram has been found to be associated with a pseudogap there is still no definitive explanation for the origin of this anomalous phase. Here normal state thermodynamic and transport properties exhibit an excitation gap of d-wave symmetry (with onset at temperature T^*) which appears to be continuous with the excitation gap of the superconducting phase (with onset at $T_c - T^*$). Theoretical schools for addressing this phenomenon fall roughly into two camps in which this pseudogap derives from (i.e., is "intrinsic") or is independent of (i.e., "extrinsic" to) the superconductivity. Despite its clear presence in thermodynamic and transport data, mysteriously, experiments¹ on the in-plane electrodynamics show few conspicuous signatures of the pseudogap. In this paper we demonstrate how, in both theoretical schools, the pseudogap enters as a rearrangement, relative to BCS predictions, of spectral weight in $\text{Re } \sigma_1(\omega) = \frac{1}{2} \sigma_2(\omega)$. Moreover, we suggest that it is the width of the range of frequencies contributing to form the condensate which provides a most effective criterion, both for discriminating between theoretical approaches, and for direct comparison with the data. The experimental observation^{2,3} that (in the underdoped regime), relatively high ω participate in the condensate poses a serious challenge for both strict BCS theory and the extrinsic school.

Strict BCS theory is overly constrained because it contains a single energy scale. Nevertheless, we argue here that a mean field theoretic approach is appropriate because of (1) the notable similarity of many (but not all) measured properties to their BCS predictions, (2) the very narrow critical regime, and (3) the large separation between T^* and T_c (which appears to be too big to derive from fluctuations around strict BCS theory). Moreover, the electromagnetic response of the superconducting state can be readily formulated at this generalized mean field level. In the standard formulation, the imaginary axis conductivity is written as $\sigma_{ab}(Q) = \frac{e^2}{i(i!n)} [\mathbb{P}_{ab}(Q) - n_{ab}]$ where $Q = (q; i!n)$. We define Green's functions

$$G(K) = \frac{i!n^0 + \epsilon_k}{i!n^2 + E_k^2} \quad F(K) = \frac{\epsilon_k}{i!n^2 + E_k^2} \quad (1)$$

$$E_k^2 = (\epsilon_k)^2 + (\epsilon_k)^2 \quad (2)$$

Here ϵ_k refers to a generalized "band structure", which may differ from the bare hopping dispersion $\epsilon_k = 2t(\cos k_x + \cos k_y)$, whereas ϵ_k refers to a generalized "gap" parameter, whose k -dependence we separate as $\epsilon_k = \epsilon'_k$ with $\epsilon'_k = \cos(k_x) - \cos(k_y)$ for d-wave pairing.

The quasiparticle velocity $v_a = \partial_{\epsilon_k}$ leads to

$$n_{ab} = \frac{1}{2} \sum_K [\partial_{\epsilon_k} \partial_{\epsilon_k} (FF + GG) + 2\partial_{\epsilon_k} \partial_{\epsilon_k} FG] \quad (3)$$

BCS theory predicts the response $\mathbb{P}_{ab}^{BCS}(Q) = \frac{1}{2} \sum_K \partial_{\epsilon_k} \partial_{\epsilon_k} (GG + FF)$ (where $G = G(K)$, $G_+ = G(K + Q)$, and similarly for F), so that the general expression for the superfluid density $(n_s)_{ab} = n_{ab} - \mathbb{P}_{ab}(0)$ reduces in the BCS case (omitting tensor indices) to

$$n_s^{BCS} = 4 \sum_K (\partial_{\epsilon_k} \partial_{\epsilon_k} FF + \partial_{\epsilon_k} \partial_{\epsilon_k} FG) \quad (4)$$

Since in BCS theory there is only one energy scale, one identifies $\epsilon_{sc} = \epsilon_c$, and n_s vanishes only when the excitation gap vanishes. More correctly, it should be clear that the superfluid density must necessarily reflect the superconducting order parameter ϵ_{sc} which may be distinguished from the total excitation gap ϵ_c , so that $n_s(T) \propto (\epsilon_{sc}(T))^2$. This serves to underline a major shortcoming⁴ of strict BCS theory.

The simplest mean field pseudogap approach (case (i)) is referred to as "rescaled BCS theory"⁵. Here, the single energy scale framework of BCS theory $\epsilon_{sc} = \epsilon_c$ is preserved while modifying the response by a frequency-independent factor as $\mathbb{P}_{ab} = (T) \mathbb{P}_{ab}^{BCS}$. This enhancement causes n_s to vanish at T_c lower than T^* . The factor (T) is related to the suppression of the superfluid $n_s = f(T) n_s^{BCS}$ by the sum rule constraint $(T) = \frac{n}{n_s^{BCS}(T)} (1 - f(T)) + f(T)$, with $f(T)$ chosen to vanish at T_c and fitted to $n_s(T)$. The microscopic physics of this otherwise phenomenological scheme is presumably connected to the approach of Lee and Wen⁶; may also reflect the renormalization of electron charge as can occur

in Fermi-liquid based approaches to the superconducting state⁷. In overdoped samples with $T_c = T^*$, BCS theory works well, i.e., $f(T) = 1$.

Alternatively, one may argue that $\epsilon_{sc} \ll \epsilon_{pg}$, so that at the mean-field level, the gap and the order parameter are distinct. The extrinsic school introduces a pseudogap ϵ_{pg} directly into the quasi-particle bandstructure ϵ_k and defines ϵ_{sc} in the above mean-field formalism, yielding n_s / n_{sc}^2 via Eq. (4). Below T_c , Eq. (2) shows that in this school the dispersion of the fermionic quasi-particles has no simply defined BCS-like excitation gap. However, in this paper (as elsewhere⁸) we will assume that one can define a meaningful excitation gap for the extrinsic case as $\epsilon_k = \sqrt{(\epsilon_k^{pg})^2 + (\epsilon_k^{sc})^2}$. We implement this picture by introducing an additional order parameter which breaks translation symmetry, leading to two bands $\epsilon_k = \sqrt{\epsilon_k^2 + (\epsilon_k^{pg})^2}$. The precise superfluid density expression is slightly more complicated than Eq. (4) due to interband effects.⁹ While we calculate P_{ab} for a d-density wave^{10,11} (DDW) here, we argue that our results are generic, applying to other extrinsic pseudogap theories.^{8,12} The Green's functions F ; G for the two bands are obtained from Eq. (1), (2) by replacing ϵ_k with ϵ_k . For the d-density-wave/superconducting coexistent state, we find

$$P_{ab}(Q) = \frac{1}{2} \sum_{\mathbf{k}; =} \frac{\hbar}{v_a^{(1)} v_b^{(1)}} (G G_+ + F F_+) \quad (5)$$

$$+ \frac{1}{2} \sum_{\mathbf{k}} \frac{\hbar}{v_a^{(2)} v_b^{(2)}} (G G_+ + F F_+)$$

where momentum is summed over the half Brillouin zone, i is the band index, $v_a^{(1)} = \partial \epsilon_k / \partial k$, and $v_a^{(2)} = \partial \epsilon_k^{pg} / \partial k$.

Finally, we consider a third mean-field alternative (iii) in which the pseudogap is intrinsically connected with the superconductivity¹³. In this picture ϵ_{pg} is associated with a stronger-than-BCS attractive interaction, so that (finite momentum) pairs form at a higher temperature T^* than that at which they Bose condense (T_c). Here the pseudogap enters on the same footing as the superconducting order parameter, and the fermionic dispersion is given by Eq. (2) with the value of ϵ_k assigned to be ϵ_k , and $\epsilon_k = \epsilon_k$. In this last approach, which has a detailed microscopic basis¹³, the superfluid density has the form

$$n_s = [n_{sc}^2] n_s^{BCS}; \quad \epsilon_{pg} = \sqrt{(\epsilon_{pg})^2 + (\epsilon_{sc})^2} \quad (6)$$

The corresponding electromagnetic response is the sum of fermionic (BCS, with full gap $\epsilon(T)$) and bosonic contributions

$$P_{ab}(Q) = \frac{1}{2} \sum_{\mathbf{k}} \epsilon_a \epsilon_b \epsilon_k (F F_+ + G G_+) \quad (7)$$

$$+ A \sum_{\mathbf{p}} \epsilon_a \epsilon_b \epsilon_p t^{pg}(p) t^{pg}(p+Q)$$

Here we have approximated¹⁴ the second bosonic term, which originates from an Aslamazov-Larkin diagram s¹⁵.

It represents the coupling of radiation to uncondensed pairs of charge-2e responsible for suppressing n_s relative to n_s^{BCS} . The pairs have a propagator $t_{pg}(P)$, which at small P can be parameterized as $t_{pg}(P) = (1 + i) \epsilon_p$ (after continuation to real frequency ω). Here $\epsilon_p = p^2/2M$ and the pair chemical potential is zero for $T < T_c$. While our microscopic theory¹⁶ yields the pair mass and lifetime parameter associated with ϵ , the diagrammatic calculations can be avoided by borrowing from general TDGL formulations¹⁷ which describe the hydrodynamics of non-condensed bosons. In particular, the optical sum rule constrains the conductivity spectral weight of this boson contribution to be $n_s^{boson} = [n_{pg}^2 = n_s^{BCS}]^2$, determining the prefactor A .

In the intrinsic school the condensate (ϵ_{sc}) grows with decreasing T at the expense of ϵ_{pg} as the fraction of (quasi-ideal Bose gas) finite momentum pair excitations decreases. Precisely at $T = 0$, ϵ_{pg} vanishes and the ground state is given by the BCS generalization first proposed in Ref. 18. By contrast, in the extrinsic model ϵ_{pg} is relatively T independent below T_c in the underdoped regime. One can summarize: to a good approximation, for the intrinsic model¹³ (case (iii)) $n_{pg}^2(T) = n_{pg}^2(T_c) (T/T_c)^{3/2}$, whereas for the extrinsic model (case (ii)) at low doping $n_{pg}^2(T) = n_{pg}^2(T_c)$.

The following calculations for $\epsilon_1(\omega)$ address an underdoped (UD) and a slightly over-doped (OD) cuprate with hole concentration x quantified by excitation gap ratio $(T_c/T^*) = (0)$ which assumes the values 0.99 and 0.5 respectively. This corresponds roughly to $x = 0.06$ and $x = 0.17$. The two quantities $n_s(0) = (0)$ and T_c/T^* were computed within each microscopic theory and roughly fit to experiment. We presume that the temperature dependence of the full excitation gap for $T < T_c$ is given by the BCS d-wave result, so that $(0)/T^*$ is a universal number, as seems to be the case experimentally¹⁹. We include scattering from random non-magnetic impurities by renormalizing F and G in the above formulae,²⁰ and, for simplicity, compute the bosonic term in Eq (7) using standard TDGL results¹⁷. Following conventional procedures,²¹ we pre-calculate a table of self-energies on the real frequency axis. We handle the complicated behavior of energy and k integrands using automatic 1d or 2d adaptive quadrature, determining ϵ_1 to 1% relative accuracy. While we have explored both Born and unitary limits, the computations are more tractable in the unitary limit, which we consider here with scattering potential $u(r)$, $u = 2t \delta(r)$, and with 0.01 impurities per unit cell. Our numerical calculations (1) conserve the integrated density of states, (2) conserve conductivity spectral weight, and (3) yield²² $\epsilon_1(T = 0; \omega = 0) = (2\pi)^{-1}$. Here and throughout we use conductance units $e^2/h = 1$.

In the insets of Figures 1a and 2a are plotted the normalized superfluid densities for the intrinsic (iii) and extrinsic cases (ii) in the underdoped regime. The strict "BCS" curves for each case are chosen to have the same excitation gap parameter, so that n_s^{BCS} vanishes at T^* .

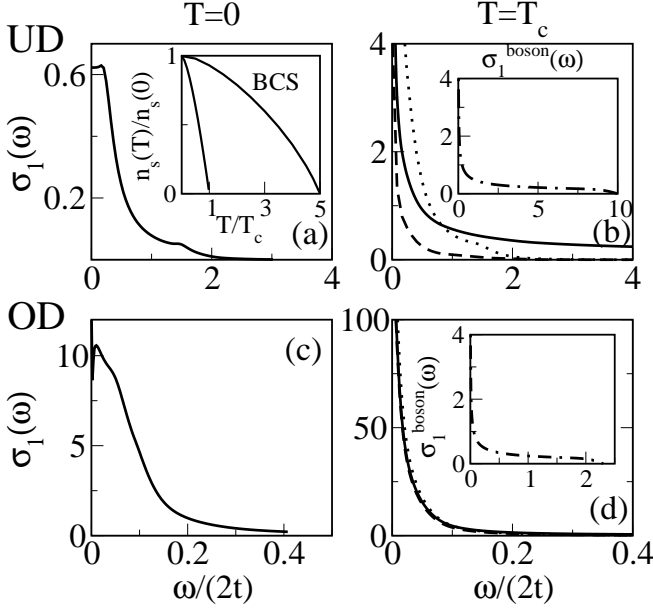


FIG. 1: Real part of ac conductivity for the intrinsic (solid), rescaled BCS (dotted) and strict BCS (dashed) models at underdoped (UD) and slightly overdoped (OD) x at $T = 0$ (1a, 1c) and $T = T_c$ (1b, 1d). Insets plot the corresponding n_s compared to n_s^{BCS} (1a) and the bosonic contribution to σ_1 (1b).

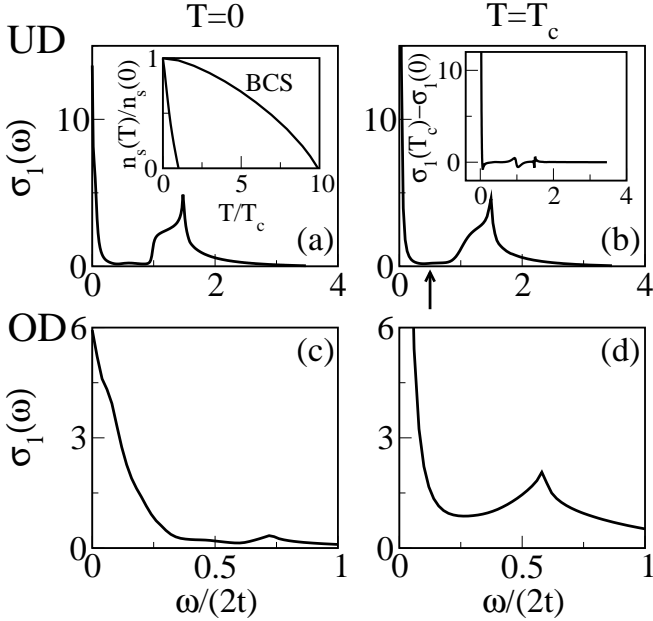


FIG. 2: $\sigma_1(\omega)$ for the extrinsic pseudogap at underdoped (UD) and slightly overdoped (OD) x at $T = 0$ (2a, 2c) and $T = T_c$ (2b, 2d). The arrow indicates $\sigma_1(0) = \sigma_{pg}(T_c)$.

It is clear from the above discussion that the calculated superfluid density is depressed and vanishes at a lower temperature (T_c) than its BCS counterpart. Sum rule

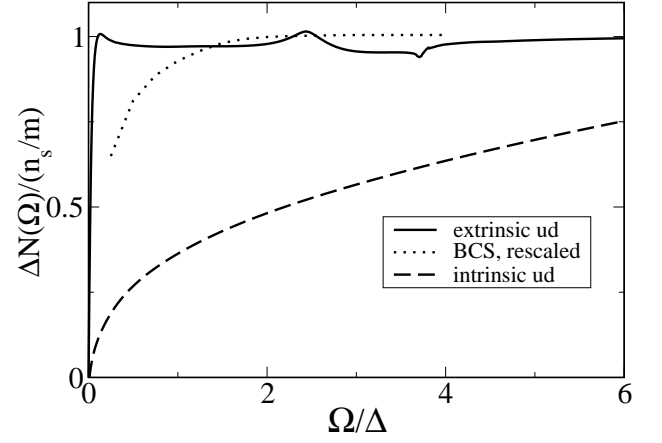


FIG. 3: Partial integral of condensing spectral weight, normalized by the total, for the three pseudogap models (underdoped).

considerations thus indicate that there must be excess spectral weight in $\sigma_1(\omega; T)$ at $\omega \neq 0$ associated with pseudogap effects.

The frequency distribution of this excess spectral weight can be inferred from the plots in Figures 1 and 2 which show $\sigma_1(\omega)$ for the UD and OD hole concentrations at $T = 0$ and $T = T_c$ in the intrinsic (solid lines) and extrinsic cases respectively. In Figures 1a, and 1c the rescaled BCS model (dotted lines) coincides with the solid curves at $T = 0$ due to the complete condensation of the pseudogap. It is clear that in the intrinsic case the added pseudogap weight (present at any $T \neq 0$) appears at very low ω , varying as $\omega \propto T$, as well as at very high ω where it introduces a long tail associated with the fermion induced damping of non-condensed pairs. Interactions with the fermionic two particle continuum (which itself is gapped) constrains the bosonic lifetime. By contrast, in the extrinsic case the pseudogap is associated with a secondary maximum which appears at the energy scale $\omega_{pg}(T_c) \approx 0$. This arises from interband effects¹¹ with threshold at $\omega = 2$.

It should be noted that a direct comparison of $\sigma_1(\omega)$ between theory and experiment is complicated because the origin of the so-called mid-infrared spectral weight is uncertain²³, and because the ratio of the $T = 0$ condensate to the total integrated spectral weight (at T_c) is anomalously small (20% or less)²³. Thus, we focus on the difference curves, and their associated integrals. We introduce the partially integrated spectral weight $N(\omega) = \frac{1}{R} \int_0^\omega [\sigma_1(\omega'; T_c) - \sigma_1(\omega'; 0)] d\omega'$, which is plotted in Figure 3 for the underdoped regime. This plot indicates which frequencies are required to account for the superfluid density in both the extrinsic and intrinsic cases.

Strikingly, the intrinsic pseudogap and rescaled BCS theories both show substantial contributions to the condensate up to relatively high frequencies of order $\omega(0) \approx 960 \text{ cm}^{-1}$ or more. By contrast, in the extrin-

sic school, the condensate derives from a much narrower range of frequencies. Since interband conductivity terms make a negligible condensate contribution, this observation holds even for extrinsic theories which lack interband effects^{8,12}. An analogous narrowing of condensate frequencies occurs in strict BCS theory at low x when

(T) is properly chosen to be T independent, so that the only relevant energy scales are the much lower T_c and scattering rate.

For $T \sim T_c$, inelastic scattering, which has been ignored in the above calculations, may affect any direct comparison between theory and experiment. This leads to non-monotonic ρ dependences and is expected to be most important in the optimal and over-doped regime, where inelastic effects are strongly T dependent below T_c , reflecting the T dependence of (T) . It follows, similarly, that in the underdoped regime where (T) is constant, inelastic effects should not contribute appreciably to N .

Finally, it can be noted that the only, nevertheless ambiguous²⁴, evidence for a pseudogap appears in the experimental literature¹ via Drude fits to $\rho(\omega)$, where the resulting $1/\rho(\omega)$ is suppressed at frequency $\omega_0 \sim 600 \text{ cm}^{-1}$. Because of its x independence we speculate that ω_0 may reflect a phonon or other boson¹ with coupling modulated by the opening of an excitation gap. Although these secondary pseudogap effects are beyond the scope of this paper, we find here that Drude fits are quite generally problematic for cases (ii) and (iii) discussed here.

In summary, in this paper (i) we have investigated competing proposals for the pseudogap origin and have presented theoretical (and rather generic) mean field expressions for $\rho(\omega)$. (ii) Both major mean field pseudogap schools lead to the prediction that pseudogap ef-

fects must enter as a rearrangement of excess spectral weight (relative to strict BCS theory predictions) in the ac conductivity. For the intrinsic school, there is a rapid growth in ρ_1 with increasing low T , at fixed low frequencies (which may have been observed experimentally²⁵), as well as long high ω tails, (possibly also observed^{2,3}) which tails become more pronounced with increasing T . While for the extrinsic school, there is a transfer of spectral weight from low to high ω . However, here the resulting secondary maximum is present at all $T \sim T_c$ and does not participate in the condensation. Direct comparison with experimental data is made complex by the small integrated spectral weight in the condensate and our neglect of inelastic scattering²³. Therefore, we have focused on the condensing portion of the spectral weight by considering the change in $\rho_1(\omega)$ from 0 to T_c . (iv) We find that when (T) is constant, strict BCS theory cannot account for the relatively high $\rho_1(\omega_0)$ frequency scale associated with the condensate. The extrinsic approach suffers from a similar problem. In an artificial way rescaled BCS theory remedies this weakness. However, the observed high frequency contributions arise naturally in an intrinsic model; their presence reflects the underlying scattering of non-condensed bosons from the two particle fermionic states.

This work was supported by NSF-MRSEC Grant No. DMR-9808595 (A.L., J.S., K.L.) and by NSERC of Canada and Research Corporation (Y.K.). We especially thank Qijun Chen for useful discussions and are grateful to D. Basov, N. Bontemps, J. Carbotte and Shi-Na Tan for multiple conversations, and to W. Putikka and E. Schachinger for consultation regarding numerical techniques.

-
- ¹ A. Puchkov, D. Basov, and T. Timusk, *J. Phys. Condens. Matter* **8**, 10049 (1996).
 - ² H. J. Molegraaf et al., *Science* **295**, 2239 (2002).
 - ³ A. F. Santander-Syro et al., *cond-mat/0111539* (2001).
 - ⁴ J. Stajic et al., *cond-mat/0205497* (2002).
 - ⁵ A. J. Berlinsky, D. A. Bonn, R. Harris, and C. Kallin, *Phys. Rev. B* **61**, 9088 (2000).
 - ⁶ P. A. Lee and X. Wen, *Phys. Rev. Lett.* **78**, 4111 (1997).
 - ⁷ A. M. Ioffe, *cond-mat/0112509* (2001).
 - ⁸ J. W. Loram et al., *Jour. of Superconductivity* **7**, 243 (1994).
 - ⁹ The new order parameter modifies the current operator such that n_{ab} and p_{ab} acquire additional interband terms; the resulting n_s agrees with a result found previously by other means with, however, the sign of interband terms reversed. See Q. Wang, J. H. Han, and D. H. Lee, *Phys. Rev. Lett.* **87**, 077004 (2001).
 - ¹⁰ S. Chakravarty, R. B. Laughlin, D. K. Morr, and C. Nayak, *Phys. Rev. B* **63**, 094503 (2001).
 - ¹¹ X. Yang and C. Nayak, *Phys. Rev. B* **65**, 064523 (2002).
 - ¹² P. Nozières and F. Pistolesi, *Eur. Phys. J. B* **10**, 649 (1999).
 - ¹³ Q. J. Chen, I. Kosztin, B. Janko, and K. Levin, *Phys. Rev. Lett.* **81**, 4708 (1998).
 - ¹⁴ F. Federici and A. Varlamov, *Phys. Rev. B* **55**, 6070 (1997).
 - ¹⁵ The non-BCS terms in the intrinsic pseudogap response arise from vertex contributions of a Zlamazov-Larkin type proportional to ρ_{pg}^2 , or the density of propagating bosonic pairs. See I. Kosztin, Q. J. Chen, Ying-Jer Kao, and K. Levin, *Phys. Rev. B* **61**, 11662 (2000).
 - ¹⁶ I. Kosztin, Q. J. Chen, B. Janko, and K. Levin, *Phys. Rev. B* **58**, R5936 (1998).
 - ¹⁷ H. Schmidt, *Z. für Physik* **336**, 336 (1968).
 - ¹⁸ A. J. Leggett, in *Modern Trends in the Theory of Condensed Matter* (Springer-Verlag, Berlin, 1980), pp. 13{27.
 - ¹⁹ M. Oda et al., *Physica C* **281**, 135 (1997).
 - ²⁰ Y. Kao, A. Iyengar, and K. Levin, *cond-mat/0206004* (2002).
 - ²¹ R. Fehrenbacher, *Phys. Rev. Lett.* **77**, 1849 (1996).
 - ²² P. Lee, *Phys. Rev. Lett.* **71**, 1887 (1993).
 - ²³ H. L. Liu et al., *J. Phys.: Condens. Matter* **11**, 239 (1999).
 - ²⁴ A. F. Santander-Syro et al., *Phys. Rev. Lett.* **88**, 097005 (2002).
 - ²⁵ A. Hosseini et al., *Phys. Rev. B* **60**, 1349 (1999).