

Anisotropic magnetic behavior of $\text{GdBa}_2\text{Cu}_3\text{O}_{6+y}$ single crystalsVladimir N. Narozhnyi^{a; b; 1}, Dieter Eckert^a, Gunter Fuchs^a, Vladimir Nekvasil^c,
Karl-Hartmut Müller^a^aLeibniz-Institut für Festkörper- und Werkstofforschung Dresden, P O Box 270116, D -01171 Dresden, Germany^bInstitute for High Pressure Physics, Russian Academy of Sciences, Troitsk, Moscow Region, 142190, Russia^cInstitute of Physics, Czech Academy of Sciences, Cukrovarnická 10, 16253 Praha 6, Czech Republic

Abstract

Magnetic properties of high-quality Al-free nonsuperconducting $\text{GdBa}_2\text{Cu}_3\text{O}_{6+y}$ single crystals grown by the flux method have been studied. The magnetic anisotropy below the Neel temperature $T_N \approx 2.3$ K corresponds to the direction of Gd^{3+} magnetic moments along the tetragonal c-axis. At $T < T_N$ clear indications of spin- \uparrow spin- \downarrow transitions for $H \parallel c$ have been observed on magnetization curves at $H_{sf} \approx 10$ kOe. Magnetic phase diagrams have been obtained for $H \parallel c$ as well as for $H \parallel ab$. A pronounced anisotropy in the magnetic susceptibility (unexpected for Gd-based compounds) has been found above T_N .

Key words: $\text{GdBa}_2\text{Cu}_3\text{O}_{6+y}$; magnetic anisotropy; spin- \uparrow spin- \downarrow transition; single crystal

Collinear antiferromagnetic ordering was found for $\text{GdBa}_2\text{Cu}_3\text{O}_{6+y}$ (Gd1236) with the Gd magnetic moments directed along the c-axis [1,2]. So far magnetism in Gd1236 single crystals were studied on Al-containing samples [3] or by indirect methods (e.g., NMR [4]). However, the reported results are controversial.

In this work we report on the magnetic properties of high quality Al-free nonsuperconducting Gd1236 single crystals grown in Pt crucibles by the flux method [5]. Atomic absorption spectroscopy has shown that the Pt contamination does not exceed $3 \cdot 10^{-3}$ at.% [6]. To reduce the oxygen concentration the samples were annealed at $T = 600$ C under high vacuum during 4 days. The magnetization M was measured by SQUID magnetometer. The data are compared with the results obtained earlier for $\text{PrBa}_2\text{Cu}_3\text{O}_{7-y}$ (Pr123) [7] as well as for the Gd-sublattice of mixed $\text{Gd}_{1-x}\text{Pr}_x\text{Ba}_2\text{Cu}_3\text{O}_{7-y}$ [(Gd-Pr)123] single crystals [6].

The temperature dependence of susceptibility $\chi = M/H$, shown in Fig. 1 for two directions of the mag-

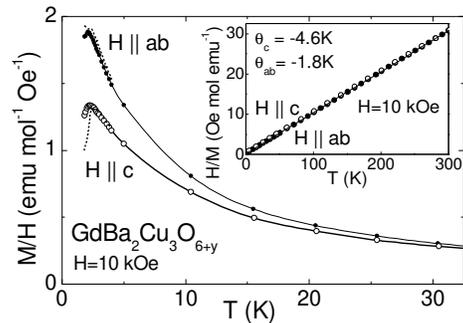


Fig. 1. Temperature dependence of the magnetic susceptibility (determined as $M = H$ at $H = 10$ kOe) of a $\text{GdBa}_2\text{Cu}_3\text{O}_{6+y}$ single crystal for $H \parallel c$ (open circles) and $H \parallel ab$ (full circles). Dotted lines - the data for $H = 1$ kOe. Inset: temperature dependence of inverse magnetic susceptibility H/M . The line shows the best fit to the Curie-Weiss law for $H \parallel c$.

netic field H , has a maximum at $T = T_N$. The position of the maximum is field dependent. The anisotropy is more pronounced for $H \parallel c$ (at least for small fields), which corresponds to the c-axis direction of the Gd^{3+} magnetic moments (in accord with neutron diffraction and Mössbauer spectroscopy [1,2]). The maximum in

¹ Corresponding author. Present address: Leibniz-Institut für Festkörper- und Werkstofforschung Dresden, P O Box 270116, D -01171 Dresden, Germany. E-mail: narozh@ifw-dresden.de

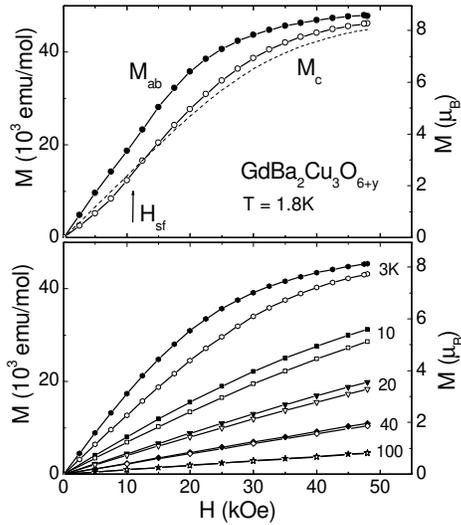


Fig. 2. Magnetization of the $\text{GdBa}_2\text{Cu}_3\text{O}_{6+y}$ single crystal for $H \parallel c$ (open symbols) and $H \parallel ab$ (full symbols). Full lines are guides for eye. The dashed line shows the data for $H \parallel c$ at $T = 2.4 \text{ K}$ which is slightly above T_N .

T_N disappears for $H = 15 \text{ kOe}$ at $T = 1.8 \text{ K}$.

The $M^{-1}(T)$ curves can be well fitted to the Curie-Weiss law $M^{-1}(T) = (T - T_0)/C$ for $5 < T < 300 \text{ K}$. The values of T_0 and the effective magnetic moment m_e (determined from the Curie constants C) are -4.6 K and 8.90 m_B and -1.8 K and 8.88 m_B for $H \parallel c$ and $H \parallel ab$, respectively. m_e^c and m_e^{ab} are very close to each other as expected for the spin-only magnetic moment of Gd. The values of m_e are little higher than the value of the free Gd^{3+} ion. This difference may be connected with some error in determination of the small mass of the sample ($m = 0.50 \text{ mg}$; the accuracy of mass determination in this case is about 10%).

The anisotropy in the paramagnetic state is clearly seen in this figure. Phenomenologically the observed anisotropy can be connected with the difference between c and ab . (From the temperature accuracy in determination is better than 0.1 K.) It is found that $j_c > j_{ab}$. The sign of magnetic anisotropy for Gd1236 is the opposite to the observed for Pr123 [6,7]. The different signs of magnetic anisotropy for Gd- and Pr-sublattices explain the crossover of magnetic anisotropy reported for (Gd-Pr)123 single crystals [6].

$M(H)$ curves clearly show an anisotropy below as well as above T_N , see Fig. 2. At lowest T there is a clear tendency for isotropization in high fields. $M_{ab} > M_c$ is in accord with our data obtained earlier from subtraction of (Y-Pr)123 data from (Gd-Pr)123 results [6]. The general agreement with these previously indirectly obtained results on the magnetization of the Gd-sublattice is fair. Even the values and the anisotropy of T_N correspond well to the directly measured for Gd1236.

Below T_N , a distinct indication of a spin-op tran-

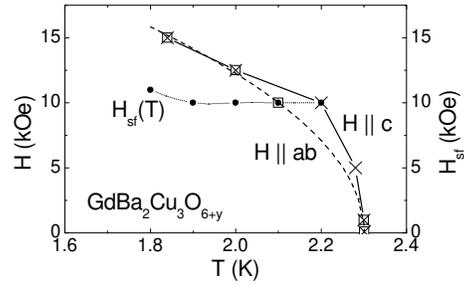


Fig. 3. Magnetic phase diagram of $\text{GdBa}_2\text{Cu}_3\text{O}_{6+y}$ for $H \parallel c$ (crosses and full line) and $H \parallel ab$ (open squares and dashed line). The temperature dependence of the spin-op field is shown by the dotted line and full circles.

sition can be seen for $H \parallel c$, see Fig. 2. The spin-op field H_{sf} was determined as an inflection point of the $M(H)$ dependence at $T < T_N$. H_{sf} is practically temperature independent in the studied temperature interval, see Fig. 3. As expected, the spin-op transition disappears above T_N . No anomaly has been detected for $H \parallel ab$ at all T .

A magnetic phase diagram is constructed from the field dependence of T_N , determined for two directions of H (see Fig. 3). The field dependence of T_N for $H \parallel ab$ is described by a quadratic dependence similar to that observed by us earlier for Pr-1237 [7]. Below H_{sf} the $T_N(H)$ dependence for $H \parallel c$ is weaker than for $H \parallel ab$. At the same time above H_{sf} the $T_N(H)$ dependencies are close for both directions of H .

The pronounced magnetic anisotropy found for Gd1236 may be connected with several mechanisms including: (i) dipole-dipole interaction of the Gd ions; (ii) interaction between Gd and Cu sublattices; (iii) anisotropic exchange interaction; (iv) crystal-field effects on the excited Gd^{3+} states. Further investigations are necessary to clarify the situation.

Acknowledgements

This work was supported by DFG (grant MU 1015/4-2), RFBF (grant 01-02-04002) and GA CR (grant 202/00/1602).

References

- [1] H. A. Mook et al., Phys. Rev. B 38 (1988) 12008.
- [2] C. Meyer et al., J. Phys. F: Met. Phys. 17 (1987) L345.
- [3] V. P. Djakonov et al., Physica C 178 (1991) 221.
- [4] K. Nehrke and M. W. Pieper, Phys. Rev. B 51 (1995) 12618.
- [5] V. N. Narozhnyi et al., JMMM 157/158 (1996) 675.
- [6] V. N. Narozhnyi et al., Physica B 284-288 (2000) 1047.
- [7] V. N. Narozhnyi et al., Physica C 312 (1999) 233.