

# Superconducting Properties of Atomic-Disordered Compound MgCNi<sub>3</sub>

A. Karkin,<sup>1,\*</sup> B. Goshchitskii,<sup>1</sup> E. Kurmaev,<sup>1</sup> Z. A. Ren,<sup>2</sup> and G. C. Che<sup>2</sup>

<sup>1</sup>*Institute of Metal Physics, UB RAS, 620219, Ekaterinburg, GSP-170, Russia*

<sup>2</sup>*National Laboratory for Superconductivity, Institute of physics,*

*Chinese academy of sciences, P. O. Box 603, Beijing 100080, P. R. China*

(Dated: March 22, 2022)

The effect of radiation-induced disordering in a nuclear reactor (fast neutrons fluence  $\Phi = 5 \cdot 10^{19}$  cm<sup>2</sup>,  $T_{\text{irr}} = 340$  K) on resistivity  $\rho$ , superconducting transition temperature  $T_C$  and upper critical field  $H_{C_2}$  of polycrystalline MgCNi<sub>3</sub> samples was investigated. It was found that  $T_C$  decreases under irradiation from 6.5 to 2.9 K and completely recovers after annealing at 600 °C. Temperature dependences  $\rho(T)$  are characteristic of compounds with strong electron-phonon interaction. The  $dH_{C_2}/dT$  behaviour testifies to a considerable decrease in density of electronic state at Fermi level  $N(E_F)$  in the course of disordering.

Radiation-induced disordering caused by irradiation with high-energy particles is a unique method of investigating the properties of superconducting and normal states of ordered crystals [1, 2]. Even in broad-band metals, such as intermetallic compounds with A15 structure, long-range ordering loss leads to considerable rearrangement of the electronic spectrum, resulting in disappearance of individual features of the electronic structure. Disordering causes decrease in densities at Fermi level  $N(E_F)$  and respective noticeable drop of  $T_C$  in compounds with high initial  $N(E_F)$  (Nb<sub>3</sub>Sn or V<sub>3</sub>Si), and considerable (from 1.5 to 7 K) rise of  $T_C$  in compounds with low  $N(E_F)$  and  $T_C$  due to growth of  $N(E_F)$  (Mo<sub>3</sub>Si and Mo<sub>3</sub>Ge) [3, 4, 5]. In type HTSC compounds, disordering leads to more significant changes in properties: fast and complete  $T_C$  degradation is accompanied with  $N(E_F)$  decrease and metal-insulator transition [2]. Thus investigation of response of a system to radiation-induced disordering serves as a kind of a test to reveal the characteristic features of its electron states. It was shown in recent papers [6, 7] that  $T_C$  drop from 38 to 5 K observed at MgB<sub>2</sub> under radiation-induced disordering is connected mainly with considerable drop of  $N(E_F)$ , similar to Nb<sub>3</sub>Sn or V<sub>3</sub>Si compounds. In our investigation, we concentrated on the effect of disordering on the properties of superconducting compound MgCNi<sub>3</sub> ( $T_C \sim 8$  K) with perovskite cubic structure of type SrTiO<sub>3</sub>, unconventional for intermetallides [8]. Our interest in this system was explained by the fact that its ground state is close to ferromagnetic due to the presence of a narrow peak in  $N(E)$  located 45 meV below the Fermi level [9]. This allowed us to regard it as a candidate for an unconventional (possibly triplet) superconductivity, similar to Sr<sub>2</sub>RuO<sub>4</sub> compound. It is known that in Sr<sub>2</sub>RuO<sub>4</sub>, as distinct from conventional superconducting compounds (intermetallides),  $T_C$  undergoes anomalously strong suppression even under a slight disorder [10]. In MgCNi<sub>3</sub>, maximum  $T_C$  is achieved at excess of carbon content only (nominal composition MgC<sub>1.5</sub>Ni<sub>3</sub>), even though, according to neutron diffraction study, the actual composition is closer to Mg<sub>0.96</sub>CNi<sub>3</sub>, and excess carbon occupies the region between sample grain boundaries [11].

In the sample preparation, fine powders Mg, C and Ni with purity better than 99.5% were used as starting materials. The mixtures of appropriate composition were pressed into pellets; the pellets were wrapped in Ta foil and enclosed in an evacuated quartz tube, placed in a furnace, heated to 950 °C at a rate of 150 °C/h and kept at this temperature for 5 h, followed by furnace-cooling to room temperature. The highest  $T_C = 6.5$  K and the best superconducting transition corresponded to the nominal composition  $x = 1.45$  [12]. Samples  $0.5 \times 1 \times 5$  mm<sup>3</sup> in size were irradiated with fast neutrons at  $T_{\text{irr}} = (330 \pm 10)$  K, then annealed during 20 min at temperatures  $T_{\text{ann}}$  from 100 to 600 °C in step of 100 °C. Resistivity  $\rho(T)$  in fields up to 13.6 T was measured using a standard four-probe method.

The initial sample resistivity curve of transition to superconducting state (Fig. 1) is stretched in the direction of higher temperatures, onset is about 8 K. Mean transition temperature is 6.5 K. We defined the superconducting transition temperature  $T_C$  as the temperature exhibiting half of the normal-state resistivity. Irradiation leads to  $T_C$  drop to 2.9 K, and transition becomes narrower. Annealing at 500 °C almost completely recovers the initial form of dependence  $\rho(T)$ , while after annealing at 600 °C, transition becomes more abrupt with a higher  $T_C = 7.1$  K compared with the initial sample.

Temperature dependences  $\rho(T)$  of the initial, irradiated and isochronally annealed MgCNi<sub>3</sub> samples (Fig. 2) present curves with saturation, typical of the systems with strong electron-phonon interaction of types Nb<sub>3</sub>Sn or V<sub>3</sub>Si [3]. A rather large value of residual resistivity  $\rho_0 = 0.137$  mOhm·cm (found by  $\rho$  extrapolation to  $T = 0$ ) of a sample in the initial state testifies to an insufficient degree of ordering. The absolute value of  $\rho(T)$  approximately coincides with the data in [13] and is three times higher than in [8], even though temperatures dependences  $\rho(T)$  are practically

---

\*Corresponding author. E-mail:karkin@uraltc.ru

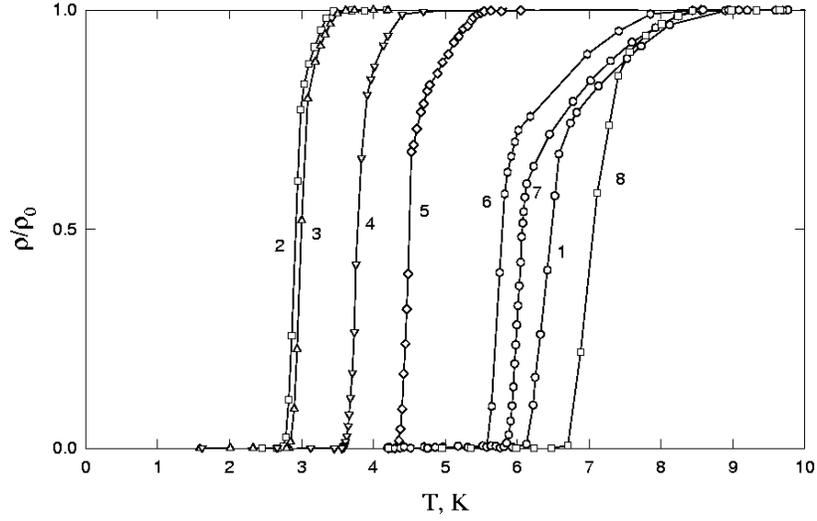


FIG. 1: Temperature dependences of reduced resistivity  $\rho/\rho_0$  of initial  $\text{MgCNi}_3$  sample (1), sample irradiated under fast neutrons fluence  $\Phi = 5 \cdot 10^{19} \text{ cm}^{-2}$  (2) and sample annealed at  $T = (100 - 600) \text{ }^\circ\text{C}$  during 20 min. (3 - 8). Solid lines are drawn across experimental points.

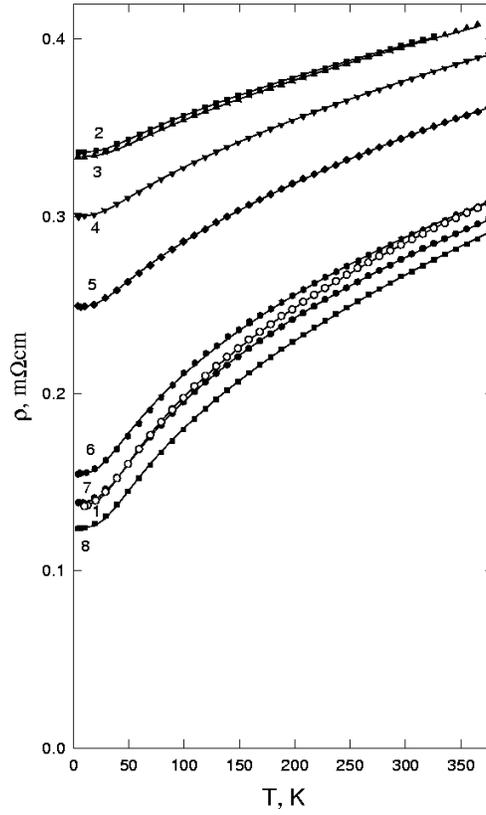


FIG. 2: Temperature dependences of  $\text{MgCNi}_3$  sample resistivity  $\rho(T)$ ; for designations, see Fig. 1. Solid lines present the calculation using expression (7).

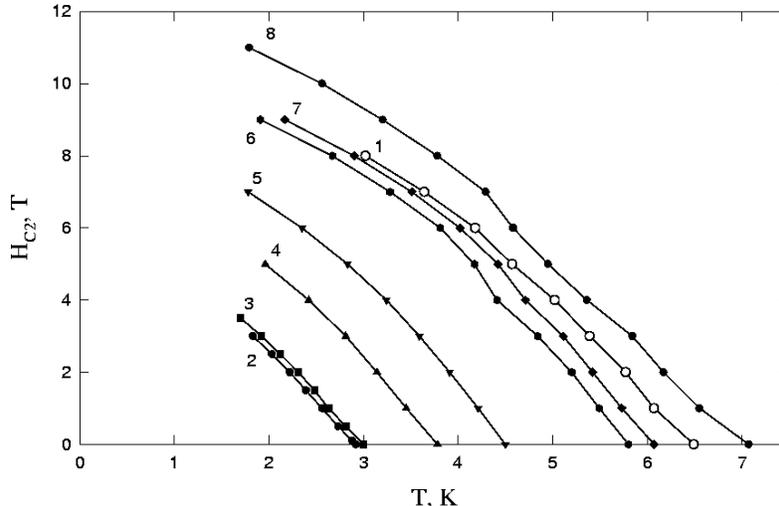


FIG. 3: Temperature dependences of upper critical field  $H_{C_2}$  for MgCNi<sub>3</sub> sample; for designations, see Fig. 1. Solid lines are drawn across experimental points.

identical in all cases. Evidently, after irradiation and subsequent annealing at 600 °C, further ordering and residual resistivity drop to  $\rho_0 = 0.124$  mOhm·cm occur in the sample.

The upper critical field  $H_{C_2}$ , as determined from the half-transition temperature (0.5 of the normal-state resistivity), has a form typical of second-order superconductors (Fig. 3), the initial sample value of  $dH_{C_2}/dT$  is in good agreement with the data of paper [13]. A relatively weak change in the slope of  $dH_{C_2}/dT$  should be noted; a very similar behaviour at disordering was observed for MgB<sub>2</sub> [6]. So, for dirty superconductor

$$(-dH_{C_2}/dT)_{\text{dirty}} = (8ek_B/\pi)(1 + \lambda)N(E_F)\rho_0, \quad (1)$$

the relatively weak change in  $dH_{C_2}/dT$  (Fig. 3) would evidently be compensated by a considerable (about 2.5 times) decrease in  $N(E_F)$ .

Deviations from the Block-Grüneisen law

$$\rho(T) = \rho_0 + \lambda_{\text{tr}}F_{\text{BG}}(\theta/T), \quad (2)$$

defining linear behaviour of  $\rho(T)$  at high  $T$ , where  $\theta$  is Debye temperature,  $\lambda_{\text{tr}}$  is electron-phonon interaction constant proportional to parameter  $\lambda$  in the McMillan expression for superconducting transition temperature

$$T_C \sim (\omega_{\text{ln}}/1.2) \exp\{-(1 + \lambda)/(\lambda - \mu)\}, \quad \mu \sim 0.1, \quad (3)$$

are often described by an empirical expression

$$1/\rho(T) = 1/\rho_{\text{sat}} + 1/(\rho_0 + \lambda_{\text{tr}}F_{\text{BG}}(\theta/T)), \quad (4)$$

so  $\rho(T)$  cannot exceed the value of saturation resistivity  $\rho_{\text{sat}}$ , which for type A15 intermetallics is about 0.2 mOhm·cm. Intuitive substantiation of (4) boils down to the fact that electron scattering becomes inefficient when the electron free path  $l_{\text{tr}}$  becomes shorter than the Fermi wavelength, inversely proportional to wave-vector  $k_F$ ; therefore, in the expression for conductivity  $\sigma \sim (k_F)^2 l_{\text{tr}}$ ,  $l_{\text{tr}}$  should be substituted by a value close to  $(k_F)^{-1}$ . The interpolation formula  $\sigma \sim (k_F)^2 l_{\text{tr}} + k_F$  is equivalent to (4).

Fitting of experimental data on MgCNi<sub>3</sub> to expression (4), containing 4 fitting parameters  $\rho_{\text{sat}}$ ,  $\rho_0$ ,  $\lambda_{\text{tr}}$  and  $\theta$ , yields good agreement with the close values of  $\theta = (140 - 155)$  K. A similar fitting procedure for MgCNi<sub>3</sub> ( $T_C \sim 8$  K) carried out in [12] with Einstein, instead of Debye, spectrum, yields the following parameters: Einstein temperature  $\theta_E = 206$  K,  $\rho_{\text{sat}} = 0.574$  mOhm·cm. The obtained value of  $\theta$  is noticeably lower than that obtained in heat capacity measurements, Debye temperature  $\theta_D \sim 235$  K [8]. However, using the value of  $\theta = 150$  K and on the assumption of the Debye spectrum, we obtain  $\omega_{\text{ln}} = \exp(-1/3) \cdot \theta \sim 105$  K, which is considerably lower than  $\omega_{\text{ln}} \sim 480$  K for

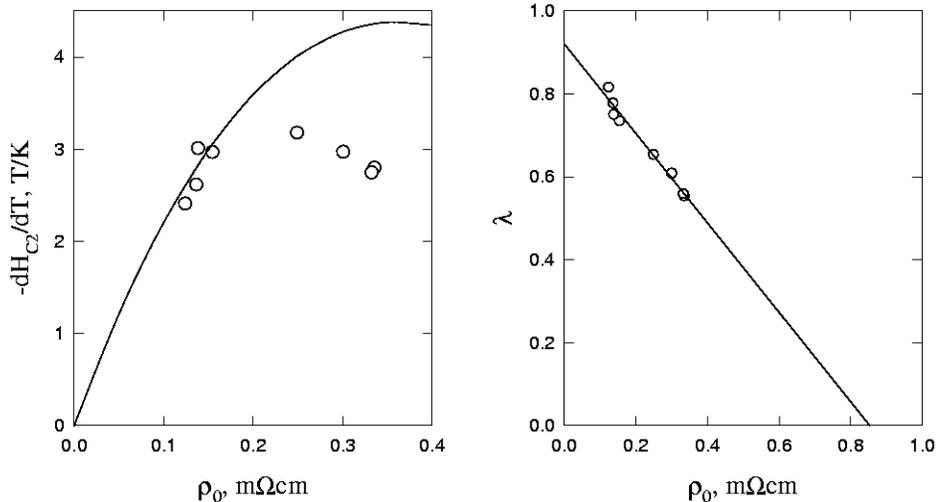


FIG. 4: Upper critical field derivative  $-dH_{C_2}/dT$  (left) and electron-phonon interaction constant  $\lambda$  (right) for MgCNi<sub>3</sub> sample as a function of residual resistivity  $\rho_0$ . Solid lines present the calculation using expressions (8) and (4), respectively.

MgB<sub>2</sub> [14]. Expression (3) yields  $\lambda \sim 0.8$ , which compares well with the value of  $\lambda \sim 1.1$  for MgB<sub>2</sub> [13]. Value  $\lambda$  as a function of  $\rho_0$  (Fig. 4) may be described with a linear dependence

$$\lambda = \lambda_0(1 - (\rho_0/R)), \quad (5)$$

where  $\lambda_0 = 0.92$ , and  $R = 0.85$  mOhm-cm.

The relatively large value of  $\lambda$  (and hence,  $\lambda_{tr}$ ) is generally in an agreement with significant nonlinearity of  $\rho(T)$  characteristic of compounds with strong electron-phonon interaction. However, fitting parameter  $\rho_{sat}$ , varies significantly from 0.85 mOhm-cm for the initial sample to 0.5 mOhm-cm for the irradiated sample, which agrees poorly with the meaning of value  $\rho_{sat} \sim (kF)^{-1}$ , which must be constant in case of a broad-band metal.

The origin of  $\rho(T)$  "saturation" for systems with strong electron-phonon interaction were analyzed in terms of the mean field theory in [15], where it was shown that (in case of a relatively weak coupling which does not lead to formation of a pseudogap) scattering rate is proportional not to the value of ions r.m.s. displacement  $\langle u^2 \rangle$ , but rather to  $(\langle u^2 \rangle)^{0.5}$ , and so, in this case, instead of (2), we have

$$\rho(T) = \{(\rho_0)^2 + \lambda_{tr}F_{BG}(\theta/T)\}^{0.5}, \quad (6)$$

which results in type  $\rho(T) \sim T^{0.5}$  behaviour at high  $T$ . However, use of (6) fails to yield a satisfactory data description. The probable reason is that value  $\lambda_{tr}$ , in its turn, also depends on disordering (is characterized by a sum of static and thermal displacements), i.e., on  $\rho(T)$ ; the same reason causes decrease in  $\lambda$  with increase in  $\rho_0$  (Fig. 4). Considering  $\lambda_{tr}$  being in dependence on  $\rho(T)$ , similar to that of  $\lambda$  on  $\rho_0$  in (4), expression (6) is transformed into an equation

$$\rho(T) = \{(\rho_0)^2 + \lambda_{tr0}(1 - \rho(T)/R_{tr})(F_{BG}(\theta/T))\}^{0.5}, \quad (7)$$

which, when solved for  $\rho(T)$ , yields the required expression, also containing four fitting parameters  $R_{tr}$ ,  $\rho_0$ ,  $\lambda_{tr}$  and  $\theta$ . Expression (7) describes data with the same accuracy as expression (4), with similar values of  $\theta$ , but with almost equal fitting parameters  $R_{tr}$  varying within (0.75 - 0.88) mOhm-cm. Such a good agreement between the values of  $R$  in (5) and  $R_{tr}$  in (7) does not look casual.

In conclusion, let us consider the probable causes of superconductivity degradation in MgCNi<sub>3</sub> under disordering. Loss of long-range order must lead to smearing of the fine structure of electron densities of state; at that, function  $N(E)$  smoothes out, but without becoming zero. For superconductors with electron-phonon interaction,  $\lambda \sim N(E_F)$ , therefore  $T_C$  should never go down exactly to zero; the latter requirement is evidently satisfied for the majority of compounds which may be related to broad-band intermetallides. A qualitatively different behaviour is observed in HTSC compounds: in all cases superconductivity is completely depressed at a much higher rate than in intermetallides, probably due to non electron-phonon mechanisms of superconductivity as well as to a proximity to metal-insulator transition [16].

Value  $\lambda$  calculated by expression (3) decreases 1.5 times at MgCNi<sub>3</sub> under irradiation (Fig. 4), while the above value of  $N(E_F)$  estimated using expression (1) decreases almost 2.5 times. Probably, such discrepancy in change of  $\lambda$  and  $(-dH_{C_2}/dT)$ , as it was similarly supposed for, e.g., MgB<sub>2</sub> [6], may be due to the fact that the dirty limit of  $l_{tr} \ll \xi$  is not reached in the given region. Coherent length  $\xi$  may be estimated from the relation

$$\xi^2 = \Phi_0 / \{2\pi(-0.69dH_{C_2}/dT)T_C\},$$

which yields  $\xi = 55$  and  $75 \text{ \AA}$  for the initial and the irradiated samples, respectively. Free path  $l_{tr}$  may be estimated from an conventional expression used for conductivity

$$(\rho_0)^{-1} = (3\pi^2)^{-1/3}(e^2/\hbar)n^{2/3}l_{tr},$$

which yields  $l_{tr} \sim 20 \text{ \AA}$  for  $\rho_0 = 0.137 \text{ mOhm}\cdot\text{cm}$  (initial sample) and  $l_{tr} \sim 8 \text{ \AA}$  for  $\rho_0 = 0.337 \text{ mOhm}\cdot\text{cm}$  (irradiated sample). These relations of  $l_{tr}$  and  $\xi$  are definitely closer to the dirty limit. Further, expression (1) allows us to estimate  $(-dH_{C_2}/dT)$  using the experimental values of  $\gamma$  and  $\rho_0$  or those obtained from band calculations  $N(E_F)$ . According to band calculations [9, 17, 18],  $N(E_F) \sim 2.5 \text{ (eV}\cdot\text{spin}\cdot\text{cell)}^{-1} = 2.8 \cdot 10^{47} \text{ (J}\cdot\text{m}^3)^{-1}$ , using  $\lambda \sim 0.8$ ,  $\rho_0 \sim 0.1 \text{ mOhm}\cdot\text{cm}$ , we obtain  $(-dH_{C_2}/dT) \sim 3 \text{ T/K}$ , which is quite commensurate with the experimental value  $(-dH_{C_2}/dT) \sim 2.5 \text{ T/K}$ . Thus there are probably no reasons to doubt the dirty limit applicability in the given case. Assuming  $\lambda \sim N(E_F)$ , using (1) and (5), we obtain the dependence

$$(-dH_{C_2}/dT)_{\text{dirty}} \sim \lambda(1 + \lambda)\rho_0 = \lambda_0\{1 - (\rho_0/R)\}(1 + \lambda_0\{1 - (\rho_0/R)\})\rho_0, \quad (8)$$

shown as a solid line in Fig. 4. The causes of noticeable deviations at  $\rho_0 > 0.25 \text{ mOhm}\cdot\text{cm}$  are unclear, it should be noted only that very similar changes in  $dH_{C_2}/dT$  at radiation-induced disordering were observed for MgB<sub>2</sub> [14]. Nevertheless, for MgCNi<sub>3</sub>, the response to disordering is similar to that observed for conventional systems (intermetallics) with strong electron-phonon interaction.

#### Acknowledgments

Work supported by Minpromnauka, Russia (State Contracts No. 40.012.1.1.1150, No. 40.012.1.1.1146/Contract No. 15/02), Program of government support to leading scientific schools of Russia (Project No. 00-15-96581) and Russian Foundation for Fundamental Research (Project No. 01-02-16877).

- 
- [1] B.N. Goshchitskii, V.Ye. Arkhipov, Yu.G. Chukalkin. Neravnovesnye sostoyania uporyadochennykh kristallov, obluchennykh bystryimi neitronami. Sov. Scient. Rev/Sec. A: Phys.Rev., (1987), v.8, pp.519-608.
  - [2] A. Ananyev, A. Gerashenko, K. Okulova, S. Verkhovskii, A. Davletshin and B. Goshchitskii. NMR Study of Magnetic Moments Arising in Superconducting Cuprates under Electron/Neutron Irradiation. Appl. Magn. Reson., (2000), v. 18, p. 235.
  - [3] A. E. Karkin, V. E. Arkhipov, V. D. Parkhomenko, B. N. Goshchitskii. Influence of defects on Nb<sub>3</sub>Sn and V<sub>3</sub>Si superconducting properties. Phys.stat.sol. (a) (1980), v.59, K53.
  - [4] V.Ye. Arkhipov, V.I. Voronin, A.Ye. Karkin, A.V. Mirmelshtein. Teployemkost soyedineniya Mo<sub>3</sub>Si: sverkhprovodimost i smyagcheniye fononnogo spektra. FMM (1983), v. 55, p.79.
  - [5] A.Ye. Karkin, V.Ye. Arkhipov, A.V. Mirmelshtein, V.I. Voronin. Strukturnoye sostoyanie i sverkhprovodimost soyedineniya Mo<sub>3</sub>Ge, obluchennogo bystryimi neitronami. FMM (1984), v. 57, p. 1021.
  - [6] A.Ye. Karkin, V.I. Voronin, T.V. Dyachkova, N.O. Kadyrova, A.P. Tutunik, V.G. Zubkov, Yu.G. Zainulin, M.V. Sadovsky and B.N. Goshchitskii. Sverkhprovodyashchiye svoystva atomno-razuporyadochennogo soyedineniya MgB<sub>2</sub>. Letters to ZhETF (2001), v. 73, issue 10, p. 640.
  - [7] A. P. Gerashenko, K. N. Mikhalev, S. V. Verkhovskii, A. E. Karkin and B. N. Goshchitskii. Reduction in the electron density of states in superconducting MgB<sub>2</sub> disordered by neutron irradiation: <sup>11</sup>B and <sup>25</sup>Mg NMR estimates. Phys. Rev. B (2002), v. 65, 132506.
  - [8] T. He, Q. Huang, A. P. Ramirez, Y. Wang, K. A. Regan, N. Rodago, M. A. Hayward, M. K. Haas, J. S. Slusky, K. Inumaru, H. W. Zandbergen, N. P. Ong, and R. J. Cava. Superconductivity in the non-oxide perovskite MgCNi<sub>3</sub>. cond-mat/0103296 (2001); Letters to Nature 411, 54 (2001).
  - [9] H. Rosner, R. Weht, M. D. Johannes, W. E. Pickett, and E. Tosatti. Superconductivity near Ferromagnetism in MgCNi<sub>3</sub>. Phys. Rev. Lett. (2002), v. 88, No. 2, p. 027001.
  - [10] Z. Q. Mao, Y. Mory, Y. Maeno. Suppression of superconductivity in Sr<sub>2</sub>RuO<sub>4</sub> caused by defects. Phys. Rev. B, 60, No. 1, p. 610. (1999).

- [11] L. D. Cooly, X. Song, J. Jiang, D. C. Larbalestier, T. He, K. A. Regan, R. J. Cava. Core pinning by intragranular nanoprecipitates in polycrystalline MgCNi<sub>3</sub>. Phys. Rev. B, 65, 214518 (2002).
- [12] Z. A. Ren, G. C. Che, S. L. Jia, H. Chen, Y. M. Ni, Z. X. Zhao, Effect of Mg and C contents in MgCNi<sub>3</sub>, and structure and superconductivity of MgCNi<sub>3-x</sub>Co<sub>x</sub>, cond-mat/0105366 (2001); Science in China (Series A) (2001) v.44, 1205.
- [13] S. Y. Li, R. Fan, X. H. Chen, C. H. Wang, W. Q. Mo, K. Q. Ruan, Y. M. Xiong, X. G. Luo, H. T. Zhang, L. Li, Z. Sun, L. Z. Cao. Normal state resistivity, upper critical field, and Hall effect in superconducting perovskite MgCNi<sub>3</sub>. Phys. Rev. B, 64, 1.2505 (2001).
- [14] Y. Wang, T. Plackowski, A. Junod. Specific heat in the superconducting and normal state (2-300K, 0-16 Teslas), and magnetic susceptibility of the 38-K superconductor MgB<sub>2</sub>: evidence for a multicomponent gap. cond-mat/0103181 (2001).
- [15] A. J. Millis, Jun Hu and S. Das Sarma. Resistivity saturation: Results from a dynamical mean field theory. Phys. Rev. Lett. (1999), v. 82, No. 11, p. 2354.
- [16] M.V. Sadovskiy. Superconductivity and Localization. Physics Reports (1997), v.282, No.5&6, pp. 225-348
- [17] D. J. Singh and I. I. Mazin. Superconductivity and electronic structure of perovskite MgCNi<sub>3</sub>. Phys. Rev. B, 64, 140507(R) (2001).
- [18] I. R. Shein, A. L. Ivanovskii, E. Z. Kurmaev, A. Moewes, S. Chiuzyan, L. D. Finkelstein, M. Neumann, Z. A. Ren and G. C. Che, The Effect of Co-doping on the electronic structure of MgCNi<sub>3</sub>. Phys. Rev. B 66, 024520 (2002).