

# Intermittency in aging

L. Buisson, L. Bellon, S. Ciliberto  
Ecole Normale Supérieure de Lyon, Laboratoire de Physique,  
C.N.R.S. UMR5672,  
46, Allée d'Italie, 69364 Lyon Cedex 07, France

22 mars 2022

## Résumé

The fluctuation-dissipation relation (FDR) is measured on the dielectric properties of a gel (Laponite) and of a polymer glass (polycarbonate). For the gel it is found that during the transition from a fluid-like to a solid-like state the fluctuation dissipation theorem is strongly violated. The amplitude and the persistence time of this violation are decreasing functions of frequency. Around  $1Hz$  it may persist for several hours. A very similar behavior is observed in polycarbonate after a quench below the glass transition temperature. In both cases the origin of this violation is a highly intermittent dynamics characterized by large fluctuations. The relevance of these results for recent models of aging are discussed.

**PACS :** 75.10.Nr, 77.22Gm, 64.70Pf, 05.20-y.

## 1 Introduction

Many systems in nature, such as glasses, spin-glasses, colloids and granular materials, present an extremely slow relaxation towards equilibrium and, when external conditions are modified, the physical properties of these materials evolve as a function of time : they are aging. For example, when a glassy material is quenched from above its glass transition temperature  $T_g$  to a temperature lower than  $T_g$ , any response function of the material depends on the time  $t_w$  elapsed from the quench [1]. Another example of aging is given by colloidal-glasses, whose properties evolve during the sol-gel transition which may last several days [2]. An important feature of aging materials is the dependence of their physical properties on the thermal history of the sample. Indeed experimental procedures, based on multiple cycles of cooling, heating and waiting times, have shown the existence of two spectacular effects : memory and rejuvenation. Specifically, aging materials present a rejuvenation for any negative temperature perturbation and at the same time during heating they remind the stops at fixed temperature done during cooling (see for example [3, 4] and references therein). Several models have been proposed to explain such a behavior but from an experimental point of view it is not easy to distinguish between them. The above mentioned experimental procedures have been, indeed, extremely useful to fix several constraints for

the phenomenological models[5, 6], but these procedures are mainly based on the study of the response of the system to an external perturbation. Therefore they are unable to give new insight on the system dynamics. Let us consider for example the trap model[5] which is based on a phase space description. Its basic ingredient is an activation process and aging is associated to the fact that deeper and deeper valleys are reached as the system evolves [7]. The dynamics in this model has to be intermittent because either nothing moves or there is a jump between two traps. This contrasts, for example, with mean field dynamics which is continuous in time[8]. Therefore, from an experimental point of view, it is extremely important to study not only the response of the system but also its thermal fluctuations. This analysis is also related to another important aspect of aging dynamics, that is the definition of the temperature. Indeed recent theories [8] based on the description of spin glasses by a mean field approach proposed to extend the concept of temperature using a Fluctuation Dissipation Relation (FDR) which generalizes the Fluctuation Dissipation Theorem (FDT) for a weakly out of equilibrium system (for a review see ref. [9, 10, 11]). In order to understand this generalization, we recall the main consequences of FDT in a system which is in thermodynamic equilibrium. We consider an observable  $V$  of such a system and its conjugate variable  $q$ . The response function  $\chi_{Vq}(\omega)$ , at frequency  $f = \omega/2\pi$ , describes the variation  $\delta V(\omega)$  of  $V$  induced by a perturbation  $\delta q(\omega)$  of  $q$ , that is  $\chi_{Vq}(\omega) = \delta V(\omega)/\delta q(\omega)$ . FDT relates the fluctuation spectral density of  $V$  to the response function  $\chi_{Vq}$  and the temperature  $T$  of the system :

$$S(\omega) = \frac{2k_B T}{\pi\omega} \text{Im} [\chi_{Vq}(\omega)] \quad (1)$$

where  $S(\omega) = \langle |V(\omega)|^2 \rangle$  is the fluctuation spectral density of  $V$ ,  $k_B$  is the Boltzmann constant,  $\text{Im} [\chi_{Vq}(\omega)]$  is the imaginary part of  $\chi_{Vq}(\omega)$ . Textbook examples of FDT are Nyquist's formula relating the voltage noise to the electrical resistance and the Einstein's relation for Brownian motion relating the particle diffusion coefficient to the fluid viscosity [12].

When the system is not in equilibrium FDT, that is eq.1, may fail. Indeed theoretical works [8] predict a violation of eq.1 which has been observed [9] in many numerical simulations ([11],[13]-[19]) and in a few experiments [20]-[24].

Because of the slow dependence on  $t_w$  of the response functions, it has been proposed to use a FDR which generalizes eq.1 and which can be used to define an effective temperature  $T_{eff}(\omega, t_w)$  of the system [11] :

$$T_{eff}(\omega, t_w) = \frac{S(\omega, t_w) \pi\omega}{\text{Im} [\chi_{Vq}(\omega, t_w)] 2k_B} \quad (2)$$

It is clear that if eq.1 is satisfied  $T_{eff} = T$ , otherwise  $T_{eff}$  turns out to be a decreasing function of  $t_w$  and  $\omega$ . The physical meaning of eq.2 is that there is a time scale (for example  $t_w$ ) which allows to separate the fast processes from the slow ones. In other words the low frequency modes, such that  $\omega t_w < 1$ , relax towards the equilibrium value much slower than the high frequency ones which rapidly relax to the temperature of the thermal bath. Therefore it is conceivable that the slow frequency modes keep memory of higher temperatures for a long time and for this reason their temperature should be higher than that of the high

frequency ones. This striking behavior has been observed in several numerical models of aging [11],[13]-[19]. Further analytical and numerical studies of simple models show that eq.2 is a good definition of temperature in the thermodynamic sense [10, 11]. In spite of the large amount of theoretical studies there are only a few experiments where FDR is studied in aging materials. The experimental analysis of the dependence of  $T_{eff}(\omega, t_w)$  on  $\omega$  and  $t_w$  is very useful to distinguish among different models of aging because the FDT violations are model dependent [11],[13]-[19]. Furthermore the direct analysis of the noise signal allows one to understand if the dynamics is either intermittent or continuous in time.

Recently, a few experiments have analyzed this problems in real materials [20], [21, 22], [23], [24]. The violation of FDT measured in an experiment on a spin glass [23] seems to be in agreement with theoretical predictions, which were originally based on mean field approach of spin glasses. In contrast, experiments done on dielectric measurements on glycerol [20], colloidal glasses[21, 22] and polymers [24] present only a qualitative agreement with theory.

The previous analysis of Laponite [21, 22] and of polycarbonate[24] was mainly based on the study of the time evolution of the noise spectra which is surprisingly similar in these two very different materials. In both cases the effective temperature defined using eq.2 is huge and the persistent time of the violation is extremely long. We have therefore analyzed directly the time evolution of the noise signal in both experiments and we find a strongly intermittent behavior in both materials. In this paper we describe the results of this analysis and we want also to point out the common features observed in the slow relaxation dynamics of these two materials.

The paper is organized as follows. In section 2 and 3 we recall the main results of the experiment on Laponite and polycarbonate respectively. We also describe the analysis performed on the time evolution of the noise signal. In section 4 we compare the results of the two experiments and we discuss their relevance for recent aging models. Conclusions are done at the end of the section.

## 2 Laponite electric properties

### 2.1 The experimental apparatus

The Laponite [25] solution is used as a conductive liquid between the two golden coated electrodes of a cell (see fig.1). It is prepared in a clean  $N_2$  atmosphere to avoid  $CO_2$  and  $O_2$  contamination, which perturbs the electrical measurements. Laponite particles are dissolved at a concentration of 2.5% mass fraction in pure water under vigorous stirring during 300s. To avoid the existence of any initial structure in the sol, we pass the solution through a  $1\mu m$  filter when filling our cell. This instant defines the origin of the aging time  $t_w$  (the filling of the cell takes roughly two minutes, which can be considered the maximum inaccuracy of  $t_w$ ). The sample is then sealed so that no pollution or evaporation of the solvent can occur. At this concentration, the light scattering experiments show that Laponite [25] structure functions are still evolving 500h after the preparation [2]. We only study the beginning of this glass formation process.

The two electrodes of the cell are connected to our measurement system, where we alternately record the cell electrical impedance  $Z(t_w, \omega)$  and the voltage noise density  $S_Z(t_w, \omega)$

(see fig.1). Taking into account that in this configuration  $Im [\chi_{Vq}(t_w, \omega)] = \omega Re [Z(t_w, \omega)]$ , one obtains from eq.2 that the effective temperature of the Laponite solution as a function of the aging time and frequency is :

$$T_{eff}(t_w, \omega) = \pi S_Z(t_w, \omega) / 2k_B Re [Z(t_w, \omega)] \quad (3)$$

which is an extension of the Nyquist formula.

The electrical impedance of the sample is the sum of 2 effects : the bulk is purely conductive, the ions of the solution follow the forcing field, whereas the interfaces between the solution and the electrodes give mainly a capacitive effect due to the presence of the Debye layer[27]. This behavior has been validated using a four-electrode potentiostatic technique [28] to make sure that the capacitive effect is only due to the surface. In order to test only bulk properties, the geometry of the cell is tuned to push the surface contribution to low frequencies. Specifically the cell is composed by two large reservoirs in contact with the electrodes which have an area of  $25cm^2$ . The reservoirs are connected by a rigid tube (see fig.1) whose section and length give the main contribution to the bulk electrical resistance. Thus by changing the sizes of the tube the bulk resistance can be changed from  $300\Omega$  to  $100K\Omega$ . We checked that the dynamics of the system does not depend on the value of the bulk resistance. For a bulk resistance of about  $10^5\Omega$  the cut-off frequency of the equivalent R-C circuit (composed by the series of the Debye layers plus the bulk resistance) is about  $0.02Hz$ . In other words above this frequency the imaginary part of the cell impedance is about zero.

## 2.2 FDR measurements

In fig.2(a), we plot the real part of the impedance as a function of the frequency  $f$ , for a typical experiment and two different times. The time evolution of the resistance of one of our sample is plotted in fig.2(b) : it is still decaying in a non trivial way after  $24h$ , showing that the sample has not reached any equilibrium yet. This aging is consistent with that observed in light scattering experiments [2]. As the dissipative part of the impedance  $Re(Z)$  is weakly time and frequency dependent, one would expect from the Nyquist formula that so does the voltage noise density  $S_Z$ . But as shown in fig.3, FDR must be strongly violated for the lowest frequencies and earliest times of our experiment :  $S_Z$  changes by several orders of magnitude between highest values and the high frequency tail <sup>1</sup>. This violation is clearly illustrated by the behavior of the effective temperature in fig.4<sup>2</sup>. For long times and high frequencies, the FDR holds and the measured temperature is the room one ( $300K$ ) ; whereas for early times  $T_{eff}$  climbs up to  $3.10^3K$  at  $1Hz$ . Moreover,  $T_{eff}$  could be even larger for lower frequencies and lower aging times : indeed, we found in all the tested samples no evidence of a saturation of this effective temperature in our measurement range. In order to

---

<sup>1</sup>This low frequency noise cannot be confused with the standard  $1/f$  noise observed in many electronic devices. We recall that the  $1/f$  appears only when an external current produced by an external potential goes through the device. In our cell no external potential is applied

<sup>2</sup>The usual representation of the effective temperature in simulations is the slope of the response versus correlation plot, but it is not suited for our experimental data : the system being almost only dissipative, the response function is close to a delta distribution, thus FDR is only one point in this representation.


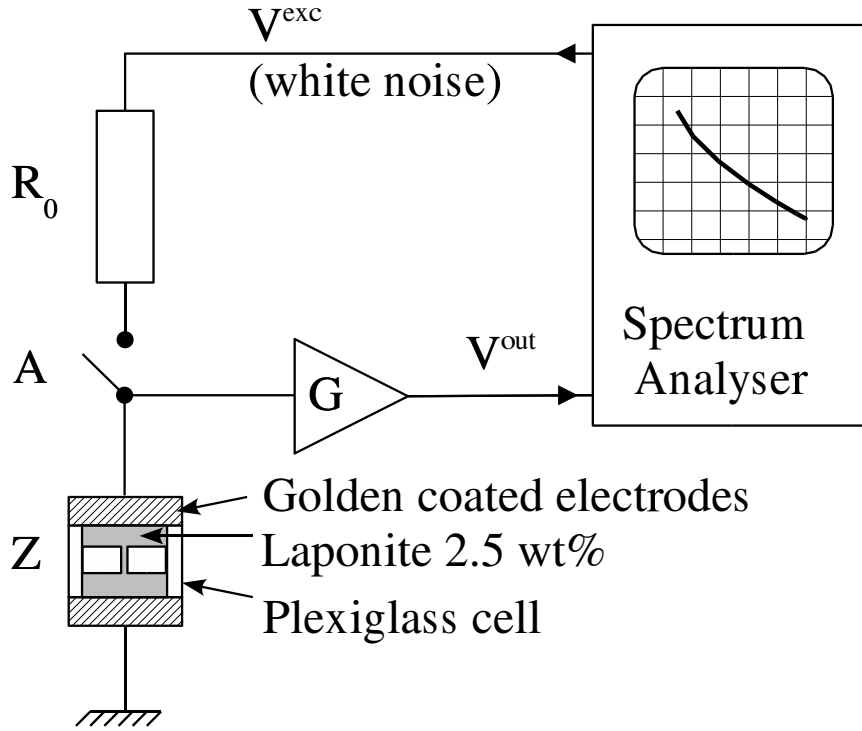


FIG. 1: **Laponite experimental set-up** The impedance under test  $Z$  is a cell filled with a 2.5wt% Laponite sol. The electrodes of the cell are golden coated to avoid oxidation. One of the two electrodes is grounded whereas the other is connected to the entrance of a low noise voltage amplifier characterized by a voltage amplification  $G$ . With a spectrum analyzer, we alternately record the frequency response  $FR(\omega) = \langle V^{out}/V^{exc} \rangle$  (switch  $A$  closed) and the spectrum  $S(\omega) = \langle |V^{out}|^2 \rangle$  (switch  $A$  opened). The input voltage  $V^{exc}$  is a white noise excitation, thus from  $FR(\omega)$  we derive the impedance  $Z(\omega)$  as a function of  $\omega$ , that is  $Z(\omega) = R_0/(G/FR(\omega) - 1)$ ; whereas from  $S(\omega)$ , we can estimate the voltage noise of  $Z$ , specifically  $S_Z(\omega) = [S(\omega) - S_a(\omega)]/G^2$  where  $S_a(\omega)$  is the noise spectral density of the amplifier

be sure that the observed violation is not due to an artifact of the experimental procedure, we filled the cell with an electrolyte solution with  $pH$  close to that of the Laponite sol such that the electrical impedance of the cell was the same. Specifically we filled the cell with  $NaOH$  solution in water at a concentration of  $10^{-3} \text{ mol.l}^{-1}$ . The results of the measurements of  $T_{eff}$  are shown in fig.5 at two different times after the sample preparation. In this case we did not observe any violation of FDR at any time.

(a)

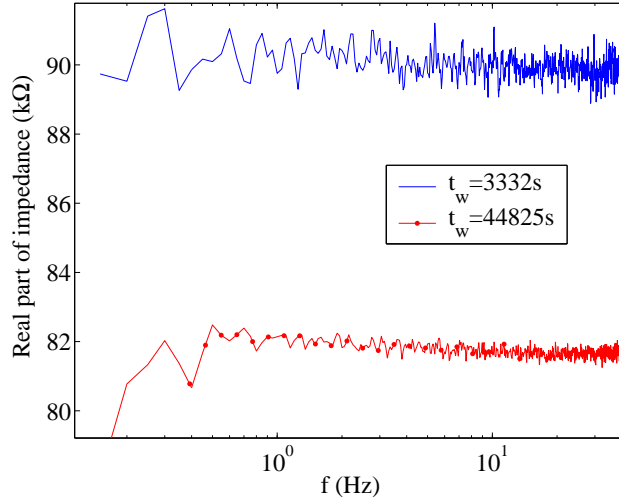

(b)

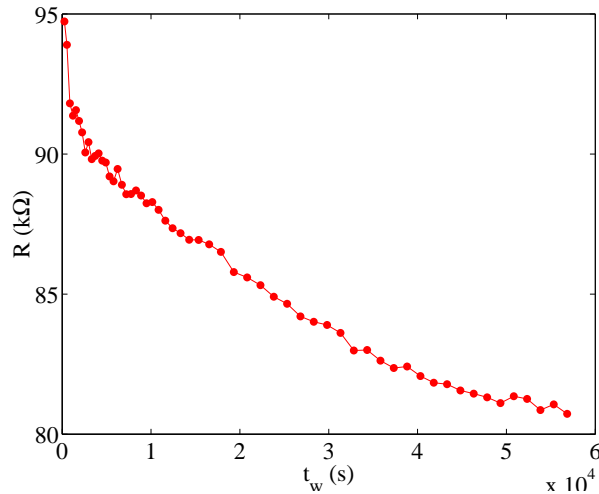


FIG. 2: **Laponite response function** (a) Frequency dependence of a sample impedance for 2 different aging times : continuous line  $t_w = 3332s$ ; ( $\bullet$ )  $t_w = 44825s$ .(b) Time evolution of the resistance. This long time evolution is the signature of the aging of the sol. In spite of the decreasing mobility of Laponite particles in solution during the gelation, the electrical conductivity increases.

### 2.3 Statistical analysis of the noise

In order to understand such a behavior we have directly analyzed the noise voltage across the Laponite cell. This test can be safely done in our experimental apparatus because the amplifier noise is negligible with respect to the thermal noise of the Laponite cell even when FDT is satisfied. In fig.6(a) we plot a typical signal measured  $2h$  after the gel preparation when the FDT is strongly violated. The signal plotted in fig.6(b) has been measured when the system is relaxed and FDT is satisfied in all the frequency range. By comparing the two signals we immediately realize that there are very important differences. The signal

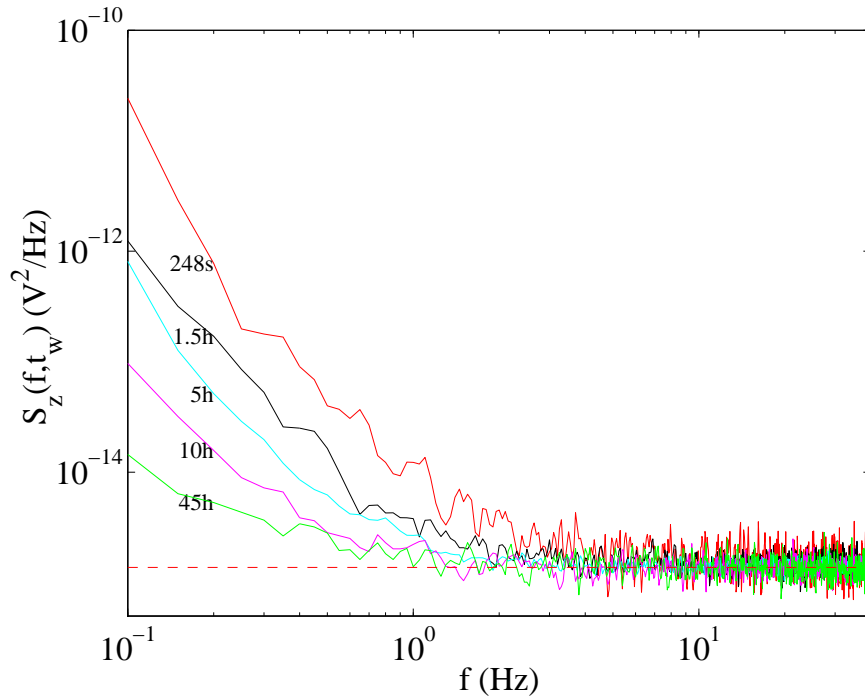


FIG. 3: **Voltage fluctuations for Laponite** Voltage noise density of one sample for different aging times. The horizontal dashed line is the FDT prediction

in fig.6(a) is interrupted by bursts of very large amplitude which are responsible for the increasing of the noise in the low frequency spectra (see fig.3). The relaxation time of the bursts has no particular meaning, because it corresponds just to the characteristic time of the filter used to eliminate the very low frequency trends. As time goes on, the amplitude of the bursts reduces and the time between two consecutive bursts becomes longer and longer. Finally they disappear as can be seen in the signal of fig.6(b) recorded after 50h when the system satisfies FDT. The evolution of the intermittent properties of the noise can be characterized by studying the probability density function(PDF) of the signal as a function of time. To compute the PDF, the time series are divided in several time windows and the PDF are computed in each of these window. Afterwards the result of several experiments are averaged. The PDF computed at different times are plotted in fig.7. We see that at short  $t_w$  the PDF presents very high tails which slowly disappear at longer  $t_w$ . Finally a Gaussian shape is recovered at  $t_w = 16h$ . This kind of evolution of the PDF clearly indicate that the signal is very intermittent at the very beginning and it relaxes to the Gaussian noise at very long times.

The comparison of these results with aging models will be done in the conclusions. We prefer to describe now another experiment in a completely different material.

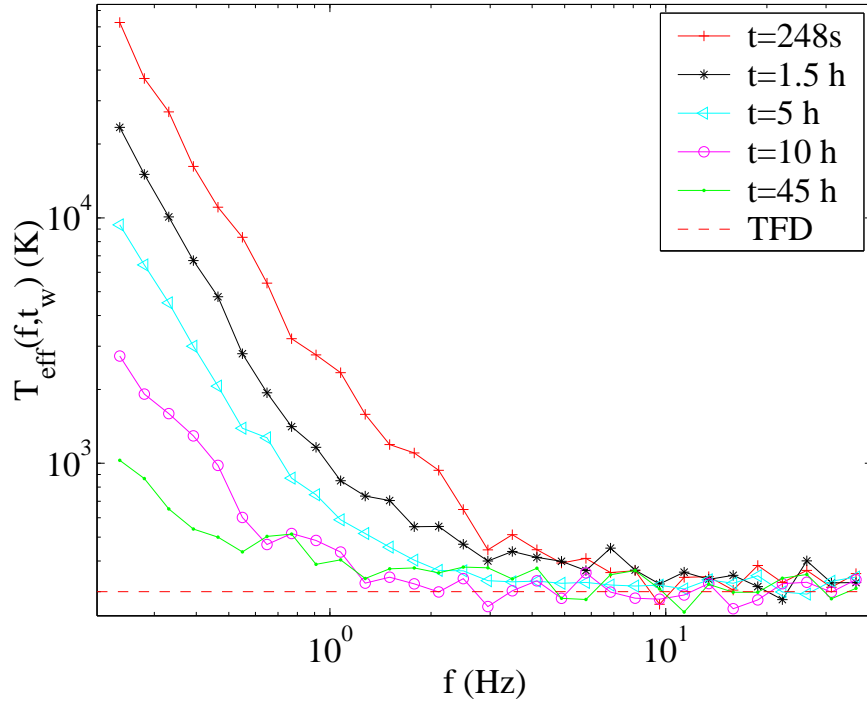


FIG. 4: **Effective temperature of Laponite** Effective temperature as a function of frequency for different aging times. As  $S_Z$  in fig.3,  $T_{eff}$  strongly increases and reaches huge values for low frequencies and short aging times.

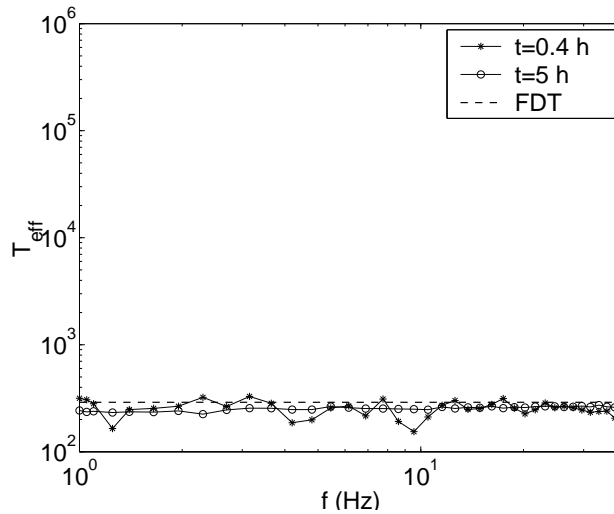


FIG. 5: **Effective temperature of an  $NaOH$  solution in water.** The effective temperature is plotted as a function of frequency for two different times after the preparation. This solution has a  $pH$  close to that of the Laponite, and no violation is observed in this case for any aging time.



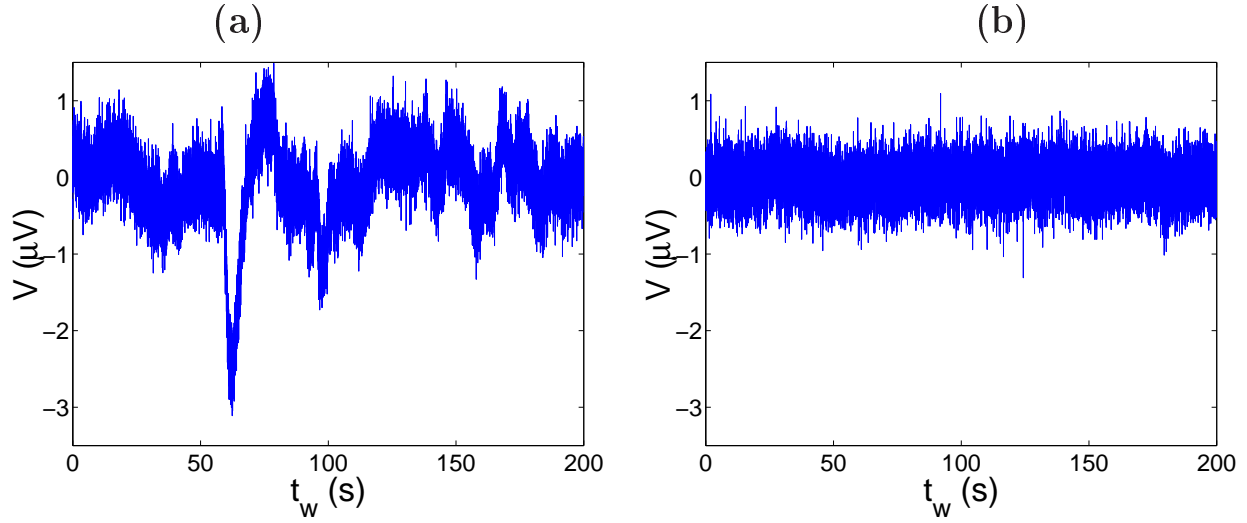


FIG. 6: **Voltage noise signal in Laponite** . (a) Noise signal, 2 hours after the Laponite preparation, when FDT is violated. (b) Typical noise signal when FDT is not violated.

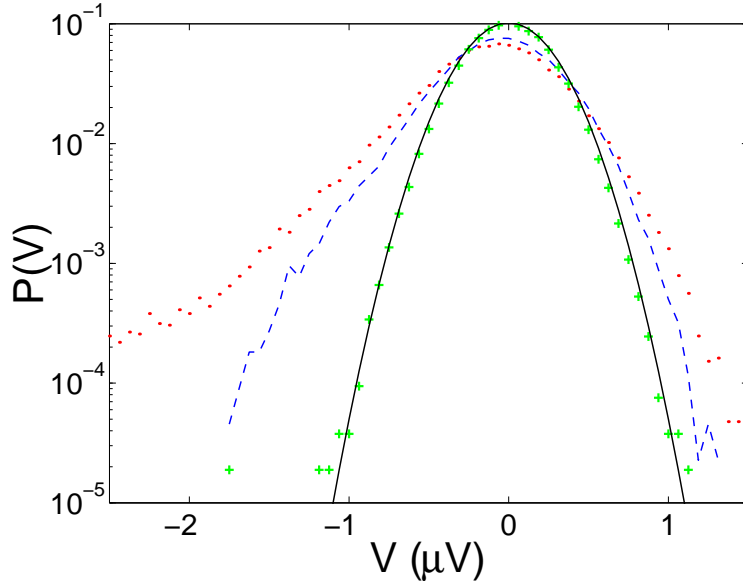


FIG. 7: **PDF of the voltage noise in Laponite** . Typical PDF of the noise signal at different times after preparation, with from top to bottom : (...)  $t_w = 1h$ , (--)  $t_w = 2h$ , (+)  $t_w = 50h$ . The continuous line is obtained from the FDT prediction.

### 3 Polycarbonate dielectric properties

In order to give more insight into the problem of the violation of FDT and of the intermittent behavior discussed in the previous section we have done wide band ( $20\text{mHz} - 100\text{Hz}$ ) measurements of the dielectric susceptibility and of the polarization noise in a polymer glass : polycarbonate. We present in this article several results which show a strong violation of the

FDT when this material is quenched from the molten state to below its glass-transition temperature. The effective temperature defined by eq.2 slowly relaxes towards the bath temperature. The violation is observed even at  $\omega t_w \gg 1$  and it may last for more than  $3h$  for  $f > 1Hz$ .

### 3.1 The experimental apparatus

The polymer used in this investigation is Makrofol DE 1-1 C, a bisphenol A polycarbonate, with  $T_g \simeq 419K$ , produced by Bayer in form of foils. We have chosen this material because it has a wide temperature range of strong aging [1]. This polymer is totally amorphous : there is no evidence of crystallinity [29]. Nevertheless, the internal structure of polycarbonate changes and relaxes as a result of a change in the chain conformation by molecular motions[1],[30],[31]. Many studies of the dielectric susceptibility of this material exist, but no one had an interest on the problem of noise measurements.

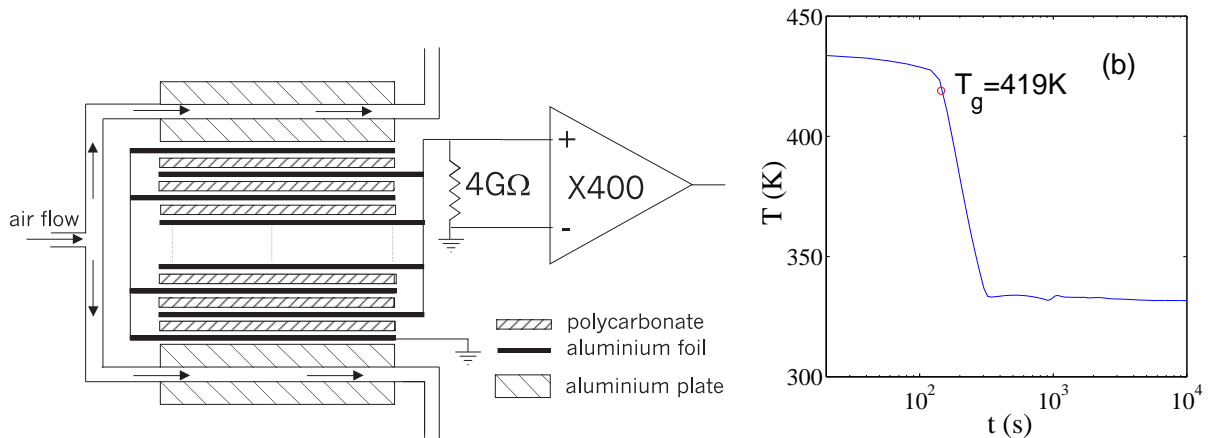


FIG. 8: (a) **Polycarbonate experimental set-up** (b) **Typical temperature quench** : from  $T_i = 433K$  to  $T_f = 333K$ , the origin of  $t_w$  is at  $T = T_g$ .

In our experiment polycarbonate is used as the dielectric of a capacitor. The capacitor is composed by 14 cylindrical capacitors in parallel in order to reduce the resistance of the sample and to increase its capacity. Each capacitor is made of two aluminum electrodes,  $12\mu m$  thick, and by a disk of polycarbonate of diameter  $12cm$  and thickness  $125\mu m$ . The experimental set-up is shown in fig.8a). The 14 capacitors are sandwiched together and put inside two thick aluminum plates which contain an air circulation used to regulate the sample temperature. This mechanical design of the capacitor is very stable and gives very reproducible results even after many temperature quenches. The capacitor is inside two Faraday screens to insulate it from external noise. The temperature of the sample is controlled within a few percent. Fast quench of about  $50K/min$  are obtained by injecting Nitrogen vapor in the air circulation of the aluminum plates. The electrical impedance of the capacitor is  $Z(\omega, t_w) = R/(1 + i\omega R C)$ , where  $C$  is the capacitance and  $R$  is a parallel resistance which accounts for the complex dielectric susceptibility. It is measured using a

Novocontrol Dielectric Analyzer. The noise spectrum of this impedance  $S_Z(\omega, t_w)$  is :

$$S_Z(f, t_w) = 4 k_B T_{eff}(f, t_w) \operatorname{Re}[Z(\omega, t_w)] = \frac{4 k_B T_{eff}(f, t_w) R}{1 + (\omega R C)^2} \quad (4)$$

where  $T_{eff}$  is the effective temperature of the sample. In order to measure  $S_Z(f, t_w)$ , we have made a differential amplifier based on selected low noise JFET(2N6453 InterFET Corporation), whose input has been polarized by a resistance  $R_i = 4G\Omega$ . Above  $2Hz$ , the input voltage noise of this amplifier is  $5nV/\sqrt{Hz}$  and the input current noise is about  $1fA/\sqrt{Hz}$ . The output signal of the amplifier is analyzed either by an HP3562A dynamic signal analyzer or directly acquired by a NI4462 card. It is easy to show that the measured spectrum at the amplifier input is :

$$S_V(f, t_w) = \frac{4 k_B R R_i ( T_{eff}(f, t_w) R_i + T_R R + S_\xi(f) R R_i)}{(R + R_i)^2 + (\omega R R_i C)^2} + S_\eta(f) \quad (5)$$

where  $T_R$  is the temperature of  $R_i$  and  $S_\eta$  and  $S_\xi$  are respectively the voltage and the current noise spectrum of the amplifier. In order to reach the desired statistical accuracy of  $S_V(f, t_w)$ , we averaged the results of many experiments. In each of these experiments the sample is first heated to  $T_i = 433K$ . It is maintained at this temperature for 4 hours in order to reinitialize its thermal history. Then it is quenched from  $T_i$  to  $T_f = 333K$  in about 2 minutes. A typical thermal history of the quench is shown in fig.8(b). The reproducibility of the capacitor impedance, during this thermal cycle is always better than 1%. The origin of aging time  $t_w$  is the instant when the capacitor temperature is at  $T_g \simeq 419K$ , which of course may depend on the cooling rate. However adjustment of  $T_g$  of a few degrees will shift the time axis by at most 30s, without affecting our results.

### 3.2 FDR measurements

In fig.9(a) and (b), we plot the measured values of  $R$  and  $C$  as a function of  $f$  at  $T_i$  and at  $T_f$  for  $t_w \geq 200s$ . We see that lowering temperature  $R$  increases and  $C$  decreases. At  $T_f$  aging is small and extremely slow. Thus for  $t_w > 200s$  the impedance can be considered constant without affecting our results. From the data plotted in fig.9 (a) and (b) one finds that  $R = 10^{10}(1 \pm 0.05) f^{-1.05 \pm 0.01} \Omega$  and  $C = (21.5 \pm 0.05)nF$ . In fig.9(a) we also plot the total resistance at the amplifier input which is the parallel of the capacitor impedance with  $R_i$ . We see that at  $T_f$  the input impedance of the amplifier is negligible for  $f > 10Hz$ , whereas it has to be taken into account at slower frequencies.

fig.10(a) represents the evolution of  $S_V(f, t_w)$  after a quench. Each spectrum is obtained as an average in a time window starting at  $t_w$ . The time window increases with  $t_w$  so to reduce error for large  $t_w$ . Then the results of 7 quenches have been averaged. The longest time ( $t_w = 1 \text{ day}$ ) the equilibrium FDT prediction (continuous line) is quite well satisfied. We clearly see that FDT is strongly violated for all frequencies at short times. Then high frequencies relax on the FDT, but there is a persistence of the violation for lower frequencies. The amount of the violation can be estimated by the best fit of  $T_{eff}(f, t_w)$  in eq.5 where all other parameters are known. We started at very large  $t_w$  when the system is relaxed and  $T_{eff} = T$  for all frequencies. Inserting the values in eq.5 and using the  $S_V$  measured at

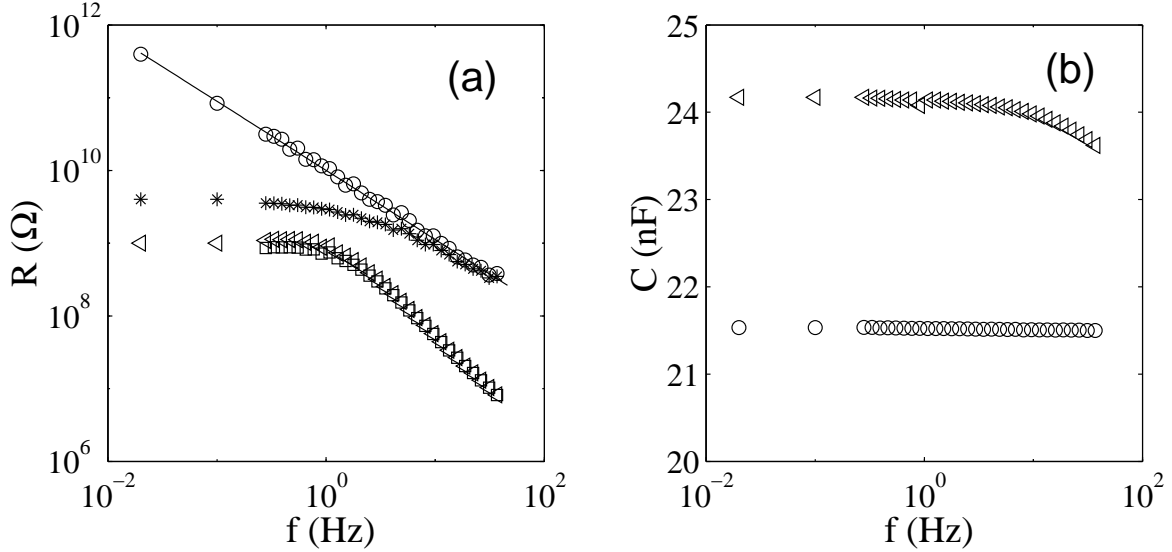


FIG. 9: **Polycarbonate response function** (a) Polycarbonate resistance  $R$  as a function of frequency measured at  $T_i = 433K$  ( $\triangleleft$ ) and at  $T_f = 333k$  ( $\circ$ ). The effect of the  $4G\Omega$  input resistance is also shown at  $T = 433K$  ( $\square$ ) and at  $T = 333K$  ( $*$ ). (b) Polycarbonate capacitance versus frequency measured at  $T_i = 433K$  ( $\triangleleft$ ) and at  $T_f = 333k$  ( $\circ$ ).

$t_w = 1days$  we find  $T_{eff} \simeq 333K$ , within error bars for all frequencies (see fig.10b). At short  $t_w$  data show that  $T_{eff}(f, t_w) \simeq T_f$  for  $f$  larger than a cutoff frequency  $f_o(t_w)$  which is a function of  $t_w$ . In contrast, for  $f < f_o(t_w)$  we find that  $T_{eff}$  is :  $T_{eff}(f, t_w) \propto f^{-A(t_w)}$ , with  $A(t_w) \simeq 1$ . This frequency dependence of  $T_{eff}(f, t_w)$  is quite well approximated by

$$T_{eff}(f, t_w) = T_f \left[ 1 + \left( \frac{f}{f_o(t_w)} \right)^{A(t_w)} \right] \quad (6)$$

where  $A(t_w)$  and  $f_o(t_w)$  are the fitting parameters. We find that  $1 < A(t_w) < 1.2$  for all the data set. Furthermore for  $t_w \geq 250$ , it is enough to keep  $A(t_w) = 1.2$  to fit the data within error bars. For  $t_w < 250s$  we fixed  $A(t) = 1$ . Thus the only free parameter in eq.6 is  $f_o(t_w)$ . The continuous lines in fig.10(a) are the best fits of  $S_V$  found inserting eq.6 in eq.5.

In fig.10(b) we plot the estimated  $T_{eff}(f, t_w)$  as a function of frequency at different  $t_w$ . We see that just after the quench  $T_{eff}(f, t_w)$  is much larger than  $T_f$  in all the frequency interval. High frequencies rapidly decay towards the FDT prediction whereas at the smallest frequencies  $T_{eff} \simeq 10^5K$ . Moreover we notice that low frequencies decay more slowly than high frequencies and that the evolution of  $T_{eff}(f, t_w)$  towards the equilibrium value is very slow. From the data of fig.10(b) and eq.6, it is easy to see that  $T_{eff}(f, t_w)$  can be superposed onto a master curve by plotting them as a function of  $f/f_o(t_w)$ . The function  $f_o(t_w)$  is a decreasing function of  $t_w$ , but the dependence is not a simple one, as it can be seen in the inset of fig.10(b). The continuous straight line is not fit, it represents  $f_o(t_w) \propto 1/t_w$  which seems a reasonable approximation for these data. For  $t_w > 10^4s$  we find the  $f_o < 1Hz$ . Thus we cannot follow the evolution of  $T_{eff}$  anymore because the contribution of the experimental noise on  $S_V$  is too big, as it is shown in fig.10(b) by the increasing of the error bars for

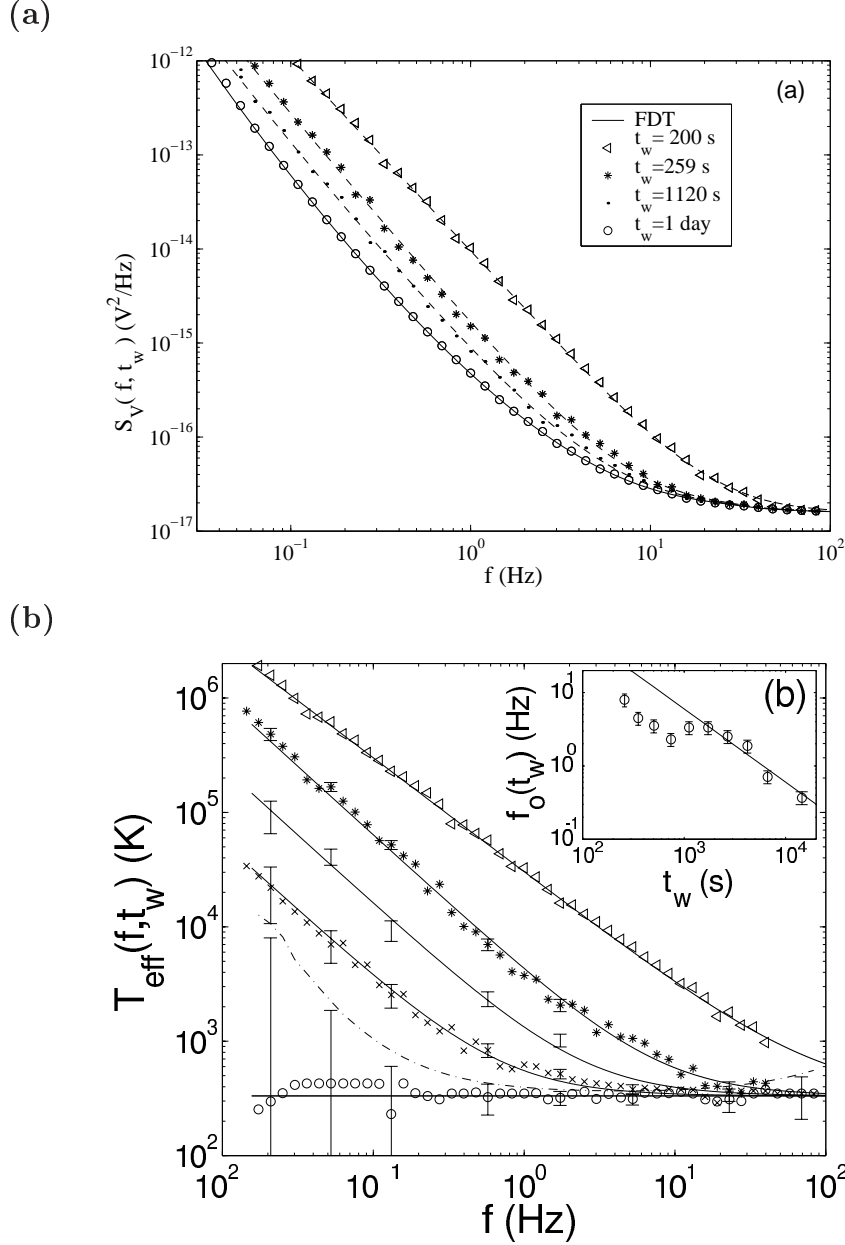


FIG. 10: **Voltage noise and effective temperature in polycarbonate** (a) Noise power spectral density  $S_V(f, t_w)$  measured at  $T_f = 333K$  and different  $t_w$ . The spectra are the average over seven quenches. The continuous line is the FDT prediction. Dashed lines are the fit obtained using eq.5 and eq.6 (see text for details). (b) Effective temperature vs frequency at  $T_f = 333K$  for different aging times : ( $\triangleleft$ )  $t_w = 200$  s, ( $*$ )  $t_w = 260$ s, ( $\bullet$ )  $t_w = 2580$ s, ( $\times$ )  $t_w = 6542$ s, ( $\circ$ )  $t_w = 1$  day. The continuous lines are the fits obtained using eq.6. The horizontal straight line is the FDT prediction. The dot dashed line corresponds to the limit where the FDT violation can be detected. In the inset the frequency  $f_o(t_w)$ , defined in eq.6, is plotted as a function of  $t_w$ . The continuous line is not a fit, but it corresponds to  $f_o(t_w) \propto 1/t_w$ .

$t_w = 1 \text{ day}$  and  $f < 0.1\text{Hz}$ .

Before discussing these experimental results we want to compare them to the single frequency experiment performed on glycerol [20]. In this experiment,  $T_{eff}$  has been measured only at  $7\text{Hz}$ . Thus we studied how  $T_{eff}(7\text{Hz}, t_w)$  depends on  $t_w$  at  $7\text{Hz}$  in our experiment. The time evolution of  $T_{eff}(7\text{Hz}, t_w)$  is plotted as a function of  $t_w$  in fig.11a). The time evolution of  $T_{eff}(2\text{Hz}, t_w)$  is also plotted just to show the large temperature difference between two frequencies. Let us consider the evolution at  $7\text{Hz}$  only. As in the experiment of ref.[20], we confirm the fact that the violation is observed even if  $\omega t_w \gg 1$ , which is in contrast with theoretical predictions. The biggest violation is for short times after the quench where the effective temperature is surprisingly huge : around  $800\text{K}$  at  $7\text{Hz}$  and  $t_w = 300\text{s}$ . In the experiment on glycerol the first data reported are for  $t_w > 1000\text{s}$ . Thus if we consider only data at  $t_w > 1000\text{s}$  in fig.11a) we see that our results are close to those of ref.[20]. Indeed at  $t_w = 1000\text{s}$  we find in our experiment  $(T_{eff} - T_f)/(T_g - T_f) \simeq 2.4$  The glycerol data give  $(T_{eff} - T_f)/(T_g - T_f) \simeq 1$ . Thus the relative violations of FDT at  $7\text{Hz}$  are very close in glycerol and polycarbonate. However it would be interesting to check whether at shorter times and at lower frequencies large  $T_{eff}$  could be observed in glycerol too.

In order to compare with theoretical predictions [8, 11] and recent spin glass experiment [23] we may plot the integrated response  $R(t, t_w)$  as a function of the correlation  $C(t, t_w)$ . The latter is obtained inserting measured  $T_{eff}(f, t_w)$  in eq.4 and by Fourier transforming this equation.  $R(t, t_w)$  can be computed by Fourier transforming  $Real[Z(\omega, t_w)]$ . FDR now takes the form [11] :

$$-C(t, t_w) + C(t_w, t_w) = k_B T_{eff}(t, t_w) R(t, t_w) \quad (7)$$

In the inset of fig.11b), we see that for  $t_w > 300\text{s}$  the shape of the decay of  $C(t_w, t)$  remains essentially the same. Indeed data for different  $t_w$  can be scaled onto a single master curve by plotting  $C(t_w, t)$  as a function  $(t - t_w)/t_o(t_w)$ , where  $t_o(t_w)$  is an increasing function of  $t_w$  : approximately  $t_o(t_w) \propto \log(t_w)$  for  $t_w > 500\text{s}$ . The self-similarity of correlation functions, found on our dielectric data, is a characteristic of the universal picture of aging [9, 11, 14, 15, 32], which has been also observed in spin-glass experiment [23] and in the structure function of the dynamic light scattering of colloidal gels [33]. Thus our results confirm that this picture of aging applies also to the polymer dielectric measurements. To further investigate this aging, we plot, in fig.11b),  $R(t, t_w)$  as a function  $(-C(t, t_w) + C(t_w, t_w))/k_B$  at different  $t_w$ . The slope of this graph gives  $1/T_{eff}$ . The symbols correspond to the data whereas the dashed line are obtained by inserting the best fit of  $T_{eff}$  in eq.6, in eq.4. We clearly see that data at small  $C(t, t_w)$  asymptotically converge to an horizontal straight line, which means that the system has an infinite temperature. At short time, large  $C(t, t_w)$ , FDT prediction is recovered (continuous straight line of slope  $1/T_f$ ). This result is quite different to what has been observed in recent experiments on spin glasses where  $T_{eff} \simeq 5T_g$  has been measured[23]. In contrast infinite  $T_{eff}$  has been observed during the sol gel transition [21] and in numerical simulation of domain growth phenomena[16].

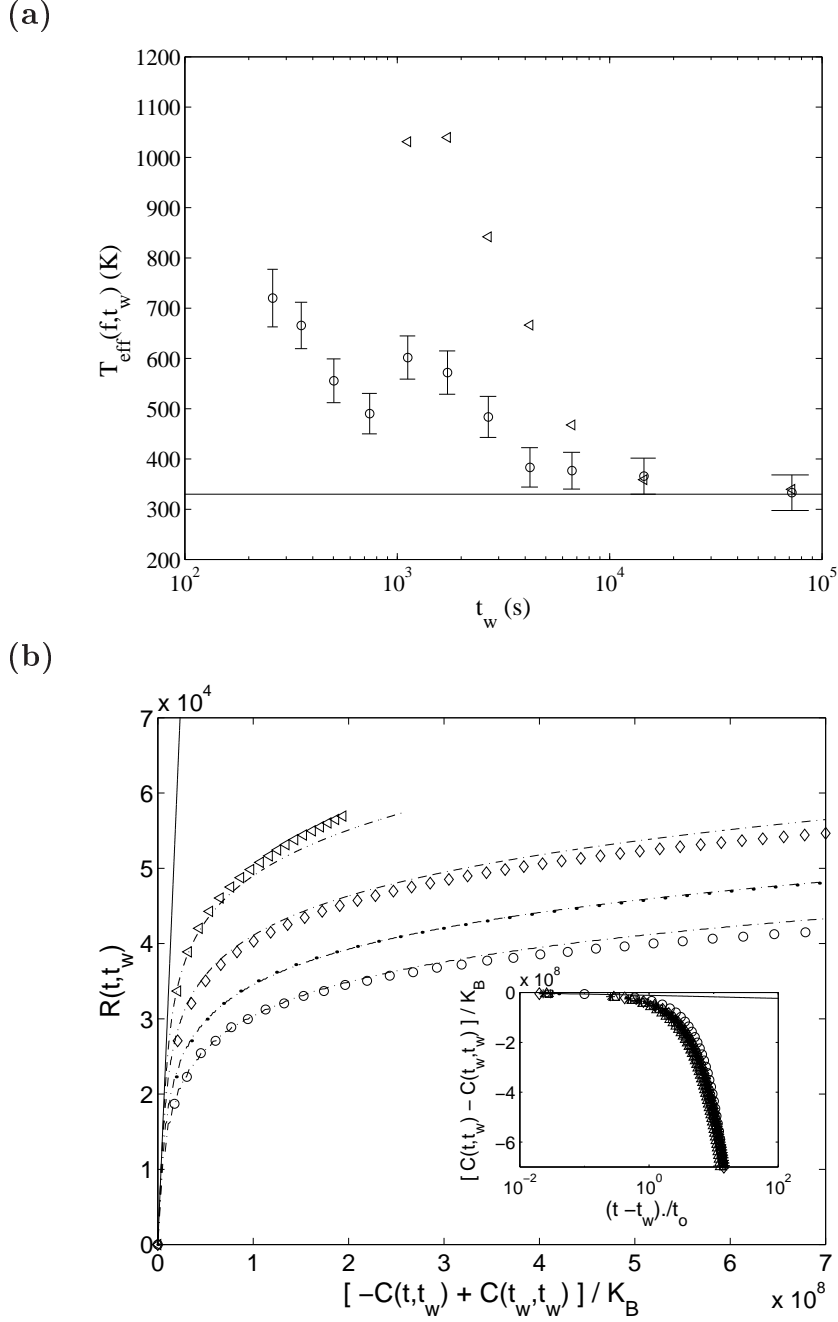


FIG. 11: **Violation of FDT in polycarbonate** (a) Effective temperature at  $7Hz$  ( $\circ$ ) and  $2Hz$  ( $\triangleleft$ ) measured as a function of  $t_w$  at  $T_f = 333K$ . b) Plot of the integrated response  $R(t, t_w)$  as a function of  $-C(t, t_w) + C(t_w, t_w)$  at different  $t_w$ . Symbols correspond to the data : ( $\circ$ )  $t_w = 256s$ , ( $\bullet$ )  $t_w = 353s$ , ( $\diamond$ )  $t_w = 4200s$ , ( $\triangleleft$ )  $t_w = 6542s$ . The dashed lines are obtained from the best fits (see text for details). In the inset  $C(t, t_w) - C(t_w, t_w)$  is plotted as a function of time for several  $t_w = 250s; 353s; 503s; 1120s; 1624s; 2583s; 4200s$ . The correlation functions have been superposed by scaling  $t - t_w$  by a characteristic time  $t_o(t_w)$  which is an increasing function of  $t_w$ .

### 3.3 Statistical analysis of the noise

In order to understand the origin of such large deviations in our experiment we have analyzed the noise signal. We find that the signal is characterized by large intermittent events which produce low frequency spectra proportional to  $f^{-\alpha}$  with  $\alpha \simeq 2$ . Two typical signals recorded at  $1500s < t_w < 1900s$  and  $t_w > 75000s$  are plotted in fig.12. We clearly see that in the signal recorded at  $1500s < t_w < 1900s$  there are very large bursts which are on the origin of the frequency spectra discussed in the previous section. In contrast in the signal (fig.12b), which was recorded at  $t_w > 75000s$  when FDT is not violated, the bursts are totally disappeared.

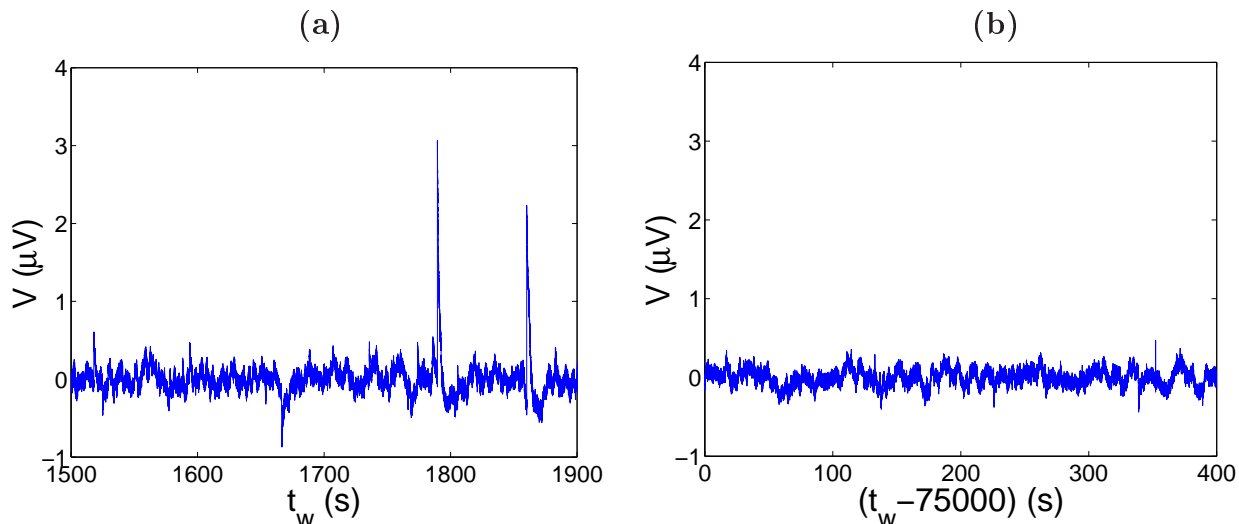


FIG. 12: **Voltage noise signal in polycarbonate** Typical noise signal of polycarbonate measured at  $1500s < t_w < 1900s$  (a) and  $t_w > 75000s$  (b)

As for Laponite we have studied the PDF of the signal as a function of  $t_w$  for polycarbonate. The results are shown in fig.13. We clearly see that the PDF, measured at small  $t_w$ , has very high tails which becomes smaller and smaller at large  $t_w$ . Finally the Gaussian profiles is recovered after  $24h$ . This strongly intermittent dynamics is reminiscent of the intermittence observed in the local measurements of polymer dielectric properties [34] and in the slow relaxation dynamics of a colloidal gel [35]

## 4 Discussion and conclusions

Let us resume the main results of the two experiments described in the previous sections. We have seen that dielectric measurements of Laponite, during the sol-gel transition, and of polycarbonate, after a temperature quench, show a strong violation of FDT. The effective temperature defined by eq.2 is huge at small  $t_w$  and slowly relaxes towards the bath temperature. In contrast to theoretical predictions the violation is observed even at  $\omega t_w \gg 1$  and it may last for more than  $3h$  for  $f > 1Hz$ . We have then investigated the behavior of the noise signals and we have shown that the huge  $T_{eff}$  is produced by very large intermittent



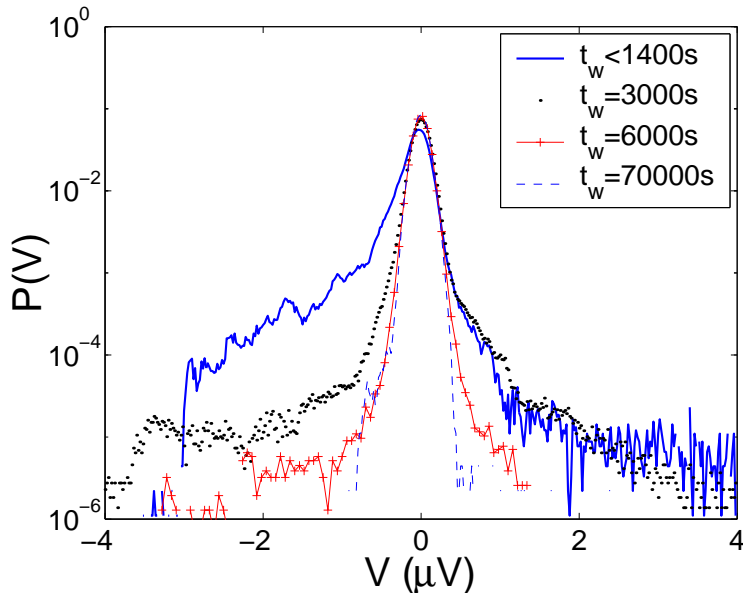


FIG. 13: **PDF of voltage noise in polycarbonate** Typical PDF of the noise signal of polycarbonate measured at various  $t_w$

bursts which are at the origin of the low frequency power law decay of noise spectra. Furthermore we have also shown that for both materials the statistic of this event is strongly non Gaussian when FDT is violated and slowly relaxes to a Gaussian one at very long  $t_w$ . Thus these two very different materials have a very similar relaxation dynamics, characterized by a strong intermittency. This strongly intermittent dynamics is reminiscent of the intermittence observed in the local measurements of polymer dielectric properties. [34]. Furthermore recent measurements done, using time resolved correlation in diffusing wave spectroscopy, have shown a strong intermittency in the slow relaxation dynamics of a colloidal gel [35]. This kind of behavior can indeed be interpreted on the basis of the trap model [5], which predicts non trivial violation of FDT associated to an intermittent dynamics. The system evolves in deeper and deeper valleys on the energy landscape. The dynamics is fundamentally intermittent because either nothing moves or there is a jump between two traps. In our case these jumps could explain the presence in the dielectric voltage noise of very large and rare peaks with a slow relaxation after the jump. Clear answers to this question can be given by a detailed study of the statistics of the time intervals between large peaks. This work is in progress.

This work clearly shows the importance of associating thermal noise and response measurements. Many questions remain opened on the subject of FDR in out of equilibrium systems. One may wonder whether different couples of conjugated variables give the same  $T_{eff}$  as defined by eq.2. For example FDR measured on the rheological properties of Laponite show no violation of FDT [22]. The reasons of these differences between electrical and mechanical measurements are unclear and much work is necessary to give new insight on these problems.

### Acknowledgments

We acknowledge useful discussion with J. Kurchan and J.P. Bouchaud. We thank P. Metz and F. Vittoz for technical support. This work has been partially supported by the Région Rhône-Alpes contract “Programme Thématique : Vieillissement des matériaux amorphes”.

## Références

- [1] L.C. Struick, *Physical aging in amorphous polymers and other materials* (Elsevier, Amsterdam, 1978).
- [2] M.Kroon, G. H. Wegdam, R. Sprik, *Dynamic light scattering studies on the sol-gel transition of a suspension of anisotropic colloidal particles*, Phys. Rev. E, **54**, p.1 (1996).
- [3] K. Jonason, E. Vincent, J. Hamman, J. P. Bouchaud, Memory and chaos effects in spin glasses, Phys. Rev. Lett., 81, 3243 (1998).
- [4] L. Bellon, S. Ciliberto, C. Laroche, Advanced Memory effects in the aging of a polymer glass, Eur. Phys. J. B., 25, 223, 2002.
- [5] J.P. Bouchaud, D. S. Dean, *Aging on Parisi’s tree*, J. Phys. I France, **5**, 265 (1995).
- [6] D. S. Fisher, D. A Huse, *Ordered phase of short range ising spin-glasses*, Phys. Rev. Lett., 56, 1601 (1986); D. S. Fisher, D. A Huse, *Nonequilibrium dynamics in spin glasses*, Phys. Rev. B, 38, 373, (1988).
- [7] J. Bertin, J. P. Bouchaud : J. Phys. A 35, 3039 (2002)
- [8] L. Cugliandolo, J. Kurchan, *Analytical Solution of the Off Equilibrium Dynamics of a Long Range Spin Glass Model*, Phys. Rev. Lett., **71**, p.173, (1993).
- [9] J.P. Bouchaud, L. F. Cugliandolo, J. Kurchan, M. Mézard, *Out of equilibrium dynamics in Spin Glasses and other glassy systems*, in *Spin Glasses and Random Fields*, ed A.P. Young (World Scientific, Singapore 1998). (also in cond-mat/9702070)
- [10] L. Cugliandolo, *Effective temperatures out of equilibrium*, to appear in *Trends in Theoretical Physics II*, eds. H Falomir et al, Am. Inst. Phys. Conf. Proc. of the 1998 Buenos Aires meeting, cond-mat/9903250
- [11] L. Cugliandolo, J. Kurchan, L. Peliti, *Energy flow, partial equilibration and effective temperatures in systems with slow dynamics*, Phys. Rev. E **55**, p. 3898 (1997).
- [12] S.R. de Groot, P. Mazur, *Non equilibrium thermodynamics*, (Dover, 1984)
- [13] G. Parisi, *Off-Equilibrium Fluctuation-Dissipation Relation in Fragile Glasses* Phys. Rev. Lett., **79**, p.3660 (1997).
- [14] W. Kob, J. L. Barrat, *Aging effects in a Lennard Jones Glass*, Phys. Rev. Lett., **78**, p.4581 (1997);
- [15] J. L. Barrat, W. Kob, *Fluctuation dissipation ratio in an aging Lennard-Jones* Europhys. Lett., bf 46, p.637 (1999).
- [16] A. Barrat, *Monte-Carlo simulations of the violation of the fluctuation-dissipation theorem in domain growth processes*, Phys. Rev.,**E57**, p. 3629 (1998).
- [17] M. Sellitto, *Fluctuation dissipation ratio in lattice-gas models with kinetic constraints*, European Physical Journal,**B4**, p.135 (1998).

- [18] E. Marinari, G. Parisi, F. Ricci-Tersenghi, J. J. Ruiz-Lorenzo, *Violation of the Fluctuation Dissipation Theorem in Finite Dimensional Spin Glasses*, J. Phys. A : Math. Gen., **31**, p.2611 (1998)
- [19] L. Berthier, J. L. Barrat, J. Kurchan, *Two-times scales, two temperature scenario for nonlinear rheology*, Phys. Rev. E, **61**, 5464 (2000).
- [20] T. S. Grigera, N. Israeloff, *Observation of Fluctuation-Dissipation-Theorem Violations in a Structural Glass*, Phys. Rev. Lett., **83**, p.5038 (1999).
- [21] L. Bellon, S. Ciliberto, C. Laroche, *Violation of fluctuation dissipation relation during the formation of a colloidal glass*, Europhys. Lett., **46** (5), 637 (1999).
- [22] L. Bellon, S. Ciliberto, *Experimental study of fluctuation dissipation relation during the aging process*, Physica D, 168, 325 (2002).
- [23] D. Herrisson, M. Ocio, *Fluctuation-dissipation ratio of a spin glass in the aging regime*, Phys. Rev. Lett., **88**, 257702 (2002). (also *cond-mat/0112378*).
- [24] L. Buisson, A. Garcimartin, S. Ciliberto, submitted.
- [25] Laponite RD is a registered trademark of Laporte Absorbents, P.O Box 2, Cheshire, UK.
- [26] D. Bonn, H. Tanaka, G. Wegdam, H. Kellay, J. Meunier, *Aging of a colloidal "Wigner" glass*, Europhysics Letters, **45**, p.52 (1999) ; D. Bonn, H. Kellay, H. Tanaka, G. Wegdam, J. Meunier, *Langmuir*, **15**, p. 7534 (1999).
- [27] R. Hunter, *The foundation of colloid science*, (Oxford Science Publications, 1989)
- [28] J. Koryta, L. Dvorak and L. Kavan, *Principles of Electrochemistry - 2nd Ed.* (Wiley, 1993).
- [29] C.G. Robertson, G. L. Wilkes, *Long term volume relaxation of bisphenol A polycarbonate and atactic polystyrene*, *Macromolecules* **33**, 3954 (2000).
- [30] L. Saviot, E. Duval, J.F. Jal, A.J. Dianoux, *Very fast relaxation in polycarbonate glass* Eur. Phys. J. B., **17** (4), 661, (2000).
- [31] R. Quinson, *Caractérisation et modélisation de la déformation non élastique des polymères amorphes à l'état solide*, *Ph.D. thesis, (INSA), (1998)*.
- [32] L. Berthier, J. P. Bouchaud, *Geometrical Aspects of Aging and Rejuvenation in the Ising Spin Glass : A Numerical Study*, *Physical Review B*, **66**, 054404 (2002) ; also *cond-mat/0202069v1*.
- [33] L. Cipelletti, S. Manley, R. C. Ball, D. A. Weitz, *Universal aging features in the restructuring of fractal colloidal gels*, *Phys. Rev. Lett.*, **84**, 2275 (2000).
- [34] E. Vidal Russel, N. E. Israeloff, *Direct observation of molecular cooperativity near the glass transition*, *Nature*, **408**, 695 (2000).
- [35] L. Cipelletti, H. Bissig, V. Trappe, P. Ballestat, S. Mazoyer, submitted *J. Phys : Cond. Mat.*