

Lattice gas models of coherent strained epitaxy

V. I. Tokar^{1,2} and H. Dreyss¹

¹ IPCM S-GEMM, UMR 7504 CNRS, 23,

rue du Loess, F-67037 Strasbourg Cedex, France

²Institute of Magnetism, National Academy of Sciences,

36-b Vernadsky str., 03142 Kiev-142, Ukraine

(Dated: March 22, 2024)

Abstract

The harmonic Frenkel-Kontorova model is used to illustrate with an exactly solvable example a general technique of mapping a coherently strained epitaxial system with continuous atomic displacements onto a lattice gas model (LGM) with only discrete variables. The misfit strain of the original model is transformed into cluster interatomic interactions of the LGM. The clusters are contiguous atomic chains of all lengths but the interaction strength for long chains is exponentially small. This makes possible the application of efficient Monte Carlo techniques developed for discrete variables both in kinetic and equilibrium simulations. The formalism developed can be applied to 1D as well as to 2D systems. As an illustrative example we consider the problem of self-organization of 1D size calibrated clusters on the steps of the vicinal surfaces.

PACS numbers: 05.65.+b, 68.66.La, 81.16.Dn

I. INTRODUCTION

The phenomena of self-assembly and self-organization of coherent (i. e., dislocation-free) size calibrated nano- and atomic-scale structures observed during the heteroepitaxial growth in some systems^{1,2} are considered to be promising tools for fabrication of microelectronic devices³.

A major factor influencing the phenomenon of self-assembly is the lattice mismatch (LSM) between the substrate and the growing overlayer commonly encountered in heteroepitaxial systems⁴. The LSM-induced strain is believed to be the driving force behind the above phenomena^{4,5}. So an adequate account of the strain effects should lie at the basis of any theory of strained epitaxy. Because strained systems exhibit complicated kinetics and morphologies, analytic approach is difficult, so a major technique in theoretical studies of strained epitaxy is the kinetic Monte Carlo simulation. The application of this technique, however, is severely hampered by the necessity to simulate the continuous atomic displacements. Because of this, atomistic models in such simulations are currently restricted to rather small systems consisting of only a few thousand atoms⁶ while experimentally observed 3D quantum dots sometimes consist of several tens of thousand atoms each².

Our research is based on the observation that as long as we are interested only in the coherent structures, there is a possibility to map the system onto a purely lattice model because in the absence of dislocations the relaxed atom can only either deviate from its symmetric position inside the same cell or to be displaced to another cell but there always exists a lattice site of a regular lattice to which this atom can be ascribed. So our first goal is to develop a formalism which would allow to map a coherent heteroepitaxial system with the continuous variables onto a lattice gas model with only discrete variables.

One of important goals of the heteroepitaxial studies is the development of techniques of growth of 1D quantum wires (QW) which can be used, e. g., for experimental investigation of the Luttinger model of interacting 1D electrons⁷. Furthermore, the QW may find application in microelectronics circuitry³, as well as in magnetic memory devices⁸. The latter applications would require the 1D structures of finite length. In the case of the memory devices it is also desirable that these atomic clusters (or chains) were of similar length and that they were arranged into periodic arrays in order to simplify the memory access. All these requirements can be satisfied by self-organized size calibrated structures similar to

quantum dots of the 2D epitaxy². A phenomenological theory explaining the mechanism of formation of quantum dots was proposed in Ref.⁵. The theory is quite general and can be applied to objects in any number of dimensions. So to illustrate the techniques developed in the present paper we will study the conditions of formation of the 1D size calibrated monatomic chains.

II. THE MODEL

A simple approach to theoretical description of the mist is provided by the 1D Frenkel-Kontorova model (FKM) which is frequently been used in qualitative^{9,10} and semi-quantitative studies¹¹ of strained epitaxy. To illustrate the generality of our approach we first present the formalism appropriate to the 2D epitaxy but in concrete examples we will restrict ourselves to the 1D case.

We consider an ensemble of a fixed number (N) of atoms coherently deposited on a surface with a square lattice of deposition sites. The rectangular lattice geometry was chosen because it allows for the separation of x and y variables (see Ref.⁹ and below). Let us first consider more general model with the energy of the epilayer of the form

$$U = \sum_i^X n_i V_s (R_i + u_i) + \frac{1}{2} \sum_{ij}^X n_i n_j V (u_i + R_i - u_j - R_j);$$

where $R_i = (a^x i_x; a^y i_y)$ (a the lattice constants in the two directions, i_x and i_y integers), $n_i = 0;1$ is the occupation number of site i , u_i the atomic displacement, V_s the potential of interaction with the substrate, and V the interatomic potential.

The analysis of the system considerably simplifies at low temperatures where it can be approximately reduced to a lattice gas model. This is achieved by exploiting the fact that the residence time of atoms at the lattice sites can be arbitrarily large due to the Arrhenius law obeyed by the probability of activated hopping over the potential barriers separating neighboring sites¹². The dynamics of the variables u_i , on the other hand, do not have any energy barriers. So at sufficiently low temperature these variables are capable of reaching their thermal equilibrium distribution during the time intervals between the atomic hops, i. e., with the atomic configuration remaining unchanged. Averaging over u_i will leave us with an effective non-equilibrium free energy function F_e of variables n_i only:

$$\exp(-F_e/k_B T) = \int \prod_{i=1}^N du_i \exp(-U/k_B T); \quad (1)$$

This purely lattice model can be further used in both equilibrium and kinetic studies.

For the purposes of qualitative analysis it will suffice to average out the displacement variables in Eq. (1) in the harmonic approximation, i. e., by expanding V_s and V_p in the above equation up to the second order in the displacement variables u_i ^{11,13} which is valid for small $|u_i|$. This allows to perform the calculation exactly (see below). However, the integration can be extended to approximately account also for anharmonic terms. This extension, besides making the approach more accurate, can also account for some qualitative phenomena¹⁰.

To facilitate comparison with other studies based on the Frenkel-Kontorova model^{9,10,11,14} we write the harmonic approximation as the second order power series expansion in u_i for V_s and in $u_i - u_j$ for the pair potential V_p :

$$\begin{aligned} U &= V_s N + \frac{1}{2} \sum_i n_i k_s (u_i)^2 + \frac{1}{2} \sum_{ij} n_i n_j V_{ij} \\ &\quad + \frac{1}{2} \sum_i k_p [(u_i - u_{i+}) - f]^2 - f^2 n_i n_{i+} \\ &= V_s N + \frac{1}{2} \sum_{ij} V_{ij} n_i n_j \\ &\quad + \frac{1}{2} \sum_{ij} k_p D_{ij} u_i u_j + \sum_i k_p f u_i r_i n_i n_{i+} \end{aligned} \quad (2)$$

where V_s and V_{ij} are the values of the substrate and the pair potentials at the lattice sites for the atom in the symmetric position (the zero order approximation), x or y component; $f = -V^0 = -V^0$ (where V is the pair potential) is interpreted as the misfit parameter in the direction x , k_s and k_p are the second derivatives of the corresponding potentials, D_{ij} is the dimensionless dynamical matrix defined by this equality, and $r_i = F_i / F_i$. A major simplification is achieved under the nearest neighbor (NN) approximation for the relaxation because, as is seen from the last line of Eq. (2), in this case the variables u_i^x and u_i^y separate, and the relaxations along the two directions are independent.

With approximation (2) the statistical average amounts to the Gaussian integration to give

$$\begin{aligned} F_e &= V_s N + \frac{1}{2} \sum_{ij} n_i n_j V_{ij} - \frac{k_B T}{2} \sum_{ij} \ln \det G \\ &\quad - \frac{k_p f^2}{2} \sum_{ij} G_{ij} r_i n_i n_{i+} - r_j n_j n_{j+} ; \end{aligned} \quad (3)$$

where $G_{ij} = 1/D_{ij}$ and in V_s we gathered all terms which are proportional to the total particle number, such as the normalization of the determinant coming from the in-plane Gaussian integration and a similar term from the integration along z-direction. We do not discuss these contributions here because in the present study we restrict ourselves to systems with a fixed number of deposited atoms N . In case of necessity these terms can be easily recovered. We also note the entropic contribution (the second term in the first line) which naturally appears in our formalism and which was shown to be crucial for proper description of the processes of deposition¹⁵ as well as for the correct prediction of the shape of the atomic clusters¹⁶.

Because of the gradient factors, only the ends of contiguous chains of atoms contribute into the last term of Eq. (3) leaving two matrix elements of G_{ij} in the sum over ij inside every chain: the diagonal one which we denote as $G_1^{(0)}$ (1 the length of the chain; we omit the superscript to simplify notation) and the matrix element $G_1^{(1,1)}$ connecting the two ends of the chain. Furthermore, in the NN approximation the matrix D is block-diagonal because the atoms belonging to different chains do not couple. Therefore, the determinant factorizes and the relaxation part of the free energy which consists of the terms in Eq. (3) containing G takes the form

$$F_{\text{relax}} = \sum_{\text{chains}} \left(\sum_{\text{chains}} \frac{k_B T}{2} \ln \det \frac{G_1}{G_1^{(0)}} + k_p f^2 [G_1^{(0)} - G_1^{(1,1)}] \right) E_1; \quad (4)$$

where the summation is over the chains consisting of two or more atoms. Besides, in the first term on the right hand side (r. h. s.) we subtracted the single atom entropy term by assuming that it is accounted for in V_s which we discarded to simplify notation. It is easy to show that F_{relax} can be expanded into an infinite sum of multiatom interactions of the form $V_1 n_i n_{i+\hat{x}} \dots n_{i+(l-1)\hat{x}}$, where \hat{x} is the unit vector in the direction \hat{x} . The expansion coefficients are given by the expression

$$V_l = E_l - 2E_{l-1} + E_{l-2} \quad (5)$$

valid for all $l \geq 2$ with $E_0 = E_1 = 0$.

III. THE RELAXATION FREE ENERGY

Omitting the superscript to simplify notation, the matrix D_{-1} for chain of length l is defined according to Eq. (2) as

$$k_p \sum_{ij} (D_{-1})_{ij} u_i u_j = k_s u_1^2 + k_p (u_1 - u_2)^2 + k_s u_2^2 + \dots + k_p (u_{l-1} - u_l)^2 + k_s u_l^2 \quad (6)$$

Hence, the square matrix $k_p D_{-1}$ have the following structure:

$$k_p D_{-1} = \begin{array}{c} \begin{array}{ccccccc} 0 & & & & & & 1 \\ \left. \begin{array}{c} \vdots \\ \vdots \\ \vdots \\ \vdots \\ \vdots \\ \vdots \\ \vdots \end{array} \right\} & \begin{array}{ccccccc} k_p + k_s & k_p & 0 & \dots & 0 & 0 & 0 \\ k_p & 2k_p + k_s & k_p & 0 & \dots & 0 & 0 \\ 0 & k_p & 2k_p + k_s & k_p & 0 & \dots & 0 \\ \vdots & \vdots & \ddots & \ddots & \ddots & \vdots & \vdots \\ 0 & \dots & 0 & k_p & 2k_p + k_s & k_p & 0 \\ 0 & 0 & \dots & 0 & k_p & 2k_p + k_s & k_p \\ 0 & 0 & 0 & \dots & 0 & k_p & k_p + k_s \end{array} & \left. \begin{array}{c} \vdots \\ \vdots \\ \vdots \\ \vdots \\ \vdots \\ \vdots \\ \vdots \end{array} \right\} \end{array} \quad (7)$$

In Appendix A we have shown that the matrix elements of $G_{-1} = 1/D_{-1}$ entering the expression for the relaxation free energy (4) can be calculated with the use of recursion formulas for the tridiagonal matrices as [see Eqs. (A 10) and (A 11)]

$$\begin{aligned} d_{l+1}^{(0)} &= 1 + d_l \\ d_{l+1}^{(1)} &= \det G_{l+1} = G_{l+1}^{(0)} b_l; \end{aligned} \quad (8)$$

where $b_l = k_s/k_p$; d_l and b_l are generated by the recursion relations

$$d_{l+1} = 1 + d_l \quad \text{and} \quad b_{l+1} = d_{l+1} b_l \quad (9)$$

The recursion relations (9) at large l drive d_l and b_l to the fixed point $d_?$; $b_?$:

$$d_? = 1 + \frac{s}{2} + \frac{s}{4} < 1 \quad (10)$$

$$b_? = 0 \quad (11)$$

This means that at large l $G_{-1}^{(0)}$ saturates to a constant value while $G_{-1}^{(1)} = \det G_{-1} - d_?^l$ [see Eqs. (8)]. This in particular means that the entropic contribution into F_{relax} which is proportional to $\ln(\det G_{-1})$ is asymptotically linear in l (see Fig. 1).

Two contributions into F_{relax} calculated with these formulas are shown in Fig. 1. The entropic contribution is negative because in our canonical ensemble formalism we discarded the entropy corresponding to N isolated atoms which is reflected in the denominator G_1 in the expression (4) for the free energy. This means, in particular, that when $k_p \rightarrow 0$ the atomic displacements within the cell become mutually independent (the on-site pair interactions do not depend on the atomic positions inside the cell), so $G_1 \rightarrow G_1 \hat{I}$, where \hat{I} is the unit matrix, and the entropy term tends to zero [see Eq. (4) and Fig. 1]. When k_p is not equal to zero, the atomic displacements become restricted by its neighbors, so their entropy diminishes. For large chains the interior atoms are practically in translationally invariant environment, so for long chains the entropy loss is proportional to L . The above restrictions on the atomic displacements are the more stringent the larger k_p . This is reflected in the slope of S_1 which is larger for smaller $k_s = k_p$ (see Fig. 1).

Because the entropic contribution in Eq. (4) is multiplied by T , at low temperature it can be neglected. The remaining term W_1 is negative and saturates to a finite value at large l (see Fig. 1b). From Eq. (2) it follows that the NN interatomic interaction $V_{NN} = V_{NN}^{\text{ch}} + k_p f^2$, where the first term (V_{NN}^{ch}) is some "chemical" interaction and the second term is the unrelaxed repulsion due to LSM. Thus, the relaxation energy in Eq. (4) is the difference between the relaxed elastic energy of the chain $E_{\text{rel}}^{\text{el}}(l)$ and the unrelaxed one $E_0^{\text{el}}(l) = (l-1)k_p f^2$ with both energies being positive, as it should be for elastic energies. Thus,

$$W_1 = E_{\text{rel}}^{\text{el}}(l) - E_0^{\text{el}}(l)$$

and is negative because relaxation lowers the energy. Now, if V_{NN}^{ch} is negative but such that V_{NN} is not too large, then the reduced chain energy $[W_1 + V_{NN}(l-1)]/l$ will have a minimum corresponding to an equilibrium chain length. In two dimensions these chains will unify in square platelets. Thus, our model contains the mechanism for the size calibration of atomic clusters which was phenomenologically described in Ref.⁵. In 2D this conclusion as well as the formula of Ref.⁵ were verified with the use of the Monte Carlo simulation¹⁷.

Because the entropic contribution S_1 (see Fig. 1a) is practically linear in l according to Eq. (5) which has the form of the discrete second derivative it essentially contributes only into the pair interaction V_2 (the multiatom contributions were found to be ~10%). Thus, the relaxation entropy formally amounts to effective NN interatomic repulsion which grows linearly with temperature. The entropic forces of this kind were earlier discovered in alloys

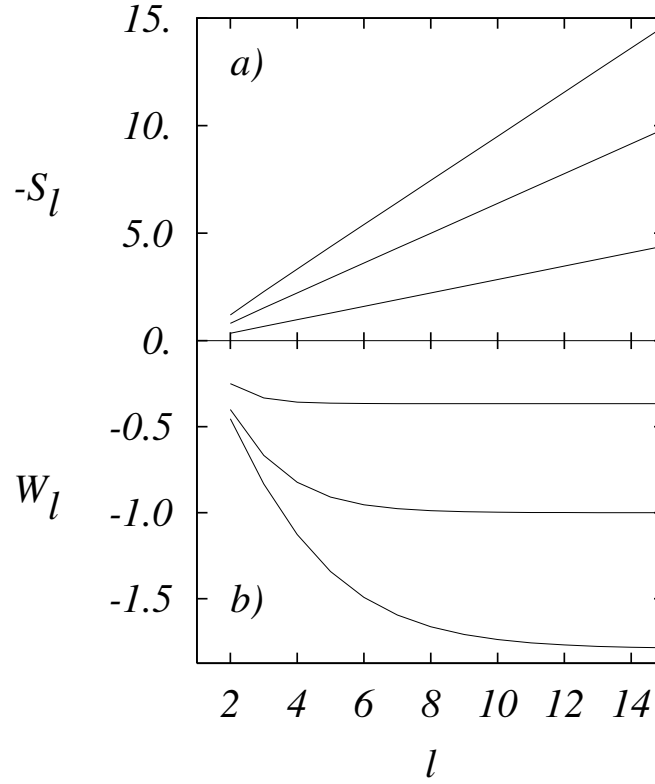


FIG. 1: Relaxation entropy in units of k_B (a) and relaxation energy in units of $k_B f^2$ (b) for chains of length l . At both figures the first curve from the horizontal zero axis corresponds to $\alpha = 2$, the second to $\alpha = 0.5$, and the third one to $\alpha = 0.2$ (note difference in scale).

(see Appendix E of Ref.¹⁸ and references to earlier literature therein).

At low temperature the main contributions into V_1 for $l \leq 3$ come from W_1 (Fig.1b). Because the r. h. s. of Eq. (5) has the form of the discrete second derivative and the curve $W_1(l)$ is concave, all multiatom interactions are repulsive. On the other hand, in the case under consideration when atoms are supposed to assemble into clusters, there should exist attractive interactions which in our model are necessarily the pair ones [see Eq. (2)].

IV. EXAMPLES FROM METALLIC HETEROEPITAXIAL SYSTEMS

To illustrate the above formalism with realistic examples of strained epitaxy we consider two metallic heteroepitaxial systems |Ag/Pt and Pt/Co| which currently are being actively studied both experimentally^{19,20,21} and theoretically^{22,23}. For simplicity we considered 1D case and used the geometry of Ref.²⁴ where the growth on the steps of the closed packed (111) vicinal surface was studied. The position of a deposited atom was relaxed to its equilibrium value in order to find the value k_s as the second derivative of the potential near equilibrium. The many-body "potentials" and corresponding parameters were taken

TABLE I: Parameters corresponding to the Pt/Co heteroepitaxial system

		$k_p f^2$ (eV)	V_{NN} (eV)
0%	0.32	0.049	-0.218
2%	0.25	0.100	-0.179
3%	0.22	0.136	-0.152

from Ref.²⁴ for the Ag/Pt system and from Ref.²³ for the Pt/Co system. These potentials were devised specially to application in the heteroepitaxy and for the (111) surfaces so we expect our results below are quite reliable. Other parameters listed in Table IV were calculated for the atomic pairs relaxed only in vertical position because in our approach we need the first and second derivatives [see discussion after Eq. (2)] calculated in the center of symmetry of the 1D cell. In both calculations only the NN interactions were taken into account because the NNN ones were found to be negligible.

According to our calculations the Ag/Pt system has the following parameters: (the energy unit is eV, the length unit Å): $V_{NN}^p = 0.57$, $V_{NNN}^p = 8.8 \cdot 10^3$, $k_p f^2 = 0.72$, and $\epsilon = 3.7$. The large value of ϵ means that the relaxation of the strain is very weak (see Fig. 1) so there is no size calibration with the above parameters. The crucial parameter ϵ , however, can strongly vary in different systems. For example, according to our estimates based on the potentials of Ref.²³, in Pt/Co $\epsilon = 0.32$ is an order of magnitude smaller. Because of this the system is quite close to the self-assembly but the misfit strain is still too small. To enhance the misfit, in our model calculations we assumed that the Co underlayer is further compressed (e.g., by means of deposition on an appropriate substrate) by the factor 1.05 (see Table IV and Fig. 2). But for ϵ below the critical value $\epsilon_c = 2\%$ there is no self-assembly at $T = 0$ because there is no minimum in $E_1(T = 0) = l$ (see Ref.⁵). However, because of the T -dependent entropic contribution in the effective energy (3), slightly below ϵ_c the system does exhibit the self-assembly at intermediate temperatures which, however, disappears as $T \rightarrow 0$ (see Fig. 2). Thus, our model predicts a new phenomenon which may be called the entropy driven transient self-assembly. For higher values of strain the $E_1(T = 0) = l$ curve does have a minimum (see Fig. 2) in which case the qualitative analysis of Ref.⁵ fully applies.

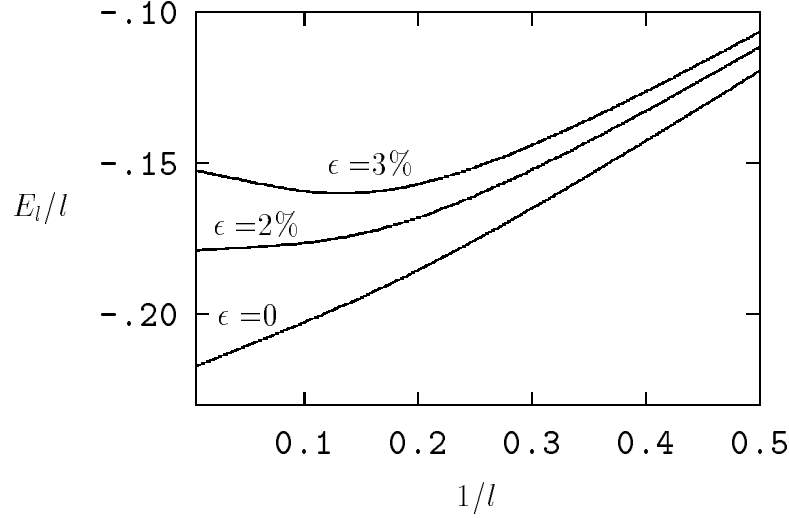


FIG. 2: Length dependence of the reduced energy at zero temperature of the Pt monatomic chains for different values of compression ϵ of the Co substrate.

V. CONCLUSION

In this paper we considered a simple model of strained 1D epitaxy and have shown that similarly to the 2D case the mechanism of self-assembly and size calibration proposed in Ref.⁵ is operative also in this case. We considered only two explicit examples for which there exist in literature reliable interatomic potentials and in one system already found the size calibration for stressed substrate. In our opinion, this shows that the above phenomena should be as common in 1D as they are in 2D heteroepitaxy. Further argument in favor of this conclusion is that for the size calibration to be plausible the crucial parameter $k_s = k_p$ should be as small as possible. This favors small values of k_s . However, the geometry considered in the present paper is not quite favorable because of the high coordination of the atoms deposited at the steps with 5 NN atoms of the substrate (see Ref.²⁴) which enhances k_s . It may be hoped that with lower coordination of the deposited atoms (as in the case of 1D structures of Ref.⁷) the conditions for the size calibration will be more favorable.

Acknowledgments

One of us (VT) expresses his gratitude to University Louis Pasteur de Strasbourg and IPCMS for their hospitality.

APPENDIX A

According to Eq. (7)

$$D_1 = \begin{pmatrix} 1+ & 1 & 0 & \cdots & 0 & 0 & 0 \\ & 1 & 2+ & 1 & 0 & \cdots & 0 & 0 \\ & 0 & 1 & 2+ & 1 & 0 & \cdots & 0 \\ & \vdots & \vdots & \ddots & \ddots & \ddots & \vdots & \vdots \\ & 0 & \cdots & 0 & 1 & 2+ & 1 & 0 \\ & 0 & 0 & \cdots & 0 & 1 & 2+ & 1 \\ & 0 & 0 & 0 & \cdots & 0 & 1 & 1+ \end{pmatrix}; \quad (A1)$$

where $\epsilon = k_s = k_p$. Because matrices D_1 are tri-diagonal, their determinants satisfy recurrence relations which can be used to calculate all quantities entering Eqs. (4) and (5). The diagonal element of the matrix $G_1 = 1/D_1$ is

$$G_1^{(0)} = r_{1-1} = \det D_1; \quad (A2)$$

where r_{1-1} is the determinant of the matrix obtained from D_1 by crossing out its first row and the first column:

$$r_{1-1} = \begin{pmatrix} 2+ & 1 & 0 & \cdots & 0 & 0 \\ & 1 & 2+ & 1 & 0 & \cdots & 0 \\ & 0 & 1 & 2+ & 1 & 0 & 0 \\ & \vdots & \vdots & \ddots & \ddots & \ddots & \vdots \\ & 0 & \cdots & 0 & 1 & 2+ & 1 \\ & 0 & 0 & \cdots & 0 & 1 & 1+ \end{pmatrix}; \quad (A3)$$

Expanding $\det D_1$ with respect to the first row we get

$$\det D_1 = (1 + \dots) r_{11} - r_{12} : \quad (A4)$$

Comparing this with Eq. (A2) we get

$$G_1^{(0)} = 1 = (1 + \dots d_{11}) ; \quad (A5)$$

where $d_{11} = r_{12} = r_{11}$. Now, expanding determinant Eq. (A3) with respect to the elements of the first row we get the following three term recurrence relation

$$r_{11} = (2 + \dots) r_{12} - r_{13} : \quad (A6)$$

But because Eq. (A2) includes only the ratio $r_{12} = r_{11}$ by dividing Eq. (A6) by r_{12} we can transform it to a simpler form

$$\frac{1}{d_{11}} = 2 + \dots d_{12} : \quad (A7)$$

The off-diagonal matrix element $G_1^{(11)}$ of the inverse matrix G_1 is equal to the ratio of the determinant of the matrix obtained from D_1 by crossing out its first row and the last column multiplied by $(-1)^{1+1}$ and divided by $\det D_1$. As is easy to see from Eq. (A1) the matrix thus obtained is a triangular matrix with the diagonal elements being all equal to -1. Hence its determinant is equal to $(-1)^{1-1}$ and

$$G_1^{(11)} = 1 = \det D_1 = \det G_1 : \quad (A8)$$

From Eq. (A4) we get

$$G_1^{(11)} = \frac{1}{\det D_1} = \frac{1}{r_{11}(1 + \dots d_{11})} = \frac{b_{11}}{1 + \dots d_{11}} = b_{11} G_1^{(0)} ; \quad (A9)$$

where $b_{11} = 1 = r_{11} = d_{11} b_{12}$ (see the definition of d_{11} above). Finally, making the shift $1-1 \rightarrow 1+1$ the above formulas can be summarized as

$$\begin{aligned} & \gtrsim G_{1+1}^{(0)} = 1 = (1 + \dots d_1) \\ & \gtrsim G_{1+1}^{(1)} = \det G_{1+1} = G_{1+1}^{(0)} b_1 ; \end{aligned} \quad (A10)$$

where d_1 and b_1 are generated by the recursion relations

$$d_{1+1} = 1 = (2 + \dots d_1) \quad \text{and} \quad b_{1+1} = d_{1+1} b_1 \quad (A11)$$

initialized by $d_0 = b_0 = 1$.

-
- ¹ D. J. Eaglesham and M. Cerullo, Phys. Rev. Lett. 64, 1943 (1990); Y.-W. Mo, D. E. Savage, B. S. Swartzentruber, and M. G. Lagally, Phys. Rev. Lett. 65, 1020 (1990); S. Guha, A. Madhukar, and K. C. Rajkumar, Appl. Phys. Lett. 57, 2110 (1990).
- ² R. Notzel, J. Temm yo, and T. Tamamura, Nature (London) 369, 131 (1994); D. Leonard et al., Appl. Phys. Lett. 63, 3203 (1993).
- ³ A. O. Orlov, I. Am lani, C. S. Lent, and G. L. Snider, Science 277, 928 (1997).
- ⁴ J. H. van der Merwe, D. L. Tonsing, and P. M. Stoop, Surf. Sci. 312, 387 (1994); M. Henzler, Surf. Sci. 357{358, 809 (1996); S. Tan, A. Ghazali, and J. C. S. Levy, Surf. Sci. 369, 360 (1996).
- ⁵ C. Priester and M. Lannoo, Phys. Rev. Lett. 75, 93 (1995).
- ⁶ K. E. Khor and S. D. Sam a, Phys. Rev. B 62, 16657 (2000).
- ⁷ P. Segovia, D. Purdie, M. Hensenberger, and Y. Baer, Nature (London) 402, 504 (1999).
- ⁸ J. Dorantes-D avila and G. M. Pastor, Phys. Rev. Lett. 81, 208 (1998).
- ⁹ J. A. Snyman and J. H. van der Merwe, Surf. Sci. 45, 619 (1974).
- ¹⁰ E. Konutcheva, A. M. Turiel, and I. Markov, Phys. Rev. B 61, 16890 (2000).
- ¹¹ S. C. Erwin, A. A. Baski, L. J. Whitman, and R. E. Rudd, Phys. Rev. Lett. 83, 1818 (1999).
- ¹² C. Uebing and R. Homer, J. Chem. Phys. 95, 7626 (1991).
- ¹³ B. G. Orr, D. Kessler, C. Snyder, and L. Sander, Europhys. Lett. 19, 33 (1992).
- ¹⁴ C. Ratsch and A. Zangwill, Surf. Sci. 293, 123 (1993).
- ¹⁵ J. A. Venables, Phys. Rev. B 36, 4153 (1987).
- ¹⁶ J. P. K. Doye and F. Calvo, Phys. Rev. Lett. 86, 3570 (2001).
- ¹⁷ V. I. Tokar and H. Dreyse, Molec. Phys. 100, 3151 (2002).
- ¹⁸ A. van de Walle and G. Ceder, Rev. Mod. Phys. 74, 11 (2002).
- ¹⁹ A. F. Becker, G. Rosenfeld, B. Poelsen a, and G. Comsa, Phys. Rev. Lett. 70, 477 (1993).
- ²⁰ P. Gambardella, M. Blanc, H. Brune, K. Kuhnke, and K. Kem, Phys. Rev. B 61, 2254 (2000).
- ²¹ P. Gambardella, M. Blanc, L. Burgi, K. Kuhnke, and K. Kem, Surf. Sci. 449, 93 (2000).
- ²² C. Goyhenex and G. Treglia, Surf. Sci. 446, 272 (2000).
- ²³ C. Goyhenex, H. Bubu, J.-P. Deville, and G. Treglia, Phys. Rev. B 60, 2781 (1999).

²⁴ F. Picaud, C. Ramseyer, C. Girardet, and P. Jensen, Phys. Rev. B 61, 16154 (2000).