Simulation study of N on-ergodicity Transitions: G elation in C olloidal System s with Short R ange A ttractions

Antonio M. Puertas

Department of Physics, University of Almeria, 04120 Almeria, Spain

Matthias Fuchs

Institut Charles Sadron, 67083 Strasbourg Cedex, France

Michael E. Cates

School of Physics, The University of Edinburgh, JCM B K ings Buildings, Edinburgh EH 9 3JZ, UK (D ated: M arch 22, 2024)

C om puter sin ulations were used to study the gel transition occurring in colloidal system s with short range attractions. A colloid-polymer mixture was modelled and the results were compared with mode coupling theory expectations and with the results for other system s (hard spheres and Lennard Jones). The self-intermediate scattering function and the mean squared displacement were used as the main dynamical quantities. Two dierent colloid packing fractions have been studied. For the lower packing fraction, -scaling holds and the wave-vector analysis of the correlation function shows that gelation is a regular non-ergodicity transition within MCT. The leading mechanism for this novel non-ergodicity transition is identied as bond formation caused by the short range attraction. The time scale and di usion coe cient also show qualitatively the expected behaviour, although dierent exponents are found for the power-law divergences of these two quantities. The non-G aussian parameter was also studied and very large correction to G aussian behaviour found. The system with higher colloid packing fraction shows indications of a nearby high-order singularity, causing -scaling to fail, but the general expectations for non-ergodicity transitions still hold.

I. IN TRODUCTION

C olloidal suspensions are often referred to as model system s for studying fundam entalproblem s in condensed m atterphysics [1]. M ost of the properties of colloidal system s are sim ilar to those of sim ple liquids, except for the di erence in the time scales involved in the processes in liquids or colloids, making the latter m ore useful in the study of some basic questions. M oreover, the interaction forces between particles in a colloidal system are easily tailored (e.g. by adding salt or polym er). How ever, there are som e features found only in colloids, such as aggregation or gelation, which makes the study of these system s even m ore fascinating.

Gel formation, or gelation, is found in systems with strong short-range attractions, and is a universal phenom enon observed experim entally in m any di erent systems, ranging from colloid-polymer mixtures [2, 3] to charged systems [4], or to globular protein systems [5]. Gelation is the form ation of a percolating network (typically fractal) of dense and more dilute regions of particles with voids which coarsen up to a certain size and freeze when the gel is form ed. This process is observed in the structure factor as a low -q scattering peak which m oves to lower q, increasing its height, and then arrests [6, 7, 8]. Description of this phenomenon has been attem pted with percolation theories, theories of phase separation for states inside the liquid-gas binodal (which is meta-stable with respect to uid-solid coexistence for short interaction ranges) or in term s of a glass transition of cluster of particles [8, 9].

Recently, acknow ledging its non-equilibrium charac-

ter, gelation has been interpreted using the form alism of mode coupling theory, MCT, for non-ergodicity transitions [10, 11, 12]. This approach views the gel as particles trapped by a network of bonds which hinders the particle motion, resulting in a non-ergodic state. Thus, gelation is caused by form ation of long lived bonds, whose collective arrest is described as a a norm alnon-ergodicity transition. (This is distinct from many earlier approaches whereby the bonds were assumed to form irreversibly from the outset.) In the present simulation study, we want to test this suggestion critically, thereby establishing the existence or otherwise of a non-ergodicity transition corresponding to bonding network form ation.

A lso present in colloidal system s is the equivalent of the usual glass transition in simple liquids, which occurs at high densities, and is driven by steric in prisonment. This transition has been studied experimentally and compared to MCT thoroughly [13, 14, 15, 16]. When two dimensions are observed in a system, MCT predicts a high order singularity in the region where the driving mechanisms for both transitions are present [17, 18, 19]. Therefore, a higher order transition is expected at high attraction strength and high density in colloidal system s with attractive interactions [10, 20, 21].

C om puter simulations have been used to test the expectations from M C T in m any di erent system s, such as a Lennard-Jones liquid [22, 23, 24, 25], water [26, 27], strong glass form ers [32, 33, 34] and polym ers [28, 29, 30, 31]. The tests have shown that the predictions from M C T are correct, not only qualitatively but also, in part, quantitatively [33, 35]. How ever, they have also pointed out som e di erences, especially in the spatial correlations

ofparticle m obility [36, 37, 38, 39]. In none of these sim – ulated system s, however, did gelation occur, presum ably because the attractions were not short-ranged enough.

In this work, we have used m olecular dynam ics sim ulations to study the properties of the gel transition, and compared them with the predictions from MCT. (This was initiated in [40] where some further results may be found.) We take the num erous universal predictions of the theory to test the scenario qualitatively. Com paring with quantitative predictions available for system s of hard spheres [41, 42], spheres with short range attractions [10, 11, 12, 21], and the mentioned simulation studies, we identify the novel mechanism driving the non-ergodicity transition which is the cause of gelation for moderately dense suspensions. Molecular dynamics were used instead of B row nian dynam ics because the choice of m icroscopic dynam ics does not a ect the relaxational dynam ics of a system close to a non-ergodicity transition [24]. By means of the Asakura-Oosawa interaction potential [43], we simulate the behaviour of a colloid-polymerm ixture, which is a well-understood system [44, 45, 46, 47]. For short interaction ranges, this system exhibits a uidcrystal transition, at interm ediate densities and increasing attraction strength, with a liquid-gas transition m etastable to the uid-crystal one. In our simulations, the system wasm odied to prevent both of these phase transitions from occurring, in order to be able to study the transition from the uid to the non-equilibrium states.

The paper is organized as follows: Section II describes some results from MCT which will be used in the subsequent analysis of the simulation results. In section III the simulation method is presented and the details are given. Section IV, deals with the results and is divided into four subsections studying i) the correlation function, ii) the time scale and the di usion coe cient, iii) the m ean squared displacement and iv) a higher colloid concentration. Finally, in section V, we present the conclusions of this work.

II. MODE COUPLING THEORY

In this section we will present the most important MCT results on non-ergodicity transitions. MCT attempts a description of the density correlator and its self part, in terms of a uctuating-force correlator [48, 49]. In this paper, only the self part of the density correlator will be studied, de ned as:

$$_{q}^{s}(t) = hexp fiq (r_{j}(t) r_{j}(0))gi$$
 (1)

where the brackets denote average over particle j and time origin, and q is the wave-vector. The equation of motion of $\frac{s}{q}$ in Brownian (coarse grained) dynamics, is given by:

$${}_{q} \mathcal{Q}_{t} {}_{q}^{s}(t) + {}_{q}^{s}(t) + {}_{q}^{s}(t) + {}_{0}^{m} {}_{q}(t t^{0}) \mathcal{Q}_{t^{0}} {}_{q}^{s}(t^{0}) dt^{0} = 0 \quad (2)$$

where $_q$ is a single particle di usive tim e scale and m $_q$ (t) is a mode coupling kernel which describes the cage effect [50]. W ithin MCT, glass states are given by non-zero solutions of this equation for the long time lim it of $_q^s$ (t! 1) = f_q^s , the so-called non-ergodicity parameter. It describes the glass structure and may also be called Lam b-M ossbauer factor. The glass transition is marked by a (generally) discontinuous transition from the unique trivial solution in the liquid, $f_q^s = 0$, to multiple solutions in the glass, $f_q^s > 0$, where only the highest solution is physical. G lass transitions can be classified according to the number, 1 1, of non-trivial solutions merging with the highest one, and the type of transition is noted as A_1.

For liquid states close to the glass, a two step decay is observed for the correlator; the plateau is at f_q^s and signals the proxim ity of the glass transition. A round this plateau, $\frac{s}{q}$ shows some universal properties, depending on the type of transition. For the m ost common type of transition, A₂, the decay to the plateau, and that from the plateau, can both be expressed as power law expansions. In particular, the decay from the plateau is given by:

$$f_q^{s}(t) = f_q^{s} + h_q^{(1)}(t=)^{b} + h_q^{(2)}(t=)^{2b} + O((t=)^{3b})$$
 (3)

with $h_q^{(1)}$ and $h_q^{(2)}$ amplitudes and the nal or relaxation time scale. b is known as the von Schweidler exponent, and depends on the details of the interaction potential. Expression (3) implies time scaling for the decay from the plateau, called -decay, for di erent states close to the glass transition. The time scale, , diverges as the glass transition is approached according to a power law, with an exponent, which can be related to the von Schweidler exponent: jj,with the distance to the transition [48, 49]. On the other hand, the wave-vector dependence of the non-ergodicity param eter and am plitudes gives som e non-universal properties of the transition, providing inform ation about the mechanism causing the non-ergodicity transition.

For high order singularities, the uid states close by show again a two step decay in the correlation function, but the decays to and from the plateau are no longer power law expansions. Instead, logarithm ic laws are obtained [18, 19]. A salient feature is that a logarithm ic decay around the plateau is predicted:

where $f_q^{\rm sA}$ is the non-ergodicity parameter of the high order singularity, C_q is an amplitude and t_1 is a time scale (the time when the correlator lies on the plateau).

The mean squared displacement (M SD) can be studied instead of the correlation function, obtaining a similar two step behaviour. Similar asymptotic laws to describe the decay to and from the plateau can be derived, and the parameters and exponents can be related to those of the correlation function [42]. The value of the plateau in the M SD de nes the localization length and is a measure of the size of the cage. How ever, it should be noticed that the cage, as formed by other particles, is constantly restructuring cooperatively. Only when the particles have broken free of their cages, di usive motion is observed, with a self-di usion coe cient, D $_{\rm s}$, that tends to zero as the glass transition is approached as D $_{\rm s}$ j j for the usual A₂ transitions.

Two di erent non-ergodicity transitions have been found in colloidal system s with a short range attraction [10, 21]: a steric hindrance driven glass transition and an attraction driven gel transition [10, 11, 12]. While the rst is found at high densities and is qualitatively sim ilar to the glass transition in the hard sphere system (HSS) or Lennard-Jones system (LJS), the gel transition occurs at high attraction strength for all volum e fractions. D i erent properties for these two transitions are predicted, the m ain di erence arising from the driving m echanism : the localization length is shorter in the gel than in the glass, resulting in higher non-ergodicity parameters. A lso, a sm aller von Schweidler exponent for the gel than for the glass is expected, im plying a higher value of , i.e. the transition as observed by $_{\rm q}$ or D $_{\rm s}$ is more abrupt.

The actual shape of the non-ergodicity transition line depends on the details of the interaction potential, although som e general features can be found. From lower to higher interaction strength, the glass line, is slanted to higher concentrations, show ing that a weak attraction uidizes the glass. However, at even higher interaction strengths, the gel transition occurs at lower colloid density the higher the attraction strength. As a result, a re-entrance transition is obtained at high colloid volum e fractions. The line may be wedge-shaped or curved in this region, depending on the range of the interaction. If the line is wedge-shaped a high-order transition (generically A₃) is present near the corner, whereas none exists if the line is sm oothly continuous. An A₄ singularity appears right at the vanishing of the A₃ point when the line rst becom es sm ooth [21].

III. SIM ULATION DETAILS

Equilibrium molecular dynamics simulations minicking a colloid-polymer mixture were performed for a system composed of 1000 soft-core polydisperse colloidal particles. The core-core interaction between particles was modeled by:

$$V_{sc}(r) = k_B T \frac{r}{a_{12}}^{36}$$
 (5)

where $a_{12} = a_1 + a_2$, with a_1 and a_2 are the radii of the interacting particles. A at distribution of radii with a width of = 0.1a, where a is the m ean radius, was used. The exponent in V_{sc} was selected high enough to avoid problem s related to the softness of the potential [51]. The

polym er induces an attractive depletion interaction between the colloidal particles, which was modeled by the A sakura-O osawa interaction potential [43, 47]. The extension of this potential to take polydispersity into account reads [52]:

$$V_{AO}(\mathbf{r}) = k_{B}T_{p} (+1)^{3} \frac{3r}{4}(+1)^{2} + \frac{r^{3}}{16^{3}} + \frac{3}{4r}(_{1})^{2}(_{1})^{2}(_{1})^{2}(_{1}+1) \frac{r}{2}^{2}$$
(6)

for r $2(a_{12} +)$ and 0 for larger distances. Here, $_{i}$ = a_{i} = ; = $(_{1} + _{2})$ =2, and $_{p}$ is the volume fraction of the polymer. Note that the range of the potential is given by the polymer size, , and its strength by $_{p}$. This potential wasm odi ed around r = a_{12} , to ensure that the m inim um of the total potential (V_{sc} + $V_{A\,0}$) occurs at this point: forr $2a_{12}$ + =5 a parabolic form , which connects analytically to $V_{A\,0}$ at $2a_{12}$ + =5 and has a m inim um in $2a_{12}$, was used. In our simulations, the range of the interaction, 2 , was set to 0.2a, which would correspond to polymers with R_{g} =a = 0.1 where R_{g} is the radius of gyration.

A long-range repulsive barrier was added to the interaction potential in order to prevent liquid-gas separation (as shown below). The barrier had a maxim all height of $1k_B T$, according to a fourth-order polynom ial:

$$V_{\text{bar}}(\mathbf{r}) = k_{\text{B}} T \qquad \frac{\mathbf{r} \quad \mathbf{r}_{1}}{\mathbf{r}_{0} \quad \mathbf{r}_{1}} \qquad 4 \qquad 2 \quad \frac{\mathbf{r} \quad \mathbf{r}_{1}}{\mathbf{r}_{0} \quad \mathbf{r}_{1}} \qquad 2 \quad \mathbf{r}_{1} \qquad \mathbf{$$

for r_0 r r_1 and zero otherwise. The limits of the barrier were set to $r_0 = 2 \, (a_{12} + \)$, and $r_1 = 4a$, which was enough to prevent phase separation. The maximum height of the barrier equals the depth of the depletion interaction at contact for $_{\rm p} = 0.0625$, much lower than the values where the gel transition takes place. The resulting total interaction potential, $V_{\rm tot} = V_{\rm sc} + V_{\rm AO} + V_{\rm bar}$, is analytical everywhere. It is shown in gure 1, where in order to indicate the spread induced by polydispersity, the potentials am ong three di erent pairs with di ering radii are plotted.

In our simulations, lengths were m easured in units of them ean radius, a, and time in units of $4a^2=3v^2$, where the therm alvelocity v was set to $4a^2=3v^2$, where the therm alvelocity v was set to $4a^2=3v^2$, where the therm alvelocity v was set to $4a^2=3v^2$, where the therm alvelocity v was set to $4a^2=3v^2$, where the therm alvelocity v was set to $4a^2=3v^2$, where the therm alvelocity v was set to $4a^2=3v^2$, where the therm alvelocity v was set to $4a^2=3v^2$, where the therm alvelocity v was set to $4a^2=3v^2$, where the thermal velocity v was set to $4a^2=3v^2$, where the thermal velocity v was set to $4a^2=3v^2$, where the thermal velocity v was set to $4a^2=3v^2$, where the colloidal dynamics. Every n_t time steps, the velocity of the particles was re-scaled to assure constant tem perature. No elect of n_t was observed for well equilibrated samples. The time step was set to 0.0025. Equilibration of the system s was tested by monitoring the total energy, and other order parameters (see below), and by measuring $\frac{s}{q}$ (t) and the M SD at di erent initial times. When the order parameters were constant and the $\frac{s}{q}$ (t) and

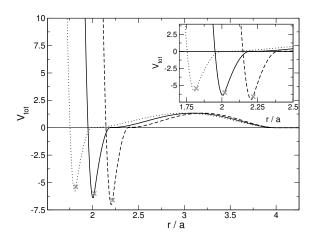


FIG.1: Total pair interaction potential V_{tot} as function of the radial distance $r = jr_1 \quad r_2 j$ for three di erent particle pairs; a pair of particles with m inim al radii $a_1 = a_2 = a$, one with average radii $a_1 = a_2 = a$, and one with maximal $a_1 = a_2 = a + (from left to right)$. The inset shows the enlarged region of the attractive m inimum. Crosses mark where the parabolic m inimum smoothly matches to eq. (6).

M SD curves showed no dependency on the initial time (ageing), the system was considered to be equilibrated.

The volume fraction of the colloidal particles, $_{c} = \frac{4}{3} a^{3} 1 + \frac{}{a}^{2} n_{c}$, with n_{c} the colloid number density, and the polymer volume fraction, $_{p}$, were the control parameters used to identify the states in the phase diagram.

In order to explore the whole p = c plane in search of the gel transition, phase transitions which forbid access (in equilibrium) to important parts of the plane must be prevented. Several order parameters were used to identify dierent kinds of ordering in our system and to monitor whether unwanted liquid-gas or uid-crystal transitions were taking place. First, the onset of phase separation involving states of dierent density can be detected by dividing the system into n³ boxes and measuring the density in every box. The dem ixing' order parameter is de ned as the standard deviation of the distribution of densities:

$$n = \frac{X^{3}}{(k + 0)^{2}} (8)$$

where $_{k}$ is the density of particles in box k, and is the mean density. This parameter is close to zero for an hom ogeneous system, and increases if it dem ixes into phases of di erent density. In our case, n has been set to 4, implying 64 boxes, and a box edge of about 5a (depending on $_{c}$). On the other hand, the orientational order parameter, Q₆, as de ned by Steinhardt et al. [53, 54], signals the presence of an ordered phase, and is used to detect crystallization.

The phase diagram was probed using these parameters. In gure 2 the results are presented for a bare

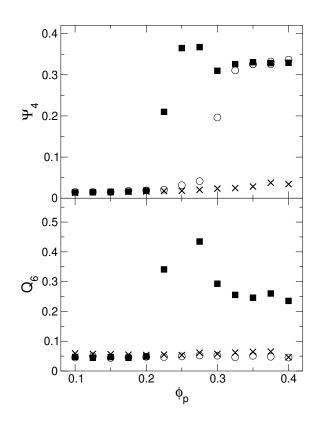


FIG.2: Dem ixing ($_4$) and orientational (Q₆) parameters for $_c = 0.40$ and increasing polymer fraction, $_p$, for dierent system s: monodisperse without long-range barrier (squares), polydisperse without barrier (circles), and polydisperse with long-range barrier (crosses).

system (monodisperse and without the long-range barrier), a polydisperse system without the long-range barrier, and the nal system with both polydispersity and barrier. In this gure, the colloid volum e fraction is constant, $_{\rm c} = 0.40$, and the polymer concentration varies; an isochore is studied. The sudden increase in both $_4$ and Q $_6$ occurring at $_{\rm p} = 0.20$ for the bare system, signals the crystallization boundary, in accordance with D i-jkstra et al. [47]. Because of the short range of the potential, this system has no liquid phase; i.e. the liquid-gas coexistence is meta-stable with respect to the crystal-gas transition.

W hen polydispersity is introduced in the system, crystallization is prevented, as indicated by the constant trend of both parameters close to $_{\rm p}$ = 0.20. How ever, as the system now does not crystallize, the liquid-gas transition can be reached upon increasing the strength of the interaction. This dem ixing is signalled by an increase in

4, not involving local ordering. In order to avoid this separation, the long-range barrier has been introduced in the interaction potential. The energy of a dense phase is raised, and dem ixing is thus energetically unfavourable. Figure 2 shows that liquid-gas separation is indeed inhibited by the repulsive barrier. Instead, individual voids of nite size are created in the system, causing a low-q peak in the structure factor, S (q), presented in Figure

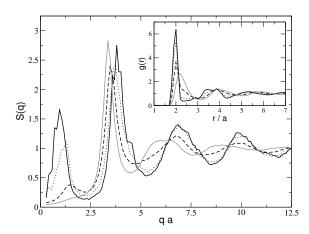


FIG.3: Structure factors for di erent polymer fractions at $_{\rm c} = 0.40$: $_{\rm p} = 0$ gray line, $_{\rm p} = 0.2$ dashed line, $_{\rm p} = 0.35$ dotted line and $_{\rm p} = 0.425$ solid black line. Note the low-q peak raise as $_{\rm p}$ is increased. Inset: Pair distribution function, q (r) for the same states.

3. There, S (q) is shown for di erent polym er fractions, ranging from no attraction ($_{\rm p}$ = 0) to the closest state to the gelwe have accessed ($_{\rm p}$ = 0:425).

In the inset to F igure 3, the pair distribution function, g(r), is presented for the same states as the structure factor. The value at contact, r = 2, increases continuously as the atraction strength grows, signalling increased local contact probabilities. This process will be shown to be responsible for the gel transition. In S_q it becomes evident as an increase in the oscillations for large q.

The low-q peak in the structure factor resembles the low-angle peak observed in light scattering experiments with colloidal gels [6, 8]. However, whereas the peak in our system is an equilibrium property, induced by the specic shape of the interaction potential, the experim ental peak has a non-equilibrium origin. W e also checked for the possibility of microphase separation, which in som e cases can be induced by a repulsive barrier [55]. In our case, the sm all angle peak continuously increases with p, but stays nite and sm aller than the neighboring peak as we approach the geltransition. We interpret this to indicate that we do not have m icrophase separation, and we also observed no other signs of such ordering. Furtherm ore, since the relevant wave vectors in the MCT calculation of the geltransition are the high ones (around 2 = 0, the change in low - g region in the structure factor is expected to have little e ect on the gel transition.

IV. RESULTS AND DISCUSSION

This system has been previously shown to undergo both the glass and gel transitions as stated by MCT. It also exhibits a logarithmic decay in the correlation function at high colloid concentration, indicating a highorder singularity in that region [40]. In this section we will discuss the properties of the gel transition, and com - pare them with MCT and with those of the HSS and other systems, which are similar to the glass transition at high colloid concentration. We test for di erences by comparing quantitatively the non-universal features of the transition, which will aid in the identi cation of the driving mechanism.

The gel line is predicted to extend to low packing fractions with the same qualitative properties. In order to test these properties we have performed simulations at two di erent colloid concentrations, $_c = 0.40$ and $_c = 0.50$, where the gel line is far away from the per-colation one. At high concentration, the higher order singularity is expected to a ect the equilibrium states, disturbing some features of the gel transition.

A. Self-Interm ediate Scattering Function

The scaling prediction for the -decay of states close to a non-ergodicity transition is tested in Figure 4, for constant colloid packing fraction, $_c = 0.40$. Two different representative wave-vectors are presented in this Figure, q = 6.9 and q = 15. As observed at the glass transition in the HSS and m any other di erent system s [22, 23, 27, 31, 34, 40], the -scaling property holds. In com paring these correlation functions with those typical for the HSS or LJS, it is noticed that in Figure 4 the

-decay of the correlators is more stretched, in plying a smaller von Schweidler exponent at the gel transition than at the glass transition. Because of this stretching in the -decay, a clear plateau is not observed, although a slowing down of more than four decades is studied. Nevertheless, extrapolating the relaxation curves to extract plateau values, much higher values are found than at the glass transition in the HSS or the LJS.

W e have analyzed the state $_c = 0.40$ and $_p = 0.42$ in m ore detail, which shows four decades of slowing down compared to the purely repulsive situation upon turning on the attraction. Because scaling is observed in Figure 4, studying only one state is enough to analyse the

-decay of the correlation function. The slowest state, $_{\rm p}$ = 0:425 was not chosen because it strongly deviates from the expected behaviour of $_{\rm q}$ vs. $_{\rm p}$ (see Figure 8 and discussion thereafter). The correlation functions at di erent wave-vectors for state $_{\rm c}$ = 0:40 and $_{\rm p}$ = 0:42 are presented in Figure 5. The range of wave-vectors studied, where the plateau height changes is much wider than the range for a sin ilar change in f_q at the glass transition of hard spheres or Lennard-Jones particles. This feature indicates that the relevant distances for the gel transition are much shorter than for the usual glass transition.

The correlation functions were measured until the average particle displacement was 5a, which is one fourth of the box size (21:95a). Thus, extending this measurement to longer times in order to observe the whole -decay at low q is troublesome. If the di usion coe cient diverges at the same rate as the -time scale (as predicted by

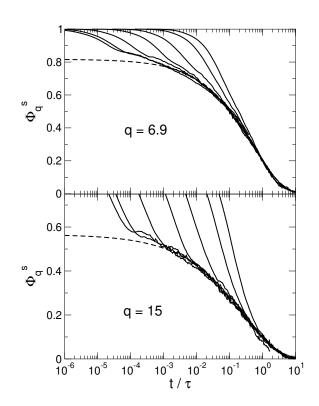


FIG.4: Interm ediate scattering function (self part), ${}^{\rm s}_{\rm q}$, vs. re-scaled time with the -time scale, q, for di erent states: c = 0.40 and p = 0.375; 0.39; 0.40; 0.41; 0.415; 0.42 and 0.425 from right to left. Two di erent wave-vectors are studied: q = 6.9 (upper panel) and q = 15 (lower panel), with the KWW ts (dashed line) included.

MCT), this problem would not appear. Thus, we are also observing a discrepancy between both time scale divergences, that will be further discussed below.

The impossibility of observing a clear plateau, as mentioned above, m akes it m ore di cult to analyse the correlators, since f_q^s cannot be xed a priori. Therefore, the -decay of the correlation functions has been tted using expression (3), with f_q^s , $h_q^{(1)}$ and $h_q^{(2)}$ as tting param eters. The von Schweidler exponent was also tted but was kept identical for di erent wave-vectors. It was found as b = 0.37, and the other results for the tting parameters, are shown in Figure 6. The trends of these param eters are sim ilar to that of the glass transitions in both HSS and LJS, but over a wider q-range in the gel case. This indicates that the localization length is quite di erent in the present system . The non-ergodicity param eter exhibits a bell shaped curve, whereas the rst order am plitude describes a maximum. The latter is determ ined from the tup to a prefactor which depends on the choice of in eq. (3). As an estimate we have used $_{q}$ for q = 9:9 ($_{q}$ is de ned by $_{q}^{s}$ ($_{q}$) = f_q=e), which yields values that are sim ilar (in m agnitude) to the HSS. The second amplitude shows a monotonously increasing behaviour with q, in accordance with the HSS, but it is always positive, unlike the HSS where it goes through

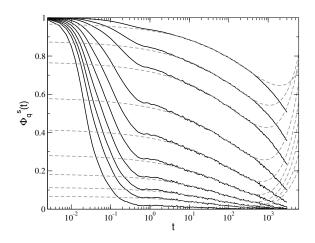


FIG. 5: Interm ediate scattering function (self part), g^{a} , for the state c = 0.40 and p = 0.42, for dierent wave-vectors; from top to botton: q = 3.9; 6.9; 9.9; 15; 20; 25; 30; 35; 40; 50. The dashed lines are ttings from eq. (3) up to second order, with the same von Schweidler exponent for all q.

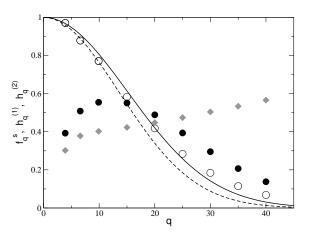


FIG.6: Non-ergodicity parameter, $f_{\rm q}^{\rm s}$ (open circles), and rst (led circles) and second order (diam onds) amplitudes from the ttings in Figure 6 with b=0.37 for all wave-vectors. The lines give the G aussian approximation from eq. (9) tted to all wave-vectors (solid line) and the three lowest wave-vectors (dashed line).

zero at the peak of $h_q^{(1)}$.

The non-ergodicity parameter, f_q^s , can be approximated using the Gaussian expression:

$$f_{q}^{s} = \exp q^{2}r_{1}^{2} = 6$$
 (9)

where r_1 is the localization length. This approximation is known to be valid for low wave-vectors, and important deviations from the Gaussian behaviour are expected close to the glass transition. However, the value for the localization length obtained from thing this curve (solid line in Fig. 6), can be used as an estimate of the one in the MSD.

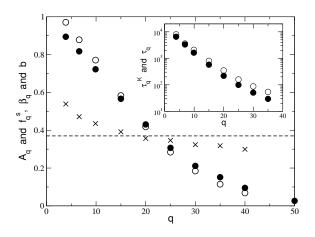


FIG.7: Parameters used in the KWW ttings and comparison with the von Schweidler tting. Main gure: A $_{\rm q}$ (closed circles) and $f_{\rm q}^{\rm s}$ (open circles), $_{\rm q}$ (crosses) and b (horizontal dashed line). Inset: $_{\rm q}^{\rm K}$ (closed circles) and $_{\rm q}$ (open circles).

The localization length so obtained is $r_1^2 = 0.0126a^2$, m uch smaller than for the HSS or the LJS, where r_1 is of the order of the Lindem ann distance. This feature shows s that the process causing the non-ergodic transition in our case has a typical distance m uch smaller than in the case of glass transitions in the HSS or the LJS. This agrees with the observation and discussion about the height of the plateaus, and of the di erent q-range covered by f_q^s in Figure 6. W hereas the glass transition is caused by the short range attraction, the geltransition is caused by the short range attraction, therefore by bonds between particles, (see inset to Figure 3) whose size is of the order of the interaction range. An interesting analogy has been established between the mechanism s driving the form ation of gels and glasses, and the freezing transition [56].

The -decay of near-non-ergodic states can be also studied using the Kohlmausch-W illiam s-W atts (KWW) stretched exponential. The KWW expression is given by:

$$\begin{pmatrix} & & \\ q \end{pmatrix} = A_q \exp \left(\frac{t}{\frac{K}{q}} \right)$$
(10)

where q is known as Kohlrausch exponent, which has been shown to coincide with the von Schweidler exponent at high wave-vectors [57]. This expression has been tted to very di erent system s, and describes the -decay down to zero. We have tted this expression to the decay in our system. However, since the correlators in Figure 5 do not show the com plete -decay, we have tted expression (10) to them aster curve, obtained from the -rescaling. Two of these ttings are presented in Figure

4 by the dashed lines, showing that the KWW stretched exponential describes well the -decay in this system.

The tting parameters, A_q , $_q$ and $_q$, are presented in Figure 7, and compared with the corresponding parameters in the von Schweidler form alism. In such a way, A_q

is compared with the non-ergodicity parameter, g with the von Schweidler exponent, and the $\frac{K}{q}$ with q. As expected, the height of the plateau can be determ ined equally well both by the KWW or von Schweidler analysis. The same holds for the time scales, $\frac{K W W}{q}$ and q. The Kohlmaush exponent is expected to tend to 1 at low wave-vectors, and to approach the value of the von Schweidler exponent at high q. The low-q lim it is explained because di usion is the dom inant process over long distances, whereas at short distances (com parable to the cage size) the dynam ics is dom inated by the cooperative local rearrangem ents. This behaviour is predicted from MCT [57], and has been observed in di erent systems, such as molecular glass formers [58], and in simulations of polymermelts [31], and of water [59]. In our case, the low -q lim it is not observed, but rises as the wave-vector decreases, indicating that the expected behaviorm ay appear at low erg below the sm all angle peak in S (q). At high wave-vector, the K ohlraush exponent crosses the von Schweidler value, but stays close to it. Although an exact agreement is not observed, we may conclude that the correct general trend is obtained.

B. Time Scale and Di usion Coe cient

A n important universal prediction of MCT is the existence of power law divergences for both the time scale, , and the inverse of the self di usion coe cient D $_{\rm s}$, with the same exponent in both cases, :

$$_{q}$$
 $_{p}$ $_{p}$ $_{p}$ and D_{s} $_{p}$ $_{p}$ (11)

where ${}_{p}^{G}$ is the polymer volume fraction where the gel transition occurs. The relation between exponent and the von Schweidler exponent, b, is also universally established by MCT [49].

Testing of the power law divergence (and measuring of) is usually carried out plotting $_q$ as a function of $_p^G$ $_p$ for di erent values of $_p^G$, looking for a straight line. This method is cumbersome, even more as deviations from it are expected for states close to the transition, and precise values for and $_p^G$ cannot be given. To avoid this di culty, we have calculated from b, as given by MCT, and with this particular value of the exponent looked for the power law divergence. In such a way, we are testing the compatibility of MCT predictions with our data.

Figure 8 shows the wave-vector dependent time scale $_{q}$ vs. $_{p}^{G}$ $_{p}$ for di erent wave-vectors. For every wave-vector, $_{q}^{1=}$ was extrapolated to zero, yielding a value for the polymer fraction at the geltransition, $_{p}^{G,q}$. The nal value of $_{p}^{G}$, used in Figure 8, was calculated as the average value for all wave-vectors studied. The linear trends in Figure 8 for $_{p}^{G}$ $_{p}$ > 5 10³, shows the power-law behaviour predicted by MCT, with exponent = 3:1

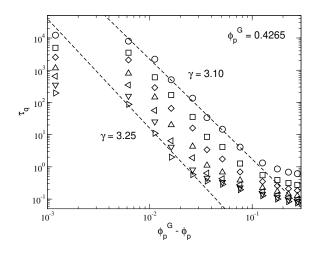


FIG. 8: Wave-vector dependent time scale, q, vs. p^{G}_{p} p for the isochore c = 0.40 for dierent wavevectors; symbols from top to botton correspond to q = 3.9; 6.9; 9.9; 15; 20; 25; 30. The lines are power law ttings to q = 3.9 and q = 30. In all cases keeps close to this two values.

and $_{p}^{G} = 0.4265$. The closest state to the gel transition, $_{p} = 0.425$ deviates from the power-law behaviour observed for low er polym er fractions. Sim ilar deviations have been observed in the HSS and LJS and can tentatively be attributed to therm ally activated processes (or hopping events) [60].

As shown in eq. (11), MCT predicts a power-law for the selfdi usion coe cient, D_s, with the same exponent as the divergence of the time scale. Simulations on HSS and LJS have shown that a power law divergence is indeed obtained, but with a di erent exponent than in the case of _q. Using the same procedure as described above (calculating from b and extrapolating D_s¹⁼ to obtain $_{p}^{G}$) yields a value for $_{p}^{G} = 0.4519$, with the same as for the time scale. This value of $_{p}^{G}$ is too far from that obtained using _q. Therefore, we cannot have similar $_{p}^{G}$ and to explain the behaviour of both _q and D_s, in – plying that the MCT prediction, eq. (11) is violated.

In Figure 9, we present D_s vs. ${}_p^G {}_p$ using for ${}_p^G$ both the value estimated from ${}_q$ and that from D_s . We consider more desirable to have similar ${}_p^G$ to explain the behaviour of ${}_q$ and D_s , even though this implies two di erent : = 3:1 for ${}_q$ and = 1:23 for D_s . As obtained in other non-ergodicity transitions [22, 31, 34], the exponent is lower in the di usion coe cient than in the time scale, although the di erence between both values of is bigger in our case.

In order to stress the di erent exponents in the divergence of the time scale and 1=D_s, we have plotted D_{s q} as a function of $_p$ for di erent wave-vectors in the inset to gure 9. This product, that should be constant according to M C T, diverges as the polym er fraction approaches $_p^G$. The divergence follows a power law with the exponent equal the di erence between both values of

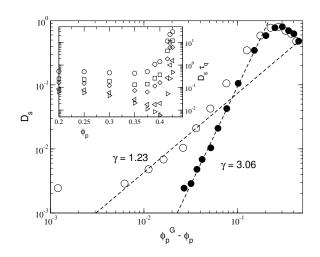


FIG.9: Self di usion coe cient, D s, vs. ${}_p^G p$ p for two values of ${}_p^G$: ${}_p^G = 0.4519$ (closed circles) and ${}_p^G = 0.4265$ (open circles). The dashed lines are the power law things to the data, with the exponent shown in the gure. Inset: D s q vs. polymer fraction for di erent wave-vectors. Symbols as in Figure 8.

The maximum in the self di usion coe cient (upperright corner of Figure 9) is a consequence of the re-entrant glass transition at high packing fractions [61, 62]. A weak short range attraction at rst destabilizes the cage and thus the glass transition moves to higher particle concentration initially as the polymer fraction is increased. At constant colloid concentration the di usion thus rst speeds up with increasing $_p$, until for intermediate attraction strengths the gel line is approached, where the opposite trend then dominates. At $_c = 0.40$, the glass transition is rather far rem oved and thus has little e ect, but the increase of D is still measurable and the di usion coe cient can be used as a measure of the distance to the closest transition. The maximum thus indicates the re-entrant shape of the non-ergodicity line.

The wave-vector dependence of the time scale $\ _{\rm q}$ can also be compared with theoretical predictions. At low q, the time scale is expected to behave as q^2 , corresponding to a di usive process over large distances. Yet, because the simulated scattering functions exhibit non{ exponential relaxation even for the sm allest w avevectors, this simple theoretical scenario is not expected to appear in our case. At interm ediate wave-vectors, where the K ohlrausch exponent becom es com parable to the von Schweidler one the theory predicts a decrease as $q^{1=b}$, whereas at even higher q, the distances involved are dom inated by the m icroscopic dynam ics, and corrections to this behaviour are expected [63]. The inset to Figure 10 shows g for di erent states close to the geltransition. In order to make clear common properties the curves have been scaled vertically to collapse (main gure).

It can be seen in this gure that the behaviour of $_q$ at low wave-vectors (below q = 10), indeed shows a q 2 behavior, which how ever is not the one explained by MCT.

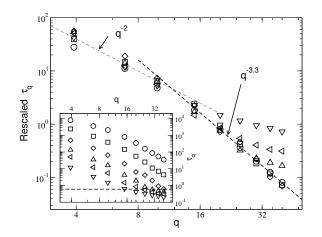


FIG.10: Inset: Time scale, $_q$ as a function of the wavevector, q, for di erent states close to the gel: $_p = 0.42$ (circles), $_p = 0.415$ (squares), $_p = 0.41$ (diam onds), $_p = 0.40$ (upward triangles), $_p = 0.39$ (left-ward triangles) and $_p =$ 0.375 (downward triangles). M ain body: Same data, re-scaled to collapse in the low-q power-law behavior. The dashed lines show power-law behaviours with exponents 2 (gray line) and 3:3 (black line).

At higher q, another power-law trend is observed, with a higher exponent: q ^{3:3}. The crossover from the low -q behaviour to the high-q one, com pares nicely with the wavevector where the K ohlraush exponent becom es equal to the von Schweidler one (Figure 7). The exponent of the high-q region yields b = 0.30, lower than the value obtained from the analysis in Figure 5. However, this value is quite close to the measured von Schweidler value and much smaller than the HSS one. Deviations from this power-law behaviour are observed at high q for the low est p presented in the gure. These deviations are caused by the microscopic dynamics, as they occur when $_{\rm q}$ is lower than a certain value, regardless the polymer fraction. This value, presented in the inset as an horizontal 0:6, which agrees with the time one would line, is t₀ estimate from the correlators in Figure 5.

C. M ean Squared D isplacem ent

We turn now our attention to the MSD curves, that were partially analysed to obtain the di usion coe cients presented in Figure 9. We are only interested in the slow – ing down close to the gel transition and thus we do not show the MSD for low polymer fractions, where the attraction speeds up the dynamics and increases the diffusivity (see gure 9 and [61]). The MSD, after a short initial regime of free ight, r^2 / t^2 , slows down because of the particle interactions and takes longer and longer to reach the long-time regime di usive, where $r^2 = 6D_s t$. An important feature that can be obtained from the MSD of the particles in the system, is the localization length, where the particle interactions hinder particle motion m ost strongly, and in the idealized glass state, arrest it.

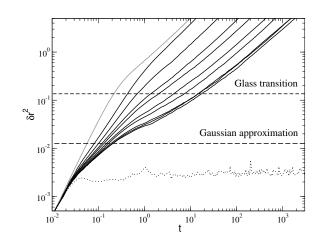


FIG.11: M ean squared displacem ent of the particles as the gel transition is approached. B lack curves from left to right: $_{p} = 0.30; 0.325; 0.35; 0.375; 0.39; 0.40; 0.41; 0.415; 0.42; 0.425$. G rey curve: $_{p} = 0$. The dashed horizontal lines indicate the localization length corresponding to the glass transition (short dash) in the H SS and the estim ate from F igure 6 (long dash). D otted curve: m ean squared displacem ent for a single particle in a frozen environm ent at $_{p} = 0.425$.

It can be compared with the estimate using the Gaussian approximation (see Fig. 6). In Figure 11 we present the MSD for increasing polymer volume fractions. As the gel transition is approached, the localization length show sup as an indication of a plateau, signaling the bond formation. As already discussed above, r_1 is much shorter than in the HSS glass transition (upper dashed line in Figure 11), because of the driving mechanism.

The lower dashed line in this gure is the localization length, as estim ated from the non-ergodicity parameter using the Gaussian approximation $(r_1^2 = 0.0126)$. Although a clear plateau has not fully developed in our curves, its height seems to be above that estimate, by a factor 1:5 2. Since the G aussian approxim ation works very well in the case of the HSS, this suggests big non-G aussian corrections at the geltransition. B efore testing the Gaussian approximation, we stress that the localization length gives a typical size of the mesh of bonds form ed between neighbouring particles, and that the slow structral units are continuously and cooperatively rearranging. In order to test this idea about a correlated region which cooperatively rearranges with and around each particle, a single mobile particle is considered in a xed environment. A well equilibrated system with $_{\rm p}$ = 0:425 is frozen, and only one particle is allowed to m ove. This mobile particle now explores a frozen environm ent, providing the structural size of the region it is con ned to. The mean squared displacement so obtained is given in Figure 11 (dotted line). Som e particles (1.6%) were able to break their bonds and di use freely in the frozen environm ent. For the particles that stay localized, it can be observed that the length of the frozen bonds is much smaller than the localization length. This fact dem onstrates that the structure of bonds, like the repulsive cage at the glass transition in the HSS or LJS, is dynamic, and constantly rearranges cooperatively. This collective restructuring of the system uidizes it, and restores ergodicity, which cannot occur in the frozen system, where the particles are not able to di use even at very long times.

W e turn now back to the G aussian approxim ation, and its accuracy. U sually, this is tested by m easuring the non-G aussian parameter, de ned as:

$$_{2} = \frac{3hr^{4}(t)i}{5hr^{2}(t)i^{2}} \qquad 1$$
(12)

where the averages im ply ensemble averaging. This param eterm easures the deviation of the probability density function for the single particle motion from Gaussian behaviour, and vanishes for di usive motion. Special care must be taken when performing the ensemble averages in polydisperse systems, as pointed out in [64]. The non-G aussian param eterm ust be calculated for every particle (the averages in the de nition above thus in plying tim eorigin averaging only), and particle averaging is taken on the values of 2 (so long as long enough time intervals are studied, each particle will sam ple the distribution relevant to its own size in an ergodic fashion). The non-Gaussian parameters for states with increasing p_p are presented as a function of time in Figure 12. At short times 2 tends to zero, since the system shows Gaussian behaviour during its unhindered ballistic regime. At long tim es, when the particles break free from their bonds and hydrodynam ic di usion holds, 2 again goes back towards zero. At interm ediate tim es, corresponding to the plateaus in both the correlation function and the mean squared displacement, 2 grows, since the single particle m otion hindered by bonding is not B row nian. A sa result, 2 shows a maximum, whose height and position grows in time, because the particles take longer and longer to break free and start di using.

The behaviour of the simulated $_2$ obeys the general expectations [36, 37, 39], but important di erences are observed in the comparison with the results for the HSS or LJS.W hereas in those cases the height of the maxim um for similar (or even higher) -relaxation times is around 2, at the gel transition much higher values are measured. Another interesting di erence is the failure of the short time scaling, observed both in the HSS and LJS. Both e ects can be rationalized considering that the cage is indeed a network of bonds in the case of a gel, rather than a cavity. The strength of these bonds is given by the intensity of the interaction, and thus, it is modied for dierent states, disabling the short time collapse. Because the bonds are short ranged, they affect the particle motion from very short times onward, so that the particles feel the hindrance much longer in the gelcase.

It can be concluded that the non-G aussian corrections are very important in the gel transition. Therefore, the localization length estim ated from the non-ergodicity pa-

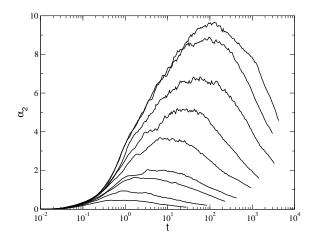


FIG.12: Non-Gaussian parameter $_2$ as a function of time for states approaching the geltransition at the same states as Figure 11. The maximum increases with increasing $_{\rm p}$.

ram eterm ay be inaccurate, as discussed above. How ever, it still provides an indication of how small the localization length is. A better indication of r_1 can be obtained within the G aussian approximation if only low wave-vectors are used in thing expression (9). The the durve is presented in Figure 6 by the dashed line, where only the three lowest q's are thed. The estimated f_q^s deviates from the data at higher wave-vectors, showing high non-G aussian corrections. The localization length is higher than the previous value: $r_1^2 = 0.0162$. Thus, this thing provides data more consistent with the M SD curves and the non-G aussian parameter.

D. Higher Colloid Volum e Fraction

We move now to a higher colloid volume fraction: $_{\rm c}$ = 0.50. These results are presented to supplement the ndings at the lower packing fraction and test for the prediction of stronger stretching closer to the higher order singularity. As indicated in the theoretical section, M CT predicts a higher order singularity in the vicinity of the junction of the gel and glass lines; i.e. at high polymer and colloid densities. In this particular system we found clear indications of this singularity in simulations at $_{\rm c}$ = 0:55 and $_{\rm p}$ = 0:375 [40]. The isochore under study now, $_{\rm c}$ = 0:50, could be close enough to the higher order singularity to show som e e ects.

In F igure 13 we present the correlation functions for increasing polym er fractions at the sam e wave-vectors as F igure 4, re-scaled to collapse in the long-time decay. It is interesting to note that the polym er concentrations studied in this case are lower than those studied at the lower colloid volum e fraction. In accordance with experiments and theory, this indicates that the gel transition takes place at lower polym er fractions the higher the colloid concentration.

In Figure 13, it can be observed that the correlators

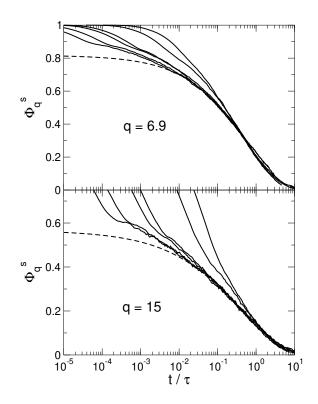


FIG. 13: Correlation functions for $_{\rm c}$ = 0.50 and different polymer concentrations. >From left to right: $_{\rm p}$ = 0.35; 0.36; 0.375; 0.38; 0.385; 0.39. Two wave-vectors are studied, as labeled in the gures. The dashed lines represent the KWW ttings to the $_{\rm c}$ = 0.40 correlation functions.

do not collapse over the whole -decay, but only in the end. These deviations are expected because of the higher order singularity, which is at higher densities. How ever, we stress that although this singularity has clear e ects on the correlation functions, they do not show so clear signatures as that of the $_c = 0.55$ isochore [40]. At this high concentration, a logarithm ic decay was observed, with a wave-vector dependent extension.

Because these corrections a ect the early -decay, analyzing the correlation functions is di cult. Furtherm ore, the plateau is not observed, and the von Schweidler analvsis is thus extrem ely di cult. In order to analyse the self interm ediate scattering function, we com pare the stretching of the curves at $_{c} = 0.40$ and $_{c} = 0.50$; in Figure 13 the -decay master function of the $_{\rm c}$ = 0:40 state, as param etrized by the KWW tting is included. It can be seen that this curve can be rescaled to collapse onto the -decay of the correlators at $_{c} = 0.50$ for both wavevectors at long times. This indicates that the von Schweidler exponent is very sim ilar in both cases, but also points out the e ect of the high order singularity. A coording to MCT, b should decrease as the singularity is approached, but this behaviour is not observed in our case. Com parison of the -decays by tting the KWW stretched exponential to the master function is troublesom e, since only the late decay is obtained unam biguosly.

The similarity of both -decays was used in the von

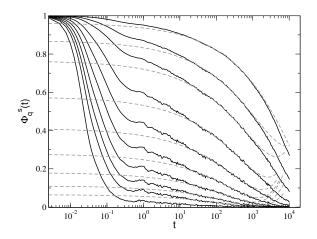


FIG.14: Interm ediate scattering function (selfpart), $_{q}^{s}$, for the sam e wave-vectors as Figure 5 wave-vectors for $_{c}$ = 0:50 and $_{p}$ = 0:39. The dashed lines are ttings from eq. (3) up to second order, with the sam e von Schweidler exponent as $_{c}$ = 0:40.

Schweidler analysis of the correlation function, and only the non-ergodicity parameter and am plitudes were tted. Since the upper part of the decay is known to be a ected by the higher order singularity close-by, that partmust be discarded in the ttings. The correlation functions and ttings are presented in Figure 14 for the state $_{c} = 0.50$ and p = 0.39, for the sam e wave-vectors as Figure 5. The main conclusion is that the late -decay at all wavevectors can be correctly described by the von Schweidler decay, with the same exponent as the state at c = 0.40. The non-ergodicity parameters obtained from the tting are slightly lower than those of $_{\rm c} = 0.40$, but sim ilar within the error bars. According to MCT , $f^{\rm s}_{\rm q}$ decreases when approaching the glass part of the non-ergodicity line (signaling an increase in the localization length). Our result is thus consistent with this prediction.

W ith these values of the non-ergodicity parameter one can de ne also the wave-vector dependent time scale, $_q$, as discussed above. In order to test the value of the von Schweidler exponent, using eq. (11) we have performed a three parameter thing to obtain and $_p^G$. In Figure 15, $_q$ is presented as a function of $_p^G$ p for dierent wavevectors. The power-law things for two wave-vectors are also plotted and the critical polymer fraction $_p^G$ is given.

The values of obtained from this analysis for di erent wave-vector range from = 3:37 to = 3:82, the mean value being = 3:70. This value of in plies a smaller von Schweidler exponent, b = 0:33, in disagreement with our previous estimate, but backing the MCT prediction. Using the same value of $_{\rm p}^{\rm G}$, the vanishing of the self-di usion coe cient, D $_{\rm s}$, can be analysed, and is presented in the inset to this gure. A power-law is observed in this case, with an exponent, = 1:92, which, again in contradiction to MCT, leaves us with a big difference between the two values of .

The diusion coe cients in the inset of gure 15 again

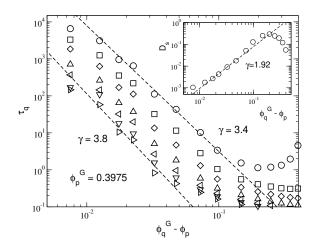


FIG.15: W ave-vector dependent time scale, q, vs. $_{p}^{G}$ p for di erent wave-vectors; sym bols from top to botton correspond to q = 3.9; 6.9; 9.9; 15; 20; 25; 30. The lines are power law ttings to q = 3.9 and q = 30. $_{p}^{G}$ and were tted.

indicate the re-entrat glass transition. They describe a maximum, more pronounced than that observed in Figure 9 because the glass line is closer to the $_{\rm c}$ = 0.50 isochore. The minimum in $_{\rm q}$, which is observed only for q = 3.9, in an equivalent way indicates the shape of the non-ergodicity transition line. At higher wave-vectors, the glass transition causes very low $f_{\rm q}^{\rm s}$ and the time scales merge with the microscopic transient and thus this feature is suppressed.

The wave-vector dependence of $_{\rm q}$ can also be studied, as done for the lower concentration, yielding another estim ate of b. In this case, a similar plot as Figure 10 is obtained, where the low q region is compatible with a q² behaviour, and a higher exponent at higher q, yielding a value of b = 0.38. This value is in agreement with the nice comparison between the $_{\rm c}$ = 0.40 and $_{\rm c}$ = 0.50 isochores, but not with or the MCT prediction. We may then conclude that analysis of this state is extrem ely di cult, but our indications state that the von Schweidler exponent is similar for both packing fractions, but probably slightly lower in the higher concentration.

Finally, we would like to point out that the non-Gaussian parameter at this packing fraction shows a behaviour sim ilar to that shown in Figure 12, i.e. the peak is as high, and no short-time scaling is observed.

V. CONCLUSIONS

In this paper, by m eans of simulations, we have tested the universal predictions of MCT for gelation in colloidal system s, viewed as an attraction (driven glass transition. The self parts of the intermediate scattering function for states close to this transition have been analysed and the results were compared with the theoretical predictions. For the $_{\rm c}$ = 0:40 isochore, which is far enough from the high order singularity, the correlation functions can be -scaled. The time scale of the -decay was shown to obey a power law divergence, with an exponent, , related to the von Schweidler exponent, obtained from the early -decay. Both features are predicted by MCT for all non-ergodicity transitions. A lso, the wave-vector analysis of the time scale follow s the behaviours predicted by MCT, with a sm all di erence in the value of the von Schweidler exponent.

The wave-vector analysis of the correlation functions depends on details of the interaction potential, and thus provides information about the mechanism, leading to the transition. In our case, it establishes that the gel transition is driven by a short-range mechanism, namely, bond formation, as observed in the pair distribution function. A dditionally, it has been shown that the KWW stretched exponential can account for the -decay of the correlation functions, as in other non-ergodicity transitions.

We have also tested the Gaussian approximation, which works very well for the HSS. The non-Gaussian param eter, 2, establishes that this approximation is much worse in the case of the gel transition than for the glass transition. It was also tested when comparing the estimated localization length from the non-ergodicity param eter with the MSD of the particles. The di usion coe cient has been also studied. It tends to zero as the transition is approached following a power-law, with an exponent much lower than , in accordance with simulations of glass transitions in other systems, but in disagreem ent with MCT, where both exponents are equal.

Finally, when the colloid concentration is increased, the system shows signatures of the high order singularity nearby and little can be discussed about the exponents b or . However, only slight changes in the numbers are expected, since the qualitative behaviour is reproduced, except for the -scaling. A loo, the di usion coeffcient follows a power law with a di erent exponent and the non-G aussian parameter reaches values similar to the $_{\rm c}$ = 0:40 case.

Therefore, our main conclusion is that MCT accounts for most features of the simulated systems on approach to the geltransition, but the discrepancies already found in other non-ergodicity transitions (such as the repulsiondriven glass transition in hard sphere systems) are also obtained here.

Acknow ledgements

The authors thank W .K ob and R .Sear for useful discussion. A M P. acknow ledges the nancial support by the C IC Y T (project M AT 2000-1550-C O 3-02).M F.was supported by the DFG under grant Fu 309/3.

- Soft and Fragile Matter, Nonequilibrium Dynamics, M etastability and Flow, edited by M E.Cates and M R. Evans (Institute of Physics, Bristol, 2000).
- [2] W C K. Poon, L. Starrs, S P. Meeker, A. Moussaid, R M L. Evans, P N P. Pusey and Robins, Faraday D iscuss. 112, 143 (1999).
- [3] A. Im hof and JK G. Dhont, Phys. Rev. Lett. 75, 1662 (1995).
- [4] L.C ipelletti, S.M anley, R C. Balland D A .W eitz, Phys. Rev.Lett. 84, 2275 (2000).
- [5] M. Muschol and F. Rosenberger, J. Chem. Phys. 107, 1953 (1997).
- [6] M. Carpineti and M. Giglio, Phys. Rev. Lett. 68, 3327 (1992).
- [7] W C K. Poon and M D. Haw, Adv. Colloid Interface Sci., 73, 71 (1997).
- [B] P N. Segre, V. Prasad, A B. Scho eld and D A. W eitz, Phys. Rev. Lett. 86, 6042 (2001).
- [9] K.K roy et al. In preparation.
- [10] J. Bergenholtz and M. Fuchs, Phys. Rev. E 59, 5706 (1999).
- [11] J.Bergenholtz and M.Fuchs, J.Phys.: Condens.M atter 11, 10171 (1999).
- [12] J.Bergenholtz, M.Fuchs and Th.Voigtmann, J.Phys.: Condens.Matter 12, 6575 (2000).
- [13] W .van M egen, T C. M ortensen, S R. W illiam s and J. M uller, Phys. Rev. E 58 6073 (1998).
- [14] S.R.W illiams and W. van Megen, Phys. Rev. E 64 041502 (2002).
- [15] C.Beck, W. Hartl, and R.Hempelmann, J.Chem. Phys. 111, 8209 (1999).
- [16] E.Bartsch, T.Eckert, C.Pies, and H.Sillescu, J.Non-Cryst. Solids (2002). In press.
- [17] W .Gotze and R.Haussmann, Z.Phys.B 72, 403 (1988).
- [18] W . G otze and L. Sjogren, J. Phys.: Condens. M atter 1 4203 (1989).
- [19] W .Gotze and M .Sperl, Phys.Rev.E 66, 011405 (2002)
- [20] L. Fabbian et al., Phys. Rev. E 59, R1347 60, 2430 (1999).
- [21] K. Dawson, G. Fo, M. Fuchs, W. Gotze, F. Sciortino, M. Sperl, P. Tartaglia, Th. Voigtmann, E. Zaccarelli, Phys. Rev. E 63, 011401 (2001).
- [22] W. Kob and H.C. Andersen, Phys. Rev. E, 51 4626 (1995).
- [23] W . Kob and H.C. Andersen, Phys. Rev. E, 52 4134 (1995).
- [24] T.Gleim, W.Kob, K.Binder, Phys. Rev. Lett., 81 4404 (1998).
- [25] T.Gleim and W.Kob, Europ. Phys. J.B, 13 83 (2000).
- [26] F. Sciortino, P. Gallo, P. Tartaglia, S.H. Chen, Phys. Rev.E 54 6331 (1996).
- [27] F. Sciortino, L. Fabian, S.H. Chen, P. Tartaglia, Phys. Rev.E 56 5397 (1997).
- [28] C. Bennem ann, W. Paul, K. Binder, and B. Dunweg, Phys. Rev. E 57, 843 (1998).
- [29] C.Bennem ann, J.Baschnagel, and W.Paul, Eur.Phys J.B.10, 323 (1999).
- [30] C.Bennem ann, J.Baschnagel, W. Paul, and K.Binder, Comput. Theor. Polym. Sci. 9, 217 (1999).
- [31] M. A ichele and J.Baschnagel, Eur. Phys. J.E 5 229; 245 (2001).
- [32] D.Caprion, H.R.Schober, Phys. Rev. B, 62, 3709 (2000).

- [33] F. Sciortino, W. Kob, Phys. Rev. Lett. 86, 648 (2001).
- [34] J.Horbach and W .Kob, Phys.Rev.E, 64, 041503 (2001).
- [35] M. Nauroth, W. Kob, Phys. Rev. E, 55, 657 (1997).
- [36] C.Donati, S.C.G btzer, P.H. Poole, Phys. Rev. Lett. 82 5064 (1999).
- [37] C.Donati, S.C.G lotzer, P.H. Poole, W. Kob, S.J. Plin pton, Phys. Rev. E 60 3107 (1999).
- [38] B.Doliwa, A.Heuer, Phys. Rev. Lett. 80, 4915 (1998).
- [39] B.Doliwa, A.Heuer, Phys.Rev.E 61, 6898 (2000).
- [40] A M. Puertas, M. Fuchs, M E. Cates, Phys. Rev. Lett. 88, 098301, (2002).
- [41] M. Fuchs, I.H ofacker and A. Latz, Phys. Rev. A, 45, 898 (1992).
- [42] M.Fuchs, W.Gotze, M.R.Mayr, Phys. Rev. E 58, 3384 (1998).
- [43] S. Asakura and F. Oosawa, J. Chem. Phys. 22 1255 (1954).
- [44] A P. Gast, C K. Hall, W B. Russel, J. Colloid Interace Sci. 96 251 (1983).
- [45] A P. Gast, W B. Russel, C K. Hall, J. Colloid Interace Sci. 109 161 (1986).
- [46] M. D ijkstra, R. van Roij, R. Evans, Phys. Rev. Lett. 81 2268 (1998).
- [47] M. Dijkstra, R. van Roij, R. Evans, Phys. Rev. E 59 5744 (1999).
- [48] W . G otze in Liquids, Freezing and G lass transition ed. JP.H ansen, d.Levesque and J.Zinn-Justin, Am sterdam, N orth-H olland (1991).
- [49] W. Gotze and L. Sjogren, Rep. Prog. Phys. 55, 241 (1992).
- [50] J.P. Hansen, IR. M cD onald, Theory of Simple Liquids (London, A cadem ic, 1986).
- [51] J.R. Melrose, Europhys. Lett. 19, 51 (1992).
- [52] JM. M endez-A lcaraz and R. K lein, Phys. Rev. E 61, 4095 (2000).
- [53] P.J. Steinhardt, D R. Nelson, M. Ronchetti, Phys. Rev. B, 28, 784 (1983).
- [54] R P.ten W olde, M J.Ruiz-M ontero, D.Frenkel, J.Chem. Phys., 104, 9932 (1996).
- [55] R.P. Sear, W. M. Gelbart, J. Chem. Phys. 110 4582 (1999).
- [56] G.Fo, G.D.M. & ullagh, A.Law lor, E.Zaccarelli, K.A. Dawson, F.Sciortino, P.Tartaglia, D.Piniand G.Stell, Phys.Rev.E, 65, 031407 (2002).
- [57] M. Fuchs, J. Non-cryst. Solids, 172-174, 241 (1991).
- [58] A. Tolle, J.W uttke, W. Schober, O.G. Randl, F. Fujara, Eur. Phys. J. B. 5, 231 (1998)
- [59] F.W. Starr, S.Harrington, F.Sciortino, and H.E.Stanley, Phys. Rev. Lett. 82, 3629 (1999).
- [60] This state was carefully checked for aging or out-ofequilibrim e ects, but within our tests, it is fully equilibrated.
- [61] K N. Pham, A M. Puertas, J.Bergenholtz, S.J. Egelhaaf, A.Moussaid, P.N. Pusey, A.B. Schoeld, M.E. Cates, M. Fuchs, W.C.K. Poon, Science, 296, 104 (2002).
- [62] G.Fo, KA.Dawson, S.V.Buldyrev, F.Sciortino, E. Zaccarelli, P.Tartaglia, Phys. Rev. E 65, 050802 (2002).
- [63] M.Fuchsand M.R.Mayr, Phys.Rev.E, 60, 5742 (1999).
- [64] B D oliwa and A Heuer, J. Phys.: Condens. M atter 11 (1999) A 277.