# The dual nature of 5f electrons and origin of heavy ferm ions in U compounds

G Zwicknaglyand P Fuldez

y Institut fur M athem atische Physik, Technische Universitat Braunschweig, M endelsschnstr. 3, 38106 Braunschweig, G erm any z M ax-P lanck-Institut fur Physik kom plexer System e, N othnitzer Str. 38, 01187 D resden, G erm any

A bstract. We develop a theory for the electronic excitations in  $UPt_3$  which is based on the localization of two of the 5f electrons. The remaining f electron is delocalized and acquires a large electron assists by inducing intra-atomic excitations of the localized ones. The measured deH aas-vanA lohen frequencies of the heavy quasiparticles are explained as well as their anisotropic heavy mass. A model calculation for a small cluster reveals why only the largest of the different 5f hopping matrix elements is operative causing the electrons in other orbitals to localize.

### 1. Introduction

There is grow ing evidence that actinide ions m ay have localized as well as delocalized 5f electrons. This picture which was suggested by transport m easurements [1] is supported by a great variety of experiments including, e.g., photoem ission and neutron inelastic scattering experiments on UPd<sub>2</sub>A  $l_3$  [2, 3, 4] as well as muon spin relaxation measurement in UGe<sub>2</sub> [5]. The assumption is further supported by quantum them ical calculations on uranocene U (C<sub>8</sub>H<sub>8</sub>)<sub>2</sub> [6] which exhibit a number of low-lying excitations which are due to rearrangements of the 5f electrons. There are speculations that the presence of localized 5f-states might even be responsible for the attractive interactions leading to superconductivity [7]. We should like to mention that the dual model should allow for a rather natural description of heavy ferm ion superconductivity coexisting with 5f-derived magnetism.

The above-mentioned observations form the basis of the dual model which provides a microscopic theory for the heavy quasiparticles in U compounds. The ansatz conjectures that the delocalized 5 f states hybridize with the conduction states and form energy bands while the localized ones form multiplets to reduce the local Coulomb repulsion. The two subsystems interact which leads to the mass enhancement of the delocalized quasiparticles. The situation resembles that in Prmetal where a mass enhancement of the conduction electrons by a factor of 5 results from virtual crystal eld (CEF) excitations of localized 4  $f^2$  electrons [8].

The dual ansatz reproduces the dH vA data in UPt $_3$  [9] and UPd $_2$ Al $_3$ . Detailed Ferm isurface studies for UGa $_3$  [10] and high-resolution photoem ission measurements for URu $_2$ Si $_2$  [11] show that the observed Ferm i surfaces cannot be explained by assuming all 5 f electrons to be itinerant or localized. Measurements of the optical conductivity in UPd $_2$ Al $_3$  and UPt $_3$  [12] indicate that the enhanced elective masses mof the quasiparticles should result from the interaction of delocalized states with localized magnetic moments.

The coexistence of itinerant and localized 5 f states is referred to as partial localization. It plays an important role in many intermetallic actinide compounds. Partial localization arises from interplay between the hybridization of the 5 f states with the conduction electrons and the local Coulomb correlations. The underlying microscopic mechanism is an area of active current research [13, 14]. LDA calculations show that the hopping matrix elements for dierent 5f orbitals vary. But it is of interest to understand why only the largest one of them is important and why the other ones are suppressed.


In order to justify the above assum ption we present model calculations which focus on the interplay between delocalization of 5 f states and Hund's rule correlations. The results [15] clearly show how partial localization can arise in 5 f systems. In addition, they suggest rather complex phase diagrams depending upon the strengths of the hopping matrix referring to dierent orbital elements. Variation of the intersite hopping by applying (hydrostatic) pressure should lead to new types of (quantum) phase transitions. We think the present model could be used to study the pressure dependence of the magnetization in  $UGe_2$ .

In addition to the full model H am iltonian, we investigate a simpli ed version which treats the local C oulom b interaction in close analogy to LDA+U. The results allow us to assess the general validity of this popular approximation scheme. Finally we compare the results of the full model H am iltonian with those obtained from a Hartree-Fock approximation.

### 2. Heavy quasiparticles in UPt3 and UPd2A l3: Dualmodel

We calculate the heavy quasiparticles in UPt<sub>3</sub> and UPd<sub>2</sub>A  $\frac{1}{8}$  within the dual model considering two of the 5f electrons as localized, in agreement with the absence of any K ram ers doublets in cases where a crystalline electric eld (CEF) splitting of U states has been observed. The calculation of the heavy bands proceeds in three steps as described in [9]: First, the band-structure is determined by solving the D irac equation for the self-consistent LDA potentials but excluding the U 5f  $\frac{5}{2}$ ,  $\frac{1}{2}$  =  $\frac{5}{2}$  and  $\frac{1}{2}$  =  $\frac{1}{2}$  states from forming bands. The localized 5f orbitals are accounted for in the self-consistent density and, concomitantly, in the potential seen by the conduction electrons. The intrinsic bandwidth of the itinerant U 5f  $\frac{5}{2}$ ,  $\frac{1}{2}$  =  $\frac{3}{2}$  electrons is taken from the LDA calculation while the position of the corresponding band-center C is chosen such that the density distribution of the conduction states as obtained within LDA remains unchanged. The f

occupancy per U atom for the delocalized 5f electrons amounts to  $n_f=0.65$  indicating that we are dealing with a mixed valent situation. The calculated dH-vA frequencies agree rather well with the observed ones [16] as shown in Figure 1. We also include the corresponding results for UP  $d_2Al_3$  which are compared to experimental data from [17].

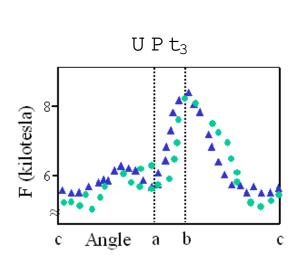

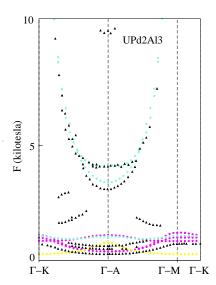


Figure 1.DeH aas-vanA lphen cross sections for the heavy quasiparticles as calculated within the dual model (circles) [9]. The experimental data for UPt $_3$  (triangles) are from [16] while those for UPd $_2$ A  $l_3$  (black triangles) are taken from [17]

In the second step, the localized U 5f states are calculated assum ing the jj-coupling scheme. The Coulomb matrix elements are calculated from the radial functions of the ab-initio band structure potentials. We nd a doubly degenerate ground state with  $J_z=3$  which must be an eigenstate of J=4 and has an overlap of 0.865 with the Hund's rule ground state  ${}^3\mathrm{H}_4$  derived from the LS-coupling scheme. In the hexagonal symmetry, the two-fold degeneracy of the ground-state is lifted by a CEF yielding the two states j  ${}_3\mathrm{i}$  and j  ${}_4\mathrm{i}$ . Note that j  ${}_4\mathrm{i}$  has been suggested as ground state of UPd ${}_2\mathrm{A}\,\mathrm{l}_3$ . We assume that the splitting energy  ${}^\sim$  between j  ${}_4\mathrm{i}$  and j  ${}_3\mathrm{i}$  is of order 20 meV for UPt ${}_3$ . The coupling between the localized and delocalized f electrons is directly obtained from the expectation values of the Coulomb interaction U  ${}_{\mathrm{Coul}}\mathrm{i}$  in the 5f ${}^3$  states M = hf ${}^1; \frac{5}{2}; \frac{3}{2}\mathrm{j}$  h  ${}_4\mathrm{j}\mathrm{j}_{\mathrm{Coul}}\mathrm{j}$   ${}_3\mathrm{i}$  jf ${}^4; \frac{5}{2}; \frac{3}{2}\mathrm{i} = 0:19\mathrm{eV}$ .

Finally, we determ ine the renormalization of the excitive masses which results from the coupling between the two 5f subsystems. The enhancement factor is calculated from the self-consistent solution of the self-energy equation [8] with the input taken from abinitio electronic structure calculations for the delocalized and the localized 5 f electrons. The density of states with two localized 5 f electrons is N (0) ' 15.5 states/(eV cell), the 5 f-weight per spin and U atom of the band states amounts to  $4a^2 = 0.13$  while the transition matrix element between the low-lying singlet states in the localized 5 f² shell in the presence of a CEF equals M  $\hat{J} = 0.036$  e V². The only adjusted parameter is the

Table 1. Me	easured and	calculated e	ective m	asses of U	$Pt_3$ for	various	directions of
the m agnetic	eld						

m	С	а	b
Experim ent	110	82	94
T heory	128	79	104

energy ~ characterizing the centers of gravity of the CEF excitations. By comparison with other U compounds such as  $UPd_2Al_3$  we estimate ~ ′  $20\,\mathrm{m}$  eV. This general concept reproduces the quasiparticles rather well as can be seen from the results sum marized in Table 1. A similar analysis applies for  $UPd_2Al_3$ .

## 3. Partial localization from competition between angular correlations and hopping

The calculations start from small clusters which model the U sites in heavy ferm ion compounds. We keep only the degrees of freedom of the 5f shells the conduction states being accounted for by (e ective) anisotropic intersite hopping. Here we consider the two-site model. The general results qualitatively agree with those found for a three-site cluster. The Ham iltonian reads

$$H = \sum_{j_z}^{X} t_{j_z} c_{j_z}^{y} (1) c_{j_z} (2) + h x : + H_{coul}$$
 (1)

Here  $c_{j_z}^y$  (i)  $(c_{j_z}$  (i)), create (annihilate) an electron at site i = 1,2) in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,2) in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,2) in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,2) in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,2) in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,2) in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,2) in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,2) in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,2) in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,2) in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,20 in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,20 in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,20 in the 5f j = 5=2 state with  $j_z = 5=2$ ; :::;5=2. The electron at site i = 1,20 in the 5f j = 5=2 state with  $j_z = 1,2$ 0 in the 5f j = 1,20 in the 5f

$$\text{H}_{\text{Coul}} = \sum_{\substack{i=1;2 \ j_{z1} > j_{z2} \ j_{z3} > j_{z4}}}^{\text{X}} \sum_{\substack{j_{z1} j_{z2} \ j_{z3} > j_{z4}}}^{\text{Y}} \text{J}_{\substack{j_{z3} j_{z3} j_{z4} \ ic_{j_{z1}}^{y}}}^{\text{Y}} \text{(i)}_{\substack{c_{j_{z3}} \ (i) \ c_{j_{z3}}}}^{\text{Y}} \text{(i)}_{\substack{c_{j_{z4}} \ (i)}}$$

depends upon the Coulomb matrix elements

where J denotes the total angular m om entum and  $J_z=j_{z1}+j_{z2}=j_{z3}+j_{z4}$ . The sum is restricted to even values of J, i. e., J=0;2;4 to satisfy the antisym m etry requirem ent. In the actual calculations, we use the parameters  $U_J$  determ ined from the LDA 5f wave functions in UPt<sub>3</sub>, i.e.,  $U_{J=4}=1721 \mathrm{eV}$ ,  $U_{J=2}=1828 \mathrm{eV}$ , and  $U_{J=0}=21:00 \mathrm{eV}$ . Finally, the h5=2 $j_{z1}$ 5=2 $j_{z2}$  jJJ<sub>z</sub>i denote the C lebsch-G ordan coexists.

To simulate the situation in the U-based heavy-ferm ion compounds we consider the model in the intermediate valence regime with an average f-valence close to 2.5.

The eigenstates of the Ham iltonian Eq. (1) are characterized by  $J_z=J_z^{(1)}+J_z^{(2)}$  where  $J_z$  is the z-component of the total angular momentum of the two-site system while  $J_z^{(1)}$  and  $J_z^{(2)}$  refer to the angular momentum projections of the individual

sites. We study the evolution of the ground state with the hopping parameters  $t_{3=2}$ ,

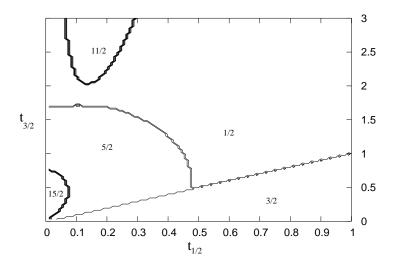
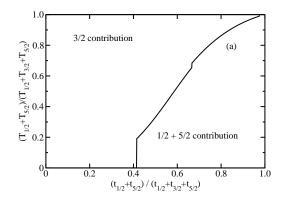


Figure 2. Magnetization of the ground state. The model predicts two \high-spin" phases ( $J_z=15=2$  and  $J_z=11=2$ ) with ferrom agnetic intersite correlations h $\mathcal{T}^{(1)}$   $\mathcal{T}^{(2)}$  if for strong anisotropy  $t_{3=2}$   $t_{1=2}=t_{5=2}$  and three \low-spin" phases  $J_z=5=2$ ; 1=2

 $t_{5=2}$ , and  $t_{1=2}$ . The energy variation is smooth except for a kink along the isotropic line  $t_{1=2}=t_{3=2}=t_{5=2}$ . The character of the ground state, however, changes as can be seen by considering the total magnetization  $J_z$  of the ground state displayed in Figure 2. The phase diagram is strongly a ected by magnetic elds. Standard electronic structure calculations for extended systems such as the Hartree-Fock method or an LDA+U-type ansatz generally overestimate the stability of the ferromagnetic phases and fail to describe the subtle breaking-up of the Hund's rule correlations. Partial



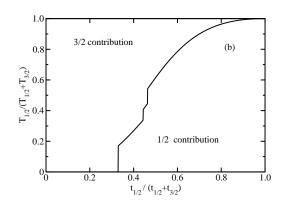


Figure 3. Partial localization is rejected in the relative contributions T (see text) of the various orbitals to the kinetic energy in the correlated ground-state for (a)  $t_{5=2}=0$  and (b)  $t_{1=2}=t_{5=2}$ . Dominant hopping strongly suppresses the remaining contributions.

localization becomes clearly evident in the contributions of the dierent j-channels to

the gain in kinetic energy as shown in Figure 3. Whenever one hopping parameter t dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates, i.e., the shown in Figure 3. Whenever one hopping parameter the dominates and its shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenever one hopping parameter the dominates are shown in Figure 3. Whenev

### A cknow ledgem ent

We would like to thank D. E frem ov, N. Hasselm ann, E. K. R. Runge, and A. Yaresko for a number of helpful discussions. We are grateful to S. R. Julian and G. G. Lonzarich form aking their experimental data available to us prior to publication. One of us (G. Z.) acknowledges support from the Niedersachsen-Israel Foundation.

#### R eferences

- [1] J. Schoenes, O. Vogt, J. Lohle, F. Hulliger, and K. Mattenberger. Phys. Rev. B, 53:14987, 1996.
- [2] Takashi Takahashi, Noriaki Sato, Takayoshi Yokoya, Ashish Chainani, Takayuki Morimoto, and Takemi Komatsubara. J. Phys. Soc. Papan, 65:156, 1995.
- [3] Naoto Metoki, Yoshinori Haga, Yoshihiro Koike, and Yoshichika Onuki. Phys. Rev. Lett., 80:5417, 1998.
- [4] N.Bemhoeft, N.Sato, B.Roessli, N.Aso, A.Hiess, G.H.Lander, Y.Endoh, and T.Komatsubara. Phys. Rev. Lett., 81:4244, 1998.
- [5] A. Yaouanc, P. Dalmas de Reotier, P. C. M. Gubbens, C. T. Kaiser, A. A. Menovsky, M. Mihalik, and S. P. Cottrell. Phys. Rev. Lett., 89:147001{1,2002.
- [6] W en jian Liu, M ichael Dolg, and Peter Fulde. Inorg. Chem., 37:1067, 1998.
- [7] N.K. Sato, N.Aso, K.M. iyake, R. Shiina, P. Thalmeier, G. Varelogiannis, C. Geibel, F. Steglich, P. Fulde, and T. Komatsubara. Nature, 410:340, 2001.
- [8] R.W hite and P.Fulde. Phys. Rev. Lett., 47:1540, 1981.
- [9] G. Zwicknagl, A. N. Yaresko, and P. Fulde. Phys. Rev. B, 65:081103 (R), 2002.
- [10] M. Biasini. preprint, 2002.
- [11] J.D.Denlinger, G.H.Gweon, J.W.Allen, C.G.Olson, M.B.Maple, , J.L.Sarrao, P.E. Arm strong, Z.Fisk, and H.Yamagami. J.Electron Spectrosc.Relat.Phenom., 117 & 118:347, 2001
- [12] M.Dressel, N.Kasper, K.Petukhov, B.Gorshunov, G.Gruner, M.Huth, and H.Adrian. Phys. Rev. Lett., 88:186404 (1, 2002.
- [13] U.Lundin, I.Sandalov, O.Eriksson, and B.Johansson. Phys. Rev. B, 62:16 370, 2000.
- [14] Per Soderlind, R.Ahuja, O.Eriksson, B.Johansson, and J.M.Wills. Phys. Rev. B, 61:8119, 2000.
- [15] D.E frem ov, N. Hasselm ann, E.K.R. Runge, P. Fulde, and G. Zwicknagl. preprint, 2002.
- [16] N.K im ura, T.K om atsubara, D.A oki, Y.O nuki, Y.H aga, E.Yam am oto, H.A oki, and H.Harim a. J.Phys. Soc. Jpn., 67:2185, 1998.
- [17] Y. Inada, Hiroshi Yam agami, Yoshinori Haga, Kenji Sakurai, Yoshihumi Tokiwa, Tetsuo Honma, Etsuji Yamamoto, Yoshichika Onuki, and Takashi Yanagisawa. J. Phys. Soc. Jpn., 68:3643, 1999.