Dynam icale ects of an unconventional current-phase relation in YBCO dc-SQUIDs

T. Lindstrom,¹, SA. Charlebois,¹ A.Ya. Tzalenchuk,² Z. Ivanov,¹ M.H.S. Amin,³ and A.M. Zagoskin^{3,4}

¹Department of Microelectronics and Nanoscience,

Chalmers University of Technology and Goteborg University, SE-412 96 Goteborg, Sweden

²N ational Physical Laboratory, Teddington, Middlesex, TW 11 OLW, UK

³D {W ave Systems Inc., 320-1985 Broadway, Vancouver, B.C., V6J 4Y3, Canada

⁴Physics and Astronom y Dept., The University of British Columbia,

6224 Agricultural Rd., Vancouver, V6T 1Z1 Canada

(Dated: April 14, 2024)

The predom inant d-wave pairing symmetry in high temperature superconductors allows for a variety of current-phase relations in Josephson junctions, which is to a certain degree fabrication controlled. In this letter we report on direct experimental observations of the elects of a non-sinusoidal current-phase dependence in YBCO dc-SQUIDs, which agree with the theoretical description of the system.

Keywords: Josephson E ect, High-Tem perature Superconductivity, d-wave symmetry

It is well established [1] that the wave function of a C ooperpair in m ost cuprate high-tem perature superconductors (HTS) has a d-wave symmetry. Its qualitative distinction from e.g. the anisotropic s-wave case is that the order parameter changes sign in certain directions, which can be interpreted as an intrinsic di erence in the superconducting phase between the lobes equal to .

The latter leads to a plethora of e ects, like form ation of A ndreev bound states at surfaces and interfaces in certain crystallographic orientations [2, 3, 4]. The current-phase dependence I_s () in Josephson junctions form ed by dd-junctions, as well as by sd-junctions com prised of a cuprate and a conventional superconductor, depends both on the spatial orientation of the d-wave order parameter with respect to the interface, and on the quality of the latter [5, 6, 7, 8, 9]. Time-reversal symmetry can also be spontaneously violated and thus spontaneous currents generated [10, 11, 12]. Another e ect can be doubling of the Josephson frequency [6, 13, 14].

In this letter we report on experim ental observations of strong e ects of an unconventional current-phase relation on the dynam ics of two dd-junctions integrated into a superconducting interference device (SQUID) con guration.

Since I_S () must be a 2 -periodic odd function, it can be expanded in a Fourier series. In the most cases only the rst two harm onics give a signi cant contribution to the current:

$$I_{\rm S}() = I_{\rm c}^{\rm I} \sin I_{\rm c}^{\rm II} \sin 2 \qquad (1)$$

In Josephson systems of conventional superconductors the second harmonic will usually be negligible [15] but in dd-junctions the second harmonic may dominate. If $I_c^{II} > I_c^{I}=2$ the equilibrium state is no longer = 0 but becomes double degenerate at = $\arccos(I_c^{I}=2I_c^{II})$!

=2. The system can then spontaneously break time reversal symmetry by choosing either state. Spontaneous currents as well as uxes can be generated in this state. The potential will have the shape of a double well and there are reasons to believe that it will be possible to observe quantum -coherence in this system. The presence of a 2^{nd} harm onic in the current-phase relation (CPR) of a dd-junction was con rm ed by Il'ichev et al. [8].

A non-sinusoidalCPR of the junctions will change the dynam ics of a dc-SQUD [16]. Regarding the junctions as m agnetically sm all, the supercurrent through the SQUD in the presence of an external ux $_x _0 (x=2)$ can be written as

$$I_{s}(; x) = I_{c1}^{I} \sin I_{c1}^{II} \sin (2) + I_{c2}^{I} \sin (+x)$$
$$I_{c2}^{II} \sin 2(+x) (2)$$

The critical current through the SQUID is given by the usual expression $I_c(x) = \max I_s(x)$. The timeaveraged voltage over the SQUID in the resistive regime is readily obtained in the resistively shunted junction (RSJ) approximation. By introducing [x] = 2 = 1and applying the same method as in [17] with the necessary generalizations, we obtain for the average voltage over the SQUID:

$$V^{1} = \frac{G_{1} + G_{2}}{2}^{Z} \quad d \quad I \quad (G_{1} \quad G_{2}) \frac{h}{2e} \frac{d}{dt}$$
$$I_{1} \quad + \frac{1}{2} \quad I_{2} \quad \frac{1}{2} \quad : \quad (3)$$

Here G $_{1;2}\,$ are the norm al conductances of the junctions, and

$$+$$
 x + $\frac{L}{0}$ (I₂ (=2) I₁ (+ =2)) = 0; (4)

gives the di erence, , in phase drops across each junction. In deriving (3,4) we have assumed that the inductance L is equally divided between the SQUID arm s. We have also neglected the spontaneous magnetic uxes in the dd-junctions, due to their sm all amplitude [11, 18].

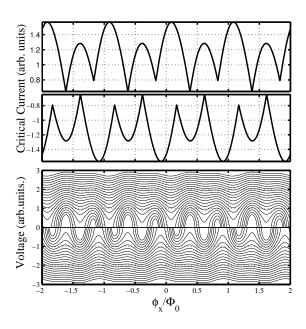


FIG.1: The results of simulations of the $I_c \ x$ and V x dependence for a dc-SQUID with $I_{c1}^{\rm I} = 1$, $I_{c2}^{\rm I} = 0$:1, $I_{c1}^{\rm II} = 0.2$ and $I_{c2}^{\rm II} = 0.4$ (arb. units). The dimenstructures correspond to bias currents in the range I = $I_{c1}^{\rm I}$ to I = $5I_{c1}^{\rm I}$ W e assume L = 0 and $G_1 = G_2$.

Though (4) is only explicitly solvable in the lim it L ! 0, it always yields [; x] = [; x]. This means that the usual inversion symmetry is retained.

The results of num erical calculations based on (2) and (3) are shown in g.1. The cusps in the critical current correspond to the points at which the global maximum in (1) switches from one localmaximum to another [16]. Note the quasi- 0=2-periodicity of the current isolines x picture, re ecting the current-phase dein the V pendence (1), and their shift along the x-axis, which depends on the sign of the bias current (as it must to maintain the central symmetry with respect to the origin). The shift does not depend on the magnitude of the current since we neglect the self-inductance. For large biases the operiodicity is restored. Indeed, as the bias grows, one set of minim a of the washboard potential, $U = (h=2e) [I^{I} \cos + (I^{II}=2) \cos 2]$ I], disappears rst unless the rst harm onic I^{I} is exactly zero.

W e have fabricated and studied a large number of dc-SQUIDs. The sam ples were fabricated from 250 nm thick YBCO - Im s deposited on SrT iO $_3$ -bicrystals. The grainboundary junctions (GBJs) are of the asymmetric [001]tilt type with the m isorientation angle of 45 (0 45 GBJ). For more information on GBJs see for example reference [19].

The pattern was de ned using E-Beam lithography and then transferred to a carbon mask employing a multistep process. Finally, the YBCO is etched through the mask using ion-milling. This scheme allows us to fabricate high-quality bicrystal junctions as narrow as 0.2 m, as has been reported elsewhere [20]. In the SQUID s under investigation the junctions are nominally 2 m wide; hence the fabrication-induced damage of the junctions is small.

The m easurem ents were done in an EMC -protected environm ent using a magnetically shielded LHe-cryostat. However, the magnetic shielding is imperfect, as is evident from the fact, that the expected zero-eld response of our SQUID s is not exactly at zero. The measuring electronics is carefully litered and battery-powered whenever possible. In order to measure the dependence of the critical current on the applied eld we used a voltage discriminator combined with a sam ple-and-hold circuit. All measurem ents reported here were perform ed at 4.2K.

The SQUID loops are 15 15 m². The numerically calculated inductance [21] is approximately 25 pH, yielding the factor = 2 $LI_c = 0$ between 0.5-2.

The SQUIDs were largerly non-hysteretic with a resistance of about 2 . The measured critical current varies from sample to sample but is in the range of tens of microam peres giving a current density of the order of $J_c = 10^3 \text{ A/cm}^2 \cdot pT$ he estimated Josephson penetration length $_J = _0 = \frac{1}{4} \frac{1}{_0 \text{ jc}} \frac{1}{_L}$ is approximately 2 m in all junctions, which means that the junctions are magnetically short. This is supported by the quasiperiod of the pattern in g2 being close to the expected value $_0=2$ LW [17]. The di erential conductance curves do not show any trace of a zero bias anom aly (ZBA), as is expected for 0 45 GBJs. ZBA shas been observed by other groups in GBJs with other orientations [2].

The critical current is plotted as a function of applied m agnetic eld for two SQUIDs in g.3. The result is in qualitative agreem ent with theory if we assume that the SQUID junctions have di errent ratios of the 1^{st} and 2^{nd} harm onics of the critical current. This assumption is supported by the fairly sm all modulation depth (it is easy to see from equation (2) that I_c would go exactly to zero in a SQUID with junctions of identical $I_{c2}=I_{c1}$).

We can t the data to equation (2), if we compensate for the residual background magnetic eld and assume that we have a small excess current (of the order of a few A) in the junctions. The tting parameters again con m that there is a large asym metry between the arm s of the SQUIDs. Note, that the model does not consider the ux penetration into the junctions,

The result for elds of the order of m T is presented in g.2 which shows the I_c -m odulation of the SQUID enveloped by an anom alous Fraunhofer-pattern quite sim – ilar to what has been reported by other groups [22, 23] for 0 45 GBJs. Note the inversion symmetry of the pattern with respect to the origin. That the globalm aximum is not in the center can be explained in several ways; it has been shown for example that this could be due to the presence of so-called —loops in the junction interface [24].

Figure 4 shows the V B-dependence of one of the

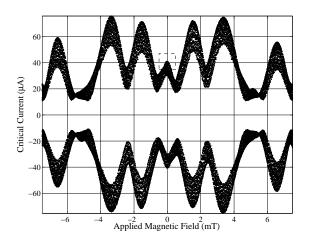


FIG. 2: Critical current as a function of magnetic eld at 4.2K. The dashed box indicates the area plotted in g. 3a.

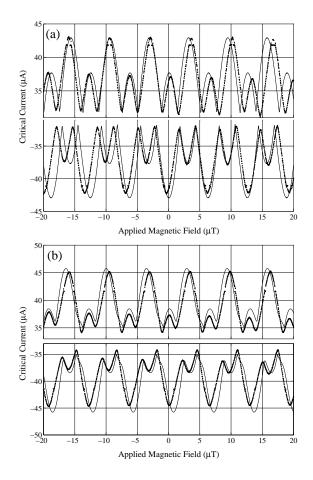


FIG. 3: Critical current as a function of applied magnetic eld for two di erent SQUIDs that are nom inally identical. The solid line represents the tted expression. The tting parameters are as follows:(a) $I_{c1}^{I} = 9 A$, $I_{c2}^{I} = 0.3 A$, $I_{c1}^{II} = 3.7 A$ and $I_{c2}^{II} = 22.7 A$ (b) $I_{c1}^{I} = 7.8 A$, $I_{c2}^{II} = 3.9 A$, $I_{c1}^{II} = 5.3 A$ and $I_{c2}^{II} = 4.3 A$. In both cases the t has been adjusted with respect to the residual background eld and the excess current of the junctions.

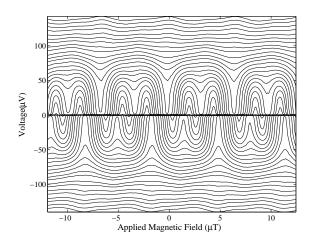


FIG.4: Voltage modulation as a function of applied magnetic eld for the SQUID whose I_c B is shown in g. 3a. The pattern is again inversion symmetric. Note the sign change at 100 V which we believe is due to a LC-resonance in the SQUID loop.

SQUIDs. The pattern is again eld inversion-symmetric. The overall structure is the same as in the model dependence of g.1, but there is also an additional shift due to self-eld e ects, which depends on the magnitude of the bias current and corresponds (at maximum) to a ux

0:1 0. In a beautiful experiment a similar dependence was recently observed by Baselmans et al in a Nb-Ag-Nb SNS junction where current-injectors were used to change the occupation of current-carrying states in the normal region [25]. A deviation from the model occurs at V = 100 V where the minima and maxima switch. This is probably due to an LC-resonance in the SQUID.Taking L = 25 pH, this would require C = 0.8 pF, which agrees with our measurements on single junctions

Remarkably, the observed o set of the V B- characteristics with respect to the direction of the bias current appears to be a much more robust manifestation of the presence of a second harmonic of the Josephson current, than the shape of the $I_{\rm c}$ B curves itself. We observed the shift even in SQUID swith the smallest junctions down to 0.5 m wide, where the deviations from the usual sinusoidal CPR were not obvious from the $I_{\rm c}$ B dependence.

Generally the nature of the transport through a GBJ will depend on its transmissivity D. Il'ichev et al. [8] have reported values of D as high as 0.3 in symmet-22:5) dd junctions as opposed to the usual ric (22:5 10 ⁵ 10^{2} . Since usually estimate for a GBJ, D $I_{c}^{II}=I_{c}^{I}$ / D, a high-transm issivity GBJ is required in order to observe e ects of the second harm onic. An estim ate of the average transm issivity of our junctions would be _{ab}l=R_NA 10² [26] assuming 1, the mean free path, to be equal to 10 nm and a resistivity in the a-b plane ab equal to 10⁴ cm. This is still too low to explain the strong 2nd harm onic we observe. However, it is known

from , e.g., TEM -studies [19], that the grain-boundary is far from uniform; the properties can signi cantly vary depending on the local properties of the interface, e ects such as oxygen di usion out of the GB etc., which are di cult to control. It is therefore reasonable to assume that there are m any parallel transport channels through the GB [27, 28]. Channels with high transm issivity dom inate the transport and m ight have D 0:1 even though the average transmissivity is much lower. This is also consistent with the fact that most of our SQUDs seem to be highly asymmetrical which is to be expected if the distribution of channels is random . The ratios of $I_{\rm c}^{\rm I}$ and I^{II} can vary as much as ten tim es between two junctions in the same $\operatorname{SQU}\mathbbm{D}$, even though the uctuations of the total I_c from sample to sample are much smaller. It is also clear from general considerations that a high value of I^{II} excludes a high value of I^I, since the 2nd harm onic usually dom inates if the odd harm onics of the supercurrent are cancelled by symmetry [29].

Recent studies of 0 45 GBJs have demonstrated that the SQUID -dynamics can be altered by the d-wave order parameter in YBCO [30]. It is however important to point out that our results do not directly relate to e.g. tetracrystal -SQUID experiments; the latter crucially depend on having one -junction with negative critical current, but still only the rst harm onic present in I_c (). O ur SQUID s have a conventional geometry, but unconventional current-phase relations.

O ne explanation for the pronounced e ects of the 2nd harm onic could be that relatively large sections of the interface are highly transparent and have a low degree of disorder. This in turn could be related to our fabrication scheme which seems to preserve the integrity of the barrier. This makes feasible their applicability in the quantum regime and supports our expectations that quantum coherence can be observed in this kind of structures.

To sum m arize, we have observed very pronounced 2^{nd} ham onic in the current-phase relation of a 'conventional' YBCO dc-SQUID with 0 45 grain boundary junctions. It has strongly in uenced the SQUID dynamics. All details of the SQUID behavior were explained within a simple model of a dd-junction with relatively high transparency. We believe that these e ects are im portant for better understanding of HTS Josephson junction and SQUID s.

D iscussions with E vgenii Il'ichev, A lexander G olubov, Tord C laeson, and John G allop are gratefully acknow ledged. The work is in part supported by The Board for Strategic R esearch (SSF) via the "O X ID E" program, the Science R esearch C ouncil, and the "Fonds qubcois de la recherche sur la nature et les technologies". The processing work is done at the M C 2 process lab at C halm ers U niversity of Technology. tobiasl@fy.chalmers.se

- [1] C.Tsuei and J.K intley, Reviews of M odem Physics 72, 969 (2000).
- [2] L.Al et al, Physical Review B 58, 11197 (1998).
- [3] T. Lofwander, V. Shum eiko, and G. W endin, Superconductor Science & Technology 14, R 53 (2001).
- [4] C.-R.Hu, Physical Review Letters 72, 1526 (1994).
- [5] S.Y ip, Physical Review B 52, 3087 (1994).
- [6] A. Zagoskin, Journal of Physics: Condensed M atter 9, L419 (1997).
- [7] E. Il'chev et al, Physical Review B 60, 3096 (1999).
- [8] E. Il'ichev et al, Physical Review Letters 86, 5369 (2001).
- [9] P.K om issinskiet al., Europhysics Letters 57, 585 (2002).
- [10] A.Huck, A.van Otterlo, and M. Sigrist, Physical Review B 56, 14163 (1997).
- [11] M.Amin, A.Omelyanchouk, and A.Zagoskin, Physical Review B 63, 212502 (2001).
- [12] S.Ostlund, Phys. Rev. B 58, R14757 (1998).
- [13] T. Lofwander, G. Johansson, M. Hurd, and G. Wendin, Physical Review B 57, R 3225 (1998).
- [14] H. Arie et al, Physical Review B 62, 11864 (2000).
- [15] M. Keene, C. Gough, and A. Rae, Journal of Physics: Condensed M atter 3, 6079 (1991).
- [16] M.H.S.Amin, M.Coury, and R.Roæ, EEE Trans. Appl.Supercond.12, 1877 (2002).
- [17] A.Barone and G.Paterno, Physics and Applications of the Josephson E ect (John W iley & Sons, 1982).
- [18] M.Amin, S.Rashkeev, M.Coury, A.Omelyanchouk, and A.Zagoskin, Physical Review B 66, 174515 (2002).
- [19] H. Hilgenkamp and J. Mannhart, Reviews of Modem Physics 74, 297 (2002).
- [20] A. Tzalenchuk et al., Applied Physics Letters Submitted (2002).
- [21] M. Khapaev, A. Kidiyarova-Shevchenko, P. Magnelind, and M. Kupriyanov, IEEE Transactions on Applied Superconductivity 11, 1090 (2001).
- [22] J. Mannhart, B. Mayer, and H. Hilgenkamp, Zeitschrift fur Physik B (Condensed Matter) 101, 175 (1996).
- [23] W .Neils and D. van Harlingen, Physica B 284-288, 587 (2000).
- [24] H. Sm ilde et al., Physical Review Letters 88, 057004 (2002).
- [25] J. Baselm ans, T. Heikkil, B. van W ees, and T. K lapwijk, Phys. Rev Lett 89, 207002 (2002), the pronounced 2nd harmonic in this experiment appears due to nonequilibrium e ects, see e.g. J.C. C larke "Charge Im balance" in K E.G ray (ed.) Nonequilibrium Superconductivity, Phonons and K apitza B oundaries, NATO A SI Series, P lenum, NY (1981), p. 353.
- [26] G.Blonder, M.Tinkham, and T.K lapwijk, Physical Review B 25, 4515 (1982).
- [27] Y. Naveh, D. Averin, and K. Likharev, Physical Review Letters 79, 3482 (1997).
- [28] E. Samelli, G. Testa, and E. Esposito, Journal of Superconductivity 7, 387 (1994).
- [29] Y.Barash, Physical Review B 61, 678 (2000).
- [30] B. Chesca et al., Physical Review Letters 88, 177003 (2002).