

# Superconducting Transition Temperature in Heterogeneous Ferromagnet-Superconductor Systems

Valery L. Pokrovsky<sup>1,2</sup> and Hongduo Wei<sup>1</sup>

<sup>1</sup>*Department of Physics, Texas A&M University, College Station, TX 77843-4242*

<sup>2</sup>*Landau Institute for Theoretical Physics, Chernogolovka, Moscow Distr. 142432, Russia*

We study the shift of the the superconducting transition temperature  $T_c$  in ferromagnetic-superconducting bi-layers and in a superconducting film supplied a square array of ferromagnetic dots. We find that the transition temperature in these two cases change presumably in opposite direction and that its change is not too small. We extend these results to multilayer structures. We predict that rather small external magnetic field  $\sim 10$  Oe can change the transition temperature of the bilayer by 10% .

PACS numbers: 74.60.Ge, 05.40.-a, 74.62.Dh

## 1. INTRODUCTION

Heterogeneous ferromagnetic-superconducting (FM-SC) systems have attracted much attention recently [1]. In majority of these systems the proximity effect is suppressed by the oxide layer between FM and SC. Inhomogeneous magnetization produces a magnetic field penetrating into the superconductor and inducing supercurrents. Supercurrents in turn produce the magnetic field acting on the magnetization. Thus, the FM and SC of systems strongly interact via magnetic field. Systems in which both, FM and SC parts are thin films represent a special interest for the experiment and can be analyzed theoretically. In these systems, spontaneous vortices appear due to the magnetic interaction [2]. Erdin et al. [3] have developed a method to calculate the arrangement of the magnetization in the FM film and supercurrents including vortices in the SC film in the London's approximation. The London's approximation is quite good for these mesoscopic systems because characteristic length scales for magnetic field (the effective penetration depth, the linear size of the textures) are much larger than the coherence length  $\xi$  of the superconductor. This method was applied recently [4] to study topological textures in a FM-SC bilayer (FSB). It was shown that the homogeneous state of the FSB with the magnetization perpendicular to the layer is unstable with respect to the formation of vortices. The ground state of the FSB represents a periodic array of stripe domains in which the direction of the magnetization in the FM film and the vorticity in the SC film alternate together.

In this article we study how the combined FM-SC textures change the superconducting transition temperature in bilayers and multilayers. For this purpose we extend theory of spontaneous SC-FM structures developed in [4] to the case of multilayers. We find that spontaneous domain-vortex structures increase the transition temperature, whereas vortex structures induced by a periodic array of magnetic dots decreases the transition temperature. The magnitude of this effect is large enough to en-

able its experimental observation. Though the influence of the textures on the transition temperature is akin to the influence of the homogeneous magnetic field, there are important differences between these two phenomena: first, the average magnetic field may be zero for magnetic textures; second, the reciprocal action of the magnetic field generated by vortices onto magnetization is substantial.

The plan of this article is as follows. In the next section we consider the change of the transition temperature in the spontaneous stripe structure formed in the FSB. In Section 3 we analyze how this stripe structure and the transition temperature change in the presence of an external magnetic field. In Section 4 we study the shift of the transition temperature in a square array of magnetic dots. Section 5 is devoted to theory of the FM-SC spontaneous textures in multilayers and to the transition temperature shift in them. Our conclusion are given in Section 6.

## 2. TRANSITION TEMPERATURE IN SPONTANEOUS STRIPE STRUCTURE OF FSB

As it was mentioned earlier, the homogeneous state of the FSB with the magnetization perpendicular to the layer is unstable with respect to formation of a stripe domain structure, in which both, the the direction of the magnetization in the FM film and the circulation of the vortices in the SC film alternate together. Let the stripe width be  $L_s$ . The magnetization can be written as  $\mathbf{m} = ms(x)\hat{z}$ , where the coordinate  $x$  is along the direction perpendicular to the domain walls,  $\hat{z}$  denotes the unit vector perpendicular to the layers,  $s(x)$  is the periodic step function with period  $2L_s$ :

$$s(x) = \begin{cases} +1 & 0 < x < L_s, \\ -1 & L_s < x < 2L_s. \end{cases}$$

The energy of the stripe structure per unit area  $U$  and the stripe equilibrium width  $L_s$  were calculated in [4].

Here we correct a calculational mistake of this work [8]:

$$U = \frac{-16\tilde{m}^2}{\lambda_e} \exp\left(\frac{-\epsilon_{dw}}{4\tilde{m}^2} + C - 1\right), \quad (1)$$

$$L_s = \frac{\lambda_e}{4} \exp\left(\frac{\epsilon_{dw}}{4\tilde{m}^2} - C + 1\right). \quad (2)$$

The notations in eqs. (1), (2) are as follows:  $\lambda_e = \frac{\lambda_L^2}{d_s}$  is the effective penetration depth in the SC film, whose thickness is denoted  $d_s$ ;  $\epsilon_{dw}$  is the linear tension of the domain wall;  $\tilde{m} = m - \epsilon_v/\phi_0$ ;  $m$  is the magnetization per unit area of the FM film;  $\epsilon_v = \frac{\phi_0^2}{16\pi^2\lambda_e} \ln \frac{\lambda_e}{\xi}$  is the single vortex energy in the absence of the FM film;  $C = 0.57721 \dots$  is the Euler constant. To find the transition temperature, we combine the energy given by eq. (1) with the Ginzburg-Landau free energy. The total free energy per unit area reads:

$$F = U + F_{GL} = \frac{-16\tilde{m}^2}{\lambda_e} \exp\left(\frac{-\epsilon_{dw}}{4\tilde{m}^2} + C - 1\right) + n_s d_s [\alpha(T - T_c) + \frac{\beta}{2} n_s]. \quad (3)$$

Here  $\alpha$  and  $\beta$  are the Ginzburg-Landau parameters. We omit the gradient term in the Ginzburg-Landau equation since the gradients of the phase are included in the energy (1), whereas the gradients of the superconducting electrons density can be neglected everywhere beyond the vortex cores. Recalling that  $\lambda_L^2 = \frac{m_s c^2}{4\pi n_s e^2}$  and plugging it into eq. (1), we find:

$$F = \frac{-256\pi^2 \chi_0 n_s}{\phi_0} \left(m + n_s \chi_0 \ln \frac{16\pi^2 \xi n_s \chi_0}{\phi_0}\right)^2 \cdot \exp\left[\frac{-\epsilon_{dw}}{4(m + n_s \chi_0 \ln \frac{16\pi^2 \xi n_s \chi_0}{\phi_0})^2} + C - 1\right] + n_s d_s [\alpha(T - T_c) + \frac{\beta d_s}{2} n_s]. \quad (4)$$

where  $\chi_0 = \frac{\phi_0 d_s e^2}{4\pi m_s c^2}$ . Minimizing the total free energy over  $n_s$ , and using the condition that  $n_s = 0$  at new transition temperature  $T_c^*$  we obtain:

$$\Delta T_c \equiv T_c^* - T_c = \frac{64\pi m^2 e^2}{\alpha m_s c^2} \exp\left(\frac{-\epsilon_{dw}}{4m^2} + C - 1\right). \quad (5)$$

Eq. (5) demonstrates that the interaction between FM and SC layers in the spontaneous stripe structure increases the transition temperature  $T_c$ . Theory [4] assumes that the ratio  $\epsilon_{dw}/m^2$  is larger than 1, so that  $\exp(\frac{\epsilon_{dw}}{4m^2}) \gg 1$ . However, this ratio can not be too large. Otherwise the width of domain becomes larger than the sample linear size. The maximum possible shift of transition temperature corresponds to  $\frac{\epsilon_{dw}}{4m^2} \sim 1$ . It is

$$\Delta T_c \sim \frac{64\pi m^2 e^2}{\alpha m_s c^2}, \quad (6)$$

The value  $\alpha$  can be estimated as  $\alpha \sim T_c/\epsilon_F$ , where  $\epsilon_F$  is the Fermi energy. It is about  $10^{-4}$  for low-temperature superconductors and about  $10^{-3} - 10^{-2}$  for high-temperature superconductors. If we take  $4\pi M \sim 1T$ ,  $T_c \sim 3K$ ,  $\epsilon_F \sim 30,000K$  and  $d_m \sim 300\text{\AA}$ , we obtain  $\Delta T_c/T_c \sim 0.1$ . The dependence  $\Delta T_c \propto m^2 = M^2 d_m^2$  on the thickness of the FM film and magnetization can be checked experimentally.

### 3. SPONTANEOUS STRIPE STRUCTURE IN EXTERNAL FIELD

In this section we study the spontaneous stripe system in the FM-SC bilayer in the presence of an external perpendicular magnetic field  $B$  (along  $\hat{z}$  direction). Since the magnetization tends to align along the external magnetic field we anticipate that the width  $L_1$  of stripes with the magnetization parallel to the external magnetic field increases, whereas the width  $L_2$  of the stripes with the antiparallel magnetization decreases. Let us define a step function with the period  $L = L_1 + L_2$  as follows:

$$s(x) = \begin{cases} +1 & (0 < x < L_1), \\ -1 & (L_1 < x < 2L_2). \end{cases}$$

The Fourier transform of  $s(x)$  is:

$$s_G = \begin{cases} 2i(1 - e^{iGL_1})/(LG) & (G \neq 0), \\ (L_1 - L_2)/L & (G = 0). \end{cases} \quad (7)$$

Here  $G = 2\pi r/L$  and  $r$  are integers. For the sake of brevity, we denote  $t = L_1 - L_2$ . At large distance from the bilayer the magnetic field asymptotically becomes equal to the external magnetic field. The total magnetic flux is the same in any cross-section of the space. Thus, the average magnetic field through superconducting layer is

$$\frac{1}{L} \int_0^L n(\mathbf{x}) \phi_0 dx = B_{ext}. \quad (8)$$

This constraint can be incorporated by the standard Lagrange multiplier method. According to it, the problem is reduced to minimization of the effective energy  $\tilde{U}_v = U_v + U_\omega$ , where  $U_v$  is the energy of the vortex system, and  $U_\omega = \omega \frac{\phi_0}{L} \int n(\mathbf{x}) x$ ,  $\omega$  is the Lagrange multiplier. The general expression for the free energy of a periodic stripe system of magnetization and vortices is given by equation (10) of the work [4]. Employing this equation and the Fourier expansion for the step function  $s(x)$  (see equation (7)) and denoting  $n_G$  the Fourier-transform of the vortex density  $n(x)$ , we obtain:

$$\begin{aligned} \tilde{U}_v = & \sum_G \tilde{\epsilon}_v s_G n_{-G} + \frac{1}{2} \sum_{G \neq 0} V_G n_G n_{-G} \\ & + \frac{\tilde{\epsilon}_v B_{ext} t}{\phi_0 L} - \omega(\phi_0 n_G - B_{ext}), \end{aligned} \quad (9)$$

where  $V_G = \phi_0^2/(2\pi|G|)$  is the Fourier-transform of the vortex interaction. An infinitely large interaction term  $V_{G=0}n_{G=0}n_{G=0}$  has been omitted since it corresponds to the fixed average magnetic field. From equation (9) we readily find that the constraint condition implies:

$$n_{G=0} = \frac{B_{ext}}{\phi_0}. \quad (10)$$

This equation confirms that  $V_{G=0}n_{G=0}n_{G=0}$  is the energy of the uniform external field. Minimization of the total vortex energy  $\tilde{U}_v$  over the vortex density  $n_G$  results in a system of equations:

$$\begin{cases} \tilde{\epsilon}_v s_G + V_G n_G = 0 & (G \neq 0), \\ \tilde{\epsilon}_v s_{G=0} = \Lambda \phi_0 & (G = 0). \end{cases}$$

Plugging the solutions of  $n_G$  ( $G \neq 0$ ),  $\omega$  and  $n_{G=0}$  from equation (10), we finally obtain

$$\begin{aligned} U = & \frac{-8\tilde{\epsilon}_v^2}{\phi_0^2 L} [C + \ln \frac{L}{\lambda} + \frac{1}{2} \ln(2 + 2 \cos \frac{\pi t}{L})] \\ & + \frac{\tilde{\epsilon}_v B_{ext} t}{\phi_0 L} + \frac{2\epsilon_{dw}}{L}. \end{aligned} \quad (11)$$

We are now in a position to minimize the total energy  $U$  over  $L$  and  $t$ . After doing that, we obtain two equations:

$$C - 1 + \ln \frac{2L}{\lambda} - \ln(1 + \tan^2 u)^{1/2} - \frac{\tilde{\epsilon}_{dw}}{4\tilde{m}^2} = 0, \quad (12)$$

$$\tan u = \frac{LB_{ext}}{4\pi\tilde{m}}. \quad (13)$$

Here  $u = \frac{\pi t}{2L}$ . From equations (12) and (13) we find solutions for  $L$  and  $t$ :

$$L = \frac{2L_s}{\sqrt{1 - (\frac{L_s B_{ext}}{2\pi\tilde{m}})^2}}, \quad (14)$$

$$t = \frac{2L}{\pi} \arctan \frac{LB_{ext}}{4\pi\tilde{m}}. \quad (15)$$

where  $L_s$  is given by equation (2). The results. (14) and (15) are similar to those for a purely ferromagnetic stripe structure in a single ferromagnetic film [10]. The critical external field  $B_{ext}^c$  at which the domain structure vanishes is

$$B_{ext}^c = 2\pi\tilde{m}/L_s, \quad (16)$$

which is in the range of 1 – 10 Oe.

In conclusion of this section, we consider how the temperature of superconducting transition of the bilayer changes in the presence of external magnetic field. Since at the field  $B_{ext}^c \sim 1-10$  Oe the stripe structure vanishes, the superconducting transition proceeds in the homogeneous state of ferromagnetic film excluding very small vicinity of  $T_c$ . Therefore, it is determined by the nucleation process as in the case of a single superconducting

film. The nucleation in a thin film for the field perpendicular to it was considered by Tinkham [12]. Though the geometry is different from the bulk geometry considered by Abrikosov [13], his solution can be directly applied. The order parameter coincides with the Landau wave function for the first Landau level. In the case of bilayer the energy of the nucleus reads:

$$U = \int \left[ \frac{1}{2m} \left| \left( \frac{\hbar}{i} \nabla - \frac{2e}{c} \mathbf{A}_0 \right) \psi \right|^2 + a |\psi|^2 \right] d^2x + \Delta U. \quad (17)$$

It differs from the energy in the absence of magnetic film by the value  $\Delta U = -m \int B_z^{(n)} d^2x$ , where  $B_z^{(n)}$  is the magnetic field generated by the nucleus at the ferromagnetic film. The magnetic field generated by the nucleus reads:

$$\mathbf{B}^{(n)}(\mathbf{r}) = \frac{1}{c} \int \nabla \frac{1}{|\mathbf{r} - \mathbf{r}'|} \times \mathbf{j}_n(\mathbf{r}') d^3x'. \quad (18)$$

We assume that the current flows in the  $x-y$  plane. Since it has zero divergence, it can be represented as  $\mathbf{j}_n = \hat{z} \times \nabla f$ , where  $f(x, y)$  is a function localized in a finite part of the plane. The flux of the induced field is:

$$\begin{aligned} & \int B_z^{(n)} d^2x \\ &= \frac{1}{c} \int \left( \hat{z} \times \nabla \frac{1}{|\mathbf{r} - \mathbf{r}'|} \right) \left( \hat{z} \times \nabla f(\mathbf{r}') \right) d^2x d^3x' \end{aligned} \quad (19)$$

Simple transformations turn this integral into a following form:

$$\int B_z^{(n)} d^2x = -\frac{1}{c} \int f(\mathbf{r}') \nabla^2 \frac{1}{|\mathbf{r} - \mathbf{r}'|} d^2x d^3x'. \quad (20)$$

This integral is equal to zero. Indeed, the 3d Laplasian of the inverse distance is proportional to  $\delta(\mathbf{r} - \mathbf{r}')$ . The radius-vector  $\mathbf{r}$  belongs to the magnetic layer, whereas the radius-vector  $\mathbf{r}'$  belongs to the superconducting one. What stays in equation (20) is the 2d Laplasian operator, which differs from the 3d one by the second derivative  $(\frac{\partial}{\partial z})^2 \frac{1}{|\mathbf{r} - \mathbf{r}'|}$ , but the integral from this function over the plane  $\mathbf{r}$  is equal to zero when  $\mathbf{r}'$  does not belong to the same plane.

Thus, the interaction of the superconducting nucleus and the homogeneously magnetized film is zero independently on the wave function of the localized nucleus. Therefore, the transition temperature is the same as in the absence of the ferromagnetic film. Earlier we have found that, without magnetic field the ferromagnetic layer increases the transition temperature and its change may be about 1/10 of initial value. Surprisingly this shift disappears at extremely small external field about 1-10 Gs. The reason of this paradox consist of unlimited expansion of domains upon approaching the transition point. An interesting and counterintuitive result of this

consideration is that a very small magnetic field about 10Oe is enough to change the transition temperature relatively by 1/10. After this fast change the transition temperature changes substantially when magnetic field becomes comparable to  $H_{c2}$ , normally in the range  $1T$ .

#### 4. TRANSITION TEMPERATURE IN A SUPERCONDUCTING FILM WITH A SQUARE ARRAY OF FERROMAGNETIC DOTS

Recently Erdin considered theoretically the vortex-antivortex textures in a superconducting film supplied with a regular square lattice of ferromagnetic dots [11]. Unfortunately, there occurred a mistake in his code for numerical calculations. Therefore, we reproduce here a part of his analysis, but our conclusions are completely different. We denote the dot lattice constant be  $a$  and assume each dot to be a circular thin disk with the radius  $R$  and constant magnetization  $m$  per unit area directed perpendicular to the plane (along  $z$ -axis). The total en-

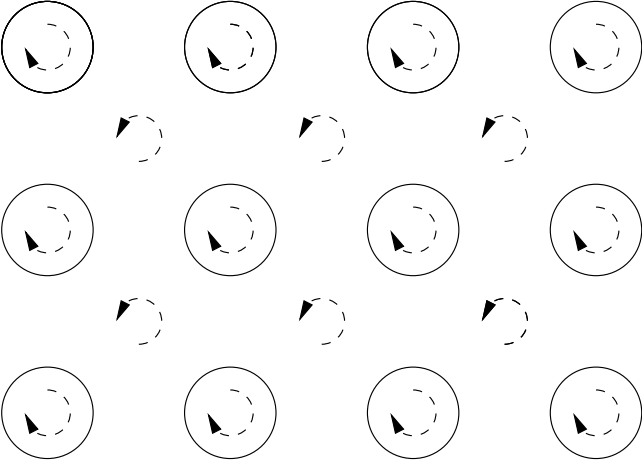


FIG. 1: Schematics representaion of FM dots with spontaneous vortices and antivortices. The circles drawn by solid line represent FM dots. The dash half-circles with clockwise and anticlockwise arrow indicate vortices and antivortices respectively.

ergy per unit area of the system is [11]:

$$U = u_{vv} + u_{mv} + u_{mm}. \quad (21)$$

The three terms in the right-hand side of the above equation can be written as follows:

$$u_{vv} = \frac{\phi_0}{4\pi a^2} \sum_{\mathbf{G}} \frac{|F_{\mathbf{G}}|^2}{G(1+2\lambda G)}, \quad (22)$$

$$u_{mv} = -\frac{\phi_0}{a^2} \sum_{\mathbf{G}} \frac{m_z \mathbf{G} F_{-\mathbf{G}}}{1+2\lambda G}, \quad (23)$$

$$u_{mm} = -2\pi\lambda \sum_{\mathbf{G}} \frac{G^2 |\mathbf{m}_z \mathbf{G}|^2}{1+2\lambda G}. \quad (24)$$

where  $\mathbf{G} = \frac{2\pi}{a}(r, s)$  ( $r, s$  are integers) are the reciprocal lattice vectors;  $F_{\mathbf{G}} = \sum_i n_i e^{i\mathbf{G} \cdot \mathbf{r}_i}$  is the structure factor of the vortex lattice;  $n_i, \mathbf{r}_i$  indicate the vorticity and the position of a  $i$ -th vortex. Only the change of energy  $\tilde{u}_{mm}$  in superconducting state compared to the normal state matters:

$$\tilde{u}_{mm} = u_{mm}(\lambda) - u_{mm}(\lambda \rightarrow \infty) \quad (25)$$

The last term in the r.h.s. of equation (25) is the dipolar energy of the FM dots above the superconducting transition. Below the superconducting transition temperature  $T_c$  the magnetic field generated by the dots penetrates into the SC film and can create vortices and antivortices if the magnetization and the size of the dots are large enough [3]. Erdin [11] considered the case when only one vortex and one antivortex appear per a magnetic dot. He stated that there is a symmetry violation in the lowest energy state. Our numerical results contradict to this statement: we find that the vortex centers are located precisely under the centers of the magnetic dots, whereas the antivortex centers are located at the centers of the magnetic dot lattice. Employing this fact and keeping in mind that  $\lambda \gg L$  near the new transition temperature  $T_c^*$ , we can rewrite the total energy (21) as follows:

$$u = \frac{\phi_0 e^2 d_s n_s}{2\pi m_s c^2 a^2} \ln \frac{a}{\xi} - \frac{\phi_0^2 e^4 d_s^2 n_s^2}{4\pi^2 m_s^2 c^4 a} I_0 - \frac{\phi_0^2 e^2 d_s n_s}{4\pi^2 m_s c^2 a^2} (I_1 + \frac{4\pi^2 m R}{\phi_0} I_2) + \frac{2\pi^2 m^2 e^2 d_s n_s R^2}{m_s c^2 a^2} I_3. \quad (26)$$

where  $\sum'$  means that the term  $r = s = 0$  are omitted.  $I_1, I_2$  and  $I_3$  are defined as series:

$$I_0 = \sum_{n,s=-\infty}^{+\infty'} \frac{1}{(n^2 + s^2)^{3/2}}$$

$$I_1 = \sum_{n,s=-\infty}^{+\infty'} \frac{(-1)^n + (-1)^s}{n^2 + s^2}$$

$$I_2 = \sum_{n,s=-\infty}^{+\infty'} \frac{J_1(\frac{2\pi R}{a} \sqrt{n^2 + s^2}) [1 - (-1)^{n+s}]}{n^2 + s^2}$$

$$I_3 = \sum_{n,s=-\infty}^{+\infty'} \frac{J_1^2(\frac{2\pi R}{a} \sqrt{n^2 + s^2})}{n^2 + s^2}. \quad (27)$$

We combine this energy with the Ginzburg-Landau free energy for the SC film as it was done in the stripe structure case:

$$F = \frac{\phi_0 e^2 d_s n_s}{2\pi m_s c^2 a^2} \ln \frac{a}{\xi} - \frac{\phi_0^2 e^4 d_s^2 n_s^2}{4\pi^2 m_s^2 c^4 a} I_0 - \frac{\phi_0^2 e^2 d_s n_s}{4\pi^2 a^2 m_s c^2} (I_1 + \frac{4\pi^2 m R}{\phi_0} I_2) + \frac{2\pi^2 m^2 e^2 d_s n_s R^2}{m_s c^2 a^2} I_3 + \alpha(T - T_c) n_s d_s + \frac{\beta}{2} n_s^2 d_s. \quad (28)$$

The condition of minimum over  $n_s$  from the free energy 28 reads:

$$\begin{aligned} & \frac{\phi_0 e^2 d_s}{2\pi m_s c^2 a^2} \ln \frac{a}{\xi} - \frac{\phi_0^2 e^4 d_s^2 n_s}{2\pi^2 m_s^2 c^4 a} I_0 \\ & - \frac{\phi_0^2 e^2 d_s}{4\pi^2 a^2 m_s c^2} (I_1 + \frac{4\pi^2 m R}{\phi_0} I_2) + \frac{2\pi^2 m^2 e^2 d_s R^2}{m_s c^2 a^2} I_3 \\ & + \alpha(T - T_c) d_s + \beta n_s d_s = 0. \end{aligned} \quad (29)$$

At a new critical temperature  $T_c^*$  the density of superconducting carriers must be zero. Plugging  $n_s(T_c^*) = 0$  into eq. (29), we obtain the shift of the critical temperature:

$$\begin{aligned} \Delta T_c = & \frac{\phi_0 e^2}{4\pi^2 m_s c^2 a^2} \left( \frac{4\pi^2 m R}{\phi_0} I_2 + I_1 \right. \\ & \left. - 2\pi \ln \frac{a}{\xi} - \frac{8\pi^4 m^2 R^2}{\phi_0^2} I_3 \right). \end{aligned} \quad (30)$$

Figure (2) shows the relation between  $\Delta T_c$  and  $R$  respectively for  $\xi = 0.21a$ . To ensure spontaneous occurrence

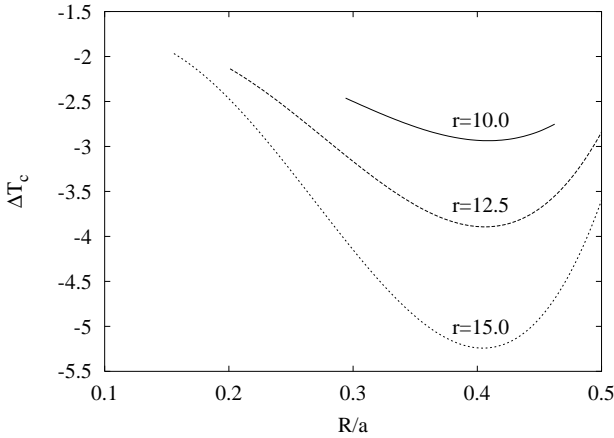


FIG. 2:  $\Delta T_c$  vs.  $R$  for  $\xi = 0.21a$  respectively for  $r = 10.0, 12, 5$  and  $15.0$ , here  $r = \frac{4\pi^2 m L}{\phi_0}$ .  $\Delta T_c$  is in the unit  $\frac{\phi_0^2 e^2}{4\pi^2 a^2 m_s c^2}$ .

of the vortices the inequality  $u_{mv} + u_{vv} < 0$  must be satisfied. It is equivalent to the following relation:

$$\frac{4\pi^2 m R}{\phi_0} I_2 + I_1 - 2\pi \ln \frac{a}{\xi} < 0. \quad (31)$$

The validity of the London's approximation implies  $\xi \ll a$ . This condition is violated in a close vicinity of the transition temperature, the smaller the larger is the dot lattice constant  $a$ . For  $a \sim 1\mu m$  this vicinity is less or of the order of  $0.01T_c$  and further we neglect it. Fig. (2) shows that the shift of transition temperature is a rather complicated function of the dots radius  $R$  and the ratio  $r = 4\pi^2 m L / \phi_0$ . For each value  $r$ , there exists a threshold radius  $R_0$ , at which the vortices first appear. The shift of the transition temperature grows near the threshold with  $R/a$  until maximum and then decreases, it remain negative in the interval  $R_0/a$  and  $1/2$ . For each fixed  $R/a$ , the shift of the transition temperature increases with the ratio  $r$  and is negative.

## 5. FERROMAGNETIC TEXTURES IN MULTILAYERS

Let us with a FM-SC multilayer consisting of  $N$  bilayers, each having the thickness  $d$  in the limit  $Nd \gg L_s$ , where  $L_s$  is the lateral size of the layers. If the magnetic films are magnetized perpendicularly, the average induction inside the multilayer is  $B = 4\pi m/d$  and it is directed perpendicularly to the layers. The situation is the same as in the layered superconductors placed into an external magnetic field [5]. Therefore, pancake vortices in each superconducting layer must appear. Together they form the Abrikosov linear vortices and satisfy a condition:  $m\phi_0/d > \epsilon_l$ , which guarantees that the vortex line is energy favorable. Here  $\epsilon_l = \epsilon_0 \ln \frac{\lambda}{\xi}$  [6] is the usual vortex line energy per unit length,  $\epsilon_0 = \phi_0^2 / (4\pi\lambda)^2$  and  $\lambda$  is the planar bulk penetration depth. There is no need to consider the Josephson coupling effect in this case since the phase difference between superconducting layers is zero if the vortex lines are perpendicular to the layers. On the other hand, the Josephson vortices appear along the layers if the magnetization  $\mathbf{m}$  is parallel to the layers and satisfy a condition  $m\phi_0/d > \epsilon_J$  where  $\epsilon_J = \gamma\epsilon_0 \ln \frac{\lambda}{d}$  is the Josephson vortex line energy and  $\gamma$  is the anisotropy parameter for the layered superconductor [5]. These ideas were applied by M. Houzet et al. [7] to explain the magnetic properties of the magnetic superconductor  $\text{RuSr}_2\text{GdCu}_2\text{O}_8$ . In this article we presumably study the opposite limit  $Nd \ll \Lambda$ , where  $\Lambda = \lambda^2/d$  is the effective penetration depth for layered superconductors.

In this section we first focus on few-layer superconductors without ferromagnetic texture, which will be discussed later. Pancake vortices in a finite stack of layers were discussed by Mints et al. [14]. We modify a method developed by Efetov [15] for a plane superconductor and by K. Fischer [16] for a layered superconductor with infinite number of layers. We consider a superconductor consisting of  $N$  layers coupled only by their magnetic field. To simplify the calculation, we assume that layers are infinitely thin and located at the planes  $z_n = nd$  ( $n$  is an integer). The vector potential  $\mathbf{A}$  due to the pancake vortices at superconducting layers satisfy a following equation:

$$\begin{aligned} & -\Delta \mathbf{A} + \frac{1}{\Lambda} \sum_n \delta(z - z_n) \mathbf{A} \\ & = \frac{\phi_0}{2\pi\Lambda} \sum_n \delta(z - z_n) \sum_\rho \delta_\rho \nabla^{(2)} \varphi_n(\mathbf{r} - \rho). \end{aligned} \quad (32)$$

The currents in equation (32) are induced by pancake vortices with the vorticity  $\delta_\rho = \pm 1$  placed at the position  $\rho$  in the  $n$ -th plane. The Coulomb gauge  $\nabla \cdot \mathbf{A} = 0$  was used. In addition,  $A_z = 0$  because the direction of  $\nabla^{(2)} \varphi_n$  is along the layers. It is useful to introduce an auxiliary potential  $\tilde{\mathbf{A}}(\mathbf{r}, z) = \sum_n \delta(z - z_n) \mathbf{A}(\mathbf{r}, z)$  confined to the layers, the "London vector" [16]  $\phi_n(\mathbf{r}) =$

$\sum_{\rho} \delta_{\rho} \frac{\phi_0}{2\pi} \nabla^{(2)} \varphi_n(\mathbf{r}-\rho)$  and corresponding auxiliary vector  $\tilde{\phi}_n(\mathbf{r}, z) = \sum_n \phi_n(\mathbf{r}) \delta(z - z_n)$ . In terms of these variables equation (32) can be rewritten as follows:

$$-\Delta \mathbf{A} + \frac{1}{\Lambda} \tilde{\mathbf{A}} = \frac{\phi_0}{2\pi\Lambda} \tilde{\phi}_n. \quad (33)$$

Equation (33) can be solved by Fourier-transformation. The partial result is:

$$\mathbf{A}(\mathbf{q}, k) = \sum_n e^{-ikz_n} \frac{\phi_n(\mathbf{q}) - \mathbf{A}_n(\mathbf{q})}{\Lambda(q^2 + k^2)}. \quad (34)$$

where  $\mathbf{A}(\mathbf{q}, k)$  is the Fourier-transform of the vector-potential  $\mathbf{A}(\mathbf{r}, z)$  and  $\mathbf{A}_n(\mathbf{q})$  is the plane Fourier-transform of the vector-potential  $\mathbf{A}(\mathbf{r}, z_n)$  taken at the  $n$ -th superconducting plane. Expressing this value by the inverse Fourier-transformation, we find a system of equations for  $\mathbf{A}_n(\mathbf{q})$ :

$$\begin{aligned} & \sum_n \left( \frac{1}{2\Lambda q} e^{-q|m-n|d} + \delta_{mn} \right) \mathbf{A}_n(\mathbf{q}) \\ &= \frac{1}{2\Lambda q} \sum_n \phi_n(\mathbf{q}) e^{-q|m-n|d}. \end{aligned} \quad (35)$$

We apply eq. (35) to study the simplest case of two superconducting layers. Let only one pancake vortex to be placed in the center of the layer  $z = 0$  at  $\rho = 0$ . The other layer is located at  $z = d$ . The solution of the system (35) for this situation reads:

$$\begin{aligned} \mathbf{A}_1(\mathbf{q}) &= \frac{1 + 2\Lambda q - e^{-2qd}}{1 + 4\lambda q + 4\Lambda^2 q^2 - e^{-2qd}} \phi_1(\mathbf{q}) \\ \mathbf{A}_2(\mathbf{q}) &= \frac{2\Lambda q e^{-2qd}}{1 + 4\lambda q + 4\Lambda^2 q^2 - e^{-2qd}} \phi_1(\mathbf{q}). \end{aligned} \quad (36)$$

In the limit  $qd \ll 1$  this solution becomes simpler:

$$\begin{aligned} \mathbf{A}_1(\mathbf{q}) &= \frac{1}{2 + 2\Lambda q} \phi_1(\mathbf{q}) \\ \mathbf{A}_2(\mathbf{q}) &= \frac{1}{2 + 2\Lambda q} \phi_1(\mathbf{q}). \end{aligned} \quad (37)$$

The current density in each layer is given by:

$$\begin{aligned} \mathbf{J}_1(\mathbf{q}) &= \frac{c}{4\pi\Lambda} (\phi_1(\mathbf{q}) - \mathbf{A}_1(\mathbf{q})) \\ \mathbf{J}_2(\mathbf{q}) &= -\frac{c}{4\pi\Lambda} \mathbf{A}_2(\mathbf{q}). \end{aligned} \quad (38)$$

Returning to the space coordinates, we find from eqs. (37), (38) in different asymptotic regions:

$$\begin{aligned} r \gg \lambda \quad d \ll r \ll \Lambda \\ \mathbf{J}_1(r) &= \frac{\phi_0 c}{16\pi^2 \Lambda r} \hat{\varphi} \quad \frac{\phi_0 c}{8\pi^2 \Lambda r} \hat{\varphi} \\ \mathbf{J}_2(r) &= -\frac{\phi_0 c}{16\pi^2 \Lambda r} \hat{\varphi} \quad -\frac{\phi_0 c}{4\Lambda^2} \hat{\varphi} \end{aligned} \quad (39)$$

The force between two pancake vortices is  $\mathbf{F} = -\frac{\phi_0}{c} \hat{z} \times \mathbf{J}$ , where  $\mathbf{J}$  is the current produced by one pancake at the

center of another one. It follows from eqs. (39) that the energy of interaction between two pancakes with the same vorticity at the same layer is logarithmic and repulsive at the distance  $R \gg d$ . A peculiarity of the few-layer structure is that the interaction energy of two pancake vortices with the same vorticity at different layers, separated by the distance at  $R \gg \Lambda$ , is logarithmic and attractive. It has the same absolute value as the repulsion of the pancakes in the same layer. This result dramatically differs from the interaction energy of two vortices at different layers, when the total number of layers is infinite: in this case the interaction in different layers differs from the interaction in the same layer by a small pre-factor  $d/\lambda$ . The result on the logarithmic attraction of two pancakes in different layers and its amplitude we have obtained persists at any number of layers  $N$  provided  $Nd \ll \lambda$ . It can be interpreted as the attraction of two "half-vortices" in the two plane, one carrying the flux  $+\phi_0/2$ , other carrying  $-\phi_0/2$ .

In the two-layer system the asymptotics for the components of magnetic field produced by the pancake vortex located in the plane  $z = 0$  at its origin directly follow from equation (37). In the range  $r \gg \Lambda$  they are:

$$B_z = \frac{\phi_0(|z| + |z - d|)}{8\pi(z^2 + r^2)^{3/2}} \quad (40)$$

$$\begin{aligned} B_r &= \frac{\phi_0}{8\pi\Lambda r} \text{sgn}(z) \left(1 - \frac{|z|}{\sqrt{r^2 + z^2}}\right) \hat{r} \\ &\quad - \frac{\phi_0}{8\pi\Lambda r} \text{sgn}(z - d) \left(1 - \frac{|z - d|}{\sqrt{r^2 + z^2}}\right) \hat{r} \\ &\quad + \frac{\phi_0(2z - d)}{8\pi(r^2 + z^2)^{3/2}} \hat{r}. \end{aligned} \quad (41)$$

In another asymptotic region  $d \ll r \ll \Lambda$  we find:

$$B_{vz} = \frac{\phi_0}{4\pi\Lambda\sqrt{r^2 + z^2}} \quad (42)$$

$$\mathbf{B}_v^{(2)}(\mathbf{r}, z) = \frac{\phi_0}{4\pi\Lambda r} \text{sgn}(z) \left(1 - \frac{|z|}{\sqrt{r^2 + z^2}}\right) \hat{r}. \quad (43)$$

Due to the strong screening effect exerted by one layer to another the magnetic field decays more quickly in the  $z$ -direction than in  $r$ -direction. The total magnetic flux through the plane  $z = 0$  and  $z = d$  is  $\Phi(z = 0) = B_{vz}(\mathbf{q} = 0, z = 0) = \frac{\Lambda + d}{2\Lambda + d} \phi_0 \approx \phi_0/2$ , and  $\Phi(z = d) = B_{vz}(\mathbf{q} = 0, z = d) = \frac{\Lambda}{2\Lambda + d} \phi_0 \approx \phi_0/2$ . The two fluxes are not exactly equal, and the net flux  $d/(2\Lambda + d)$  escapes through the remote side surface.

The self-energy of a single pancake vortex reads:

$$\begin{aligned} E_{sv} &= \frac{1}{8\pi\Lambda} \int \frac{d^2 q}{(2\pi)^2} [|\phi_1(\mathbf{q})|^2 - \phi_1(-\mathbf{q}) \cdot \mathbf{A}_1(\mathbf{q})] \\ &= \frac{1}{8\pi\Lambda} \int \frac{d^2 q}{(2\pi)^2} \left[ \frac{\phi_0^2}{q^2} - \frac{\phi_0^2}{2q^2(1 + \Lambda q)} \right] \\ &= \frac{\phi_0^2}{16\pi\Lambda} \ln \frac{R_s}{\xi}. \end{aligned} \quad (44)$$

Here  $R_s$  is the lateral linear size of the sample. Due to divergence of  $E_{sv}$ , it is energy unfavorable to produce single pancake in a layer below the Berezinsky-Kosterlitz-Touless transition. The energy of a pair of pancake vortices located one opposite another at different planes is:

$$\begin{aligned} E_{lv} &= \frac{2}{8\pi\Lambda} \int \frac{d^2q}{(2\pi)^2} [|\phi_1(\mathbf{q})|^2 - \phi_1(-\mathbf{q}) \cdot (\mathbf{A}_{v1}(\mathbf{q}) + \mathbf{A}_{v2}(\mathbf{q}))] \\ &= \frac{1}{4\pi\Lambda} \int \frac{d^2q}{(2\pi)^2} \left[ \frac{\phi_0^2}{q^2} - \frac{\phi_0^2}{q^2(1+\Lambda q)} \right] \\ &= \frac{\phi_0^2}{8\pi\Lambda} \ln \frac{\Lambda}{\xi}. \end{aligned} \quad (45)$$

The interaction of two such a pairs separated by a distance  $R \gg d$  is:

$$\begin{aligned} V_{ll}(R) &= \frac{2}{8\pi\Lambda} \int \frac{d^2q}{(2\pi)^2} [|\phi_1(\mathbf{q})(1 + e^{-i\mathbf{q}\cdot\mathbf{R}})|^2 - \phi_1(-\mathbf{q}) \cdot (\mathbf{A}_{v1}(\mathbf{q}) + \mathbf{A}_{v2}(\mathbf{q}))|1 + e^{-i\mathbf{q}\cdot\mathbf{R}}|^2] \\ &\quad - 2E_{lv} \\ &= \frac{\phi_0^2}{4\pi^2} \int \frac{J_0(qR)}{1+\Lambda q} dq \\ &= \frac{\phi_0^2}{8\pi\Lambda} [\mathbf{H}_0(\frac{R}{\Lambda}) - Y_0(\frac{R}{\Lambda})]. \end{aligned} \quad (46)$$

In the last step we used the formula [17]:

$$\int_0^\infty \frac{1}{x+z} J_0(cx) dx = \frac{\pi}{2} [\mathbf{H}_0(cz) - N_0(cz)], \quad (47)$$

where  $\mathbf{H}_0(x)$  is the zeroth Struve function, and  $N_0(x)$  is the zeroth Neumann function. The asymptotics of the interaction energy (46) at small and large distances are as follows:

$$V_{ll}(R) = \begin{cases} \frac{\phi_0^2}{4\pi^2\Lambda} \ln \frac{\Lambda}{R} & (r \ll \Lambda) \\ \frac{\phi_0^2}{4\pi^2 R} & (r \gg \Lambda). \end{cases} \quad (48)$$

Equation (35) can be solved by the same method for any number of layers, though calculations become more cumbersome. However, in the region  $R \gg Nd$  equation (35) can be solved quite easily. The vector potential of a line vortex, identical at all layers reads:

$$\mathbf{A}_1 = \dots = \mathbf{A}_N = \frac{iN\phi_0\hat{q} \times \hat{z}}{q(N+2\Lambda q)}. \quad (49)$$

Equation (49) allows to calculate the magnetic field, the current, and the interaction energy. Specifically, the single line self-energy and the interaction energy of two linear vortices for an  $N$ -layer superconductor are:

$$E_{lv} = \frac{N\phi_0^2}{16\pi^2\Lambda} \ln \frac{\Lambda}{\xi}; \quad (50)$$

$$V_{ll}(R) = \begin{cases} \frac{N\phi_0^2}{4\pi^2\Lambda} \ln \frac{\Lambda}{R} & (r \ll \Lambda) \\ \frac{\phi_0^2}{4\pi^2 R} & (r \gg \Lambda). \end{cases} \quad (51)$$

From these equations we see that the energy of the vortex line in a few-layer system is the same as that of the Pearl vortex in a thin-film superconductor (if we replace  $Nd$  by  $d_s$ ), but their interaction at short distances is  $N$  times stronger than the corresponding Pearl vortex interaction. At long distance, the interaction energy is the same as for the Pearl vortices.

Next, we discuss ferromagnetic textures in a few-layer system. We assume that the SC and FM layers form very thin bi-layers separated by a finite distance  $d$ . The London-Pearl equations for the vector potential  $\mathbf{A}_m$  induced by the magnetic layers and screened by superconducting layers are:

$$\begin{aligned} -\Delta\mathbf{A}_m + \frac{1}{\Lambda} \sum_n \delta(z - z_n) \mathbf{A}_m \\ = 4\pi \sum_n \nabla \times [\mathbf{m}\delta(z - z_n)]. \end{aligned} \quad (52)$$

Comparing it with equation (32), we find that they become identical if we replace  $i\phi_0\hat{q} \times \hat{z}/q$  by  $i4\pi m_q \Lambda \mathbf{q} \times \hat{z}$ . Therefore, it is straightforward to obtain the result for the magnetic vector potential from that for the vector potential induced by superconducting vortices. The Fourier-transform of vector potential at each layer produced by an FM texture, identical in each plane, reads:

$$\mathbf{A}_{m1} = \dots = \mathbf{A}_{mn} = \frac{i4N\pi m_q \Lambda \mathbf{q} \times \hat{z}}{N + 2\Lambda q}. \quad (53)$$

Equations (49) and (53) allow to calculate the interaction of ferromagnetic textures and vortex-ferromagnet interaction energy given the configuration of the magnetic texture.

Let us consider the spontaneous stripe structure in a few-layer ferro-superconducting system. Under the same assumption about the stripe width  $L \gg \Lambda$  and the average distance  $\bar{R}$  between vortices  $\bar{R} \gg \Lambda$ , we find from equations (50) and (51) that the interaction energy between two vortex lines is the same as that in single layer, but the single line energy increases  $N$  times. The total vortex-ferromagnet interaction energy also increases  $N$  times, because the magnetic vector potential and vortex vector potential both increase  $N$  times if  $L \gg \Lambda$ . That means that the condition  $m\phi_0 > \epsilon_v$  required for spontaneous formation of vortices and anti-vortices does not change. The domain width for a few-layer is:

$$L'_s = \frac{\Lambda}{4} \exp\left(\frac{\epsilon_{dw}}{4N\tilde{m}^2} - C + 1\right). \quad (54)$$

The factor  $1/N$  in the exponent (54) significantly reduces the domain width in the few-layer system. The sum of widths of parallel and antiparallel domains in an external magnetic field (the period of the domain structure) is:

$$L'(B_{ext}) = \frac{2L'_s}{\sqrt{1 - (\frac{L'_s B_{ext}}{2N\pi\tilde{m}})^2}}; \quad (55)$$

whereas the ratio of the width parallel domain to the period reads:

$$t' = \frac{2L'}{\pi} \arctan \frac{L' B_{ext}}{4N\pi\tilde{m}}. \quad (56)$$

The critical field, at which the stripe structure vanishes follows from eq. (55):

$$B_{ext}^{ct} = \frac{2N\pi\tilde{m}}{L'_s}; \quad (57)$$

Note that it is proportional to the number of layers. The shift of the transition temperature  $\Delta T'_c$  is:

$$\Delta T'_c = \frac{64N\pi m^2 e^2}{\alpha m_s c^2} \exp\left(\frac{-\epsilon_{dw}}{4N\tilde{m}^2} + C - 1\right). \quad (58)$$

It also grows with increasing  $N$ . For the case of few SC films with the square array of of FM columnar dots, the shift of the SC transition temperature is the same as for a single SC film with the square array of o ferromagnetic dots. This result can be readily seen from the observation observe that  $\Lambda \gg Na$  near the transition temperature. Then equation (50) implies that the vortex line energy in a few-layer system is  $N$  times larger than for one layer. The total Ginzburg-Landau free energy for few layers is  $N$  times larger than that for one layer (28). Thus, equation for  $n_s$  will not change and the shift of the transition temperature will not change either.

## 6. CONCLUSIONS

We studied the SC transition temperature in heterogeneous FM-SC system in the London's approximation. The stripe structure of FSB, if exists, leads to the positive shift of the transition temperature. It can reach the value  $\Delta T_c \sim 0.1T_c$ , when the width of the stripe becomes comparable with the effective penetration depth. Theory predicts that the shift of the transition temperature is proportional to the square of magnetization per unit area  $m^2$ . This fact can be checked experimentally. It was demonstrated that that the stripe structure must vanish at a very small external magnetic field between 1 and few tens Oersted. Simultaneously the transition temperature changes by the same value  $\Delta T_c \sim 0.1T_c$ . This theoretical prediction opens way to may be the strongest magneto-resistive effect.

In the multilayers the value of the value of the magnetic field at which the stripes disappear increases proportionally to the number of layers and the shift of the transition temperature grows even faster.

The shift of transition temperature in the superconducting layers supplied with a periodic array of magnetic dots may be of the same order of magnitude, but is negative at reasonable values of parameters.

## ACKNOWLEDGEMENTS

This work was supported by the NSF under the grants DMR 0072115, DMR 0103455, by the DOE under the grant DE-FG03-96ER45598 and by Telecommunications and Informatics Task Force at Texas A&M University. We appreciate the fruitful discussion with Dr. Serkan Erdin on the numerical calculation codes.

- 
- [1] Y. Otani, B. Pannetier, J.P. Nozieres and D. Givord, J. Mag. Mat. **126**, 622(1993); O. Geoffroy, D. Givord, Y. Otani, B. Pannetier and F. Ossart, J. Magn. mag. met. **121**,233(1993); Y. Nozaki, Y. Otani, K. Runge, H. Miyaima, B. Pannetier, J.P. Nozieres and G. Fillion, J. Appl. Phys. **79**,8571(1996); I.K. Marmorkos, A. Matulis and F.M. Peeters, Phys. Rev. B **53**,2677(1996); J. Martin, M. Velez, J. Nogues and I.K. Schuller, Phys. Rev. Lett. **79**, 1929(1997); D.J. Morgan and J.B. Ketterson, Phys. Rev. Lett. **80**,3614(1998); I.F. Lyuksyutov and V.L. Pokrovsky, Phys. Rev. Lett. **81**, 2344(1998); I.F. Lyuksyutov and D.G. Naugle, Modern Phys. Lett. B **13**,491(1999); A. Terentiev, D.B. Watkins, L.E. De Long, D.J. Morgan and J.B. Ketterson, Physica C **332**, 5(2000); M.J. Van Bael, L.Van Look, K. Temst, M. Lange, J. Bekaert, U. May, G. Guntherodt, V.V. Moshchalkov and Y. Bruynseraede, Physica C **332**, 12(2000); Feldman D.E., Lyuksyutov I.F., Pokrovsky V.L. and V.M. Vinokur, Europhys. Lett. **51**, 110(2000); J.E. Santos, E. Frey and F. Schwabl, Phys. Rev. B **63**, 4439(2001); L.E. Helseth, Phys. B **66**, 104508(2002); M.A. Kayali, Phys. Lett. A **298**, 432(2002).
  - [2] I. E. lyuksyutov and V. L. Pokrovsky, Mod. Rev. Lett. B **14**, 409(2000).
  - [3] S. Erdin, A. M. Kayali, I.F. Lyuksyutov, and V.L. Pokrovsky, Phys. Rev. B **66**,014414(2002).
  - [4] S. Erdin, I.F. Lyuksyutov, V.L. Pokrovsky, V.M. Vinokur, Phys. Rev. Lett. **88**,017001(2002).
  - [5] G. Blatter, M.V. Feigel'man, V.B. Geshkenbein, A.I. Larkin, V.M. Vinokur, Rev. Mod. Phys. **66**,1125(1994).
  - [6] J.R. Clem, Phys. Rev. B **43**, 7837(1991).
  - [7] M. Houzet, A. Buzdin, and M.I. Kulić, Phys. Rev. B **64**,184501(2001).
  - [8] The renormalized energy of vortices is equal to  $\tilde{\epsilon}_v = \epsilon_0 - m\phi_0$  instead of  $\tilde{\epsilon}_v = \epsilon_0 - \frac{3}{2}m\phi_0$  found in [4]). This leads to a change of the domain width  $L$  and energy  $U$  (eqs. (18) and (19) in [[4]]). The corrected values are given by eqs. (U) and (2) of this article.
  - [9] P.G. de Gennes, *Superconductivity of Metals and Alloys* (Addison-Wesley, New York, 1989).
  - [10] A.B. Kashuba and V.L. Pokrovsky, Phys. Rev. Lett. **70**, 3155(1993); A. Abanov, V. Kalatsky and V.L. Pokrovsky, Phys. Rev. B **51**,1023(1995).
  - [11] S. Erdin, con-mat/0211117.
  - [12] M. Tinkham, *Introduction to Superconductivity*, 2nd ed. (Mc-Graw-Hill, New York, 1996).
  - [13] A.A. Abrikosov, JETP. **5**, 1174(1957).
  - [14] R.G. Mints, V.K. Kogan, and J.R. Clem, Phys. Rev. B **61**,1623(2000).
  - [15] K.B. Efetov, Sov. Phys. JETP **49**, 905(1979).



- [16] K.H. Fischer, Physica C, **178**, 161(1991).
- [17] A.P. Prudnikov, Yu.A. Brychkov, O.I. Marichev, *Integrals and Series*, Vol. **2** (Gordon and Breach Science Publishers).