

Optical Response of Solid CO_2 as a Tool for the Determination of the High Pressure Phase

S. Sharma, J. K. Dewhurst, and C. Ambrosch-Drahl

Institute for Theoretical Physics, Karl-Franzens-Universität Graz, Universitätsplatz 5, A-8010 Graz, Austria.

(Dated: March 22, 2024)

We report first-principles calculations of the frequency dependent linear and second-order optical properties of the two probable extended-solid phases of CO_2 (V), i.e. $\overline{\text{I42d}}$ and $\text{P}2_12_12_1$. Compared to the parent Cmca phase the linear optical susceptibility of both phases is much smaller. We find that $\overline{\text{I42d}}$ and $\text{P}2_12_12_1$ differ substantially in their linear optical response in the higher energy regime. The nonlinear optical responses of the two possible crystal structures differ by roughly a factor of two. Since the differences in the nonlinear optical spectra are pronounced in the low energy regime, i.e. below the band gap of diamond, measurements with the sample inside the diamond anvil cell are feasible. We therefore suggest optical experiments in comparison with our calculated data as a tool for the unambiguous identification of the high pressure phase of CO_2 .

PACS numbers: 61.50.A, 42.65.K, 61.50.K, 78.66.H

A few years after the synthesis of the extended-solid phase of CO_2 at 40 GPa the crystal structure of this phase is still not known. This phase was found to be similar to one of the noncentrosymmetric polymorphs of quartz [1, 2] and was designated as CO_2 (V). Since solid CO_2 has very high tensile strength (comparable to that of boron nitride [3]) this discovery could be very useful in device applications. There is also considerable interest in the role of CO_2 in planetary geology [4].

Experimental work done to identify the exact crystal structure of CO_2 at high pressure suggests a low symmetry tridymite phase ($\text{P}2_12_12_1$) [5]. The presence of a nonlinear optical signal also indicated the absence of inversion symmetry in the crystal structure [1]. Most of the theoretical work has been concentrated around the lattice relaxations and total energy calculations in search of the minimum energy structure [6, 7, 8]. Theory predicts the α -cristobalite phase ($\overline{\text{I42d}}$) to be lower in energy than $\text{P}2_12_12_1$ by around 0.19 eV per formula unit [7]. However, none of the SiO_2 -like polymorphs of CO_2 gave a satisfactory fit to the experimental XRD data [5, 8]. Other possible quartz polymorphs have been eliminated by their much higher total energies [6]. Since all experiments were performed at elevated temperatures (1800 K) and the theoretical energy difference between the two phases is small, the energy minimization is not sufficient to solve the discrepancy between theory and experiments and to predict the actual high pressure phase. In order to understand the nature of this phase transition there is the need for analyzing other physical properties and finding a satisfactory agreement between theory and experiment. Since the two probable phases have very different electronic structure it is possible to distinguish them by their optical response. So far, neither a theoretical or experimental study of the linear optical response have been performed. Although second harmonic generation (SHG) by CO_2 has been seen experimentally, there exist no experimental data or calculations of the frequency de-

pendent SHG susceptibility. The aim of the present work is to show that the linear and nonlinear optical spectra indeed allow an unambiguous identification of the CO_2 (V) crystal structure. To this extent we have calculated the linear and second-order optical response of solid carbon dioxide, CO_2 (V), in the two possible phases. The linear optical spectra of these probable phases are compared to each other and also to that of the Cmca phase, which under high pressure and temperature conditions leads to CO_2 (V). Since quartz is often used as a standard in second-harmonic (SH) experiments, a detailed comparison is made between the second-order optical response of the two CO_2 (V) phases and that of SiO_2 ($\overline{\text{I42d}}$ phase). We propose that on basis of our results, future experimental work will help to resolve the present disagreement between theory and experiment and hence clarify the high pressure phase of CO_2 .

Total energy calculations are performed using the state-of-the-art full-potential linearized augmented plane wave FPLAPW method implemented in the WIEN2k code [9]. For the exchange-correlation potential we use the generalized gradient approximation (GGA) derived by Perdew and Wang [10]. The detailed formalism for the determination of the linear susceptibility tensor $\chi^{(1)}$ (!) within the FPLAPW formalism has been presented before [11]. The susceptibility for the SHG $\chi^{(2)}$ (!; !; !) has been calculated using an extension to this program [12]. The SHG susceptibility obtained satisfies all the theoretical sum rules presented by Scandolo and Bassani [13]. All the calculations are converged in terms of basis functions as well as in the size of the k-point mesh representing the Brillouin zone. The optical properties are calculated on a mesh of 1500 k-points in the irreducible wedge of the Brillouin zone.

The phases of CO_2 under investigation in the present work are the Cmca phase and the two probable extended-solid phases for CO_2 (V), namely $\overline{\text{I42d}}$ and $\text{P}2_12_12_1$. For the $\text{P}2_12_12_1$ phase the starting point is the experimen-

tal lattice parameters [5] with the atomic positions of the $C22_1$ phase (which is the supergroup of the space group $P2_12_12_1$). In a first step, the lattice parameters are kept constant at the experimental values and the internal parameters are fully relaxed. This structure is referred to as $P2_12_12_1\{\text{expt}\}$ in the present work. Next, the lattice and the internal parameters are simultaneously relaxed (keeping a constant volume [14]) to attain the minimum energy configuration. This structure is referred to as $P2_12_12_1\{\text{rel}\}$. The energy lowering on going from $P2_12_12_1\{\text{expt}\}$ to the $P2_12_12_1\{\text{rel}\}$ structure is 0.81 eV per formula unit, which is around 0.16 eV more than the previous theoretical value [7]. The larger energy in the present calculations compared to the previous theoretical value could be due to the difference in the method of calculation, since in the previous work the pseudopotential approach was used [7]. In case of the $I\bar{4}2d$ phase, due to the lack of experimental data, the starting lattice constants and internal parameters are taken to be those of SiO_2 in the same phase. Then the atoms as well as the cell volume are fully relaxed to attain the minimum energy configuration. The lattice parameters for all the structures are presented in Table I. In accordance with the previous theoretical work [7, 8] we find cristobalite ($I\bar{4}2d$) to be lower in energy compared to the $P2_12_12_1\{\text{rel}\}$ phase. The difference in energy between the $P2_12_12_1\{\text{rel}\}$ and the theoretically determined $I\bar{4}2d$ phase at 40 GPa is 0.38 eV/ CO_2 .

TABLE I: Lattice parameters for various phases. The cell parameters are in Å. The atomic positions are in lattice coordinates.

Phase	a (Å)	b (Å)	c (Å)	atom	position (a,b,c)
$I\bar{4}2d$	4.162	4.162	5.886	C	(0,0,0)
				O	(0.880,0.250,0.125)
$P2_12_12_1\{\text{expt}\}$	6.214	4.351	6.064	C (1)	(0.434,0.620,0.690)
				C (2)	(0.920,0.940,0.710)
				O (1)	(0.890,0.599,0.200)
				O (2)	(0.550,0.200,0.020)
				O (3)	(0.228,0.577,0.214)
				O (4)	(0.469,0.257,0.351)
$P2_12_12_1\{\text{rel}\}$	6.767	3.773	6.420	C (1)	(0.900,0.920,0.700)
				C (2)	(0.420,0.494,0.690)
				O (1)	(0.589,0.190,0.990)
				O (2)	(0.247,0.703,0.211)
				O (3)	(0.430,0.220,0.293)
				O (4)	(0.934,0.757,0.161)

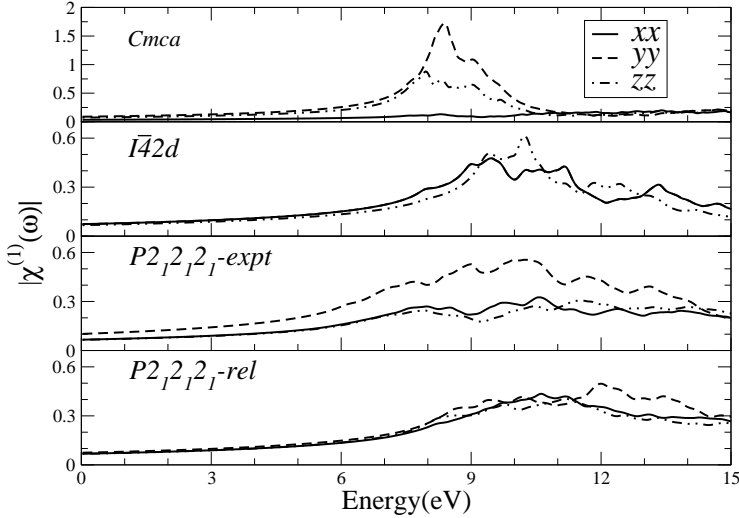


FIG. 1: The magnitude of the linear susceptibility components for solid CO_2 in (a) the Cmca phase, (b) the $I\bar{4}2d$ phase at 40 GPa, (c) the $P2_12_12_1\{\text{expt}\}$ structure and (d) the $P2_12_12_1\{\text{rel}\}$ structure.

The results for the linear optical spectra of CO_2 in

various phases are presented in Fig. 1. None of the optical spectra are scissors corrected. Both the $P2_12_12_1$ and the $I\bar{4}2d$ phase are taken at 40 GPa. The Cmca phase shows a strong anisotropy with $j_{yy}^{(1)}(!)$ much larger in amplitude than $j_{xx}^{(1)}(!)$ and $j_{zz}^{(1)}(!)$ lying in between the two. The reason for this anisotropy is the orientation of the molecules within the crystal. The neighbouring molecules are parallel to each other in the ab plane and form a herringbone pattern in the ac and bc planes [Fig. 2(b) in Ref. 15]. This causes the yy and zz polarized transition matrix elements (TMEs) to be large. On the other hand the xx polarized TMEs are close to zero, leading to small values for $j_{xx}^{(1)}(!)$. $j_{zz}^{(1)}(!)$ is smaller than $j_{yy}^{(1)}(!)$ because the lattice parameter b is smaller than c . On going from the low pressure Cmca phase to any other phase of $\text{CO}_2\text{-V}$, $j_{yy}^{(1)}(!)$ and the anisotropy between $j_{yy}^{(1)}(!)$ and $j_{xx}^{(1)}(!)$ decrease dramatically. The latter fact can again be explained by the orientation of the molecules inside the unit cell [Fig. 3E and 3F in Ref. 8]. The neighbouring CO_2 molecules are no more parallel or perpendicular in any direction leading to a weakening of the very strong transitions and an enhancement of the TMEs which were forbidden in the Cmca phase. For all the probable phases of $\text{CO}_2\text{-V}$ the spectral weights are shifted to higher energies. The optical band gap of the $P2_12_12_1\{\text{expt}\}$ structure is smaller than that of the Cmca phase, while the other two structures show almost equal optical band gaps, which are higher than that of the Cmca phase. Compared to the Cmca phase the maximum peak height is around 3 times smaller in the $I\bar{4}2d$ phase, while it is about 4 times smaller in the $P2_12_12_1$ structures. Beyond 11 eV, the response of all the probable phases of $\text{CO}_2\text{-V}$ is on average similar in magnitude, but differs in the amount of anisotropy.

For $\bar{I}42d$ there are two independent tensor components. Compared to the zz component, the xx component is approximately up to 2 times as large in the energy range below 10 eV. Up to 10.5 eV and between 11.5 and 13 eV the effect is opposite, while the two are nearly the same for higher energies. For the $P2_12_12_1$ structures there are three inequivalent components and the anisotropy between the xx and zz components is very small compared to the $\bar{I}42d$ phase. We also find the lattice relaxation effects which have already been described in detail by Dong et al. [7]. They have some consequences for the optical spectra. On going from the $Cmca$ phase to $P2_12_12_1$ {expt}, the optical band gap decreases, while it increases in case of $P2_12_12_1$ {rel}. Another noticeable feature is that the anisotropy is much larger in the $P2_12_12_1$ {expt} structure. Since CO_2 {V} is not quenchable into ambient pressure at room temperature the optical measurements need to be performed with the sample inside the diamond and anvil cell (DAC). The band gap of diamond is 5.5 eV. Therefore the energy regime below 5.5 eV is most interesting, since the optical response in this energy regime is purely from the sample inside the DAC. The difference between the linear optical spectra of various probable phases of CO_2 below this energy range is not as pronounced as in the higher energy regime. The results though are of theoretical interest and help in identification of various features in the nonlinear optical spectra (which is rather difficult to do from the band structure plots), but may not be very good in phase distinction under these experimental conditions.

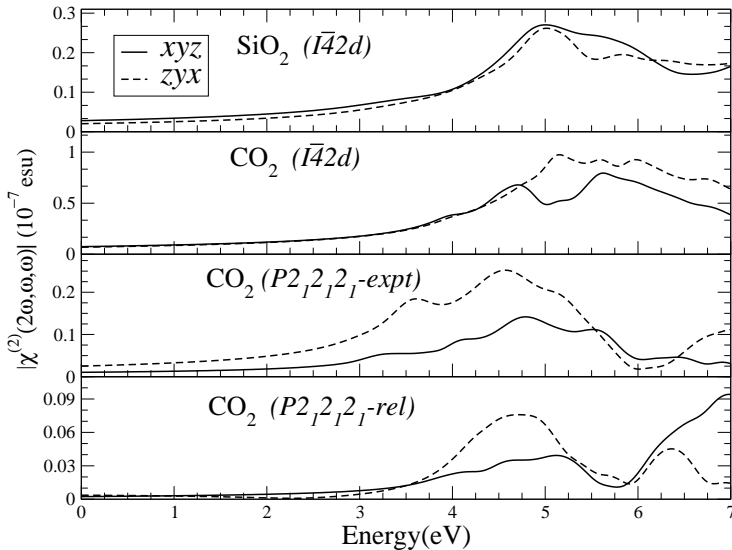


FIG. 2: The magnitude of the second-harmonic generation susceptibility components xyz and zyx for (a) SiO_2 in the $\bar{I}42d$ phase, (b) CO_2 in the $\bar{I}42d$ phase at 40 GPa, (c) in the $P2_12_12_1$ {expt} structure and (d) in the $P2_12_12_1$ {rel} structure.

The nonlinear optical properties are much more sensitive to small changes in the band structure than the linear optical spectra. The calculated magnitude of the SHG susceptibility by CO_2 {V} in various probable phases are presented in Fig. 2. Due to the presence of inversion symmetry in the $Cmca$ phase the SHG susceptibility is zero. The second-order response of SiO_2 ($\bar{I}42d$), which is often used as standard in SHG experiments, is also presented in the figure. In the energy range between 3 and 5.5 eV the magnitude of the SHG susceptibility by CO_2 in the $P2_12_12_1$ {expt} phase is 1.5 {2 times smaller than that of quartz. On the other hand the $\bar{I}42d$ phase of CO_2 shows a SHG susceptibility 3 {4 times larger than that of SiO_2 . These pronounced differences make the phases easily identifiable. The energy range of 3 {5.5 eV lies below the band gap of diamond and corresponds to laser light of wavelengths between 413.3 – 247.9 nm. Previous SH experiments were performed using laser light of 1054 nm wavelength [1], which correspond to 1.176 eV. At this energy our calculated value of $j_1^{(2)}(2\omega; \omega, \omega)$ for CO_2 in the $\bar{I}42d$ phase is 2.7 times larger than that of SiO_2 . While, the SHG susceptibility by CO_2 in the $P2_12_12_1$ {expt} phase is 2.6 times smaller than that of SiO_2 . The previous experimental work [5] reports the SH conversion efficiency of the CO_2 {V} phase, which is not just proportional to the square of the SHG susceptibility but also depends on the input intensity and sample parameters. So no direct comparison of the existing experimental data can be made with the present results. Since the difference in the second-order response by the probable phases of CO_2 {V} are more pronounced in the energy range between 3 and 5.5 eV than in between 1 {2 eV, experiments at higher energies would be favourable. Experimental determination of the SHG susceptibility by CO_2 {V} and SiO_2 , over some frequency range, and a comparison with our work could lead to conclusive results.

The two structures of the $P2_12_12_1$ phase are also differentiable by their SHG response. Due to the large optical band gap of $P2_12_12_1$ {rel} the SHG susceptibility is approximately 3 times smaller than that of $P2_12_12_1$ {expt}. As shown in Ref. 7 the XRD patterns for neither of these structures matches the experiments. The theoretically calculated XRD pattern of $P2_12_12_1$ {rel} shows a better agreement with the experimental XRD pattern at higher values of 2θ (13 degrees), while the XRD pattern for $P2_12_12_1$ {expt} is in better agreement at low values of 2θ (8 degrees). It is possible that under the experimental conditions of high temperatures the material is a polycrystalline mixture of these two structures or has a configuration in between the two, in which case the difference between the optical spectra of the two phases would represent a measure of the uncertainty in the optical response of this phase. Despite this fact, we want to point out that in general the differences in the optical response between the two phases are much more pronounced than "the lattice relaxation effects" for the

$P2_12_12_1$ phase making them distinguishable by optical probes.

The optical coefficients in the static limit are directly measurable quantities. The calculated inequivalent components of $\chi_1(0)$ and $j^{(2)}(0)$ are presented in the Table II.

TABLE II: The static dielectric constants $\chi_1^{xx}(0)$, $\chi_1^{yy}(0)$ and $\chi_1^{zz}(0)$, and the SHG susceptibility components in the static limit $j_{zyx}^{(2)}(0)$ and $j_{xyz}^{(2)}(0)$ in 10^{-8} esu for CO_2 in various phases.

Phase	$\chi_1^{xx}(0)$	$\chi_1^{yy}(0)$	$\chi_1^{zz}(0)$	$j_{xyz}^{(2)}(0)$	$j_{zyx}^{(2)}(0)$
Cmca	1.87	3.23	2.84	0.00	0.00
I42d	2.82	2.82	2.66	0.74	0.69
$P2_12_12_1\{\text{expt}\}$	2.69	3.57	2.67	0.10	0.25
$P2_12_12_1\{\text{rel}\}$	2.69	2.86	2.68	0.02	0.04

In the Cmca phase, the anisotropy between $\chi_1^{xx}(0)$ and $\chi_1^{yy}(0)$ is 54%, and between $\chi_1^{xx}(0)$ and $\chi_1^{zz}(0)$ it is 41%. In the I42d phase, the anisotropy between the xx and zz components is 6% only. For the tridymite phase at experimental lattice parameters ($P2_12_12_1\{\text{expt}\}$) the maximum anisotropy found between $\chi_1^{yy}(0)$ and $\chi_1^{zz}(0)$ (28%), while between $\chi_1^{xx}(0)$ and $\chi_1^{zz}(0)$ it is only 1%. In the case of $P2_12_12_1\{\text{rel}\}$ the anisotropy between the xx and yy components is 7%, and between the xx and zz components is close to zero.

Amongst the phases under investigation in the present work the anisotropy in the xyz and zyx components of $j^{(2)}(0)$ is maximum for $P2_12_12_1\{\text{expt}\}$ with 86% and minimum for I42d with 7%. $P2_12_12_1\{\text{rel}\}$ lies in between the two with an anisotropy of 67%. For SiO_2 in the I42d phase, our calculated values of $j_{xyz}^{(2)}(0)$ and $j_{zyx}^{(2)}(0)$ are 0.28 and 0.20 10^{-8} esu, respectively. It may be noted that the anisotropy as well as the magnitude of $\chi_1^{(2)}(0)$ for CO_2 in the $P2_12_12_1\{\text{expt}\}$ phase are close to that of SiO_2 . The fact that $j^{(2)}(0)$ of CO_2 is around 3 times larger in the I42d phase, and 5{10 times smaller in the $P2_12_12_1\{\text{rel}\}$ phase compared to SiO_2 makes the distinction between the two phases clear and hence the identification of the high pressure phase feasible.


In summary we find that the optical properties are excellent tools for an unambiguous determination of the high pressure phase of CO_2 . Particularly, the second-order response of $\text{CO}_2\{\text{V}\}$ compared to that of SiO_2 can be used for phase determination even with the sample inside

the DAC. Experiments of this kind and a detailed comparison with the present theoretical results would shed light on the existing discrepancy between theory and experiments regarding the space group of the $\text{CO}_2\{\text{V}\}$ phase.

The work is supported by the Austrian Science Fund (projects P13430, P14004 and P16227) and the EXCIT-ING network funded by the EU (Contract HPRN-CT-2002-00317). One of the authors (SS) would also like to thank Dr. Valentin Iota (Lawrence Livermore National Lab., California) for valuable comments and suggestions.

Electronic address: sangeeta.sharma@uni-graz.at

- [1] V. Iota, C. S. Yoo, and H. Cynn. Science 283, 150 (1999).
- [2] S. Serra, C. Cavazzoni, G. L. Chiarotti, S. Scandolo, and E. Tosatti. Science 284, 788 (1999).
- [3] C. S. Yoo. In Proceedings of the AIRAPT-17 International Conference on High Pressure Science and Technology, Honolulu, Hawaii, 1999.
- [4] K. L. Tanaka, J. S. Kargel, D. J. Mackinnon, T. M. Hare, and N. Horn. Geophys. Res. Lett. 29, (8), (2002). doi: 10.1029/2001GL013885.
- [5] C. S. Yoo, H. Cynn, F. Gygi, G. Galli, V. Iota, M. Nicol, S. Carlson, D. Hasegawa, and C. M. Ailiot. Phys. Rev. Lett. 83 5527, (1999).
- [6] J. Dong, J. K. Tomfohr, and O. F. Sankey. Phys. Rev. B 61 5967, (2000).
- [7] J. Dong, J. K. Tomfohr, O. F. Sankey, K. Lieneweber, M. Somayazulu, and P. F. McMillan. Phys. Rev. B, 61 5967, (2000).
- [8] B. Holm, R. Ahuja, A. Belonoshko, and Borje Johansson. Phys. Rev. B, 85 1258, (2000).
- [9] P. Blaha, K. Schwarz, G. K. H. Madsen, D. Kvasnicka, and J. Luitz, 2001. WIEN2k, Vienna University of Technology, An Augmented Plane Wave + Local Orbitals Program for Calculating Crystal Properties.
- [10] J. P. Perdew and Y. Wang. Phys. Rev. B, 45 13244, (1992).
- [11] C. Ambrosch-Drahl and J. O. Sofo. preprint.
- [12] S. Sharma, J. K. Dewhurst, and C. Ambrosch-Drahl, <http://xxx.lanl.gov/abs/cond-mat/0211512> (2002).
- [13] S. Scandolo and F. Bassani. Phys. Rev. B, 51 6925, (1995).
- [14] Since GGA is known in general to be good in reproducing crystal volumes, no volume relaxation has been performed.
- [15] C. S. Yoo, H. Kohlmann, H. Cynn, M. F. Nicol, V. Iota, and T. LeBihan. Phys. Rev. B, 65 104103, (2002).

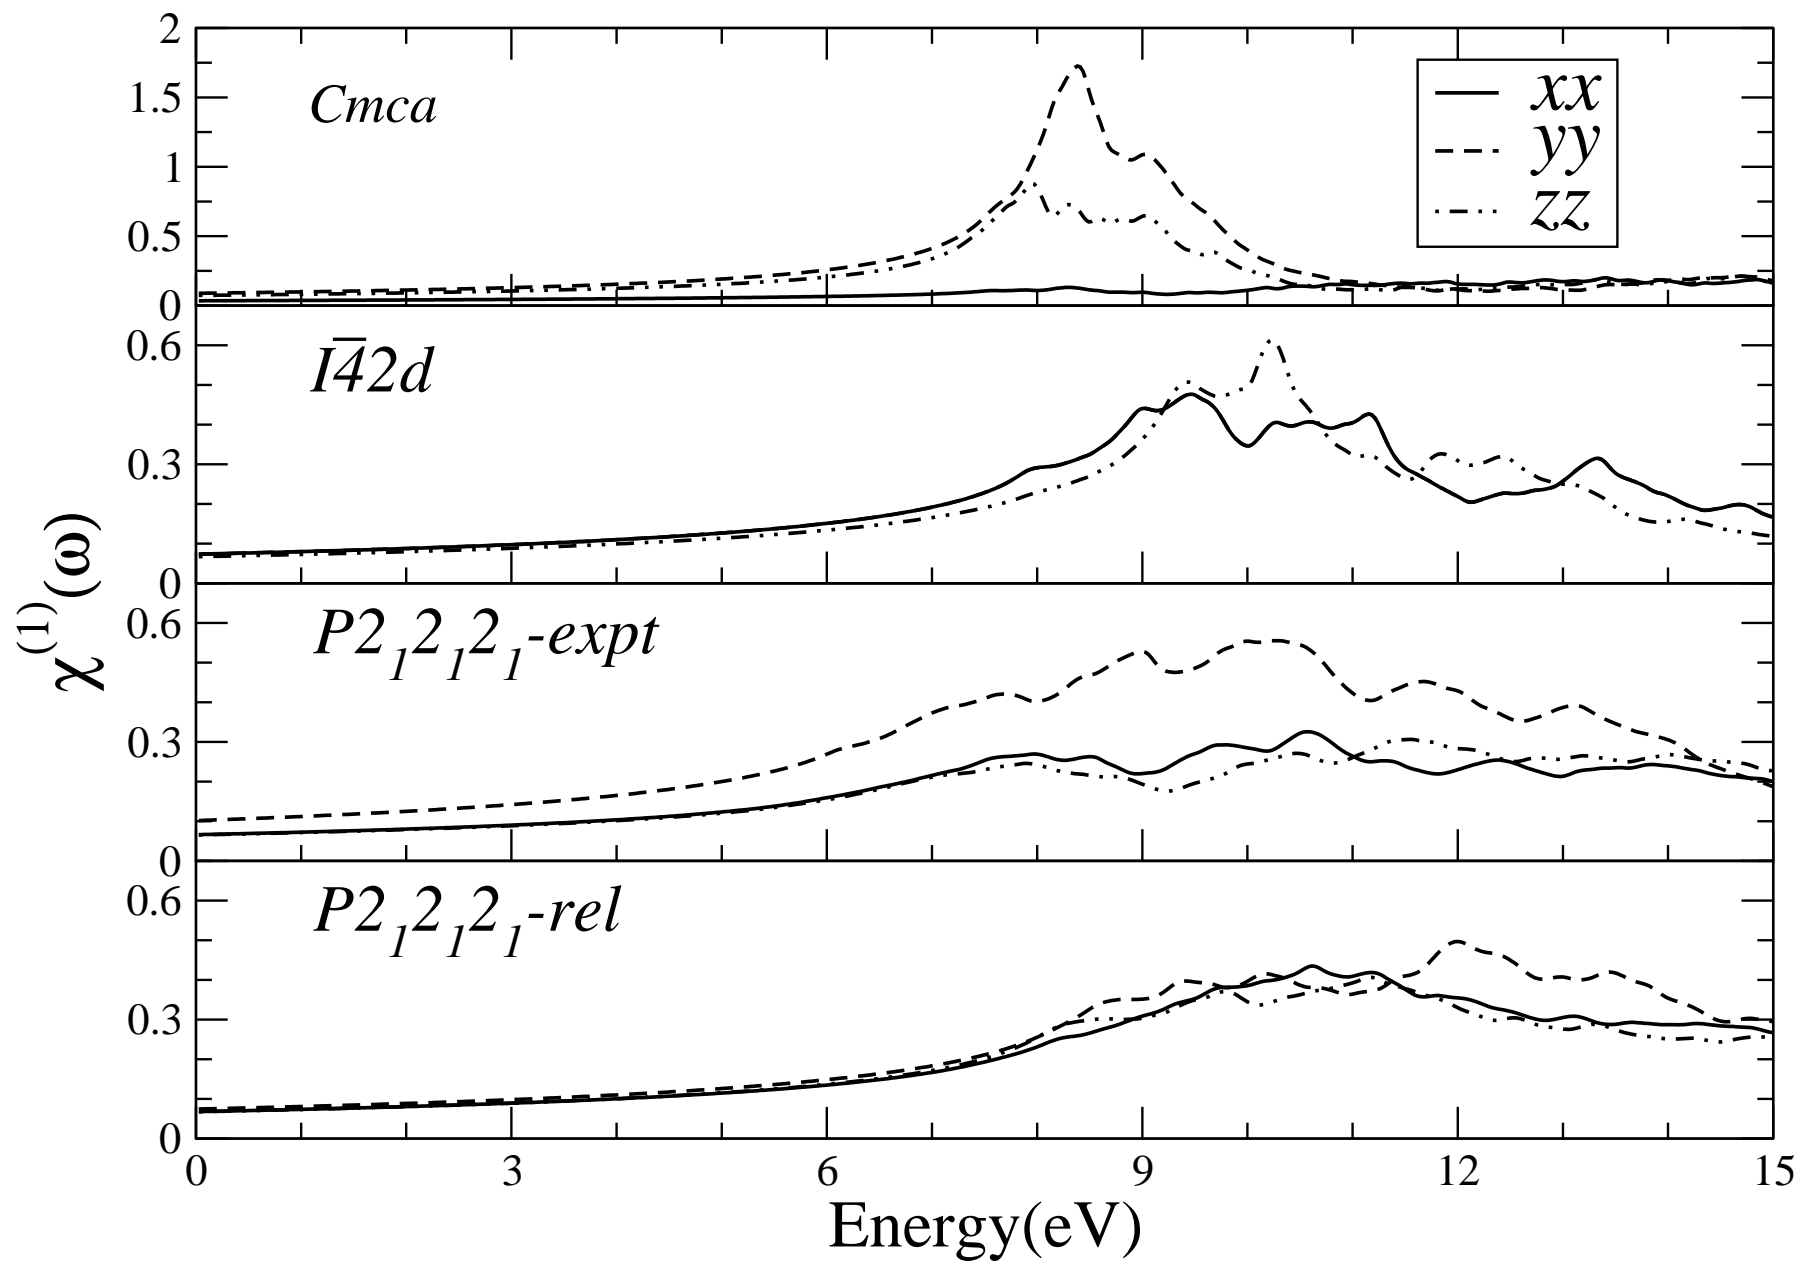

Optical Response of Solid CO₂ as a Tool for the Determination of the High Pressure Phase

S. Sharma,* J. K. Dewhurst, and C. Ambrosch-Draxl

Institute for Theoretical Physics, Karl-Franzens-Universität Graz, Universitätsplatz 5, A-8010 Graz, Austria.

(Dated: March 28, 2003)

We report first-principles calculations of the frequency dependent linear and second-order optical properties of the two probable extended-solid phases of CO₂-V, i.e. $I\bar{4}2d$ and $P2_12_12_1$. Compared to the parent $Cmca$ phase the linear optical susceptibility of both phases is much smaller. We find that $I\bar{4}2d$ and $P2_12_12_1$ differ substantially in their linear optical response in the higher energy regime. The nonlinear optical responses of the two possible crystal structures differ by roughly a factor of five. Since the differences in the nonlinear optical spectra are pronounced in the low energy regime, i.e. below the band gap of diamond, measurements with the sample inside the diamond anvil cell are feasible. We therefore suggest optical experiments in comparison with our calculated data as a tool for the unambiguous identification of the high pressure phase of CO₂.

PACS numbers: 61.50A, 42.65K, 61.50K, 78.66H

A few years after the synthesis of the extended-solid phase of CO₂ at 40 GPa the crystal structure of this phase is still not known. This phase was found to be similar to one of the noncentrosymmetric polymorphs of quartz [1, 2] and was designated as CO₂-V. Since solid CO₂ has very high tensile strength (comparable to that of boron nitride [3]) this discovery could be very useful in device applications. There is also considerable interest in the role of CO₂ in planetary geology [4].

Experimental work done to identify the exact crystal structure of CO₂ at high pressure suggests a low symmetry tridymite phase ($P2_12_12_1$) [5]. The presence of a nonlinear optical signal also indicated the absence of inversion symmetry in the crystal structure [1]. Most of the theoretical work has been concentrated around the lattice relaxations and total energy calculations in search of the minimum energy structure [6–8]. Theory predicts the β -cristobalite phase ($I\bar{4}2d$) to be lower in energy than $P2_12_12_1$ by around 0.19 eV per formula unit [7]. However, none of the SiO₂-like polymorphs of CO₂ gave a satisfactory fit to the experimental XRD data [5, 8]. Other possible quartz polymorphs have been eliminated by their much higher total energies [6]. Since all experiments were performed at elevated temperatures (1800K) and the theoretical energy difference between the two phases is small, the energy minimization is not sufficient to solve the discrepancy between theory and experiments and to predict the actual high pressure phase. In order to understand the nature of this phase transition there is the need for analyzing other physical properties and finding a satisfactory agreement between theory and experiment. Since the two probable phases have very different electronic structure it is possible to distinguish them by their optical response. So far, neither a theoretical or experimental study of the linear optical response have been performed. Although second harmonic generation (SHG) by CO₂ has been seen experimentally, there exist no experimental data or calculations of the frequency de-

pendent SHG susceptibility. The aim of the present work is to show that the linear and nonlinear optical spectra indeed allow an unambiguous identification of the CO₂-V crystal structure. To this extent we have calculated the linear and second-order optical response of solid carbon dioxide, CO₂-V, in the two possible phases. The linear optical spectra of these probable phases are compared to each other and also to that of the $Cmca$ phase, which under high pressure and temperature conditions leads to CO₂-V. Since quartz is often used as a standard in second-harmonic (SH) experiments, a detailed comparison is made between the second-order optical response of the two CO₂-V phases and that of SiO₂ ($I\bar{4}2d$ phase). We propose that on basis of our results, future experimental work will help to resolve the present disagreement between theory and experiment and hence clarify the high pressure phase of CO₂.

Total energy calculations are performed using the state-of-the-art full-potential linearized augmented plane wave FPLAPW method implemented in the WIEN2k code [9]. For the exchange-correlation potential we use the generalized gradient approximation (GGA) derived by Perdew and Wang [10]. The detailed formalism for the determination of the linear susceptibility tensor $\chi^{(1)}(\omega)$ within the FPLAPW formalism has been presented before [11]. The susceptibility for the SHG $\chi^{(2)}(2\omega, \omega, \omega)$ has been calculated using an extension to this program [12]. The SHG susceptibility obtained satisfies all the theoretical sum rules presented by Scandolo and Bassani [13]. All the calculations are converged in terms of basis functions as well as in the size of the k -point mesh representing the Brillouin zone. The optical properties are calculated on a mesh of 1500 k -points in the irreducible wedge of the Brillouin zone.

The phases of CO₂ under investigation in the present work are the $Cmca$ phase and the two probable extended-solid phases for CO₂-V, namely $I\bar{4}2d$ and $P2_12_12_1$. For the $P2_12_12_1$ phase the starting point is the experimen-

tal lattice parameters [5] with the atomic positions of the $C222_1$ phase (which is the supergroup of the space group $P2_12_12_1$). In a first step, the lattice parameters are kept constant at the experimental values and the internal parameters are fully relaxed. This structure is referred to as $P2_12_12_1\text{-expt}$ in the present work. Next, the lattice and the internal parameters are simultaneously relaxed (keeping a constant volume [14]) to attain the minimum energy configuration. This structure is referred to as $P2_12_12_1\text{-rel}$. The energy lowering on going from $P2_12_12_1\text{-expt}$ to the $P2_12_12_1\text{-rel}$ structure is 0.81 eV per formula unit, which is around 0.16 eV more than the previous theoretical value [7]. The larger energy in the present calculations compared to the previous theoretical value could be due to the difference in the method of calculation, since in the previous work the pseudopotential approach was used [7]. In case of the $I\bar{4}2d$ phase, due to the lack of experimental data, the starting lattice constants and internal parameters are taken to be those of SiO_2 in the same phase. Then the atoms as well as the cell volume are fully relaxed to attain the minimum energy configuration. The lattice parameters for all the structures are presented in Table I. In accordance with the previous theoretical work [7, 8] we find β -cristobalite ($I\bar{4}2d$) to be lower in energy compared to the $P2_12_12_1\text{-rel}$ phase. The difference in energy between the $P2_12_12_1\text{-rel}$ and the theoretically determined $I\bar{4}2d$ phase at 40 GPa is 0.38 eV/ CO_2 .

TABLE I: Lattice parameters for various phases. The cell parameters are in Å. The atomic positions are in lattice coordinates.

Phase	a (Å)	b (Å)	c (Å)	atom	position (a,b,c)
$I\bar{4}2d$	4.162	4.162	5.886	C	(0,0,0)
				O	(0.880,0.250,0.125)
$P2_12_12_1\text{-expt}$	6.214	4.351	6.064	C(1)	(0.434,0.620,0.690)
				C(2)	(0.920,0.940,0.710)
				O(1)	(0.890,0.599,0.200)
				O(2)	(0.550,0.200,0.020)
				O(3)	(0.228,0.577,0.214)
				O(4)	(0.469,0.257,0.351)
$P2_12_12_1\text{-rel}$	6.767	3.773	6.420	C(1)	(0.900,0.920,0.700)
				C(2)	(0.420,0.494,0.690)
				O(1)	(0.589,0.190,0.990)
				O(2)	(0.247,0.703,0.211)
				O(3)	(0.430,0.220,0.293)
				O(4)	(0.934,0.757,0.161)

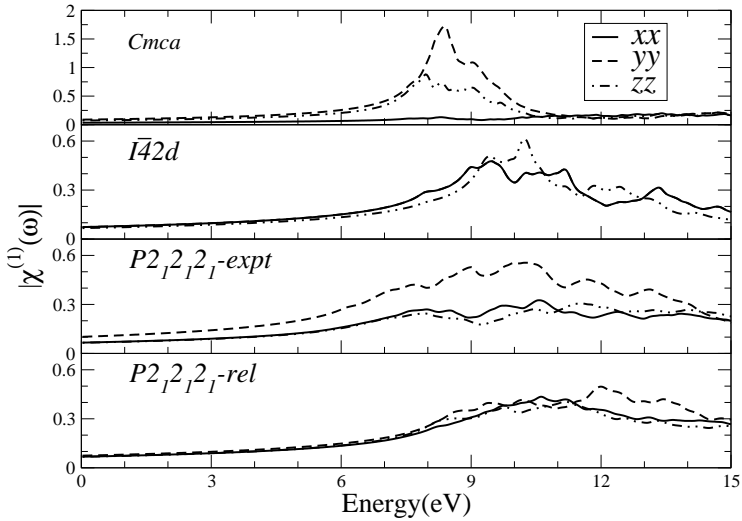


FIG. 1: The magnitude of the linear susceptibility components for solid CO_2 in (a) the $Cmca$ phase, (b) the $I\bar{4}2d$ phase at 40 GPa, (c) the $P2_12_12_1\text{-expt}$ structure and (d) the $P2_12_12_1\text{-rel}$ structure.

The results for the linear optical spectra of CO_2 in

various phases are presented in Fig. 1. None of the optical spectra are scissors corrected. Both the $P2_12_12_1$ and the $I\bar{4}2d$ phase are taken at 40 GPa. The $Cmca$ phase shows a strong anisotropy with $|\chi_{yy}^{(1)}(\omega)|$ much larger in amplitude than $|\chi_{xx}^{(1)}(\omega)|$, and $|\chi_{zz}^{(1)}(\omega)|$ lying in between the two. The reason for this anisotropy is the orientation of the molecules within the crystal. The neighbouring molecules are parallel to each other in the ab plane and form a herringbone pattern in the ac and bc planes [Fig. 2(b) in Ref. 15]. This causes the yy and zz polarized transition matrix elements (TMEs) to be large. On the other hand the xx polarized TMEs are close to zero, leading to small values for $|\chi_{xx}^{(1)}(\omega)|$. $|\chi_{zz}^{(1)}(\omega)|$ is smaller than $|\chi_{yy}^{(1)}(\omega)|$ because the lattice parameter b is smaller than c . On going from the low pressure $Cmca$ phase to any other phase of $\text{CO}_2\text{-V}$, $|\chi_{yy}^{(1)}(\omega)|$ and the anisotropy between $|\chi_{yy}^{(1)}(\omega)|$ and $|\chi_{xx}^{(1)}(\omega)|$ decrease dramatically. The latter fact can again be explained by the orientation of the molecules inside the unit cell [Fig. 3E and 3F in Ref. 8]. The neighbouring CO_2 molecules are no more parallel or perpendicular in any direction leading to a weakening of the very strong transitions and an enhancement of the TMEs which were forbidden in the $Cmca$ phase. For all the probable phases of $\text{CO}_2\text{-V}$ the spectral weights are shifted to higher energies. The optical band gap of the $P2_12_12_1\text{-expt}$ structure is smaller than that of the $Cmca$ phase, while the other two structures show almost equal optical band gaps, which are higher than that of the $Cmca$ phase. Compared to the $Cmca$ phase the maximum peak height is around 3 times smaller in the $I\bar{4}2d$ phase, while it is about 4 times smaller in the $P2_12_12_1$ structures. Beyond 11 eV, the response of all the probable phases of $\text{CO}_2\text{-V}$ is on average similar in magnitude, but differs in the amount of anisotropy.

For $I\bar{4}2d$ there are two independent tensor components. Compared to the zz component, the xx component is approximately upto 2 times as large in the energy range below 10 eV. Upto 10.5 eV and between 11.5 and 13 eV the effect is opposite, while the two are nearly the same for higher energies. For the $P2_12_12_1$ structures there are three inequivalent components and the anisotropy between the xx and zz components is very small compared to the $I\bar{4}2d$ phase. We also find the lattice relaxation effects which have already been described in detail by Dong *et al.* [7]. They have some consequences for the optical spectra. On going from the $Cmca$ phase to $P2_12_12_1-expt$, the optical band gap decreases, while it increases in case of $P2_12_12_1-rel$. Another noticeable feature is that the anisotropy is much larger in the $P2_12_12_1-expt$ structure. Since $\text{CO}_2\text{-V}$ is not quenchable into ambient pressure at room temperature the optical measurements need to be performed with the sample inside the diamond anvil cell (DAC). The band gap of diamond is 5.5 eV. Therefore the energy regime below 5.5 eV is most interesting, since the optical response in this energy regime is purely from the sample inside the DAC. The difference between the linear optical spectra of various probable phases of CO_2 below this energy range is not as pronounced as in the higher energy regime. The results though are of theoretical interest and help in identification of various features in the nonlinear optical spectra (which is rather difficult to do from the band structure plots), but may not be very good in phase distinction under these experimental conditions.

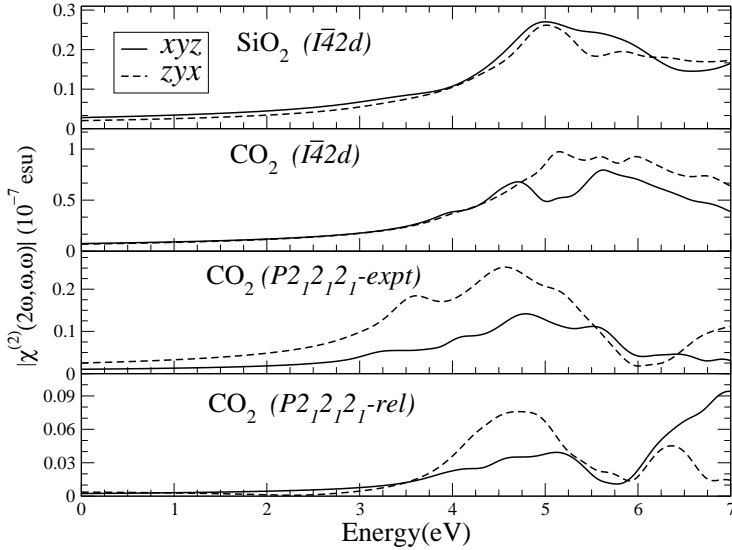


FIG. 2: The magnitude of the second-harmonic generation susceptibility components xyz and zyx for (a) SiO_2 in the $I\bar{4}2d$ phase, (b) CO_2 in the $I\bar{4}2d$ phase at 40 GPa, (c) in the $P2_12_12_1-expt$ structure and (d) in the $P2_12_12_1-rel$ structure.

The nonlinear optical properties are much more sensitive to small changes in the band structure than the linear optical spectra. The calculated magnitude of the SHG susceptibility by $\text{CO}_2\text{-V}$ in various probable phases are presented in Fig. 2. Due to the presence of inversion symmetry in the $Cmca$ phase the SHG susceptibility is zero. The second-order response of SiO_2 ($I\bar{4}2d$), which is often used as standard in SHG experiments, is also presented in the figure. In the energy range between 3 and 5.5 eV the magnitude of the SHG susceptibility by CO_2 in the $P2_12_12_1-expt$ phase is 1.5–2 times smaller than that of quartz. On the other hand the $I\bar{4}2d$ phase of CO_2 shows a SHG susceptibility 3–4 times larger than that of SiO_2 . These pronounced differences make the phases easily identifiable. The energy range of 3–5.5 eV lies below the band gap of diamond and corresponds to laser light of wavelengths between 413.3 - 247.9 nm. Previous SH experiments were performed using laser light of 1054 nm wavelength [1], which correspond to 1.176 eV. At this energy our calculated value of $|\chi_1^{(2)}(2\omega, \omega, \omega)|$ for CO_2 in the $I\bar{4}2d$ phase is 2.7 times larger than that of SiO_2 . While, the SHG susceptibility by CO_2 in the $P2_12_12_1-expt$ phase is 2.6 times smaller than that of SiO_2 . The previous experimental work [5] reports the SH conversion efficiency of the $\text{CO}_2\text{-V}$ phase, which is not just proportional to the square of the SHG susceptibility but also depends on the input intensity and sample parameters. So no direct comparison of the existing experimental data can be made with the present results. Since the difference in the second-order response by the probable phases of $\text{CO}_2\text{-V}$ are more pronounced in the energy range between 3 and 5.5 eV than in between 1–2 eV, experiments at higher energies would be favourable. Experimental determination of the SHG susceptibility by $\text{CO}_2\text{-V}$ and SiO_2 , over some frequency range, and a comparison with our work could lead to conclusive results.

The two structures of the $P2_12_12_1$ phase are also differentiable by their SHG response. Due to the large optical band gap of $P2_12_12_1-rel$ the SHG susceptibility is approximately 3 times smaller than that of $P2_12_12_1-expt$. As shown in Ref. 7 the XRD patterns for neither of these structures matches the experiments. The theoretically calculated XRD pattern of $P2_12_12_1-rel$ shows a better agreement with the experimental XRD pattern at higher values of 2θ (9–13 degrees), while the XRD pattern for $P2_12_12_1-expt$ is in better agreement at low values of 2θ (6–8 degrees). It is possible that under the experimental conditions of high temperatures the material is a polycrystalline mixture of these two structures or has a configuration in between the two, in which case the difference between the optical spectra of the two phases would represent a measure of the uncertainty in the optical response of this phase. Despite this fact, we want to point out that in general the differences in the optical response between the two phases are much more pronounced than “the lattice relaxation effects” for the

$P2_12_12_1$ phase making them distinguishable by optical probes.

The optical coefficients in the static limit are directly measurable quantities. The calculated inequivalent components of $\epsilon_1(0)$ and $|\chi^{(2)}(0)|$ are presented in the Table II.

TABLE II: The static dielectric constants $\epsilon_1^{xx}(0)$, $\epsilon_1^{yy}(0)$ and $\epsilon_1^{zz}(0)$, and the SHG susceptibility components in the static limit $|\chi_{xyz}^{(2)}(0)|$ and $|\chi_{zyx}^{(2)}(0)|$ in $\times 10^{-8}$ esu for CO_2 in various phases.

Phase	$\epsilon_1^{xx}(0)$	$\epsilon_1^{yy}(0)$	$\epsilon_1^{zz}(0)$	$ \chi_{xyz}^{(2)}(0) $	$ \chi_{zyx}^{(2)}(0) $
$Cmca$	1.87	3.23	2.84	0.00	0.00
$I\bar{4}2d$	2.82	2.82	2.66	0.74	0.69
$P2_12_12_1\text{-}expt$	2.69	3.57	2.67	0.10	0.25
$P2_12_12_1\text{-}rel$	2.69	2.86	2.68	0.02	0.04

In the $Cmca$ phase, the anisotropy between $\epsilon_1^{xx}(0)$ and $\epsilon_1^{yy}(0)$ is 54%, and between $\epsilon_1^{xx}(0)$ and $\epsilon_1^{zz}(0)$ it is 41%. In the $I\bar{4}2d$ phase, the anisotropy between the xx and zz components is 6% only. For the tridymite phase at experimental lattice parameters ($P2_12_12_1\text{-}expt$) the maximum anisotropy found between $\epsilon_1^{yy}(0)$ and $\epsilon_1^{zz}(0)$ (28 %), while between $\epsilon_1^{xx}(0)$ and $\epsilon_1^{zz}(0)$ it is only 1%. In the case of $P2_12_12_1\text{-}rel$ the anisotropy between the xx and yy components is 7%, and between the xx and zz components is close to zero.

Amongst the phases under investigation in the present work the anisotropy in the xyz and zyx components of $|\chi^{(2)}(0)|$ is maximum for $P2_12_12_1\text{-}expt$ with 86 % and minimum for $I\bar{4}2d$ with 7%. $P2_12_12_1\text{-}rel$ lies in between the two with an anisotropy of 67 %. For SiO_2 in the $I\bar{4}2d$ phase, our calculated values of $|\chi_{xyz}^{(2)}(0)|$ and $|\chi_{zyx}^{(2)}(0)|$ are 0.28 and 0.20×10^{-8} esu, respectively. It may be noted that the anisotropy as well as the magnitude of $\chi_1^{(2)}(0)$ for CO_2 in the $P2_12_12_1\text{-}expt$ phase are close to that of SiO_2 . The fact that $|\chi^{(2)}(0)|$ of CO_2 is around 3 times larger in the $I\bar{4}2d$ phase, and 5–10 times smaller in the $P2_12_12_1\text{-}rel$ phase compared to SiO_2 makes the distinction between the two phases clear and hence the identification of the high pressure phase feasible.

In summary we find that the optical properties are excellent tools for an unambiguous determination of the high pressure phase of CO_2 . Particularly, the second-order response of $\text{CO}_2\text{-V}$ compared to that of SiO_2 can be used for phase determination even with the sample inside

the DAC. Experiments of this kind and a detailed comparison with the present theoretical results would shed light on the existing discrepancy between theory and experiments regarding the space group of the $\text{CO}_2\text{-V}$ phase.

The work is supported by the Austrian Science Fund (projects P13430, P14004 and P16227) and the EXCITING network funded by the EU (Contract HPRN-CT-2002-00317). One of the authors (SS) would also like to thank Dr. Valentin Iota (Lawrence Livermore National Lab., California) for valuable comments and suggestions.

* Electronic address: sangeeta.sharma@uni-graz.at

- [1] V. Iota, C. S. Yoo, and H. Cynn. Science **283**, 150 (1999).
- [2] S. Serra, C. Cavazzomi, G. L. Chiarotti, S. Scandolo, and E. Tossati. Science **284**, 788 (1999).
- [3] C. S. Yoo. In *Proceedings of the AIRAPT-17 International Conference on High Pressure Science and Technology, Honolulu, Hawaii*, 1999.
- [4] K. L. Tanaka, J. S. Kargel, D. J. MacKinnon, T. M. Hare, and N. Hoffman. Geophys. Res. Lett. **29**, (8), (2002). doi: 10.1029/2001GL013885.
- [5] C. S. Yoo, H. Cynn, F. Gygi, G. Galli, V. Iota, M. Nicol, E. Carlson, D. Hausermann, and C. Mailhot. Phys. Rev. Lett. **83** 5527, (1999).
- [6] J. Dong, J. K. Tomfohr, and O. F. Sankey. Phys. Rev. B **61** 5967, (2000).
- [7] J. Dong, J. K. Tomfohr, O. F. Sankey, K. Lienenweber, M. Somayazulu, and P. F. McMillan. Phys. Rev. B, **61** 5967, (2000).
- [8] B. Holm, R. Ahuja, A. Belonoshko, and Borje Johansson. Phys. Rev. B, **85** 1258, (2000).
- [9] P. Blaha, K. Schwarz, G. K. H. Madsen, D. Kvasnicka, and J. Luitz, 2001. WIEN2k, Vienna University of Technology, An Augmented Plane Wave + Local Orbitals Program for Calculating Crystal Properties.
- [10] J. P. Perdew and Y. Wang. Phys. Rev. B, **45** 13244, (1992).
- [11] C. Ambrosch-Draxl and J. O. Sofo. preprint.
- [12] S. Sharma, J. K. Dewhurst, and C. Ambrosch-Draxl, <http://xxx.lanl.gov/abs/cond-mat/0211512> (2002).
- [13] S. Scandolo and F. Bassani. Phys. Rev. B, **51** 6925, (1995).
- [14] Since GGA is known in general to be good in reproducing crystal volumes, no volume relaxation has been performed.
- [15] C. S. Yoo, H. Kohlmann, H. Cynn, M. F. Nicol, V. Iota, and T. LeBihan. Phys. Rev. B, **65** 104103, (2002).