

# Normal-state Hall Angle and Magnetoresistance in quasi-2D Heavy Fermion $\text{CeCoIn}_5$ near a Quantum Critical Point

Y. Nakajima<sup>1</sup>, K. Izawa<sup>1</sup>, Y. Matsuda<sup>1</sup>, S. Ujii<sup>2</sup>, T. Terashima<sup>2</sup>,  
H. Shishido<sup>3</sup>, R. Settai<sup>3</sup>, and Y. Onuki<sup>3</sup>, and H. Kontani<sup>4</sup>

<sup>1</sup>Institute for Solid State Physics, University of Tokyo, Kashiwanoha, Kashiwa, Chiba 277-8581, Japan

<sup>2</sup>National Institute of Material Science, Sakura, Tsukuba, Ibaraki 305-0003, Japan

<sup>3</sup>Graduate School of Science, Osaka University, Toyonaka, Osaka, 560-0043 Japan and

<sup>4</sup>Department of Physics, Saitama University, Shimookubo, Saitama 338-8570, Japan

(dated: April 14, 2024)

The normal-state Hall effect and magnetoresistance (MR) have been measured in the quasi-2D heavy fermion superconductor  $\text{CeCoIn}_5$ . In the non-Fermi liquid region where the resistivity  $\rho_{xx}$  exhibits an almost perfect  $T$ -linear dependence, the Hall angle varies as  $\cot \theta_H / T^2$  and the MR displays a strong violation of Kohler's rule. We demonstrate a novel relation between the MR and the Hall conductivity,  $\rho_{xx} = \rho_{xx} / (\rho_{xy} \rho_{xx})^2$ . These results bear a striking resemblance to the normal-state properties of high- $T_c$  cuprates, indicating universal transport properties in the presence of quasi-2D antiferromagnetic fluctuations near a quantum critical point.

PACS numbers: 71.27.+a, 73.43.Qt, 74.70.Tx

The transport and thermodynamic properties in most metals are well described by the conventional Landau Fermi liquid theory. Within the last decade, however, an increasing number of strongly correlated materials, including heavy fermion (HF) intermetallics, organics, and cuprates, have been found to display striking deviations from the Fermi liquid, when they are located close to a quantum critical point (QCP) [1]. In each of these materials, chemical doping, pressure, or magnetic field can tune the quantum fluctuations at zero temperature. As a result, these systems develop a new excitation structure and display novel thermodynamic and transport properties over a broad temperature range. It is generally believed that the abundance of low lying spin fluctuations near the QCP gives rise to a serious modification to the quasiparticle masses and scattering cross section of the Fermi liquid. In addition, some of these metals show a superconductivity. It appears that in these superconductors many-body effects originating from the strong spin fluctuations associated with the QCP often gives rise to unconventional superconductivity, in which Cooper pairs with angular momentum greater than zero are formed [2]. The relation, therefore, between unconventional superconductivity and quantum criticality emerges as an important issue in strongly correlated systems.

Despite extensive studies on the non-Fermi liquid behavior in the vicinity of the QCP, many properties in the normal state remain unresolved. In particular the detailed transport properties, i.e. how the magnetic excitations influence the transport properties, are unsettled. For instance, in high- $T_c$  cuprates the normal state transport properties above the pseudogap temperature are known to be quite unusual; the resistivity shows a  $T$ -linear dependence in a wide  $T$ -range, the Hall angle  $\theta_H$  varies as  $\cot \theta_H / T^2$  [3], and the magnetoresistance (MR) displays a strong violation of the Kohler's rule [4]. These non-Fermi liquid features have been controversial because they should ultimately be related to the mechanism

of the unconventional superconductivity. Therefore, in order to obtain deep insight into such unusual electronic transport phenomena, it is crucial to clarify whether they are universal electronic properties in the vicinity of QCP or are specific to high- $T_c$  cuprates.

Recently a new class of HF compounds with chemical formula  $\text{CeMIn}_5$ , where M can be either Rh, Ir, and Co, have been discovered [5]. Among them  $\text{CeCoIn}_5$  is a superconductor with the highest transition temperature ( $T_c = 2.3$  K) among all known HF superconductors. The normal state of  $\text{CeCoIn}_5$  exhibits all the hallmarks of quantum criticality. The two key parameters of a Fermi liquid, the electronic specific heat coefficient  $\gamma = C/T$  and uniform susceptibility  $\chi_0$ , increase with decreasing temperature as  $\gamma / \ln T$  and  $\chi_0 / 1 = (T + )$ , in marked contrast with the  $T$ -independent Fermi liquid behavior [5, 6]. Moreover an almost perfect  $T$ -linear resistivity [7, 8] is observed from  $T_c$  up to 20 K. These non-Fermi liquid properties have been discussed in the light of the antiferromagnetic (AF) fluctuation near a QCP. In fact the NMR spin-lattice relaxation rate obeys  $T_1^{-1} / T^{1/4}$ , indicating that  $\text{CeCoIn}_5$  is situated near an AF instability [9]. Moreover the microscopic coexistence of superconductivity and static AF order has been reported in  $\text{Ce}(\text{Co}_{1-x}\text{Rh}_x)\text{In}_5$  and  $\text{Ce}(\text{Ir}_{1-x}\text{Rh}_x)\text{In}_5$  systems [10]. It should be noted that  $\text{CeCoIn}_5$  has some resemblance with high  $T_c$  cuprates. First, the electronic structure is quasi-2D, as revealed e.g. by de Haas-van Alphen measurements [6]. Second, the superconducting gap symmetry most likely belongs to the d-wave class, indicating that the AF fluctuation plays an important role for the occurrence of superconductivity [9, 11, 12]. Third, a possible existence of the pseudogap was suggested [13]. In general, extraction of non-Fermi liquid properties near the QCP requires high quality single crystals, since the physical properties are seriously affected by small amounts of disorder induced by the chemical doping or pressure.  $\text{CeCoIn}_5$  is suitable for such a pur-

pose because non-Fermi liquid effect can be observed in the undoped compound at ambient pressure. Thus CeCoIn<sub>5</sub> provides an unique opportunity for investigating the transport properties in the presence of strong 2D AF fluctuation in the proximity of the QCP.

In this Letter, we used the Hall effect and the MR to clarify the microscopic scattering mechanism responsible for the unusual physical properties in the quasi-2D HF superconductor CeCoIn<sub>5</sub>. The zero field resistivity, Hall effect and the MR, all demonstrate a spectacular breakdown of Fermi-liquid behavior and show a striking similarity to high- $T_c$  cuprates. These results enable us, as mentioned above, to gain strong insights into the transport properties in the presence of the quasi-2D AF fluctuations associated with the QCP.

The high quality single crystals of CeCoIn<sub>5</sub> ( $T_c = 2.3$  K) were grown by the self-flux method. On cooling from room temperature,  $\rho_{xx}(H = 0)$  shows a slight increase below 200 K, followed by a crossover to metallic  $T$ -dependence below 40 K which seems to correspond to the coherent temperature  $T_{coh}$ . Below  $T \sim 20$  K  $\rho_{xx}$  displays an almost perfect linear  $T$ -dependence down to  $T_c$ , as shown in the main panel of Fig. 1. The in-plane diagonal ( $\rho_{xx}$ ) and Hall ( $\rho_{xy}$ ) resistivities were measured with current  $j$   $\parallel$   $a$  and  $H$   $\parallel$   $c$ , up to 25 T and up to 14 T, respectively. We obtained  $\rho_{xy}$  from the transverse resistance by subtracting the positive and negative magnetic field data. We have measured three different crystals and obtained similar results.

We first discuss the Hall effect. Figure 2 (b) depicts the  $H$ -dependence of  $\rho_{xy}$ . The Hall sign is negative in the present  $T$ - and  $H$ -range. At high temperatures above 40 K,  $\rho_{xy}$  is nearly proportional to  $H$ , while at lower temperatures  $\rho_{xy}$  shows a distinct deviation from the  $H$ -linear dependence. This also can be seen by the inset of Fig. 1, in which  $\rho_{xy}/H$  is plotted as a function of  $T$ . The data  $\rho_{xy}/H$  at  $H = 0$  are obtained by taking the low field

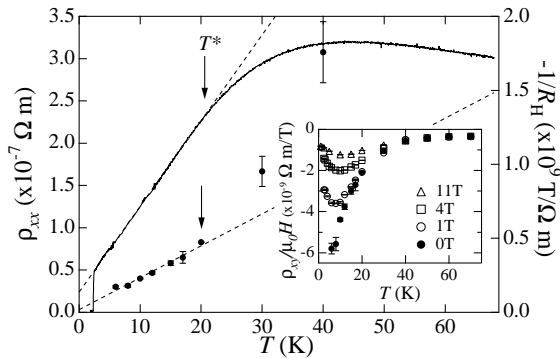


FIG. 1: Main panel: Temperature dependence of  $\rho_{xx}(0)$  and  $1/R_H$  in zero field limit. The dashed straight lines are guide for eyes. The arrows indicate  $T \sim 20$  K, below which  $T$ -linear  $\rho_{xx}$  and  $1/R_H$  are observed. Inset:  $\rho_{xy}/H$  vs.  $T$  at low fields.

limit of  $\frac{d\rho_{xy}}{dH}$ . At high temperatures,  $\rho_{xy}/H$  is nearly  $T$ -independent. As the temperature is lowered,  $\rho_{xy}/H$  at  $H = 0$  decreases monotonically down to  $T_c$ , while  $\rho_{xy}/H$  at  $H \sim 1$  T turns to increase after going through a minimum above  $T_c$ . In the main panel of Fig. 1,  $1/R_H$  is plotted as a function of  $T$ , where  $R_H = \lim_{H \rightarrow 0} \frac{d\rho_{xy}}{dH}$  is the Hall coefficient. A  $T$ -linear dependence of  $1/R_H$  is observed above  $T_c$  up to  $T \sim 20$  K, as shown by the dashed line, while a striking deviation from the  $T$ -linear dependence is observed at higher temperature. It should be stressed that the temperature region of  $T$ -linear  $1/R_H$  coincides nicely with that of  $T$ -linear  $\rho_{xx}$  (see arrow in Fig. 1), indicating an intimate relation between  $\rho_{xx}$  and  $R_H$ . The peculiar feature of the Hall effect is further pronounced by plotting the Hall angle  $\cot \theta_H = \frac{\rho_{xx}}{\rho_{xy}} = R_H H$  at  $\mu_0 H = 1$  T vs  $T^2$ , as shown in Fig. 3 [3]. The data fall on a straight line in the temperature range below  $T \sim 20$  K and can be quite well fitted as,

$$\cot \theta_H = T^2 + \text{const.} \quad (1)$$

A very small "residual"  $\cot \theta_H$ ,  $\neq 0$ , is similar to the high- $T_c$  cuprates with low impurity concentration (see Fig. 2 in Ref. [3]). We will discuss the origin of this  $T$ -dependence later.

The Hall effect in the conventional HF systems has been studied extensively and is known to exhibit a universal behavior (see Figs. 1 and 2 in Ref. [14]). At high temperatures exceeding  $T_K$ , the Kondo temperature, where the  $f$ -electrons are well localized with well-

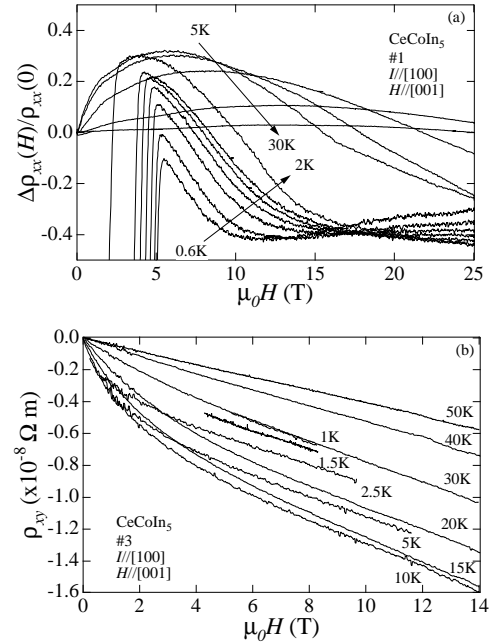


FIG. 2: (a) The magnetoresistance,  $\rho_{xx}(H) - \rho_{xx}(0)$ , as a function of  $H$ . (b) The field dependence of Hall resistivity  $\rho_{xy}(H)$ .

defined magnetic moments,  $R_H$  is mostly positive and is much larger than  $R_H$  in conventional metals. With the development of the Kondo coherence as the temperature is lowered,  $R_H$  decreases rapidly with decreasing  $T$  after showing a broad maximum at the temperature  $T \sim T_{\text{coh}}$ . At very low temperature,  $R_H$  becomes very small and becomes nearly  $T$ -independent. These temperature dependence of  $R_H$  have been explained as follows. Generally the Hall effect can be decomposed into two terms;  $R_H = R_H^n + R_H^a$ . Here  $R_H^n$  is the ordinary Hall effect due to the Lorentz force and is nearly  $T$ -independent within the Boltzmann approximation. Meanwhile  $R_H^a$  represents the so-called "anomalous Hall effect" due to skew scattering. The latter originates from the asymmetric scattering of the conduction electrons by the angular momenta of  $f$ -electrons, induced by the external magnetic field. This term is strongly temperature dependent and well scaled by the uniform susceptibility,  $R_H^a / \chi_{\text{xx}}$  [14, 15] or  $1/\rho$  [16, 17, 18], above  $T_{\text{coh}}$ . The magnitude of  $R_H^a$  is much larger than  $R_H^n$  except at  $T \sim T_{\text{coh}}$  where the contribution of the skew scattering vanishes; hence  $R_H \sim R_H^n$  at very low temperatures.

We will show that the Hall effect in  $\text{CeCoIn}_5$  shown in Figs. 1 and 2(b) is markedly different from those in ordinary HF systems. The first important signature is that above  $T_{\text{coh}} \sim 40$  K,  $R_H$  is nearly  $T$ -independent and can be scaled neither by  $\chi_{\text{xx}}$  nor by  $1/\rho$ , both of which have a strong  $T$ -dependence above 30 K. In addition, although we do not show here,  $\rho$  is almost strictly  $H$ -linear up to 12 T at  $T > 2$  K, while  $\chi_{\text{xy}}$  shows a nonlinear  $H$ -dependence below 30 K as shown in Fig. 2(b). Moreover the magnitude of  $R_H$  above  $T_{\text{coh}}$  is much smaller than those in other HF systems at high temperatures and in the same order to  $R_H$  ( $R_H^n$ ) at very low temperatures  $T \sim T_{\text{coh}}$  where the skew scattering vanishes in other HF systems. Thus both the amplitude and the  $T$ -dependence of  $R_H$  are obviously in conflict with the conventional skew scattering mechanism. These results lead us to conclude that the skew scattering in  $\text{CeCoIn}_5$  is negligibly small

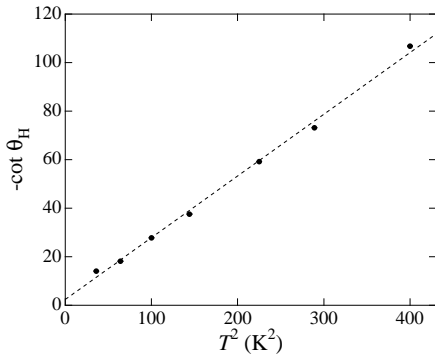


FIG. 3: The Hall angle  $\cot \theta_H$  as a function of  $T^2$ . For details, see the text. A fit by  $\cot \theta_H = T^2 + \text{const}$  gives  $\text{const} = 0.254 (\text{K}^2)$  and  $\text{slope} = 2.39$  (dashed line)

and  $T$ -dependence of  $R_H$  mainly stems from the normal part of the Hall effect  $R_H^n$ . The absence of skew scattering has also been reported in  $\text{CeMIn}_5$  [19] and double layered  $\text{Ce}_2\text{CoIn}_8$  [20]. At present the absence of skew scattering in these Ce compounds is an open question. The absence of the skew scattering enable us to analyze the normal Hall effect  $R_H^n$  in detail. Having established the evidence of strongly  $T$ -dependent  $R_H^n$ , which is incompatible with the conventional Fermi liquid theory, we move on to the MR.

The MR in most conventional HF materials also shows a similar behavior [21]. At very low temperature  $T \sim T_K$ , the MR is positive due to the orbital effect. Then the MR decreases with temperature, changes the sign reaching the negative minimum at  $T \sim T_K/2$ . The negative MR is due to the suppression of the spin-orbit scattering by magnetic field. Figure 2 (a) depicts the MR,  $\rho_{\text{xx}}(H) - \rho_{\text{xx}}(0)$ , as a function of  $H$ . A notable MR with an initial positive slope are observed at all temperatures. At high field the MR shows a crossover from positive to negative. The crossover field increases with temperature. Below 2 K the MR turns positive at very high field after showing a broad minimum. Thus the MR of  $\text{CeCoIn}_5$  displays a peculiar  $H$ -dependence, which is very different from ordinary HF systems [23]. The positive MR at very high field below 2 K is most likely to be an usual orbital MR due to the cyclotron motion of the electrons. The negative MR at high field seem to appear as a result of the suppression of the spin-orbit scattering, similar to the other HF compounds. The fact that the negative MR can be observed even at 25 T indicates the presence of a characteristic energy scale of the AF fluctuation which corresponds to a few meV. We note that recent scaling argument based on the measurements of  $C$  and  $\rho$  for  $\text{Ce}_{1-x}\text{La}_x\text{CoIn}_5$  suggests a presence of the new energy

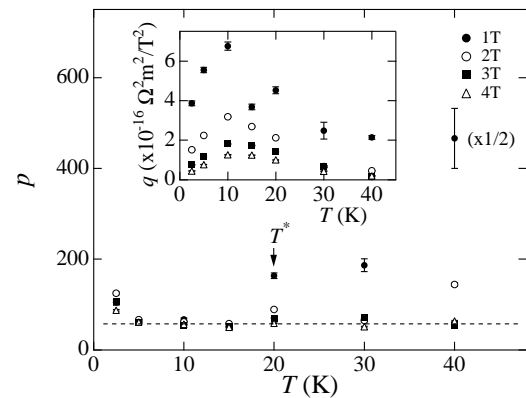


FIG. 4: Main panel:  $p(\rho_{\text{xx}}(H) - \rho_{\text{xx}}(0)) = \frac{2}{\rho_{\text{xy}}(H)} \frac{3}{\rho_{\text{xx}}(0)}$  is plotted as a function of  $T$  at low fields. The modified Kohler's rule represented by Eq.(5) well describes the data below  $T \sim 20$  K. Inset:  $q(\rho_{\text{xx}}(H) - \rho_{\text{xx}}(0)) = (\rho_{\text{xy}}(H))^2$  vs.  $T$  at various  $H$  is plotted. The strong violation of the Kohler's rule given by Eq.(2) is observed.

scale of the excitation which is an order of  $\sim 4$  meV [22]. We believe a close relation exists between the negative MR and the new energy scale suggested in Ref.[22]. In the conventional Fermi liquid metals the MR should obey the Kohler's rule which reads

$$\rho_{xx}(H) / \frac{H^2}{\rho_{xx}(0)} : \quad (2)$$

To examine this relation, we plot  $\rho_{xx}(H) / \rho_{xx}(0) = H^2$  against  $T$  at various  $H$  in the inset of Fig. 4. As shown in Fig. 4(a), this quantity is constant neither in  $T$  nor in  $H$ , in strong violation of Kohler's rule.

We are now in the position to make a quantitative analysis for the  $T$ -linear resistivity, the Hall angle  $\cot \theta_H / T^2$ , and the violation of the Kohler's rule in the MR, all of which signal a fundamental breakdown the Fermi-liquid behavior. All of these peculiar transport properties reminds one of high- $T_c$  cuprates. In the latter materials, two opposing views have been put forth to explain these transport properties. The first is the existence of two distinct relaxation time scales, each associated with the spinon and holon excitation in 2D  $\text{CuO}_2$ -planes [3, 4]. However, the existence of such excitations would seem unlikely in the present Kondo system with different electronic structures and different ground states, though we cannot completely exclude this possibility. The second is the modification of the transport quantities arising from the AF spin fluctuation near the QCP. According to the spin fluctuation theory, the transport properties are governed by the staggered susceptibility  $\chi_Q$  [24, 25]. For instance,  $\rho_{xx}$  and  $R_H$  are given as,

$$\rho_{xx} \propto \frac{2}{\Lambda_F} T^2 \propto Q T^2; \quad (3)$$

$$R_H \propto \frac{2}{\Lambda_F} \propto Q; \quad (4)$$

where  $\Lambda_F$  is the AF correlation length [24]. Since  $Q$  obeys the Curie-Weiss law near the QCP,  $Q / 1 = (T + \theta)$ ,  $\rho_{xx}$  is proportional to  $T$  and  $R_H$  is inversely proportional to  $T$ , consistent with the present results. Moreover since  $Q$  generally exhibits a non-linear  $H$ -dependence,

in contrast to  $\rho_0$  with a linear  $H$ -dependence, the deviation from  $H$ -linear dependence of  $\rho_{xy}$  shown in Fig. 2(b) is also consistent with Eq.(4). The spin fluctuation theory near the AF QCP predicts that the MR is also strongly influenced by  $Q$  and Kohler's rule should accordingly be modified as [25],

$$\frac{\rho_{xx}(H)}{\rho_{xx}(0)} / \frac{Q(H)}{Q(0)} = \frac{2}{(\rho_{xx}(0) \rho_{xy}(H))^2} \quad (5)$$

where  $\rho_{xy}(\rho_{xy} = (\frac{2}{\rho_{xx}} + \frac{2}{\rho_{xy}}))$  is the Hall conductivity. We now examine the MR in accordance with this "modified Kohler's rule", which well explains the MR of high- $T_c$  cuprates [4, 25]. The main panel of Fig. 4 depicts  $p(\rho_{xx}(H) = \frac{2}{\rho_{xy}(H)} \frac{3}{\rho_{xx}(0)})$  vs  $T$  at several fields. Below  $T \sim 20$  K,  $p$  is nearly constant in  $T$  and  $H$ , providing a support for the validity of Eq.(5). (The deviation of  $p$  from the high temperature value at 2.5 K is possibly due to the influence of the superconducting fluctuation just above  $T_c$  or the pseudogap reported in Ref.[13].) A strong deviation can be seen above  $T_c$ . Thus both the Hall effect and the MR at low field below  $T_c$  in the coherent region are well described by Eqs.(4) and (5).

Summarizing the salient features in the normal state transport properties of quasi-2D HF superconductor  $\text{CeCoIn}_5$ , which is located near the QCP; (1) almost perfect  $T$ -linear  $\rho_{xx}$ , (2)  $T^2$ -dependent  $\cot \theta_H$ , (3) the MR which obeys a modified Kohler's rule. All of these peculiar properties are observed in the same temperature range between  $T_c$  and  $T \sim 20$  K. These are new hallmarks of the non-Fermi liquid behavior in the transport property and well explained by the spin fluctuation theory near the QCP. These results also bear striking resemblance to high- $T_c$  cuprates. It should be noted that the ground state of high- $T_c$  cuprates is a Mott insulator while the ground state of  $\text{CeCoIn}_5$  appears to be an AF metal. The striking similarity between two different systems implies a universal excitation structure of AF fluctuation near the QCP, which promotes future study.

We thank S. Ohara, Y. Ohkawa, I. Sakamoto, H. Sato, K. Ueda, S. Watanabe, and V. Zlatić for valuable discussions.

- 
- [1] T. Moriya, and T. Takimoto, J. Phys. Soc. Jpn, 64, 960 (1995), P. Coleman et al., J. Phys. C 13 R 723 (2001).  
[2] M. Sigrist and K. Ueda, Rev. Mod. Phys. 63, 239 (1991).  
[3] T. R. Chien et al., Phys. Rev. Lett. 67, 2088 (1991).  
[4] J. M. Harris et al., Phys. Rev. Lett. 75, 1391 (1995).  
[5] C. Petrovic et al., J. Phys. C 13, L337 (2001).  
[6] H. Shishido et al., J. Phys. Soc. Jpn 71, 62 (2002).  
[7] O. Tjoraveili et al., Phys. Rev. Lett. 85, 626 (2000).  
[8] A. Rosch, Phys. Rev. Lett. 82, 4280 (1999).  
[9] G.-q. Zheng et al., Phys. Rev. Lett. 86, 4664 (2001), Y. Kohori et al., Phys. Rev. B 64, 134526 (2001).  
[10] V. S. Zapf et al., Phys. Rev. B 65, 014506 (2002) R. A. Fisher et al., Phys. Rev. B 65, 224509 (2002), P. G. Pagliuso et al., Phys. Rev. B 64, 100503 (2001).  
[11] R. Movshovich et al., Phys. Rev. Lett. 86, 5152 (2001).  
[12] K. Izawa et al., Phys. Rev. Lett. 87, 057002 (2001).  
[13] V. A. Sidorov et al., Phys. Rev. Lett. 89, 157004 (2002).  
[14] A. Fert, and P. M. Levy, Phys. Rev. B 36, 1907 (1987).  
[15] P. Coleman, P. W. Anderson, and T. V. Ramakrishnan, Phys. Rev. Lett. 55, 414 (1985).  
[16] Y. Onuki et al., J. Phys. Soc. Jpn 58, 2126 (1989).  
[17] J. Schoenes and J. J. M. Franse, Phys. Rev. B 33, 5138 (1986).  
[18] H. Kontani, and K. Yamada, J. Phys. Soc. Jpn 63, 2627 (1994).  
[19] S. Ohara, private communication.

- [20] G. Chen et al, a preprint.
- [21] V. Zlatić, J Phys. F 11, 2147 (1981), M. C. Aronson et al, Phys. Rev. Lett. 63, 2311 (1989), F. J. Ohkawa *ibid.* 64, 2300 (1990)
- [22] S. Nakatsuji et al, Phys. Rev. Lett. 89, 106402 (2002).
- [23] J. Paglione et al, cond-mat/0212502.
- [24] H. Kontani, K. Kanki, and K. Ueda, Phys. Rev. B 59, 14723 (1999).
- [25] H. Kontani, J Phys. Soc. Jpn, 70, 1873 (2001).