

T. Jarlborg

Département de Physique de la Matière Condensée, Université de Genève, 24 quai Ernest Ansermet, CH-1211 Genève 4, Switzerland

(April 14, 2024)

The T -dependence of magnetic moments in SrB_6 is studied through spin-polarized band calculations for a supercell of $\text{Sr}_{27}\text{B}_{156}$ containing a B_6 vacancy. The magnetic moment decays rather quickly with T despite the fact that only electronic Fermi-Dirac effects are included. This result and the T -dependence of moments near a La impurity can hardly explain the reports of a very high Curie temperature in hexaborides, but suggest that the magnetism is caused by some other type of impurity.

Early reports of weak ferromagnetism (FM) in lightly doped CaB_6 or SrB_6 , associated with an unusually high Curie temperature (T_C)¹, have been followed by several theoretical and experimental studies. For instance, it has been speculated that the FM could be of excitonic origin², be a spontaneous polarization of the dilute electron gas³, or be caused of special conditions around impurities and thereby lead to band magnetism^{4,5}. The band structure of the pure hexaboride⁶, which is metallic when calculated within the density functional (DF) approach, has been questioned, since one GW-calculation found a gap at the Fermi energy, E_F ⁷. These results are in contrast to a recent independent GW-calculation by Kino et al, where the ground state is metallic⁸. Also, there are conflicting results concerning the interpretation of the experimental results on the weak magnetism. Quantum oscillations indicate that the FM state is not intrinsic to the bulk, but that impurities might be important⁹. This conclusion was supported by Mori and Ohtani¹⁰ who found that the FM signal could be removed by a treatment of the crystals, and suggested that the FM is due to iron impurities. Other defects such as vacancies have been suggested as well¹¹. Possible vacancies of whole B_6 -clusters were anticipated in calculations by Monnier and Delley¹² who showed that a sizable FM moment surrounded such a vacancy in a supercell of CaB_6 . They suggest that the observation of weak ferromagnetism in dilute doped hexaborides is caused either by a surface or interface effect, since the B_6 vacancy is modeling the natural cleavage planes in polycrystals, or by some amount of B_6 vacancies in pure crystals.

In the present letter, by use of the linear Murn-Tin orbital (LMTO) band method in the local spin-density approximation, we study the variation of the magnetic moment around a B_6 vacancy in Sr_6 as function of temperature. This is done by self-consistent spin-polarized calculations, in which T -dependent electronic excitations are modeled by the Fermi-Dirac distribution, but no thermal disorder of the lattice is taken into account. As in

ref.¹² we consider a $3 \times 3 \times 3$ supercell with one B_6 vacancy in SrB_6 so that the total cell is $\text{Sr}_{27}\text{B}_{156}$. The missing B_6 atoms form empty MT-spheres, and the calculations include additional empty spheres in the open part structure. The cell contains 19 nonequivalent MT-spheres, 4 Sr, 8 B and 7 empty ones. Other details of the calculation are as in ref.⁵. The density-of-states (DOS) functions near E_F for the non-polarized case, are shown in Fig. 1 for two sets of k -points (4 and 10) in the irreducible part of the Brillouin zone. It is seen that the essential features of the DOS are developed already when using 4 k -points, with only small differences in the details. In particular, the DOS peak at E_F is similar in the two sets of k -points, so that the criterion for Stoner magnetism should come out well already when using only 4 k -points. The Stoner factor is calculated to be 1.05, just above the limit for ferromagnetism, 1.0, indicated by the horizontal line in Fig. 1. The broken line shows the partial DOS from the six equivalent B-atoms closest to the B_6 -vacancy. It is seen that roughly 1/3 of the total DOS at E_F comes from these sites although they represent only about 3 percent of the total number of atoms in the cell. In the spin-polarized calculations (at low T), when using 4 k -points, one finds a magnetic moment, $m = 2.1 \mu_B$ per cell, in agreement with ref.¹². This moment decreases to about $1.8 \mu_B$ when the number of k -points is increased to 10 for the same temperature. This type of magnetism is a standard Stoner magnetism¹³, where the large DOS on the 6 B-atoms nearest to the vacancy contribute most to the Stoner instability, cf. Fig 1. Similarly, about 40 percent of the total moment in the spin-polarized calculations comes from these six B-sites closest to the vacancy.

Spin-polarized calculations at different temperatures in the Fermi-Dirac distribution, show that the moment goes to zero when T is increased to about 700 K. The two sets of k -points have been used at the lowest and highest T , and both sets give a vanishing moment at $T = 700 \text{ K}$. Calculations for intermediate T , using 4 k -points, show

first a gradual decrease of m at low T , while the curve drops sharply as T is approaching 700 K, as shown in Fig 2. This T -dependence is understood from the fact that E_F falls on a narrow peak in the DOS, so that thermal smearing, due to electronic excitations, can reduce the effective DOS and the Stoner factor. Since T_C in the doped hexaborides is of the same order, 700 K, it is tempting to assign the observed T_C to the mechanism of Stoner magnetism due to the B_6 vacancy. However, the typical behavior for ferromagnets is that the temperature at which S goes below the critical value for ferromagnetism,

is generally much larger than the Curie temperature (T_C) for real materials⁴. By taking into account additional smearing effects on the DOS coming from thermally induced disorder of the structure one obtains more realistic values of T_C in mean-field calculations¹⁵. The atomic displacements from thermal vibrations at 700 K can be of the order 0.25 a.u. (corresponding to 7-8 percent of the B-B distance) for a material with a Debye temperature of 350 K, while large smearing effects on DOS peaks appear already at a lower degree of disorder¹⁶. The present calculations include only the T-dependence via the Fermi-Dirac distribution and the effects from thermal disorder are expected to reduce the moment further. Therefore, it is difficult to understand the high T_C in the real materials from the T-dependence of the moments within the Stoner mechanism. One possibility would be that the local structure around a B_6 vacancy somehow can escape effects of thermal disorder, in which case it is justified to consider only the effect Fermi-Dirac smearing. The position of E_F relative to the peak appears to be at the optimal place for the largest possible Stoner factor for this supercell, and an increased height of the peak at larger T would be opposite to the normal T-dependence of the DOS.

Another mechanism leading to magnetism is due to a gain of Coulomb energy in addition to the exchange energy, by means of charge transfers. This mechanism can be activated if there is a large derivative N^0 of the DOS of an impurity band, leading to very small moments near the impurity⁴. This difference with the normal Stoner mechanism, suggests that this weak magnetism could resist better to temperature and broadening of the DOS by disorder, since N^0 can be large within a wider energy interval compared to that of a peak in the DOS. However, the results from calculations for a La impurity in a $3 \times 3 \times 3$ cell give only a partial support to this expectation⁵. The DOS of this cell is such that N^0 is maximal a bit below E_F , and even if there is a small moment at 600 K, it tends to zero at low T. It is difficult to have a sizable moment both at low and high T. By optimizing the position of N^0 relative to E_F (and the amplitude of N) by a combination of the virtual crystal approximation and a non-conventional choice of linearization energies in the band calculation, it is possible to have a weak moment within some range of T. Such band results are not ab-initio, but they are useful to show a correlation of moment and charge transfers. They also show that magnetism within this mechanism depend on the details of the electronic structure near the impurity, which in turn suggest that such magnetism should be a result of circumstances. Furthermore, it is expected that thermal disorder should be as important for this type of magnetism as it is for the standard Stoner magnetism.

In conclusion, the band results confirm that weak magnetism is possible, either as standard Stoner magnetism around a B_6 vacancy or assisted by Coulomb energies near a La-impurity, but it is more difficult to understand the high T_C values from both of these mechanisms. These

results and recent experimental reports^{9,10} motivate similar electronic structure studies of the properties near iron impurities in these materials. However, the exact state of iron contamination, in purity sites or clustering on surfaces, is yet not clear.

-
- ¹ D.P. Young, D. Hall, M.E. Torelli, Z. Fisk, J.L. Sarrao, J.D. Thompson, H.R. Ott, S.B. Osero, R.C. Goodrich and R. Zysler, *Nature* 397, 412 (1999).
 - ² M.E. Zhitomirsky, T.M. Rice and V.I. Anisimov, *Nature* 402, 251, (1999); L. Balents and C.M. Varma, *Phys. Rev. Lett* 84, 1264, (2000); V. Barzykin and L.P. Gorkov, *Phys. Rev. Lett.* 84, 2207, (2000).
 - ³ G. Ortiz, M. Harris and P. Balone, *Phys. Rev. Lett* 82, 5317, (1999).
 - ⁴ T. Jarlborg, *Phys. Rev. Lett.* 85, 186 (2000).
 - ⁵ T. Jarlborg, *Physica B* 307, 291, (2001).
 - ⁶ S. Massidda, A. Continenza, T. de Pascale and R. Monnier, *Z. Phys. B* 102, 83, (1997).
 - ⁷ H.J. Tromp, P. van Gelderen, P.J. Kelly, G. Brooks and P.A. Bobbert, *Phys. Rev. Lett.* 87, 016401, (2001).
 - ⁸ H. Kikino, F. Aryasetiawan, M. van Schilfegaarde, T. Kotani, T. Miyake and K. Terakura, *J. Phys. Chem. Solids* 63, 1595, (2002).
 - ⁹ T. Terashima, C. Terakura, Y. Umeda, N. Kimura, H. Aoki and S. Kunii, *J. Phys. Soc. Jap.* 69, 2423, (2000).
 - ¹⁰ T. Mori and S. Otani, *Solid State Commun.* 123, 287, (2002).
 - ¹¹ Z. Fisk, H.R. Ott, V. Barzykin and L.P. Gorkov, *Physica B* 312-313, 808, (2002).
 - ¹² R. Monnier and B. Delley, *Phys. Rev. Lett.* 87, 157204 (2001).
 - ¹³ T. Jarlborg and A.J. Freeman, *Phys. Rev. B* 22, 2332, (1980).
 - ¹⁴ O. Gunnarsson, *J. Phys. F* 6, 587 (1976).
 - ¹⁵ T. Jarlborg and M. Peter, *J. Magn. and Magn. Mater.* 42, 89, (1984).
 - ¹⁶ T. Jarlborg, *Phys. Rev. B* 59, 15002, (1999).

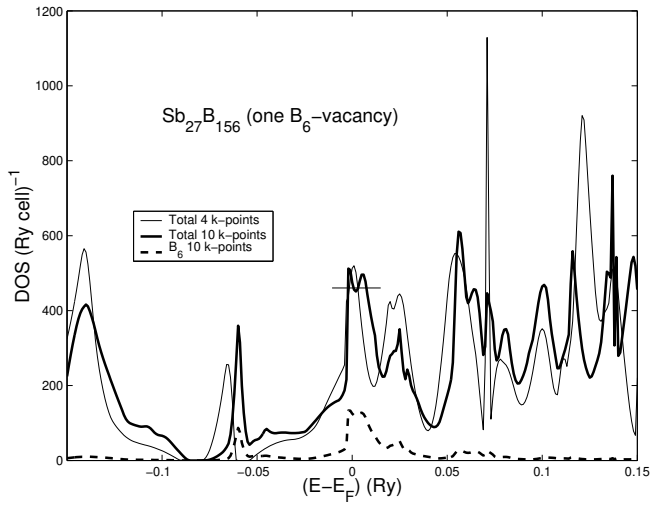


FIG .1. Total DOS of $\text{Sr}_{27}\text{B}_{156}$ near E_F , using 4 and 10 k-points. The broken line is the partial DOS on B_6 closest to the vacancy. The vertical line indicate the limit for Stoner magnetism.

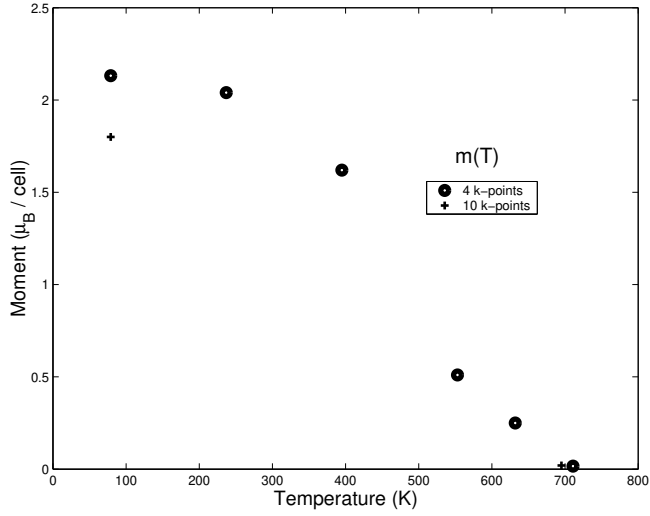


FIG .2. Calculated magnetic moment (μ_B per cell) as function of temperature for $\text{Sr}_{27}\text{B}_{156}$.