

Superconductivity Phase Diagram of $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$

R.E. Schaak¹, T. Klimczuk^{1,2}, M.L. Foo¹, and R.J. Cava^{1,3}

¹Department of Chemistry, Princeton University, Princeton NJ 08544

²Faculty of Applied Physics and Mathematics, Gdansk University of Technology, Narutowicza 11/12, 80-952 Gdansk, Poland

³Princeton Materials Institute, Princeton University, Princeton NJ 08540.

Although the microscopic origin of the superconductivity in high T_c copper oxides remains the subject of active inquiry, several of their electronic characteristics are well established as universal to all the known materials, forming the experimental foundation that all theories must address. The most fundamental of those characteristics is the dependence of the superconducting transition temperature on the degree of electronic band filling. Since the discovery of cuprate superconductivity in 1986 (1), the search for other families of superconductors that might help shed light on the superconducting mechanism of the cuprates has been of great interest. The recent report of superconductivity near 4K in the triangular lattice, layered sodium cobalt oxyhydrate, $\text{Na}_{0.35}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$, suggests that superconductors related to the cuprates may be found (2). Here we show that the superconducting transition temperature of this compound displays the same kind of chemical-doping controlled behavior that is observed in the cuprates. Specifically, the optimal superconducting T_c occurs in a narrow range of sodium concentrations, and therefore electron concentration, and decreases for both underdoped and overdoped materials, in analogy to the phase diagram of the cuprate superconductors. Our results suggest that detailed characterization of this new superconductor may help establish which of the many special characteristics of the cuprates is fundamental to their high T_c superconductivity.

Like the high T_c superconductors, the $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ crystal structure (2) consists of electronically active planes (in this case, edge sharing CoO_6 octahedra) separated by layers (in this case, $\text{Na}_x \cdot 1.3\text{H}_2\text{O}$) that act as spacers, to yield electronic two-dimensionality, and also act as charge reservoirs. We have found that varying the Na content in $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ results in the same type of out-of-plane chemical doping control of in-plane electronic charge that is found for the cuprate superconductors. This is achieved by changing the Br concentration used in the deintercalation of the host material. (See caption of Fig. 1 for the synthesis procedure). Powder X-ray diffraction (XRD) patterns for the synthesized samples are shown in Fig. 1. The bromine-treated samples made with substoichiometric (0.5X) and stoichiometric (1X) bromine solutions consist primarily of a partially deintercalated, anhydrous, non-superconducting Na_xCoO_2 phase ($c \approx 11.2 \text{ \AA}$). A small amount of the hydrated superconducting phase $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ ($c \approx 19.6 \text{ \AA}$) is detectable by XRD for the 1X sample. Single phase,

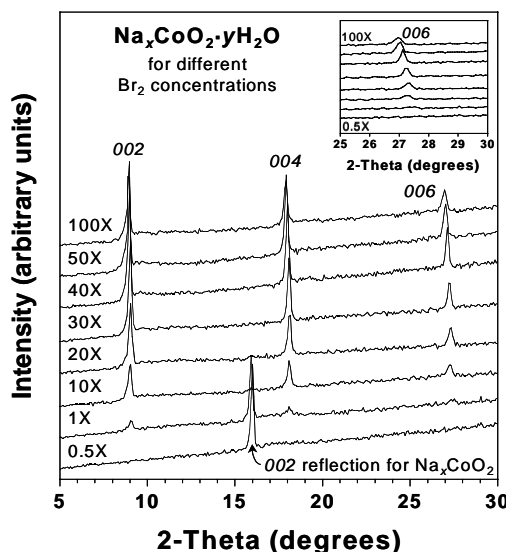


Figure 1. Powder X-ray diffraction patterns (Cu $K\alpha$ radiation) for $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ samples prepared using different concentrations of the bromine deintercalant. The inset shows an enlargement of the 006 reflections for each sample, highlighting the shift in the layer spacing as a function of sodium content. The $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ samples were prepared by chemically deintercalating sodium from $\text{Na}_{0.7}\text{CoO}_2$ using bromine as an oxidizing agent (2,3). One-half gram of $\text{Na}_{0.7}\text{CoO}_2$ was stirred in 20 mL of a Br_2 solution in acetonitrile at room temperature for five days. Bromine concentrations representing substoichiometric (0.5X), stoichiometric (1X), and molar excess (10X – 100X) relative to sodium content were employed. (“1X” indicates that the amount of Br_2 used is exactly the amount that would theoretically be needed to remove all of the sodium from $\text{Na}_{0.7}\text{CoO}_2$.) The product was washed several times with acetonitrile and then water, and then dried briefly under ambient conditions. The sodium content of the phases was determined by the inductively coupled plasma atomic emission spectroscopy (ICP-AES) method. Very high Na diffusion coefficients facilitate homogenization of the Na contents of the samples at ambient temperature.

superconducting, fully hydrated $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ occurs for higher Br concentrations, with a small amount of Na_xCoO_2 in the 10X sample. Chemical analysis indicates that the sodium content of the resulting materials generally varies systematically in the samples prepared in different Br concentrations, over a range of $x = 0.26$ to 0.45 (Table 1). Thermogravimetric analysis of all the samples on very slow heating in oxygen showed that their behavior was identical to that reported previously for $\text{Na}_{0.3}\text{CoO}_2 \cdot y\text{H}_2\text{O}$ (3). The interlayer water content remains essentially const-

Table 1. Characterization of $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ prepared by bromine deintercalation and hydration of $\text{Na}_{0.7}\text{CoO}_2$.

Sodium content ^a (x in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$)	Bromine concentration	a axis of $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}^b$ (Å)	c axis of $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}^b$ (Å)	T_c^c (K)
0.45	0.5X	N/A	N/A	2.0
0.40	1X	2.823(3)	19.43(2)	2.0
0.32	10X	2.825(2)	19.52(2)	2.1
0.33	20X	2.823(2)	19.58(1)	2.2
0.32	30X	2.822(2)	19.58(1)	3.0
0.30	40X	2.823(2)	19.69(2)	4.3
0.29	100X	2.819(3)	19.77(2)	4.0
0.26	50X	2.821(2)	19.77(2)	2.4

^aSodium content determined by ICP-AES. The estimated error of analysis is ± 0.02 per formula unit. ^bDetermined by least squares refinement of powder XRD data, from 6-10 reflections between 5 and 60 degrees 2θ . ^c T_c s determined from the AC susceptibility data, from the extrapolation of the steepest slope of the M vs. T curves in Fig. 3 to $M = 0$.

ant, at approximately 1.3 per formula unit, despite differences in sodium content, as illustrated in the inset to figure 2. Figure 1 shows a noticeable shift in the positions of the $00l$ reflections for the fully hydrated $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ phases, yielding a systematic variation in the c axes of the unit cells (Table 1) from 19.43 Å for the $x = 0.45$ sample to 19.77 Å for the $x = 0.26$ sample. This increase in layer separation with decreasing sodium content for the hydrated superconducting phase is similar to that observed in the dehydrated Na_xCoO_2 phase (3,4). The a axis, reflecting the in-plane CoO_6 dimensions, is independent of Na content within the precision of our measurements.

Zero-field cooled DC magnetization data measured in a field of 5 Oe for selected samples are shown in the main panel of Fig. 2. The magnetizations at 1.8 K represent approximately 100% of the theoretical value expected for perfect diamagnetism. Such strong diamagnetic signals provide evidence for bulk superconductivity. Na concentration inhomogeneities in the samples are likely the primary source of rounding of the superconducting transitions. An important point revealed by the data in figure 2 is that T_c for each sample is clearly different, indicating that differences in sodium content significantly affect the superconductivity of $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$.

In order to characterize fully the dependence of T_c on sodium content, we used AC susceptibility, which is more sensitive to weakly superconducting samples. Figure 3 shows the AC susceptibility for all the $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ samples. For the multiple phase $x = 0.45$ and $x = 0.40$ samples, the T_c s are approximately 2.0 K (see table 1), and the diamagnetic AC signals are very small, consistent with their phase analysis by x-ray diffraction, which shows primarily non-superconducting, anhydrous Na_xCoO_2 . In the $x = 0.40$ sample, the fully hydrated $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ phase accounts for approximately 15% of the sample, allow-

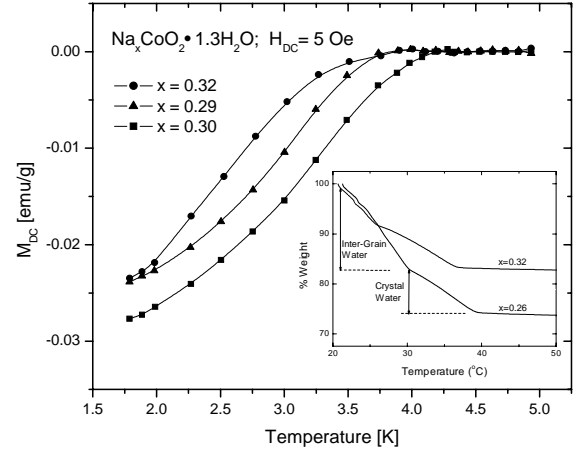


Figure 2. Zero field cooled DC magnetization (Quantum Design PPMS magnetometer, $H_{DC} = 5$ Oe) for superconducting samples of $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ ($x = 0.29, 0.30, 0.32$). The inset shows the loss in weight of single phase $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ ($x = 0.26$, and 0.32) samples heated extremely slowly in O_2 (0.25 degrees per minute) illustrating the method by which we distinguish the amount of crystal water (the higher temperature weight loss) from the inter-grain water (the lower temperature weight loss). The change in weight that occurs on loss of crystal water is seen to be essentially the same in both low Na and high Na content materials.

ing us to estimate the maximum sodium content of the $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ phase to be approximately $x = 0.35$. The data suggest that at its highest possible Na content, the $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ phase has a T_c near 2K.

All other samples are single phase sodium cobalt oxyhydrate with the crystal structure of the superconductor. The $x = 0.32$ and $x = 0.33$ samples yield slightly higher T_c s (between 2.1 and 2.2 K) and signals that are one to two orders of magnitude higher than the multiple phase $x = 0.40$ sample. Single phase samples with sodium contents of $x = 0.32, 0.30$, and 0.29 display superconducting transition temperatures of 3.0 K, 4.3 K, and 4.0 K, respectively (Fig. 3). Significantly, the single phase sample with $x = 0.26$ has a T_c of only 2.4 K.

Fig. 4 shows the superconducting phase diagram of $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. The variation of T_c as a function of x is shown in the main panel, and the magnitude of the DC magnetizations measured in an applied field of 5 Oe at 1.8 K, plotted on a logarithmic scale, are shown in the inset. These results clearly show that there is an optimal sodium composition for the occurrence of superconductivity ($x = 0.30$) and that both the T_c and quality of the superconductivity (inset, fig. 4) decrease at both lower and higher Na contents. As the sodium content increases between $x = 0.26$ and $x = 0.35$, the formal oxidation state of the Co decreases from 3.74+ to 3.65+. Consequently, T_c varies dramatically with the degree of electronic doping of the CoO_2 planes, in analogy with the behavior observed in

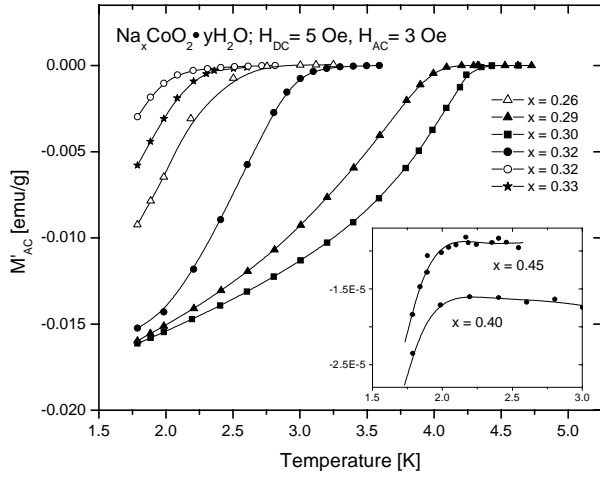


Figure 3. Zero field cooled AC magnetization for all superconducting $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ samples. ($H_{\text{DC}} = 3$ Oe, $H_{\text{AC}} = 5$ Oe, $f = 10$ kHz) Magnetization data for the weakly superconducting samples $x = 0.45$ and $x = 0.40$ are shown in the inset.

the cuprate superconductors. We note that the synthesis method we have employed, and other ambient temperature synthesis methods that might be used in this system, are likely to result in a distribution of sodium contents for each sample. If ideally uniform sodium content samples can be prepared, we expect that the superconducting “dome” shown in figure 4 may become more narrow in sodium content.

Preliminary correlation of the chemical doping due to the Na content and the true electronic doping state of the CoO_2 planes can be accomplished by electron counting in the context of electronic pictures already being developed for both the dehydrated Na_xCoO_2 and $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ phases (see, for example refs. 5-10). For $x = 0$, the formal Co oxidation state is Co^{4+} , with a t_{2g}^5 electron configuration in the low spin state. For $x = 1$, Co is formally $3+$, with an electron configuration of t_{2g}^6 in the low spin state. Electronic structure calculations for $\text{Na}_{0.5}\text{CoO}_2$ (7) indicate that the t_{2g} band would be completely filled at $x = 1$, and that an “ordinary” semiconductor is expected. However, it has been pointed out that the trigonal distortion of the CoO_6 octahedra in these structures may lead to splitting of the t_{2g} band (6,11). The proposed t_{2g} band splitting instead would result in a fully filled four-electron band, and a half filled two-electron band for $x = 0$. In this scenario, $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ for $x = 0$ bears a striking similarity to La_2CuO_4 , the ground state for the cuprate superconductors, where electrons at the Fermi Energy also reside in a half filled two-electron band. It has not yet been determined whether this half filled state in the layered triangular lattice cobaltates at $x = 0$ gives rise to a Mott-Hubbard insulator as it does in the cuprates. In this scenario, then, each added Na above $x = 0$ in $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ results in the addition of one electron per cobalt to the half-filled band, and the opti-

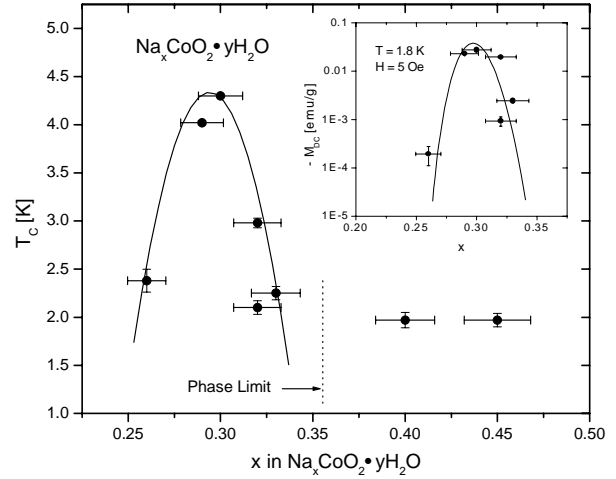


Figure 4. The superconducting phase diagram for $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. Main panel: T_c as a function of x as determined from the AC susceptibility measurements in Fig. 3. Inset: the magnitude of the diamagnetic DC magnetization measured at 1.8 K in an applied DC field of 5 Oe, plotted on a logarithmic scale.

mal chemical doping level for superconductivity, $x = 0.3$, represents the addition of 0.3 electrons to the half-filled band per formula unit. Values of x less than 0.3 would then represent underdoped materials, and values of x greater than 0.3 would represent overdoped materials. More detailed characterization of the electronic state of the triangular cobaltates will be needed to determine just how closely the electronic analogies to the cuprates hold.

This work reveals several experimental findings that are critical for understanding the superconductivity of $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$. The discovery of correlated maxima in both T_c and diamagnetic shielding as a function of the Na content clearly establish the optimal chemical doping level for superconductivity. A fundamental similarity between the layered cuprate and layered cobaltate superconductors is seen in the decrease in T_c for both the underdoped and overdoped materials. The optimal doping level for superconductivity appears to be relatively higher in the cobaltates than in the cuprates. Observations of unusual electronic properties in the host material $\text{Na}_{0.7}\text{CoO}_2$ itself (11,12) suggest that coupled spin and charge dynamics may be implicated in the superconductivity. Observations that the lower hydrates with closer CoO_2 - CoO_2 interplanar distances are not superconducting above 2K (3), and that T_c decreases under pressure (13) indicate that the two dimensional character of the structure is important. Though the intrinsically complex materials chemistry of the $\text{Na}_x\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ superconductor makes it difficult to characterize, we believe that potentially fruitful comparisons to the cuprates, and the fact that this compound may represent the literal embodiment of Anderson’s original proposal for the RVB (resonating valence bond) state (14), make it highly worthy of further study.

Acknowledgements

This work was supported by the US National Science Foundation, Division of Materials Research, and the US Department of Energy, Division of Basic Energy Sciences. T. Klimczuk would like to thank The Foundation for Polish Science for support.

References

1. Bednorz, J. G. & Müller, K. A., "Possible high T_c superconductivity in the Ba-La-Cu-O system", *Z. Phys. B* **64**, 189-193 (1986)
2. Takada, K., Sakurai, H., Takayama-Muromachi, E., Izumi, F., Dilanian, R.A., Sasaki T., "Superconductivity in two-dimensional CoO_2 layers", *Nature* **422**, 53 – 55 (2003)
3. Foo, M.L., Schaak, R.E., Miller, V.L., Klimczuk, T., Rogado, N.S., Wang, Yayu, Lau, G.C., Craley, C., Zandbergen, H.W., Ong, N.P., and Cava, R.J., "Chemical Instability of the Cobalt Oxyhydrate Superconductor under Ambient Conditions", *Sol. St. Comm.*, in press.
4. Foussassier, C., Matjeka, G., Reau, J.-M., and Hagenmuller, P., "Sur de nouveaux bronzes oxygènes de formulae Na_xCoO_2 ($x \leq 1$). Le système cobalt—oxygène-sodium", *J. Sol. St. Chem.* **6**, 532-537 (1973).
5. Baskaran, G., "An Electronic Model for CoO_2 Layer Based Systems: Chiral RVB metal and Superconductivity", cond-mat/0303649
6. Kumar, B., and B.S. Shastry, B.S., "Superconductivity in CoO_2 Layers and the Resonating Valence Band Mean Field Theory of the Triangular Lattice t-J Model", cond-mat/0304210
7. Singh, D. J., Electronic Structure of NaCo_2O_4 ", *Phys. Rev. B* **61**, 13397-13402 (2000)
8. Honer camp, Carsten, "Instabilities of interacting electrons on the triangular lattice", cond-mat/0304460
9. Tanaka, A., and Hu, X., "Possible spin triplet superconductivity in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$," cond-mat/0304409
10. Wang, Q.-H., Lee, D.-H., and Lee, P.A., "Doped t-J Model on a Triangular Lattice: Possible Application to $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ and Na_xTiO_2 ", cond-mat/0304377
11. Terasaki, I., Sasago, Y. & Uchinokura, K. "Large thermoelectric power in NaCo_2O_4 single crystals", *Phys. Rev. B* **56**, R12685 – R12687 (1997).
12. Wang, Yayu, Rogado, N.S., Cava, R.J., and Ong, N.P., "Spin Entropy as the likely source of enhanced thermopower in $\text{Na}_x\text{Co}_2\text{O}_4$ ", *Nature*, in press.
13. Lorenz, B., Cmaidalka, J., Meng, R.L., and Chu, C.W., "Effect of Hydrostatic Pressure on the Superconductivity in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$," con-mat/0304537
14. Anderson, P.W., "Resonating Valence Bonds: A New Type of Insulator," *Mat. Res. Bull.* **8** 153-160 (1973).