

Direct observation of the oxygen isotope effect on the in-plane magnetic field penetration depth in optimally doped $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$

R. Khasanov,^{1,2} D. G. Eshchenko,^{1,2} H. Luetkens,^{2,3} E. Morenzoni,² T. Prokscha,² A. Suter,² N. Garijanov,² M. Mali,¹ J. Roos,¹ K. Conder,⁴ and H. Keller¹

¹Physik-Institut der Universität Zürich, Winterthurerstrasse 190, CH-8057, Switzerland

²Laboratory for Muon Spin Spectroscopy, PSI, CH-5232 Villigen PSI, Switzerland

³Institut für Metallphysik und Nukleare Festkörperphysik,

TU Braunschweig, 38106 Braunschweig, Germany

⁴Laboratory for Neutron Scattering, ETH Zürich and PSI, CH-5232 Villigen PSI, Switzerland

We report the first direct observation of the oxygen-isotope ($^{16}\text{O}/^{18}\text{O}$) effect on the in-plane penetration depth λ_{ab} in a nearly optimally doped $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$. In using the novel low-energy muon-spin rotation technique. Spin polarized low energy muons are implanted in the film at a known depth z beneath the surface and precess in the local magnetic field $B(z)$. This feature allows us to measure directly the profile $B(z)$ of the magnetic field inside the superconducting film in the Meissner state and to make a model independent determination of λ_{ab} . A substantial isotope shift $\lambda_{ab} = \lambda_{ab} = 2.8(7)\%$ at 4 K is observed, implying that the in-plane effective supercarrier mass m_{ab} is oxygen-isotope dependent with $m_{ab} = m_{ab} = 5.5(1.4)\%$.

PACS numbers: 76.75.+i, 74.72.Bk, 74.78.Bz, 82.20.Tr

One of the fundamental questions concerning the physics of cuprate high-temperature superconductors (HTSC) is whether the electron-phonon interaction plays an essential role in these systems or not. The high values of the superconducting transition temperature T_c and the observation of only a tiny oxygen-isotope shift of T_c in optimally doped HTSC (see, e.g. [1]) were taken as important arguments to propose alternative pairing mechanisms of purely electronic origin. The conventional phonon-mediated theory of superconductivity is based on the Migdaladiabatic approximation in which the effective supercarrier mass m^* is independent of the mass M of the lattice atoms. However, if the interaction between the carriers and the lattice is strong enough, the Migdaladiabatic approximation breaks down and m^* depends on M (see, e.g. [2]). The ideal experiment to explore a possible coupling of the supercarriers to the lattice is an isotope effect study of the magnetic field penetration depth. For HTSC, which are superconductors in the clean limit, the in-plane penetration depth λ_{ab} obeys the relation:

$$\lambda_{ab}^2 = \frac{c}{4\pi n_s m_{ab}}; \quad (1)$$

where n_s is the superconducting charge carrier density and m_{ab} is the in-plane effective mass of the charge carriers. Note that there is no such simple relation for T_c . Since n_s was found to be predominantly isotope independent [3, 4, 5, 6, 7, 8, 9], isotope effect experiments on the penetration depth turned out to be a unique tool to investigate unconventional lattice effects in HTSC. Previous oxygen-isotope effect studies of the penetration depth in $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ [3], $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ [4, 5, 6], $\text{Bi}_{1.6}\text{Pb}_{0.4}\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_{10+x}$ [7] and $\text{Y}_{1-x}\text{Pr}_x\text{Ba}_2\text{Cu}_3\text{O}_{7-x}$ [9] showed indeed a pronounced oxygen isotope dependence of the supercarrier mass. In all these experiments, however, the penetra-

tion depth was determined indirectly from magnetization measurements [3], the Meissner fraction [4, 5], magnetic torque [6], and muon-spin rotation (SR) experiments [9]. The expression "indirectly" means that all these techniques require a model to extract the absolute value of the penetration depth. In contrast, measurements of the exponential field decay $B(z) = B_0 \exp(-z/\lambda_{ab})$ in the Meissner state allow to determine λ_{ab} in a direct way. Recently, such a direct measurement of the in-plane magnetic penetration depth λ_{ab} in a thin $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ film was performed [10] at the Paul Scherrer Institute (PSI, Switzerland) by using the novel low-energy SR (LE SR) technique [11]. In this experiment the muon implantation depth was controlled by the variation of the incoming muon energy and the magnitude of the field was monitored by the muon spin precession frequency, alike in standard SR.

In this Letter, we report on the oxygen-isotope ($^{16}\text{O}/^{18}\text{O}$) effect (OE) on the in-plane magnetic field penetration depth in a high-quality $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ film near optimal doping measured directly by LE SR. The experiments revealed that in the Meissner state the magnetic field $B(z)$ in the ^{16}O substituted sample decreases stronger with distance z than in the ^{18}O substituted sample, clearly demonstrating that $\lambda_{ab}^{16} < \lambda_{ab}^{18}$.

The samples used for the LE SR experiments were high quality $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ film with an area of $2 \times 3 \text{ cm}^2$ and a thickness of 600 nm supplied by Theva [12]. The

films were grown by thermal coevaporation of the constituents onto a single-crystal barium titanate substrate. The oxygen-isotope exchange was performed by annealing the samples in $^{18}\text{O}_2$ gas. In order to ensure that the ^{16}O and ^{18}O substituted samples are subject of the same thermal history, the annealing (in $^{16}\text{O}_2$ and $^{18}\text{O}_2$) was performed simultaneously. The exchange process was

carried out at 600°C during 25 h, followed by slow cooling (20°C/h) in order to oxidize them completely. The fraction of the ^{18}O content in the film was estimated to be 95%, corresponding to the ^{18}O content in the initial gas used for the annealing process. The oxygen content (7%) and the quality of the films were estimated from magnetization measurements. The observed T_c onsets are $^{16}\text{T}_c = 89.3(1)$ K

and $^{18}\text{T}_c = 89.1(1)$ K. The transition widths are ~ 0.9 K for both samples. A comparison of the T_c 's with the known experimental T_c vs. curves for ^{16}O and ^{18}O substituted $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ [13] yields $x = 0.150(5)$ for both films. While indicates that the samples are slightly underdoped the narrow transition shows that the oxygen distribution over the film is quite homogeneous. The results of the OIE on T_c are summarized in Table I.

TABLE I: Summary of the OIE results for $\text{YBa}_2\text{Cu}_3\text{O}_7$ extracted from the experimental data (see text for an explanation).

Method	Sample	$^{16}\text{T}_c$ (K)	$^{18}\text{T}_c$ (K)	$T_c = T_c$ (%)	$\Delta T_c = \Delta T_c$ (%)	$\Delta T_c = \Delta T_c$ (%)
LE SR	Thin film	89.3(1)	89.1(1)	-0.22(16)	2.8(7)	5.5(1.4)
Magnetization	Fine powder	91.66(3)	91.42(3)	-0.26(5)	3.0(1.1)	6.0(2.2)
		91.71(3) ^a	91.45(1) ^b	-0.28(5)	2.4(1.0)	4.8(2.0)

^a results for the back-exchange ($^{18}\text{O} \rightarrow ^{16}\text{O}$) sample

^b results for the back-exchange ($^{16}\text{O} \rightarrow ^{18}\text{O}$) sample

The transverse-field LE SR experiments were performed on the E3 muon beam line at PSI. A weak external magnetic field $B_0 = 9.2$ mT was applied parallel to the sample surface after the sample was cooled in zero magnetic field from a temperature above T_c to 4 K. Spin-polarized muons were implanted at a depth ranging from 20-150 nm beneath the surface of the film by varying the energy of the incident muons from 3 to 30 keV. For each implantation energy a time-differential SR spectrum was measured. The muon implantation depth profile $n(z)$ for the given implantation energy was calculated using a Monte-Carlo code TRIM.SP [14]. The reliability of the calculated $n(z)$ was crosschecked by previous LE SR experiments on thin metal layers [15].

The experimental data were analyzed in the following way. For each implantation energy the average value of the magnetic field B and correspondent average value of the stopping distance z were extracted. The value of B was taken from the fit of the time evolution of the muon-spin polarization spectrum by using the Gaussian relaxation function:

$$a(t) = a_0 \exp(-t^2/2) \cos(Bt + \phi); \quad (2)$$

where a_0 is the initial asymmetry, Γ is the Gaussian relaxation rate, and $\gamma = 2 \cdot 135 \text{ MHz/T}$ is the gyromagnetic ratio of the muon. Note that at our level of statistics ($\sim 5 \cdot 10^5$ events per spectrum) the fit of experimental data with Eq. (2) satisfies the χ^2 criterion. The value of z was taken as the first moment of the simulated $n(z)$ distribution. Results of this analysis for the ^{16}O and ^{18}O substituted $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ films are shown in Fig. 1.

The data points for the ^{18}O film are systematically higher than those for the ^{16}O film, showing that $\Delta T_c^{16} < \Delta T_c^{18}$. The solid lines represent a fit to the B data by the function:

$$B(z) = B_0 \frac{\cosh[(t - z)/\Delta T_c]}{\cosh(t/\Delta T_c)}; \quad (3)$$

This is the form of the classical exponential field decay in the Meissner state $B(z) = B_0 \exp(-z/\Delta T_c)$, modified for a film with thickness $2t$ with flux penetrating from both sides. The value of z was corrected by $z_0 = 8$ nm, corresponding to a "dead layer", which mainly arises from the surface roughness of the film [10]. Fits with Eq. (3) to the extracted $^{16}\text{B}(z)$ and $^{18}\text{B}(z)$ yield $\Delta T_c^{16}(4\text{K}) = 151.85(75)$ nm and $\Delta T_c^{18}(4\text{K}) = 155.82(68)$ nm. Taking into account a ^{18}O content of 95%, the relative shift was found to be $\Delta T_c^{18} - \Delta T_c^{16} = 2.8(7)\%$ at 4 K. This value is consistent with previous results for optimally doped $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ [3] and $\text{Bi}_{1-x}\text{Pb}_{0.4}\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_{10+x}$ [7] obtained from indirect magnetization measurements. Here we would like to mention two important points: (i) The good agreement between the experimental points and theoretical curves (Eq. (3)) indicates that the films are homogeneous over the whole thickness. (ii) ΔT_c obtained from LE SR is model independent. It is extracted from the measured field profile in the Meissner state using only one fit parameter ΔT_c .

We also performed additional OIE experiments on ΔT_c based on measurements of the Meissner fraction in the $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ powder. The powder samples were

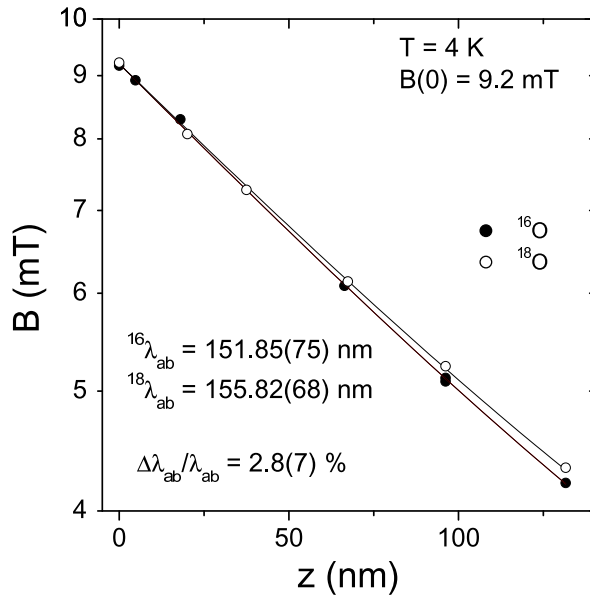


FIG. 1: Magnetic field penetration profiles $B(z)$ for a ^{16}O substituted (closed symbols) and a ^{18}O substituted (open symbols) $\text{YBa}_2\text{Cu}_3\text{O}_7$ film measured in the Meissner state at 4 K and an external field of 9.2 mT, applied parallel to the surface of the film. The data are shown for implantation energies 3, 6, 10, 16, 22, and 29 keV starting from the surface of the sample. Solid curves are best fits by Eq.(3).

ground for about 60 min and then passed through a 10 μm sieve. The oxygen exchange procedure was analogous to the one described above for the thin film samples. The ^{18}O content in the sample, as determined from the change of the sample weight after the isotope exchange, was found to be 89(2)%. The value of the Meissner fraction f was calculated from 1 mT FC SQUID magnetization measurements. The absence of weak links between grains was confirmed by the linear magnetic field dependence of the FC magnetization measured at 5 K in 0.5 mT, 1 mT, and 1.5 mT. The temperature dependence of the magnetic field penetration depth λ_e (powder average) was calculated from f under the assumption that the sample grains are spherical [16]. The in-plane penetration depth $\lambda_{ab}(T)$ (Fig. 2) was determined from the measured $\lambda_e(T)$ using the relation $\lambda_e = 1.31 \lambda_{ab}$ which holds for highly anisotropic superconductors ($\lambda_c = \lambda_{ab} > 5$) [17]. Taking into account a ^{18}O content of 89%, the relative shift at 4 K was found to be $\lambda_{ab} = \lambda_{ab} = 3.0(1.1)\%$ in a good agreement with the LEIS data (see Table I). In order to substantiate the intrinsic character of the observed OIE on λ_{ab} , we performed a back exchange experiment. For this purpose the ^{16}O sample was annealed in $^{18}\text{O}_2$ gas ($^{16}\text{O} \rightarrow ^{18}\text{O}$) and the ^{18}O sample in $^{16}\text{O}_2$ gas ($^{18}\text{O} \rightarrow ^{16}\text{O}$). The annealing procedure was analogous to the one described above for the thin film samples. The results of the back exchange experiments are also shown in Fig. 2 (cross symbols). All

the results of the OIE on T_c and λ_{ab} are summarized in Table I.

According to Eq. (1) the OIE on λ_{ab} is due to a shift in n_s and/or m_{ab} :

$$\frac{\lambda_{ab}}{\lambda_{ab}} = \frac{1}{2} \frac{m_{ab}}{m_{ab}} = \frac{1}{2} \frac{n_s}{n_s} : \quad (4)$$

Previous OIE studies in HTSC's [3, 4, 5, 6, 7, 8, 9] showed a pronounced OIE on m_{ab} with negligible OIE on n_s . In the present work we provide further evidence of this scenario from measurements of the nuclear quadrupole resonance (NQR) frequency (ν_Q) of the plane (ν_Q^{pl}) and the chain (ν_Q^{ch}) ^{63}Cu in ^{16}O and ^{18}O substituted $\text{YBa}_2\text{Cu}_3\text{O}_7$ powder samples. It is known [18, 19] that in HTSC ν_Q^{pl} and ν_Q^{ch} are very sensitive to changes in the density of mobile carriers n in the superconducting CuO_2 planes (n^{pl}) and CuO chains (n^{ch}). Both ν_Q^{pl} and ν_Q^{ch} increase with doped hole concentration roughly 20 MHz per one doped hole per Cu atom [20]. The NQR measurements of ^{63}Cu at 94 K show that within 5 kHz error bar limits the plane copper and the chain copper NQR frequencies are the same in ^{16}O and ^{18}O substituted $\text{YBa}_2\text{Cu}_3\text{O}_7$ powder samples (see Table II). This implies that by the oxygen substitution n^{pl} and n^{ch} change for less than $3 \cdot 10^{-4}$ hole per Cu atom. In optimally doped $\text{YBa}_2\text{Cu}_3\text{O}_7$ one has two plane and one chain Cu atom in the unit cell. From the NQR measurements we can thus conclude that the change of the hole number per unit cell is less than $3 \cdot 10^{-4} \cdot 10^3$ hole. Since in optimally doped $\text{YBa}_2\text{Cu}_3\text{O}_7$ there is approximately one doped hole per unit cell, the relative change of hole density $n = n$ at the oxygen exchange must be less than 10^{-3} . The NQR results are summarized in Table II. For $\text{YBa}_2\text{Cu}_3\text{O}_7$ it was shown [21] that $n_s = n$ at $T < 70$ K. Based on this observation we thus can conclude that $j_l = 2$ $n_s = n_s j < 0.05\%$ in Eq.(4). Consequently, the main contribution to the OIE on λ_{ab} has to come from the isotope dependence of the in-plane charge carrier mass m_{ab} , so that $\lambda_{ab} = \lambda_{ab}' (m_{ab} = m_{ab})/2$. With $\lambda_{ab} = \lambda_{ab} = 2.8(7)\%$ we obtain $m_{ab} = m_{ab} = 5.5(1.4)\%$ at 4 K (see Table I). This result is remarkable in spite of the fact that the observed OIE on T_c in optimally doped $\text{YBa}_2\text{Cu}_3\text{O}_7$ is rather small ($T_c = T_c = 0.26(5)\%$, see Table I).

Note that such an isotope effect on m_{ab} is not expected for a conventional weak-coupling phonon-mediated BCS superconductor. In fact in HTSC the charge carriers are strongly coupled to optical phonons, as demonstrated by measurements of the static and high-frequency dielectric constants [22], photoemission [23] and tunnelling [24] experiments. Strong interaction between the charge carriers and the lattice ions leads to a breakdown of the adiabatic Migdal approximation [2], and consequently the effective supercarrier mass m_{ab} depends on the mass of the lattice atoms. To our knowledge there are just a few

TABLE II: Results of plane and chain ^{63}Cu NQR in ^{16}O and ^{18}O substituted $\text{YBa}_2\text{Cu}_3\text{O}_7$ powder samples at 94 K (see text for an explanation).

	^{16}O		^{18}O		$q = q_c$ (%)
	q (MHz)	Linewidth (KHz)	q (MHz)	Linewidth (KHz)	
Planes	31.580 (5)	336 (10)	31.580 (5)	340 (10)	0.00 (2)
Chains	22.050 (5)	161 (5)	22.050 (5)	161 (5)	0.00 (3)

theoretical models which predict an OIE on the effective carrier mass (see e.g. Refs. 2, 25, 26, 27).

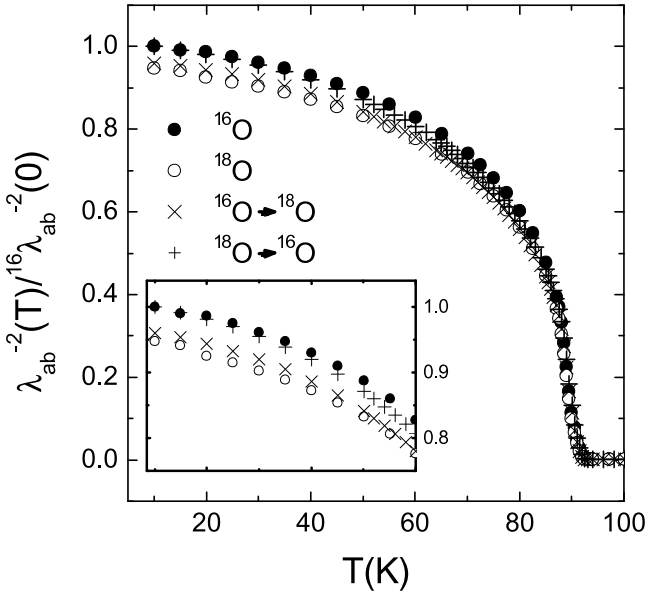


FIG. 2: Temperature dependence of $\lambda_{ab}^{-2}(T)/\lambda_{ab}^{-2}(0)$ for ^{16}O and ^{18}O substituted $\text{YBa}_2\text{Cu}_3\text{O}_7$ powder samples as obtained from low-eld SQUID magnetization measurements. The inset shows the low-temperature region between 10 K and 60 K. The reproducibility of the oxygen exchange procedure was checked by the backexchange (crosses).

In conclusion, we used LE SR to measure directly the oxygen isotope ($^{16}\text{O}/^{18}\text{O}$) effect on the in-plane magnetic field penetration depth λ_{ab} in optimally doped $\text{YBa}_2\text{Cu}_3\text{O}_7$ films. The OIE on λ_{ab} at 4 K was found to be $\lambda_{ab} = \lambda_{ab} = 2.8(7)\%$. The intrinsic character of the OIE on λ_{ab} was confirmed by back exchange experiments on the powders with low-eld SQUID magnetization measurements. It is concluded that the OIE arises mainly from the isotope dependence of the in-plane charge carrier mass m_{ab} with $m_{ab} = m_{ab} = 5.5(1.4)\%$ at 4 K. This finding implies that even in optimally doped cuprate superconductors for which only a small isotope effect on T_c is observed, the supercarriers are strongly coupled to the lattice.

This work was partly performed at the Swiss Muon Source (S S) at the Paul Scherrer Institute (Villigen, Switzerland). The authors are grateful to A. Busmann-Holder, K. A. Müller, T. Schneider, and Z. X. Shen for stimulating discussions. This work was supported by the Swiss National Science Foundation and by the NCCR program Materials with Novel Electronic Properties (MaNEP) sponsored by the Swiss National Science Foundation.

Electronic address: rustem.khasanov@psi.ch

- [1] J.P. Franck, in *Physical Properties of High Temperature Superconductors IV*, Singapore, 1994 edited by D.M. Ginsberg (World Scientific, Singapore, 1994), p. 189.
- [2] A.S. Alexandrov and N.F. Mott, *Int. J. Mod. Phys. B* 8, 2075 (1994).
- [3] G.M. Zhao and D.E. Morris, *Phys. Rev. B* 51, 16487 (1995).
- [4] G.M. Zhao et al, *Nature (London)* 385, 236 (1997).
- [5] G.M. Zhao, K. Conder, H. Keller, and K.A. Müller, *J. Phys.: Condens Matter* 10, 9055 (1998).
- [6] J. Hofer et al, *Phys. Rev. Lett.* 84, 4192 (2000).
- [7] G.M. Zhao et al, *Phys. Rev. B* 63, 220506-1 (2001).
- [8] G.M. Zhao, H. Keller, and K. Conder, *J. Phys.: Condens Matter* 13, R569 (2001).
- [9] R. Khasanov et al, *J. Phys.: Condens Matter* 15, L17 (2003).
- [10] T.J. Jackson et al, *Phys. Rev. Lett.* 84, 4958 (2000).
- [11] E. Morenzoni et al, *Phys. Rev. Lett.* 72, 2793 (1994).
- [12] www.theva.com, info@theva.com
- [13] D. Zech, Ph.D. thesis, University of Zurich, 1995.
- [14] W. Eckstein, *Computer Simulations of Ion-Solid Interactions* (Springer-Verlag, Berlin, 1992).
- [15] E. Morenzoni et al, *Nucl. Instrum. Methods B*, 192, 254 (2002).
- [16] D. Shoenberg, *Proc. R. Soc. Lond. A* 175, 49 (1940).
- [17] V.I. Fesenko, V.N. Gorbunov, and V.P. Smilga, *Physica C* 176, 551 (1991).
- [18] T. Imai et al, *Phys. Rev. Lett.* 70, 1002 (1993).
- [19] J. Karpinski et al, *Phys. Rev. B* 64, 094518 (2001).
- [20] R. Stern et al, *Phys. Rev. B* 50, 426 (1994).
- [21] A.T. Fiory et al, *Phys. Rev. Lett.* 65, 3441 (1990).
- [22] A.S. Alexandrov and A.M. Bratkovsky, *Phys. Rev. Lett.* 84, 2043 (2000).
- [23] Z.X. Shen et al, cond-mat/0108381.
- [24] Yu.G. Ponomarev et al, *Solid State Commun.* 111, 315 (1999).
- [25] D.J. Scalapino, R.T. Scalettar, and N.E. Bickers, in *Proceedings of the International Conference on Novel Mechanisms of Superconductivity*, New York, 1987, edited by S.E. Wolf and V.Z. Kresin (Plenum, New York, 1987), p. 475.
- [26] C. Grimaldi, E. Cappelluti, and L. Pietronero, *Europhys. Lett.* 42, 667 (1998).
- [27] A. Busmann-Holder and R. Mlynars, *J. Supercond.* 15, 321 (2002).