## Dipole Interaction in Triplet Superconductivity with Horizontal Line Nodes; Orientation of the Superconducting Order Parameter in $Sr_2RuO_4$

Yasumasa Hasegawa

Department of Material Science, Graduate School of Science, Himeji Institute of Technology Ako, Hyogo 678-1297, Japan

(Received June 12, 2003)

Dipole interaction in the triplet superconductivity is studied. If the Cooper pairs are formed by the electrons at  $\mathbf{r}$  and  $\mathbf{r} + (\pm \frac{a}{2}, \pm \frac{a}{2}, \pm \frac{c}{2})$  in the body centered tetragonal lattice, (in this case the line nodes run horizontally on the cylindrical Fermi surface), the dipole energy is low when the *d*-vector is perpendicular to the direction of the angular momentum of the Cooper pairs (*l*-vector). This result is in contrast with the dipole energies in the ABM state of superfluid <sup>3</sup>He, where *d*-vector is forced to be parallel or antiparallel to the *l*-vector by the dipole interaction. The recent NQR experiment in Sr<sub>2</sub>RuO<sub>4</sub> by Ishida et al. can be explained by this result.

KEYWORDS: triplet superconductivity, line nodes, Sr<sub>2</sub>RuO<sub>4</sub>, dipole interaction

The triplet superconductivity is realized in  $\operatorname{Sr}_2\operatorname{RuO}_4^{(1,2)}$  The key experiment confirming the triplet pairing is the observation of the temperatureindependent Knight shift,<sup>3)</sup> which means that the spin susceptibility is not changed in the superconducting state. It is well known that the spin susceptibility is the same as the normal-state value,  $\chi_N$ , if the *d*-vector of the spin-triplet pairing is perpendicular to the external magnetic field, while it reduces as temperature becomes low if *d* is not perpendicular to the external magnetic field;<sup>4)</sup>

$$\chi_{ij}(T) = \chi_N\left(\delta_{ij} + \frac{1 - Y(T)}{1 + \frac{1}{4}Z_0Y(T)}d_id_j\right), \quad (1)$$

where  $Z_0$  is the Landau parameter ( $Z_0 \approx -3$  in liquid <sup>3</sup>He and Sr<sub>2</sub>RuO<sub>4</sub>) and Y(T) is the Yosida function for anisotropic pairing,

$$Y(T) = \int \frac{d\Omega}{4\pi} \int_0^\infty d\epsilon_{\mathbf{k}} \frac{1}{2k_B T} \operatorname{sech}^2 \frac{E_{\mathbf{k}}}{2k_B T}, \qquad (2)$$

where

$$E_{\mathbf{k}} = \sqrt{\epsilon_{\mathbf{k}}^2 + |\mathbf{\Delta}_{\mathbf{k}}|^2}.$$
 (3)

Therefore, if there are no other mechanism, the d-vector is perpendicular to external magnetic field in order to gain the magnetic energy,

$$\Delta F_{\text{magn}} = -\frac{1}{2}\chi_{ij}(T)H_iH_j + \frac{1}{2}\chi_N H^2.$$
 (4)

Due to the small upper critical field  $(H_{c2})$  for the z direction, Knight shift in the superconducting state with H parallel to c axis had not been observed. Recently, Ishida et al.<sup>5)</sup> have succeeded to observe the Knight shift in the superconducting state of Sr<sub>2</sub>RuO<sub>4</sub> by using NQR with small external field along c axis ( $H \approx 500$ G). They observed that Knight shift does not change from the value in the normal state. This observation may be understood by assuming that d-vector can move perpendicular to the magnetic field even at the strength of 500G. In this paper we show another explanation that the dvector is in the x-y plain due to the dipole interaction. In this paper we use the Leggett's notation,<sup>4)</sup> i.e. the order parameter and the energy gap in the unitary state is given by

$$F_{\alpha,\beta}(\mathbf{r}) \equiv \langle \Psi_{\alpha}(\mathbf{R})\Psi_{\beta}(\mathbf{R}+\mathbf{r}) \rangle,$$
 (5)

$$m{F}(m{r}) = -rac{i}{2} \sum_{lpha,eta=\uparrow,\downarrow} (\sigma_2 m{\sigma})_{lphaeta} F_{lpha,eta}(m{r})$$

$$=\sum_{\boldsymbol{k}} \boldsymbol{F}_{\boldsymbol{k}} \exp(i\boldsymbol{k}\cdot\boldsymbol{r}), \tag{6}$$

$$\boldsymbol{F}_{\boldsymbol{k}} = \frac{\boldsymbol{\Delta}_{\boldsymbol{k}}}{2E_{\boldsymbol{k}}} \tanh \frac{E_{\boldsymbol{k}}}{2k_B T},\tag{7}$$

where  $\sigma_1$ ,  $\sigma_2$ ,  $\sigma_3$  are Pauli matrixes..

The spin-triplet paring has been studied comprehensively in superfluid <sup>3</sup>He. In that case the Fermi surface is spherical and the order parameter is the *p*-wave state with very small mixing of higher-wave (such as f-wave) components. The identification of the order parameter is well established by the shift of the NMR frequency and existence of the collective modes; A phase is identified as the Anderson-Brinkman-Morel (ABM) state, B phase as the Ballian-Welthermer (BW) state, and  $A_1$  phase as the non-unitary state with pairs of only one component of spins. The ABM state breaks the time-reversal symmetry and it is the so-called equal-spin paring state, i.e. the Cooper pairs consist of the parallel spins by taking the suitable direction of the quantization axis in the spin space. In the ABM state the direction of the order parameter in the vector notation (d-vector) is independent of the wave number,

$$\boldsymbol{F}_{\boldsymbol{k}}^{(ABM)} = \Psi(T)\hat{\boldsymbol{d}}\sqrt{\frac{3}{2}}\frac{k_x + ik_y}{k}.$$
(8)

and the direction of  $\hat{d}$  is controlled by the external magnetic field and the dipole interaction (and by the super-fluid current, which we do not consider in this paper).

Leggett<sup>4</sup>) has shown that the dipole interaction plays important role in the triplet pairing. Dipole interaction breaks a spin-orbit symmetry in the triplet superconductivity. The dipole interaction is given by

$$\hat{H}_{D} = \frac{1}{2} \sum_{\boldsymbol{r}, \boldsymbol{r}'} \left\{ \frac{\boldsymbol{\mu} \cdot \boldsymbol{\mu}'}{|\boldsymbol{r} - \boldsymbol{r}'|^{3}} - \frac{3\boldsymbol{\mu} \cdot (\boldsymbol{r} - \boldsymbol{r}')\boldsymbol{\mu}' \cdot (\boldsymbol{r} - \boldsymbol{r}')}{|\boldsymbol{r} - \boldsymbol{r}'|^{5}} \right\}, \quad (9)$$

where  $\mu$  and  $\mu'$  are the operator of the magnetic moment at r and r', respectively. The dipole energy per unit volume from triplet Cooper pairs is written as

$$H_D^{\text{(triplet pairs)}} = -2|\boldsymbol{\mu}|^2 \sum_{\boldsymbol{r}} \frac{|\boldsymbol{F}(\boldsymbol{r})|^2 - 3|\hat{\boldsymbol{r}} \cdot \boldsymbol{F}(\boldsymbol{r})|^2}{r^3},$$
(10)

where  $\hat{\mathbf{r}} = \mathbf{r}/r$ . For the pure *p*-wave pairing, the contribution of the Cooper pairs in the dipole energy per unit volume is given by<sup>4</sup>)

$$H_D^{(\text{pure } p \text{ wave})} = g_D(T) \int \frac{d\Omega}{4\pi} \left\{ |\hat{\boldsymbol{d}}(\hat{\boldsymbol{k}})|^2 - 3|\hat{\boldsymbol{k}} \cdot \hat{\boldsymbol{d}}(\hat{\boldsymbol{k}})|^2 \right\}, \qquad (11)$$

where  $\hat{\mathbf{k}} = \mathbf{k}/k$  is the unit vector parallel to  $\mathbf{k}$ , the integration should be done for the direction of  $\hat{\mathbf{k}}$  and

$$g_D(T) = 2\pi |\boldsymbol{\mu}|^2 |\Psi(T)|^2.$$
 (12)

For the ABM state the dipole energy depends on the angle between the d-vector and the angular momentum of the Cooper pairs (l-vector) as

$$H_D^{\text{ABM}} = g_D(T) \left( 1 - \frac{3}{5} \left( \hat{\boldsymbol{d}} \cdot \hat{\boldsymbol{l}} \right)^2 \right).$$
(13)

Since l is perpendicular to the boundary surface, d is forced to be perpendicular to the surface by the dipole force. Near the transition temperature (Ginzburg-Landau region),  $g_D(T)$  is estimated for superfluid <sup>3</sup>He as  $g_D^{(^{3}\text{He})}(T) \approx 10^{-3}(1 - \frac{T}{T_c})\text{erg/cm}^3$ . By using the estimation of orientational energy due to the anisotropy of the spin susceptibility,  $\Delta F_{\text{magn}}^{(^{3}\text{He}\text{ ABM})} \approx 5 \times 10^{-7}(1 - \frac{T}{T_c})$   $(\hat{d} \cdot H)^2 \text{ erg/(cm}^3 \text{ G}^2)$ , Leggett obtained that the orientational energy due to the dipole interaction corresponds to the energy due to the the external magnetic field of the order of 50 G.

For Sr<sub>2</sub>RuO<sub>4</sub> we use  $\mu = 9.27 \times 10^{-21}$  erg G<sup>-1</sup>,  $T_c = 1.5$ K,  $N(0) = 8.4 \times 10^{34}$  erg<sup>-1</sup> cm<sup>-3</sup> and  $\chi_N = 8.2 \times 10^{-6}$  emu cm<sup>-3</sup>, and obtain

$$\Psi(T) \approx \sqrt{\frac{9.3}{2}} N(0) k_B T_c \log \frac{1.13\omega_c}{k_B T_c} \sqrt{1 - \frac{T}{T_c}}$$
$$\approx 2 \times 10^{20} \sqrt{1 - \frac{T}{T_c}} \text{ cm}^{-3}.$$
(14)

Although the transition temperature of Sr<sub>2</sub>RuO<sub>4</sub> is about 500 times higher than the transition temperature of superfluid <sup>3</sup>He,  $\Psi(T)/\sqrt{1-\frac{T}{T_c}}$  in Sr<sub>2</sub>RuO<sub>4</sub> is about 1/5 of that in superfluid <sup>3</sup>He, since the density of states is much smaller in Sr<sub>2</sub>RuO<sub>4</sub> than in superfluid <sup>3</sup>He. We estimate  $g_D(T) \approx 2 \times 10(1-\frac{T}{T_c}) \text{ erg/cm}^3$  and  $\Delta F_{\text{magn}} \approx 4 \times 10^{-5} H^2 \left(1-\frac{T}{T_c}\right) \text{erg/(cm}^3\text{G}^2)$ . Then the magnetic field of the order of 700 G is necessary to overcome the dipole energy, if they are competing. Since both Yasumasa Hasegawa

the dipole energy  $H_D$  and the magnetic energy  $\Delta F_{\text{magn}}$ are proportional to  $|\boldsymbol{\mu}|^2$ , the difference of the magnitude of the dipole moments in Sr<sub>2</sub>RuO<sub>4</sub> and superfluid <sup>3</sup>He does not cause the difference of the typical magnetic field for competing dipole energy and magnetic energy.

Due to the topology of the Fermi surface, the *l*-vector is thought to be aligned to the *z* direction in Sr<sub>2</sub>RuO<sub>4</sub>. If the magnetic energy for  $H \parallel \hat{z}$  competes the dipole energy as in the ABM state, the above estimation seems to be inconsistent with the recent observation by Ishida et al.,<sup>5)</sup> who observed that the Knight shift does not depend on temperature when the magnetic field ( $H \approx 500$ G) is applied in the z-direction. If the above estimation is applied, the *d*-vector cannot completely determined by the external magnetic field and the spin susceptibility (and the Knight shift) should be decreased as temperature becomes lower than  $T_c$ .

We show that the dipole energy makes the d-vector not parallel to l but perpendicular to l in the case of the order parameter with horizontal line nodes,<sup>6–8)</sup>

$$\boldsymbol{F}_{\boldsymbol{k}}^{\text{(horizontal line nodes)}} = \Psi(T)\hat{\boldsymbol{d}} \\ \times \left(\sin\frac{ak_x}{2}\cos\frac{ak_y}{2} + i\cos\frac{ak_x}{2}\sin\frac{ak_y}{2}\right)\cos\frac{ck_z}{2}, \quad (15)$$

which is thought to be realized in  $\text{Sr}_2\text{RuO}_4$ ,<sup>6)</sup> where *a* and *c* are the lattice constants. This order parameter is consistent with the  $D_{4h}$  symmetry of the point group and can explain most of the experiments such as existence of the line nodes in the energy gap,<sup>9,10)</sup> breaking of the time reversal symmetry,<sup>11)</sup> and very small angular dependence of the thermal conductivity.<sup>12,13)</sup> If the spin-orbit coupling were strong,  $\hat{d}$  would be aligned to the  $\hat{z}$  direction from the point of view in the lattice symmetry. If the spin-orbit coupling is small and can be neglected, however, the direction of the *d*-vector should be controlled by the external magnetic field and the dipole interaction. In this paper we neglect the spin-orbit coupling for the driving force for the orientation of the *d*-vector.

Since the order parameter given in Eq. (15) correspond to the pair at  $\mathbf{r}$  and  $\mathbf{r} + (\pm \frac{a}{2}, \pm \frac{a}{2}, \pm \frac{c}{2})$ , the dipole energy can be easily calculated from Eq. (10). By using

$$\boldsymbol{F}^{\text{(horizontal line nodes)}}(r) = \frac{1}{8}\Psi(T)\hat{\boldsymbol{d}}f(\boldsymbol{r}) \qquad (16)$$

where

$$f(\mathbf{r}) = \begin{cases} (1+i) & \text{if } \mathbf{r} = (\frac{a}{2}, \frac{a}{2}, \pm \frac{c}{2}) \\ (-1+i) & \text{if } \mathbf{r} = (-\frac{a}{2}, \frac{a}{2}, \pm \frac{c}{2}) \\ (-1-i) & \text{if } \mathbf{r} = (-\frac{a}{2}, -\frac{a}{2}, \pm \frac{c}{2}) \\ (1-i) & \text{if } \mathbf{r} = (\frac{a}{2}, -\frac{a}{2}, \pm \frac{c}{2}) \\ 0 & \text{otherwise} \end{cases}$$
(17)

we get

$$H_D^{\text{(horizontal line nodes)}} = -\frac{1}{\pi}g_D(T)$$
$$\times \frac{v_0}{4r_0^3} \left(1 - \frac{3}{r_0^2} \left[\left(\frac{a}{2}\right)^2 \sin^2\theta + \left(\frac{c}{2}\right)^2 \cos^2\theta\right]\right) \quad (18)$$

where  $\theta = \cos^{-1}(\hat{\boldsymbol{d}} \cdot \hat{\boldsymbol{z}}), v_0 = \frac{1}{2}a^2c$  and  $r_0 = \sqrt{2\left(\frac{a}{2}\right)^2 + \left(\frac{c}{2}\right)^2}.$ (19)

Since c > a in Sr<sub>2</sub>RuO<sub>4</sub> (a = 0.387nm and c = 1.274nm),<sup>1)</sup> the dipole energy is small when the *d*-vector is in the x - y plane ( $\theta = \frac{\pi}{2}$ ). When magnetic field is applied in the *z* direction the *d*-vector does not change the direction. As a result, spin susceptibility is the same as that in the normal state. When magnetic field is applied in the *x* direction, the *d*-vector is aligned to the *y* direction. The spin susceptibility in this case is also the same as that in the normal state.

On the other hand if the Cooper pair is formed in the nearest sites in the x - y plane, we get

$$\boldsymbol{F}_{\boldsymbol{k}}^{(\text{nodeless})} = \Psi \hat{\boldsymbol{d}} \left( \sin a k_x + i \sin k_y \right), \qquad (20)$$

and

$$H_D^{\text{(nodeless)}} = -\frac{1}{\pi} g_D(T) \frac{v_0}{2a_0^3} \left( 1 - \frac{3}{2} \sin^2 \theta \right)$$
(21)

In this case the dipole energy is minimized when d-vector is parallel to  $\hat{z}$ , as in the ABM state. Then the magnetic field smaller than the critical value ( $\approx 700$ G estimated in Sr<sub>2</sub>RuO<sub>4</sub>) cannot rotate the d vector and the spin susceptibility becomes small as temperature becomes low.

The above result can be understood as follows; along the *d*-vector the Cooper pair is made of antiparallel spins,  $(|\uparrow\downarrow\rangle + |\downarrow\uparrow\rangle)/\sqrt{2}$ . For the pair of spins at  $\boldsymbol{r}$  and  $\boldsymbol{r} + (a, 0, 0)$ , a pair of the up and the down spins has lower energy than a pair of spins parallel to +x and -x (Fig. 1, a1 and a2). In the body-centered tetragonal lattice a pair of the up spin at  $\boldsymbol{r}$  and the down spins at  $\boldsymbol{r} + (\frac{a}{2}, \frac{a}{2}, \frac{c}{2})$ has higher energy than a pair of spins +x at  $\boldsymbol{r}$  and -xat  $\boldsymbol{r} + (\frac{a}{2}, \frac{a}{2}, \frac{c}{2})$ , when c > a (Fig. 1, b1 and b2).

The direction of the d-vector can be observed by the Josephson effect between triplet and singlet superconductors.<sup>14,15</sup>) The Josephson current between triplet and singlet superconductors is possible due to the spin-orbit coupling in the triplet superconductivity, if the conservation of the total (spin and orbital) angular momentum,  $L_{\perp} = -S_{\perp} = \pm \hbar$ , or the selection rule,  $\langle \boldsymbol{n} \times \boldsymbol{k} \cdot \boldsymbol{d}(\boldsymbol{k}) \rangle \neq 0$ , is satisfied, where  $\boldsymbol{n}$  is the surface normal vector and  $L_{\perp}$  $(= \boldsymbol{L} \cdot \boldsymbol{n})$  and  $S_{\perp}$   $(= \boldsymbol{S} \cdot \boldsymbol{n})$  are the normal components of the total angular momentum and the total spin of the Cooper pair, respectively. Note that if  $l \parallel \hat{z}$ , the average values of the x and y components of the Cooper-pair's total angular momentum are zero, but Josephson current in the x-y plane is possible, since this state is the superposition of  $L_x = \hbar$  and  $L_x = -\hbar$ . Jin et al.<sup>16</sup> have observed the Josephson current between  $Sr_2RuO_4$  and s-wave superconductor (In) in the in-plane direction but not along the c-axis. This result is consistent with the state that the d-vector is along the c-axis. However, we should be careful to conclude the direction of the d-vector from the Josephson junction experiments, because the Josephson current may be reduced by the anisotropy of the coherence length or the pair-breaking effect at the boundary. The observation of the Josephson current along the caxis is reported,  $^{17)}$  where the authors pointed out the

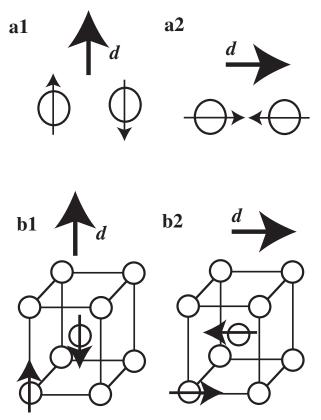


Fig. 1. Dipole interaction between electrons on the lattice. Since the *d*-component of the total magnetic moment of the Cooper pair is zero, the dipole energy for the Cooper pair in the plain perpendicular to the *d*-vector (*a*1) is lower then that for the Cooper pair along the *d*-vector (*a*2). For the body centered tetragonal lattice, the Cooper pair with  $d \parallel \hat{z}$  (*b*1) has higher dipole energy than the Cooper pair with  $d \perp \hat{z}$  (*b*2), when c > a.

possibility of the Josephson current due to the existence of the steps or Ru lamellas.

The Fermi surface of  $Sr_2RuO_4$  consists of three cylindrical sheets. If the energy gap has horizontal nodes in some sheet(s) of the Fermi surface and it has no nodes on the other sheet(s) of the Fermi surface,<sup>8, 18)</sup> dipole force to align the *d*-vector competes each other. Then the net dipole force to orient the *d*-vector may be small.

In conclusion, the *d*-vector is shown to be perpendicular to the *l*-vector due to the dipole interaction if the order parameter is in the form given in Eq. (15), which has horizontal line nodes of the energy gap.<sup>6)</sup> Since the *l*-vector is thought to be aligned to the *z* direction in  $Sr_2RuO_4$ , the *d* vector can locate in the *x-y* plane. Therefore the magnetic energy does not conflict with the dipole energy, and if the spin-orbit coupling can be neglected, the spin susceptibility does not depend on temperature regardless of the direction of the magnetic field, which is consistent with the temperature-independent Knight shift.<sup>3,5)</sup>

The author thanks K. Ishida for showing the experimental data prior to publication and valuable discussion. He also thanks A. Sumiyama, Y. Kohori, Y. Takahashi and H. Nakano for discussions.

- Y. Maeno, H. Hashimoto, K. Yoshida, S. Nishizaki, T. Fujita, J.G. Bednorz and F. Lichitenberg: Nature (London) **372** (1994) 532.
- 2) A.P. Mackenzie and Y. Maeno: Rev. Mod. Phys. 75 (2003) 657.
- K. Ishida, H. Mukuda, Y. Kitaoka, K. Asayama, Z. Q. Mao, Y. Mori and Y. Maeno: Nature (London) **396** (1998) 658.
- 4) A.J. Leggett: Rev. Mod. Phys. 47 (1975) 331.
- 5) K. Ishida et al. unpublished.
- Y. Hasegawa, K. Machida and M. Ozaki: J. Phys. Soc. Jpn. 69 (2000) 336.
- Y. Hasegawa and M. Yakiyama, J. Phys. Soc. Jpn. (2003), cond-mat/0303238.
- M. E. Zhitomirsky and T. M. Rice: Phys. Rev. Lett. 87 (2001) 057001.
- S. NishiZaki et al., S. NishiZaki, Y. Maeno and Z. Q. Mao: J. Phys. Soc. Jpn. 69 (2000) 572.
- 10) K. Ishida, H. Mukuda, Y. Kitaoka, Z. Q. Mao, Y. Mori, and Y. Maeno Phys. Rev. Lett. 84 (2000) 5387.

- 11) G. M. Luke, Y. Fudamoto, K. M. Kojima, M. I. Larkin, J. Merrin, B. Nachumi, Y. J. Uemura, Y. Maeno, Z. Q. Mao, Y. Mori, H. Nakamura and M. Sigrist: Nature (London) **394** (1998) 558.
- 12) M. A. Tanatar, M. Suzuki, S. Nagai, Z. Q. Mao, Y. Maeno and T. Ishiguro: Phys. Rev. Lett. 86 (2001) 2649.
- 13) K. Izawa, H. Takahashi, H. Yamaguchi, Y. Matsuda, M. Suzuki, T. Sasaki, T. Fukase, Y. Yoshida, R. Settai and Y. Onuki: Phys. Rev. Lett. 86 (2001) 2653.
- 14) V.B. Geshkenbein and A.I. Larkin: JETP Lett. 43 (1986) 395.
- 15) Y. Hasegawa: J. Phys. Soc. Jpn. 67 (1998) 3699.
- 16) R. Jin, Y. Liu, Z.Q. Mao and Y. Maeno, Europhys. Lett. 51 (2000) 341.
- 17) A. Sumiyama, T. Endo, Y. Oda, Y. Yoshida, A. Mukai, A. Ono and Y. Onuki: Physica C 367 (2002) 129.
- 18) M. Yakiyama and Y. Hasegawa: Phys. Rev. B 67 (2003) 014512.