

Structural transitions in aqueous suspensions of natural graphite

Vasily Moraru, Nikolai Lebovka and Dmitrii Shevchenko
*Biocolloid Chemistry Institute named after F. D. Ovcharenko,
 NASU, bulv. Vernadskogo, 42, 03142, Kyiv, Ukraine*

The electric conductivity σ and plastic viscosity η of aqueous suspensions at different volume fraction of graphite φ and concentration of nonionic surfactant (Triton X-305) are investigated. The correlations between conductivity and rheological properties are discussed. A model of structural transitions in aqueous graphite suspensions is discussed. Two structural transitions, corresponding to changes in electrical and rheomechanical properties, are identified as percolation and sol-gel transitions, respectively. An unusual initial decrease of the bulk electrical conductivity with graphite volume fraction φ increase was observed in surfactant solution. This fact is explained as a result of isolating coating formation around the graphite particles.

Keywords: Aqueous graphite suspensions, Electric conductivity; Viscosity; Percolation transition; Sol-Gel transition

I. INTRODUCTION

Colloidal suspensions of carbon have many industrial applications and are used for production of conducting composite materials, liquid electrophotographic toners, pigments in inks and paints, rubber reinforcing and fillers, electrodes and conducting films [1-7]. The highly dispersed carbon materials (natural graphite, carbon black etc.) display a strong tendency to agglomerate and form highly disordered ramified aggregates with the fractal structures [8-10]. Recently, the properties of these systems are intensively studied experimentally, but here remain many problems in understanding of correlations between morphology of the aggregates and physical properties. Especially, we may note the practically important problem related with electrical percolation behavior of the carbon-based composite materials [11-15].

In this work we studied the structural transitions in the aqueous suspensions of natural graphite in the presence of nonionic surfactant by means of electrical conductivity and viscosity measurements. Because of high hydrophobicity of graphite, its particles tend to aggregate in water suspensions and to form a gel phase, but addition of a surfactant allows to achieve fine adjustment of aggregation processes through changes in surfactant concentration.

II. MATERIALS AND METHODS

A. Materials

The natural graphite (product of Zavalie Plant, Ukraine, carbon content 99.5%, type C-0) was chosen for investigation. An example of the transmission electron micrograph of the natural graphite sample is presented in Fig. 1. The electron microscopy data confirm the presence of particles with plate-like geometry. The granulometric composition of dispersions was studied by laser diffraction microanalyzer Analysette-22 (Fritsch). The distribution curves cover the size range 1-10 μm and have a narrow maximum at $\approx 5 \mu\text{m}$ (Fig.2).

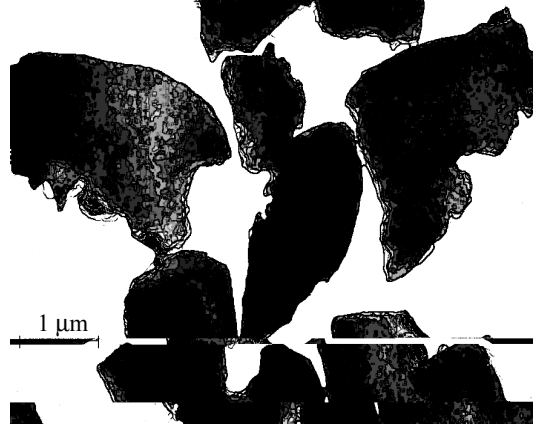


FIG. 1: Transmission electron micrograph of the natural graphite sample.

Table. Some properties of the natural graphite

Property	Value
Diameter of particle, d (μm)	≈ 5
Plate thickness, h (μm)	0.1-0.5
Particle aspect ratio, d/h	10-50
Specific surface area, S (m^2/g)	20
Exchange capacity, q (meq/g)	0.05
Surface charge density (pH=10), σ_s (C/m^2)	0.12
Specific heat wetting, w (J/m^2)	0.09

The Table presents the main properties of our sample of natural graphite. Here, the value of the specific surface area S was determined from the water vapor adsorption isotherms using the vacuum microbalance apparatus and from the dye (methylene blue) adsorption isotherms in water solutions. The exchange capacity, q and the surface charge σ_s were determined using the conductometric and potentiometric titration of dispersions by 0.1 M KOH solution and 0.2 M KCl solution. The heat of wetting w was determined with the help of DAK-1M microcalorimeter (Pribor, Moscow).

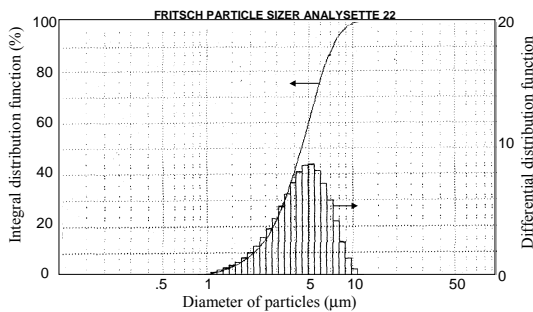


FIG. 2: Integral and differential distribution functions of particle diameters d for the natural graphite.

We used Triton X-305, $\text{CH}_3\text{-C}(\text{CH}_3)_2\text{-CH}_2\text{-C}(\text{CH}_3)_2\text{-C}_6\text{H}_5\text{-O}(\text{CH}_2\text{CH}_2\text{O})_n\text{H}$, where $n=30$, as a non-ionic surfactant. The background electrolyte concentration of 0.01M KCl was present in all the cases. The stated values of pH and ionic strength of dispersions were adjusted by the combination of 0.01 M HCl, KCl and KOH solutions. The water, used in this study, was double distilled and had conductivity 5×10^{-6} S/cm at 20C. All the reagents were of analytical grade. The suspensions were prepared by sonicating (UZDN-2T sonifier, Russia) during 1 minute. The sonifier was operated at a frequency of 22 kHz, with the output power 150 w. Then, after cooling, the sample was placed into the thermo-stabilized cells for measurements of conductivity and rheological parameters.

B. Experimental methods

The electrical conductivity, zeta potential and rheological parameters of natural graphite in aqueous suspensions were measured at fixed temperature $T=293$ K.

1. Electrical conductivity

The electrical conductivity measurements were made using -5021 (Tochelectropribor, Kiev, Ukraine) at the frequency of $f=1$ kHz in a cell with platinum electrodes with the surface area of 1 cm^2

2. Zeta potential

The zeta potential measurements were made using microelectrophoresis technique at the electric field strength $E = 5\text{-}6$ V/cm and the volume fraction of graphite particles $\varphi \sim 10^{-4}$. The average of, at least, three measurements for each sample was recorded. No corrections were made for polarization and relaxation effects of the electrical double layer, as far as in our case the condition $d/\lambda \geq 100$ (where d is the average particle diameter and λ is Debye screening length) is fulfilled [16].

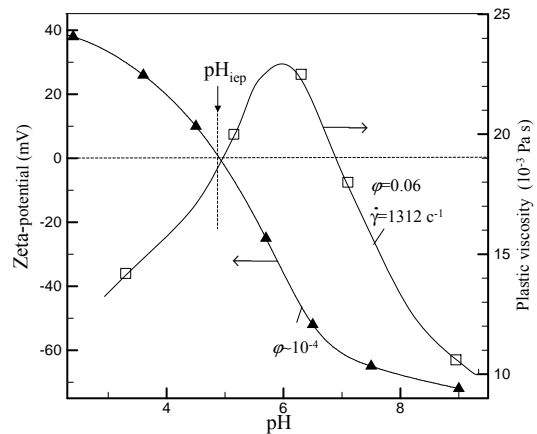


FIG. 3: Electrokinetic zeta-potential and plastic viscosity η as a function of pH.

3. Rheological behavior

The viscosity measurements were made using the coaxial cylinder viscometer of Rheotest-2 model (Germany) for shear rates $\dot{\gamma}$ from 0 to 1312 s^{-1} .

4. Influence of pH

The pH values of suspensions were measured using the pH meter with glass electrodes EV-74 (Electrotochpribor, Kiev). It should be noted that pH of is an important parameter, which controls the structure of graphite suspension. The graphite surface displayed weak π -basic properties owing to the presence of π -electrons, delocalized over the entire macroaromatic skeleton. From the other side, the graphite surface displays acidic properties owing to the presence of small quantity of the chemically grafted oxygen-containing groups. As a result, the natural graphite always displays properties of a typical ampholyte. The isoelectric point, where the zeta potential is zero, $\zeta=0$, was found to be at $\text{pH}_{iep} \approx 4.5\text{-}5.5$ (Fig.3). So, the graphite colloidal particles have a positive charge at $\text{pH} < \text{pH}_{iep}$, and a negative charge at $\text{pH} > \text{pH}_{iep}$. This strong dependence of the acid-basic and electrical surface properties of graphite from pH values results also in the structural changes of graphite suspensions with pH. As an example, we may refer to the fact that the plastic viscosity of graphite suspension η may be an extreme function of pH (Fig.3). In this work, all the investigations were done at the fixed value of $\text{pH} = 6.3$.

III. RESULTS AND DISCUSSION

Electrical conductivity and rheological properties of suspensions are very sensitive to their structural organization, which is controlled by the balance of interparticle

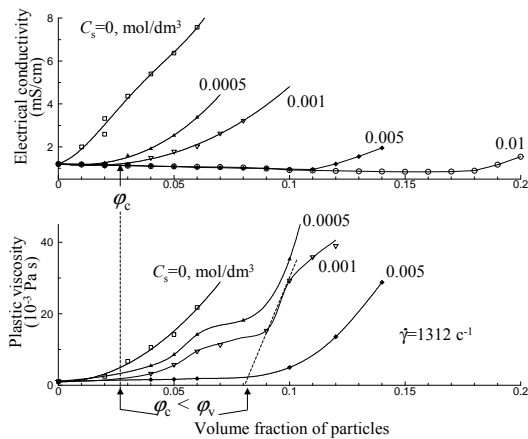


FIG. 4: Plots of the electrical conductivity σ and plastic viscosity η of suspensions versus volume fraction of graphite particles φ at different Triton X-305 concentrations C_s .

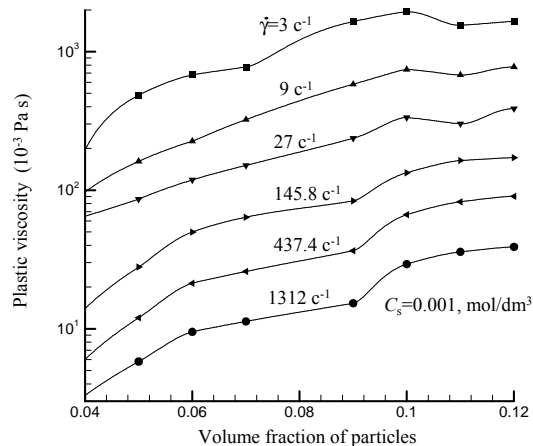


FIG. 5: Plots of the plastic viscosity of suspensions η versus volume fraction of the natural graphite particles φ measured at different $\dot{\gamma}$.

forces [17]. An important information about the structural transitions and mechanisms of particle aggregation in water suspensions may be obtained from analysis of experimental data on these characteristics. Figure 4 shows electrical conductivity σ and plastic viscosity η , measured at shear rate $\dot{\gamma} = 1312$ s⁻¹ versus volume fraction of the natural graphite φ in water at different concentrations C_s of Triton X-305. In the absence of any surfactant, the electrical conductivity σ and viscosity η increase sharply even at very small volume fractions $\varphi \approx 0.01 - 0.02$ (1-2 vol.%). It reflects existence of a strong aggregation between the carbon particles and formation of a highly interconnected network between the particles of anisotropic geometry [18-20]. In the presence of a surfactant, the fluidifying effect is observed, It results from decrease of the aggregation of particles. The surfactant molecules form the stabilizing layers on the surfaces of the graphite.

Because of a high electrical contrast of these systems

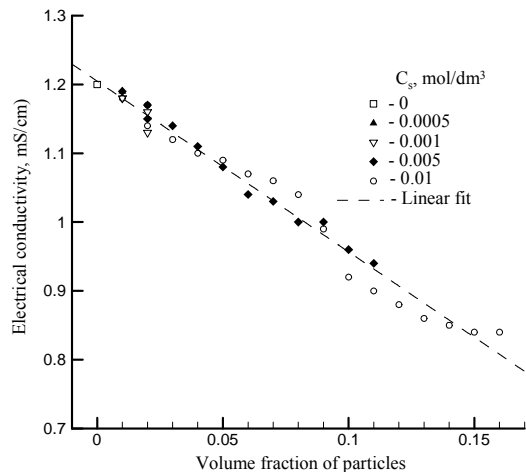


FIG. 6: Initial linear decrease of the electrical conductivity of suspensions σ with increase of the volume fraction of natural graphite particles φ .

(specific conductivity of graphite particles is of an order $\sigma \approx 10^3 - 10^5$ S/cm [21] and is very high as compared with conductivity of water solutions, $\sigma \approx 10^{-3}$ S/cm) the typical percolation behavior of conductivity σ is observed [22]. A considerable increase of the conductivity of suspensions begins only after the certain threshold value of $\varphi = \varphi_c$ is exceeded (Fig. 4). The similar behavior was observed for other highly conductive carbon-based composites [8,10,11,13,15,18,19]. The viscosity of suspensions continuously decreases with volume fraction φ increase. However, as rule, the observed η versus φ dependencies are step-like (Fig.4). The viscosity begins to increase sharply only at concentrations $\varphi > \varphi_v$, and φ_v value is noticeably high than value of φ . As surfactant concentration C_s increases, both threshold values, φ_c and φ_v , also increase. For example, in Fig. 4, two concentrations of φ and φ_v are shown for the case when $C_s = 0.001$ mol/dm³. The similar step-like behavior $\eta(\varphi)$ was observed also for other values of $\dot{\gamma}$ (Fig. 5). In the region where φ do not exceed the threshold value φ_c , the initial linear decrease of the bulk electrical conductivity σ with φ increase is observed (Fig. 6)

$$\sigma(\varphi) = \sigma_i = \sigma(0)(1 - \alpha\varphi), \quad \text{at } \varphi \leq \varphi_c. \quad (1)$$

Here, $\sigma(0) = 1.23$ mS/cm is the conductivity of the 0.01 N aqueous solution of KCl at $T = 293$ K and $\alpha = 2.05$ is the fitting parameter.

This behavior is rather unusual, as far as electrical conductivity of the system decreases with increasing of the ratio of more conductive component. In fact, Maxwell obtained first the Eq. (1) for dilute dispersions of isolating spherical inclusions in a conductive host matrix [23]. It is valid for $\varphi < 0.1$ and the coefficient α is equal to 1.5.

The initial decrease of electrical conductivity may be interpreted in view of the low effective conductivity of

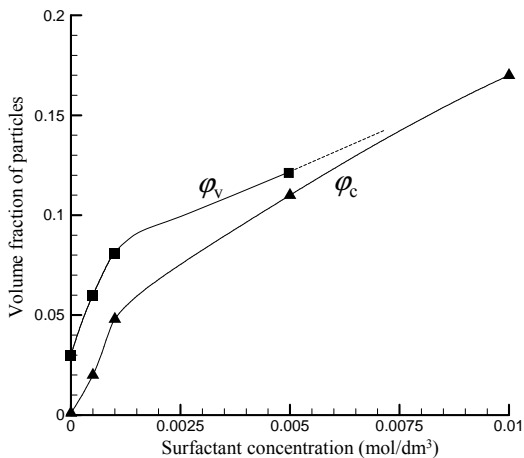


FIG. 7: Critical volume fractions of particles φ_c and φ_v (estimated from measurements of electrical conductivity and viscosity, respectively) versus surfactant concentration C_s .

carbon particles in the presence of surfactant as compared with the water solution matrix. The larger slope $\alpha = 2.05$ as compared with Maxwell approximation may be explained by existence of the particle size distribution and anisotropy of the particle geometry. When concentration of the particles exceeds a certain threshold value ($\varphi \geq \varphi_c$), which depends on the surfactant content, a usual scaling percolation law is observed

$$\sigma = \sigma_i + \beta(\varphi - \varphi_c)^t, \quad \text{at} \quad \varphi > \varphi_c, \quad (2)$$

where β is a parameter and t is the critical index of conductivity.

The value of the critical conductivity index t was estimated from the best fits to data and it was found to be close to $t \approx 2.0$, which corresponds to a classical random percolation case [22]. It means that long-range correlations, able to change universality of a short range random percolation, are absent at the percolation threshold. It should be noted that measured values of t varied within a wide interval for composites of carbon-black [15].

The concentrations of the first and second structural transitions φ_c and φ_v versus surfactant concentration C_s are presented in Fig. 7. As surfactant concentration C_s increases, the threshold values of φ_c and φ_v also increase. At high enough surfactant concentration, the two-step form of the η versus φ curve disappears, and here $\varphi \approx \varphi_v$.

The complex behavior observed for electrical conductivity σ and plastic viscosity η evidences existence of several structure levels in suspensions and reflects specific features of coagulation and thixotropic properties of these suspensions. The three-dimensional network structures of disperse systems may display different topological properties, depending on the volume fraction of the solid phase, geometry of particles and presence of the chemical additives and structure-forming agents [24]. In concentrated suspensions, different structures may arise, such as periodical colloid structures and random statisti-

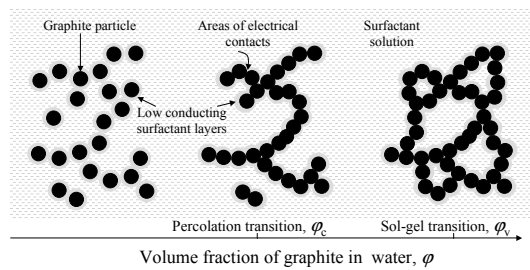


FIG. 8: Illustration of a model of structural transitions in aqueous graphite suspensions. Black circles represent the carbon particles and gray shells represent the low-conducting surfactant layers.

cal networks formed from chains of aggregated particles, or compact aggregates linked by coagulation chains.

The structural transitions at φ_c and φ_v correspond to changes in electrical (conductivity σ) and rheomechanical (viscosity η) properties of a system, and we believe that they may be identified as percolation and sol-gel transitions, respectively.

An illustration of our model of structural transitions in aqueous suspensions of graphite is presented in Fig. 8. At low concentration of solid phase, the long-range type mechanism of structure formation prevails. We can assume that surfactant molecules form nonconductive films on the hydrophobic surface and stabilize a graphite suspension through modification of the hydrophilicity and zeta potentials of colloidal particles. These films have low conductivity, and the coated graphite particles behave effectively as nonconductive. With φ increase at given C_s the isolation of particles destroys. At the critical concentration $\varphi = \varphi_c$ an infinite percolation cluster of the conducting graphite particles appears for the first time. The critical concentration φ_v corresponds to the critical concentration of the structure formation. At this point $\varphi = \varphi_v$, an infinite cluster with non-local elastic properties appears for the first time, and this point may be identified as the sol-gel transition point.

IV. CONCLUSIONS

Experimental data on electric conductivity and plastic viscosity of aqueous natural graphite suspensions as function of solid volume fraction and nonionic surfactant concentration were presented. Electric conductivity and plastic viscosity displays different sensitivity to structural transitions in suspensions. Two different concentration points, corresponding to changes in electrical and rheomechanical properties, were identified as percolation and sol-gel transitions, respectively. We obtained the critical index value as close to $t \approx 2.0$, which corresponds a classical random percolation case. The surfactant molecules may form isolating coating around particles of conductive graphite, and it results in initial decrease of suspension conductivity with increase of solid

content.

Acknowledgements

This material is based upon work partially supported by the National Academy of Science of Ukraine under

the program “Nanosystems, Nanomaterials and Nanotechnologies” and Grants No. 2.16.1.4 (0102V007058) and 2.16.2.1(0102V007048). Authors also thank Dr. N.S. Pivovarova for her help with preparation of the manuscript.

-
- [1] J. Read, D. Foster, J. Wolfenstine, W. Behl, SnO₂-carbon composites for lithium-ion battery anodes, *J. Power Sources* 96 (2001) 277-281.
- [2] Christopher Joseph, Christopher Viney, Electrical resistance curing of carbon-fibre/epoxy composites, *Composites Science and Technology* 60 (2000) 315-319.
- [3] Charles B. Duke, Jaan Noolandi, and Tracy Thieret, The surface science of xerography, *Surface Science* 500 (1-3) (2002) 1005-1023
- [4] G.Raos, G. Allegra, L. Asseconi, C. Croci, Rigid filler particles in a rubber matrix: effective force constants by multipolar expansion, *Computational and Theoretical Polymer Science* 10 (2000) 149-157.
- [5] Matilde Luque, Angel Rios, Miguel Valcarcel, A poly(vinyl chloride) graphite composite electrode for flow injection amperometric determination of antioxidants, *Analytica Chimica Acta* 395 (1999) 217-223.
- [6] M. Olteanu, S. Peretz, G. Popescu, Stabilization of solid/liquid suspensions, *Colloids and Surfaces A80* (2-3) (1993) 127-130.
- [7] N. Kovtyukhova, E. Bazaneva, A. Senkevich, Ultrathin supported graphite oxide and carbon films, *Carbon* 36 (5-6) (1998) 549-554.
- [8] L. Salome, F. Carmona, Fractal structure study of carbon blacks used as conducting polymer fillers, *Carbon* 29(4-5) (1991) 599-604.
- [9] X. Bourrat, A. Oberlin, H. Van Damme, C. Gateau, R. Bachelar, Mass fractal analysis of conducting carbon black morphology, *Carbon* 26(1) (1988) 100-103.
- [10] K-M. Juger, D. H. McQueen, Fractal agglomerates and electrical conductivity in carbon black polymer composites, *Polymer* 42(23) (2001) 9575-9581.
- [11] V. I. Roldughin, V. V. Vysotskii, Percolation properties of metal-filled polymer films, structure and mechanisms of conductivity, *Progress in Organic Coatings* 39 (2-4) (2000) 81-100.
- [12] F.A. Modine, A.R. Duggal, D.N. Robinson, E.L. Churnetski, M. Bartkowiak, G.D. Mahan, L.M. Levinson, Electrical properties of polyethylene highly filled with carbon, *Journal of Materials Research* 11(11) (1996) 2889-2894.
- [13] M. Hindermann-Bischoff, F. Ehrburger-Dolle, Electrical conductivity of carbon black-polyethylene composites Experimental evidence of the change of cluster connectivity in the PTC effect, *Carbon* 39 (2001) 375-382.
- [14] T. A. Ezquerra, M. T. Connor, S. Roy, M. Kuleszcza, J. Fernandes-Nascimento, F. J. Balt-Calleja, Alternating-current electrical properties of graphite, carbon-black and carbon-fiber polymeric composites, *Composites Science and Technology* 61(6) (2001) 903-909.
- [15] I. Balberg, A comprehensive picture of the electrical phenomena in carbon black-polymer composites, *Carbon* 40 (2002) 139-143.
- [16] R.J. Hunter, *Zeta Potential in Colloid Science: Principles and Applications*, Academic Press, New York, 1981.
- [17] Th. F. Tadros, Correlation of viscoelastic properties of stable and flocculated suspensions with their interparticle interactions, *Advances in Colloid and Interface Science* 68 (1-3) (1996) 97-200.
- [18] R. Schueler; J. Petermann, K. Schulte, H-P. Wentzel, Agglomeration and electrical percolation behavior of carbon black dispersed in epoxy resin, *Journal of Applied Polymer Science*, 63(13) (1997) 1741-1746.
- [19] J. Vilcakova, P. Saha, V. Kresalek, O. Quadrat, Pre-exponential factor and activation energy of electrical conductivity in polyester resin-carbon fibre composites, *Synthetic Metals* 113 (2000) 83-87.
- [20] V.N. Moraru, F.D. Ovcharenko, Investigation of the gel-formation mechanism in aqueous dispersions of the oxidized graphite and diamond. *J. Chim Phys.(France)* 93 (1996) 1051-1064.
- [21] A. Celzard, J. F. Mareche, G. Furdin, S. Puricelli, Electrical conductivity of anisotropic expanded graphite-based monoliths. *J. Phys. D: Appl. Phys.* 33 (1999) 3094-3101.
- [22] D. Stauffer, A. Aharony, *Introduction to Percolation Theory*, Taylor and Francis, London, 1992.
- [23] J.C. Maxwell, *A treatise on electricity and magnetism*, vol. 1., Clarendon Press, Oxford, 1881.
- [24] K. Strenge, H. Sonntag, Beziehungen zwischen interparticularer wechselwirkung und rheologischen verhalten kozentrieren disperser systeme, *Colloid & Polymer Sci.* 252 (1974) 133-137.