

Nanomachines Based on Carbon Nanotubes

Yu.E. Lozovik¹, A.V. Minogin, A.M. Popov²

Institute of Spectroscopy, Russian Academy of Science, 142190, Troitsk, Moscow region, Russia

Abstract

Possibility for double-wall carbon nanotube to operate as the bolt-and-nut pair is studied. The barriers to relative motions of walls along the helical "thread" line and to jumps on neighbouring helical lines are calculated as functions of the wall lengths for the set of double-wall carbon nanotubes. The dynamics of the relative motion of carbon nanotube walls along the helical line under the action of external forces is considered. Perforated nanodrill, variable nanoresistor and other principally new nanotube based mechanical nanodevices using this motion are proposed. Possible operation modes of proposed nanodevices are discussed.

PACS: 61.44+w, 85.42+m, 85.65+h

Keywords: nanotube, nanomechanics, nanomachine

1 Introduction

Progress in nanotechnology in last decades have given rise to the possibility to manipulate with nanometer-size objects [1]. The principal schemes of nanometer-size machines (nanomachines) where the controlled motion can be realized are considered [2]. Thus, the search of nanoobjects that can be used as movable elements of nanomachines is a very actual challenge for development of nanomechanics. The low frictional relative motion of carbon nanotube walls [3, 4, 5] and unique elastic properties [6] of these walls allows to be considered as promising candidates for such movable elements. A set of nanomachines based on relative sliding of walls along nanotube axis or their relative rotation is proposed: a constant-force nanospring [5], nanobearings [7] and nanogears [8] driven by laser electric fields; a mechanical nanoswitch [9] operated by electrostatic forces; a gigahertz oscillator [10].

All these nanomachines correspond to the case where the corrugation of the interwall interaction energy has little or no effect on relative motion of nanotube walls. However, all of carbon nanotube walls have the helical symmetry and this gives the possibility for neighbouring walls of nanotube to be bolt-and-nut pair. The present work is devoted to principally new type of nanomachines where the relative motion of nanotube walls occurs along helical "thread" lines. The possibility of controlling this motion by the potential relief of the interwall interaction energy is considered. A theory for dynamics of relative motion of nanotube walls is developed. Possible types of these nanomachines are discussed. Two operation modes for these nanomachines are analyzed: Fokker-Planck operation mode, where a relative motion of walls occurs as diffusion with drift under the action of external forces and the accelerating operation mode, where the relative motion of walls is controlled by external forces. The values of the controlling forces corresponding to these modes are estimated.

2 Potential relief of the interwall interaction energy.

By potential relief we mean the dependence of the interwall interaction energy U of two neighbouring nanotube walls on the coordinates describing the relative position of the wall. Such coordinates are the angle ϕ of relative rotation of the wall about the nanotube axis and the length z of relative displacement of the wall along it. It is convenient to visualize the potential relief as a map plotted on a cylindrical surface. In the general case a nanotube wall has a helical symmetry (see, for example, [11]). Therefore, the double-wall nanotubes with the potential relief having valleys directed along the helical line analogously to a thread of

¹E-mail: lozovik@isan.troitsk.ru

²E-mail: popov@ttk.ru

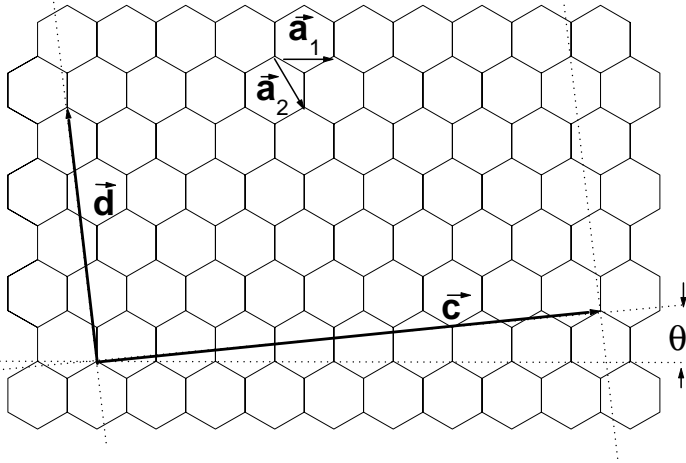


Figure 1: Graphene sheet used to construct a nanotube wall (see [17]). The wall is determined by the lattice vector \mathbf{c} . The wall unit vector is denoted by \mathbf{d} . The chiral angle is denoted by θ . The unit vectors of graphene sheet are denoted by \mathbf{a}_1 and \mathbf{a}_2 .

bolt were found [12]. Here we study the properties of nanotubes having the potential relief of the interwall interaction energy that allows them to be a bolt-and-nut pair. We have restricted ourselves to the case of double-wall carbon nanotubes. Such nanotubes were produced as by the standard method of synthesis in arc discharge [13] (see also review [14] devoted to the problems of growth of different carbon nanostructures) as recently from the pea-pod nanotubes by electron irradiation [15] or by heating [16].

The structure of nanotube wall is determined by the pair of integers (n, m) corresponded to a lattice vector $\mathbf{c} = n\mathbf{a}_1 + m\mathbf{a}_2$ on the graphene plane used to perform mapping, where \mathbf{a}_1 and \mathbf{a}_2 are the unit vectors of the graphene sheet [17, 18] (see Fig 1). The wall radius R is defined as

$$R = \frac{|\mathbf{c}|}{2\pi} = \frac{a_0\sqrt{(n^2 + mn + m^2)}}{2\pi}, \quad (1)$$

where a_0 is the length of graphite lattice vector. The length of the wall unit vector \mathbf{d} is given by the relation

$$|\mathbf{d}| = \frac{3a_0\sqrt{n^2 + mn + m^2}}{GCD(2n + m, 2m + n)}, \quad (2)$$

where $GCD(q, s)$ is the greatest common divisor of integers q and s . The number of graphite unit cell N_c in a unit cell of a wall is

$$N_c = \frac{2(n^2 + mn + m^2)}{GCD(2n + m, 2m + n)}, \quad (3)$$

The walls of a double-wall nanotube are commensurate if the ratio d_1/d_2 of wall unit cell lengths is a rational fraction and incommensurate otherwise. The chiral angle θ of wall is defined as the angle between between vectors \mathbf{c} and \mathbf{a}_1 . This angle equals to

$$\theta = -\arccos \frac{2n + m}{\sqrt{n^2 + m^2 + mn}} \quad (4)$$

Several works were devoted to study of the interwall interaction energy of double-wall carbon nanotubes [12,19-22] and double-shell carbon nanoparticles [23, 24]. The barriers to the relative rotation of

the walls about the nanotube axis and to sliding along it were calculated for the (5,5)@(10,10) [12, 19, 20], (7,7)@(12,12) [22] and (12,12)@(17,17) [22] nanotubes. The dependencies of barriers to the relative sliding along the nanotube axis on number of atoms in the nanotube are studied for several commensurate and incommensurate double-wall nanotubes [21]. The maps of potential relief of the interwall interaction energy as function of the relative displacement of the wall along the nanotube axis and angle of the relative rotation of the wall were considered by Dresselhaus *et. al.* for a set of double-wall nanotubes [12]. They found several types of the potential relief including the type where the valleys form helical lines analogous to a "thread" of bolt. However, the barriers to the relative motion of walls along the helical thread line and for jumps on neighbouring helical lines were not calculated until now.

Here, the structure of walls is constructed by folding of graphene sheet with the bond length equals to 1.42 Å (the bond length of many-wall nanotubes coincides with the bond length of graphite within the accuracy of the neutron diffraction measurements 0.01 Å [25]). The interwall interaction is adopted here to be 6-12 Lenard-Jones potential $U = 4\epsilon((\sigma/r)^{12} - (\sigma/r)^6)$ with parameters $\epsilon = 2.968$ meV and $\sigma = 3.407$ Å. These parameters of the potential were fitted to the interlayer distance and modulus of elasticity of graphite and used to study the ground state and phase transition in solid C₆₀ [26] and recently by Dresselhaus *et. al.* in study of the potential relief of double-wall nanotubes [12]. The upper cutoff distance of the potential 10σ is used. This cutoff distance defines the accuracy of barriers to the wall relative rotation and sliding within 0.001 meV per atom without visible discontinuities of potential relief. The length of outer wall H corresponds to an integer number of lattice constants of this wall, namely, 1–10, 1–11, and 1–30 lattice constants for the (6,4)@(16,4), (8,2)@(12,8), and (8,2)@(17,2) nanotubes, respectively. The length of the inner wall is chosen so that all pairs of atoms with interatomic distances within the cutoff distance are taken into consideration. The walls are considered to be rigid. Account of the deformation of walls is not essential for the shape of the potential relief both for double-wall carbon nanotubes [21] and nanoparticles [24]. The barriers to the relative wall rotation and sliding for the (5,5)@(10,10) nanotube calculated here for walls with unannealed structure coincide within 20 % with results of Dresselhaus *et. al.* (used annealed wall structure) [12].

We have studied the potential relief for the (6,4)@(16,4), (8,2)@(12,8), and (8,2)@(17,2) nanotubes, corresponding to the case of the potential relief with the helical lines of "thread" [12]. For the long inner wall only hexagons that are far from the wall edge take part in the walls interaction. Since such hexagons of the network are equivalent, than the same positions of the short outer wall relative to any hexagon of the long inner wall are also equivalent. To the contrary, the hexagons of the short outer wall are not equivalent due to the different distances to the wall edge. For this reason, the short outer wall can be considered as one large molecule "adsorbed" on the surface of the inner wall. Consequently, the potential relief reproduces only the structure of the long inner wall. Thus we have plotted the potential relief for the (6,4)@(16,4) nanotube and the structure of the inner wall network on the same figure (see Fig. 2). Evidently that the minima of potential relief form the lattice that correlates with the lattice of the inner wall network. Such correlation is observed for all considered nanotubes. Two types of the potential relief minima lattices are found. The type I, shown in Fig. 3a, corresponds to the rectangular lattice of minima. Such a relief have the (6,4)@(16,4) (see Fig. 2) and (8,2)@(12,8) nanotubes. The type II of potential relief, shown in Fig. 3b, corresponds to the oblique lattice of minima with the lattice vectors having the equal lengths and angle between lattice vectors equals to 60°. Such a relief has (8,2)@(17,2) nanotube. Let us convert the angle coordinate to the length $\phi = L/R_1$, where L represents the length of projection of any wall atom path along the wall surface on the wall circumference, R_1 is the inner wall radius. In this coordinate system the lattice vectors have the lengths $b_1 = a_0/2$ and $b_2 = \sqrt{3}a_0/2$ for the type I of the potential relief and $b_1 = b_2 = a_0$ for the type II of the potential relief. For both types of the potential relief the angle χ between the thread line and the wall circumference equals to the chirality angle θ of the inner wall.

The barriers U_1 and U_2 between neighbouring minima in the directions along the lattice vectors \mathbf{b}_1 and \mathbf{b}_2 are different. The threadlike pattern of the potential relief arise due to the essential difference between barriers U_1 for relative motion of walls along the thread line and U_2 for transition of the system to neighbouring thread line ($U_1 \ll U_2$). The nanotubes considered are incommensurate. Therefore the

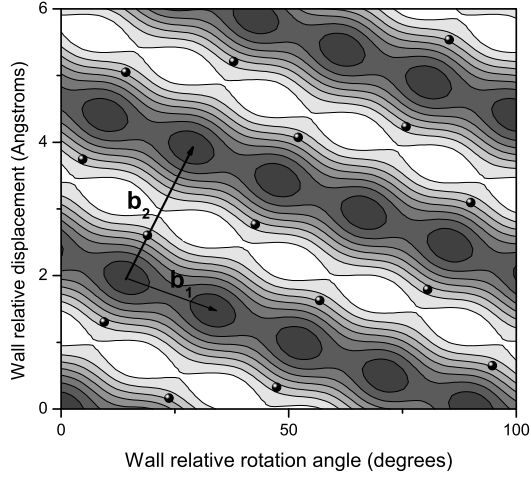


Figure 2: The potential relief of the interwall interaction energy of the $(6,4)@(16,4)$ nanotube as a function of the relative displacement of the wall along the nanotube axis and the angle of the relative rotation of the wall about the nanotube axis; \mathbf{b}_1 and \mathbf{b}_2 are the unit vectors of the lattice formed by the minima of the potential relief. The energy is measured from its minimum. The equipotential lines are drawn at an interval 10^{-2} meV per atom. The spheres present the atoms positions of the inner wall in cylindrical coordinate system with the axis Z coincides with the axis of nanotube. The relative position of the coordinate systems corresponding to the potential relief and atomic structure of outer wall is arbitrary.

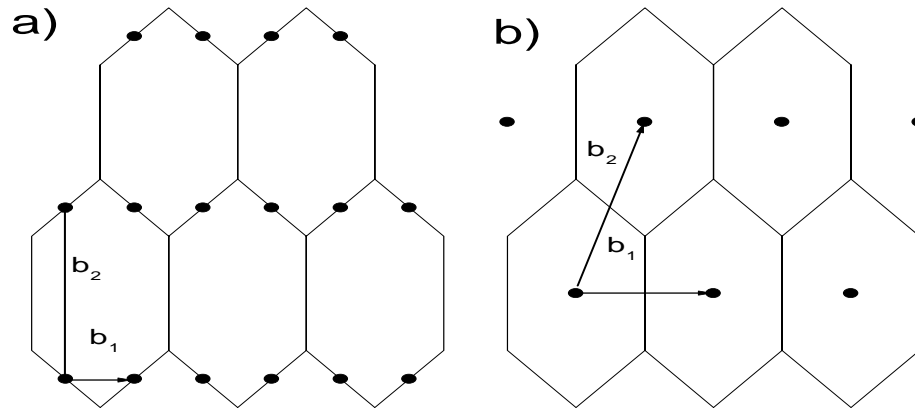


Figure 3: The lattice of minima of the potential relief of the interwall interaction energy (the minima positions are shown by the filled circles); \mathbf{b}_1 and \mathbf{b}_2 are the unit vectors of the lattice formed by minima of the potential relief. Thin lines of the network structure of the inner wall are only guides for eye that illustrate the network structure correlation with the lattice of minima. a) type I of the potential relief, b) type II of the potential relief.

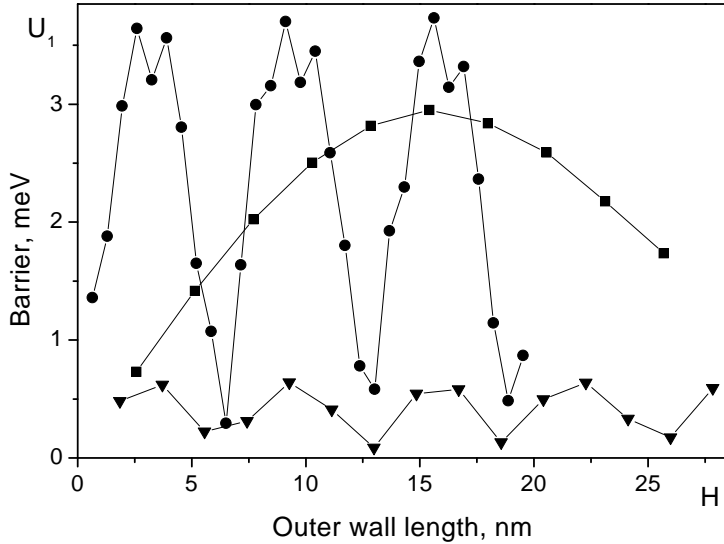


Figure 4: The dependence of the barrier U_1 for relative motion of walls along the thread line on the length H of outer wall. Filled circles, filled triangles and filled squares correspond respectively to $(6,4)@(16,4)$, $(8,2)@(12,8)$ and $(8,2)@(17,2)$ nanotubes.

threadlike pattern of the potential relief change with changing of outer wall length. The barriers to any kind of relative motion of incommensurate walls fluctuate near their average value analogously to the sum of functions $\cos l$, where l is an integer [21]. That is the barriers for the long nanotubes are the same order of magnitude as the analogous barriers for the nanotubes with the outer wall length to be equal to few unit cell lengths. The dependencies of barriers U_1 and U_2 on the outer wall length are shown in Fig. 4 and Fig. 5, respectively. One can see that the barriers change by order of magnitude for all nanotubes considered, while the outer wall length changes by only few nanometers. Note that these dependencies for both barriers, at least for two of three considered nanotubes, are quasiperiodic functions.

As was discussed above the quantity that characterize the possibility for double-wall nanotube to have threadlike pattern of potential relief is not barrier itself but rather ratio $\gamma = U_2/U_1$ of barriers to the motion across the thread line and along it, respectively. It is naturally to call this ratio as relative thread depth. The dependence of relative thread depth on outer wall length is shown in Fig. 6. If average periods of mentioned quasiperiodic functions are close and oscillations of functions are in phase for both barriers then the relative thread depth can be large for essential changes of outer wall length. The example of such a possibility is $(8,2)@(12,8)$ nanotube. In this case fabrication of double-wall nanotube with given relative thread depth can be possible. If average periods of mentioned quasiperiodic functions are not close or oscillations of function are not in phase then changes in relative thread depth under changes of outer wall length can be of orders of magnitude. The examples of such a possibility are $(6,4)@(16,4)$ and $(8,2)@(17,2)$ nanotubes. Moreover the relative thread depth for $(6,4)@(16,4)$ nanotube is less than 1 at some lengths of outer wall. This means disappearance of threadlike relief or possible appearance of threadlike relief with different parameters.

*****8

Thus our calculations show that both for relative motion of walls along the thread line and for transition of the system to neighbouring thread line, respectively, barriers change by order of magnitude for all nanotubes considered as the outer wall length changes by only few nanometers. Therefore it is difficult to fabricate the double-wall nanotube with incommensurate walls but with *controlled* values of barriers U_1 and U_2 . Thus nanotubes with incommensurate walls are too hard to use in nanomachines based on relative motion of walls where the *precise control* of relative position of walls is necessary. However such nanotubes can be used in nanomachines based on fast relative motion of walls where only the presence of "threadlike" potential relief

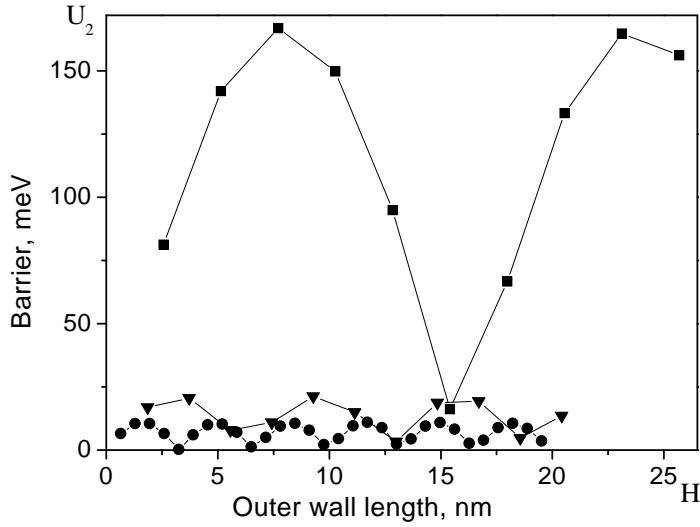


Figure 5: The dependence of the barrier U_2 for transition of the system on neighbouring thread line on the length H of outer wall. Filled circles, filled triangles and filled squares correspond respectively to $(6,4)@(16,4)$, $(8,2)@(12,8)$ and $(8,2)@(17,2)$ nanotubes.

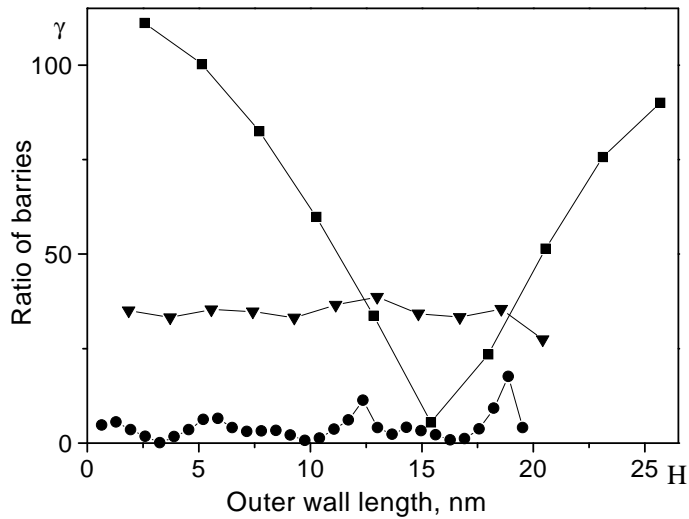


Figure 6: The dependence of the ratio $\gamma = U_2/U_1$ characterizing the "thread" depth on the length H of outer wall. Filled circles, filled triangles and filled squares correspond respectively to $(6,4)@(16,4)$, $(8,2)@(12,8)$ and $(8,2)@(17,2)$ nanotubes.

with high value of relative thread depth γ is necessary.

The barriers to any kind of relative motion of commensurate walls with lengths corresponding to integer number of nanotube elementary cells are given by relation $U_a = U_u N_u$, where U_u is the barrier per unit cell of the nanotube, N_u is a number of unit cells in the nanotube (the interaction with atoms on the edge of wall is disregarded here). Thus the barrier U_a for sufficiently long nanotube is proportional to its length and can be possible to obtain the given value of barrier by choice of nanotube length. The analysis show that for some two-wall nanotubes with integer number of elementary cells the barriers can be extremely small in comparison with total interwall interaction energy. The reason the fact is following. The potential field produced by each wall can be expanded in the basis of harmonics invariant under symmetry group of the wall [27]. Only harmonics with symmetry compatible with both walls can contribute in the interwall interaction potential relief $U(\phi, z)$. As was shown on example of nonchiral wall (12,12) the amplitudes of these harmonics sharply decrease and rapidly becomes negligible. For example, in (7,7)@(12,12) nanotube only 24-th harmonic of expansion of potential field produced by wall (7,7) can contribute in the angle dependence of the interwall interaction energy. Therefore it was found that barrier for relative wall rotation for this nanotube is less than calculation accuracy [22]. The analogous results one can expect for the majority of nanotubes with chiral commensurate walls.

To systemize the search of nanotubes with commensurate walls and threadlike potential relief the notion of equivalence class of walls can be introduced (see details in [28]). An equivalence class is the set of all walls with chirality indexes (kf, kg) , where k is integer, f and g are coprime natural numbers, k is called diameter index and pair (f, g) is called chirality indexes of the class. If the walls from different equivalence classes (f_1, g_1) and (f_2, g_2) are commensurate then the interwall distance for the nanotube $(k_1 f_1, k_1 g_1)$ @ $(k_2 f_2, k_2 g_2)$ composed of these walls is given by the formula

$$\Delta R = \frac{a_0}{2\pi} \sqrt{f_2^2 + f_2 g_2 + g_2^2 (k_2 - k_1 \frac{d_1}{d_2})}, \quad (5)$$

Such a pair of equivalence classes generates double-wall nanotubes families with the geometrical parameters that are the same for all nanotubes of each family: the interwall distance, unit cell length of nanotube and difference of chirality angles of walls.

3 Dynamics of relative motion of walls.

Let us study now the nanomechanical problem, dynamics of relative motion of double-wall nanotube interacting walls under the action of external forces. The wall interaction potential is denoted as $U(\phi, z)$, where ϕ is the angle of wall relative rotation about nanotube axis and z is the wall relative displacement along nanotube axis. One wall is treated as fixed and the motion of second wall relative to the one is examined. We consider the case where external force causes the relative motion of walls but does not cause their deformation. In this case forces \mathbf{F}^a that acts on each atom of movable wall have equal magnitudes. This forces can be divided into two components $\mathbf{F}^a = \mathbf{F}_z^a + \mathbf{F}_L^a$ where components \mathbf{F}_z^a and \mathbf{F}_L^a are directed along the nanotube axis (first type forces) and along the tangent to nanotube circumference (second type forces), respectively. The forces of considered type can have, for example, electrostatic nature [9] or can be applied by the nanomanipulator [5] or by laser electric fields [7, 8].

The analysis shows that for case considered resultant force \mathbf{F}_r corresponding to components \mathbf{F}_L^a can be majorize as

$$|\mathbf{F}_r| \leq \frac{F_L^a N_c}{\pi p}, \quad (6)$$

where N_c is number of graphite unit cell in a unit cell of one-dimensional crystal corresponding to the movable wall, p is the number of complete revolutions of helical line determined by the wall symmetry [11, 18] per unit cell of the wall. Thus for sufficiently long wall the contribution of tangential components \mathbf{F}_L^a in resultant force acting on movable wall center of mass can be disregarded. Therefore tangential components \mathbf{F}_L^a cause

only rotation of wall and wall center of mass moves only along nanotube axis. On using once again the transformation $\phi = L/R_1$ it is easily to show that equations of motion of center of mass and rotation for movable wall are equivalent to one vector equation

$$M\ddot{\mathbf{r}} = -\frac{dU(\mathbf{r})}{d\mathbf{r}} + \mathbf{F} \quad (7)$$

where M is the movable wall mass, \mathbf{r} is vector with components z and L and $\mathbf{F} = (N_a F_z^a, N_a F_L^a)$, N_a is number of atoms in the movable wall.

Thus the motion of one wall of double-wall carbon nanotube relative to fixed wall in the absence of external forces or under the action of external forces satisfying the conditions described above is equivalent to two-dimensional motion of particle with mass M in the potential field $U(\mathbf{r})$ and under the action of external force \mathbf{F} .

Now we shall obtain Fokker-Planck equation describing relative diffusive motion of carbon nanotube walls and their drift under the action of force \mathbf{F} . We consider the case corresponding to the simulations performed. Firstly let the length of movable wall is considerably less than length of fixed wall and movable wall is placed far from fixed wall edges so that interaction of movable wall with atoms at the edge of fixed wall has negligible effect on the potential relief. Thus we leave aside the case where relative motion of walls is telescopic with the extension of outer wall outside inner one. In last case contact area of walls and, consequently, corresponding surface energy substantially depend on z , and, consequently, the minima of potential relief can disappear. Secondly, let the minima U_{min} of potential relief $U(\mathbf{r})$ form the lattice with lattice vectors \mathbf{b}_1 and \mathbf{b}_2 as it is shown in Fig. 2. The relative motion of walls can be diffusion with drift only in the case $kT \ll U_1, U_2$, where U_1 and U_2 are the barriers between minima U_{min} for motion along lattice vectors \mathbf{b}_1 and \mathbf{b}_2 , respectively. We restrict ourselves by the case of $U_1 \ll U_2$, that is the case of one-dimensional diffusion in direction along lattice vector \mathbf{b}_1 . In this case, if the direction of \mathbf{b}_1 coincides with the direction of vertical z -axis or horizontal ϕ -axis, the considered relative motion of walls is relative sliding or rotation, respectively. Otherwise this motion is analogous to the relative motion of bolt-and-nut pair.

Let us consider the ensemble of "particles" with the motion described by equation (7), where potential $U(\mathbf{r})$ and force \mathbf{F} have all properties described above. The number of particles dN passing during the time dt through normal to diffusion direction segment $d\xi$ is given by

$$dN = dN_1 - dN_2 = \frac{1}{2}(n_1 u_1 - n_2 u_2) d\xi dt, \quad (8)$$

where dN_1 and dN_2 are numbers of particles passing in opposite directions \mathbf{b}_1 and $-\mathbf{b}_1$ between neighbouring minima U_{min} separated by segment $d\xi$; n_1 and n_2 are concentrations of particles at some distances λ from segment $d\xi$ corresponding to particles moving in directions \mathbf{b}_1 and $-\mathbf{b}_1$; λ is the collision mean free path of particles before passing through segment $d\xi$; u_1 and u_2 are average velocities of particle displacement in directions \mathbf{b}_1 and $-\mathbf{b}_1$, respectively. These velocities are given by

$$u_1 = \frac{\delta}{\tau_1}, \quad u_2 = \frac{\delta}{\tau_2} \quad (9)$$

where δ is the distance between neighbouring minima in the motion direction, τ_1 and τ_2 are average times of displacement between two neighbouring minima for motion in directions \mathbf{b}_1 and $-\mathbf{b}_1$, respectively, $\tau_1 = 1/w_1$ and $\tau_2 = 1/w_2$, w_1 and w_2 are probabilities of corresponding displacements. The quantities w_1 and w_2 are not equal in result of force \mathbf{F} action. Namely, the barriers U_1 between neighbouring minima change by the work $W = F_x \delta/2$, where F_x is the projection of \mathbf{F} on particle motion direction. This change is decrease if F_x is directed along the particle motion and increase otherwise. The probabilities w_1 and w_2 are given approximately by Arrhenius formula

$$w_1 = \Omega \exp\left(-\frac{U_1 - F_x \delta/2}{kT}\right), \quad w_2 = \Omega \exp\left(-\frac{U_1 + F_x \delta/2}{kT}\right), \quad (10)$$

where Ω is a frequency which has the same order of magnitude as oscillation frequency of the particle near the minimum.

The particle motion is diffusion if $kT \ll U_1, U_2$ and drift (that is the time-average acceleration is zero) if $F_x\delta/2 \ll U_1$. To produce the Fokker-Planck equation the first term of exponent $\exp(F_x\delta/2kT)$ expansion must be used, therefore the condition $F_x\delta/2 \ll kT$ is also necessary.

Substituting (9)–(10) in (8), we get

$$dN = \frac{1}{2}\Omega\delta \exp\left(-\frac{U_1}{kT}\right) \left[(n_1 - n_2) + (n_1 + n_2)\frac{F_x\delta/2}{kT} \right] d\xi dt \quad (11)$$

With the substitutions $n_1 + n_2 \approx n$ and $n_1 - n_2 \approx \delta\partial n/\partial x$ equation (11) takes the form of Fokker-Planck equation:

$$\frac{\partial n}{\partial t} = D\frac{\partial^2 n}{\partial x^2} + \frac{\partial n}{\partial x}BF_x \quad (12)$$

Here D and B are, respectively, diffusion coefficient and mobility of particles given by

$$D = \frac{1}{2}\Omega\delta^2 \exp\left(-\frac{U_1}{kT}\right) \quad (13)$$

$$B = \frac{\Omega\delta^2}{2kT} \exp\left(-\frac{U_1}{kT}\right) \quad (14)$$

Note, that Einstein ratio $D = kTB$ is fulfilled.

The behaviour of one particle with fixed coordinates at $t = 0$ is described by solution $n_s(x, t)$ of the equation (12) that satisfy two conditions: 1) at $t = 0$ all the concentration is placed on a line normal to the diffusion direction and the concentration elsewhere on the plane is zero; 2) the total number of particles is equal to 1.

4 Discussion

We consider here two types of nanomachines based on relative motion of nanotube walls. Let us discuss firstly possible advantages of application of nanotubes with threadlike potential relief of the interwall interaction energy in nanomachines where the direction of forces applied on movable wall does not correspond to desirable kind of wall motion. In the case where the potential relief has negligible effect on relative motion of walls, the directions of forces applied on movable wall must correspond to direction of relative motion of walls. Namely, if the relative motion of walls is sliding along nanotube axis, as it take place in constant-force nanosprings [5], gigahertz oscillators [10], and mechanical nanoswitch [9], than the forces applied on movable wall are bound to be directed along nanotube axis (first type forces). If the relative motion of walls is relative rotation, as it take place in nanobearings [7] and nanogears [8] than the forces applied on movable wall must to be directed along the tangent to its circumference (second type forces).

However the presence of threadlike potential relief of the interwall interaction energy remove the restriction on directions of forces applied on movable wall. The analysis above shows that relative motion of walls along helical line of "thread" is possible for both discussed types of external forces and any their superposition. Therefore the first type forces produce not only a relative sliding of walls along axis but also their relative rotation. Therefore a nanomachine based on wall motion can operate as a *nanowhirligig*. The proposed way to convert the forces directed along nanotube axis into relative rotation of walls can be used in nanobearings and nanogears. The second type forces producing a rotational moment gives rise not only a relative rotation but also a relative motion of walls along nanotube axis. This effect provides a possibility to construct a nanomachine based on carbon nanotube that is analogous to old-desinged *faucet* where rotation of handle converts into forward motion of rod.

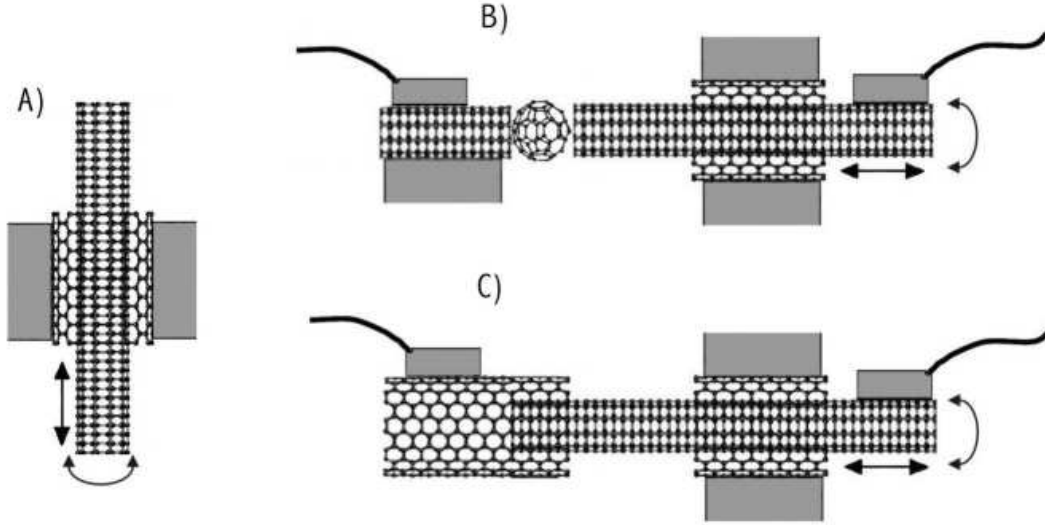


Figure 7: Nanomachines based on a threadlike relative motion of nanotube walls: A) nanodrill, B) and C) two types of variable nanoresistors.

We propose here also principally new type of nanomachines that may be based on nanotubes with only threadlike potential relief of the interwall interaction energy. The using of alternating-sign force to operate the relative position of walls can produce a motion of walls that is analogeous to the motion of auger in a perforating drill. Such a *perforating nanodrill* can be used for modification of surface in nanometer size (see Fig. 7B).

Another new type of nanodevices which we propose here are based on relative motion of nanotube walls are electromechanical nanodevices. Two nanometer size systems with the conductivity which can be tuned within orders of magnitude by the rotation of a nanotube wall or its displacement along the axis were considered. The first one consists of two single-wall nanotubes and a fullerene between them [29] (see Fig. 7B), and the second one is an telescoping nanotube [30] (see Fig. 7C). The tuning can be controlled with the help of nanodevice based on relative motion of nanotube walls. As a result a *variable nanoresistor* can be constructed, where nanotube wall is both movable element and element of the electric circuit.

Another new type of nanodevices which we propose here based on relative motion of nanotube walls are electromechanical nanodevices. For example, the conductivity of system consisting of two carbon nanotubes and a fullerene between them [29] can be tuned within orders of magnitude by rotation of a one nanotube or its displacement along the axis. This tuning can be controlled with the help of nanodevice based on relative motion of nanotube walls. In result a *variable nanoresistor* can be constructed, where wall of nanotube is both movable element and element of electric circuit.

Let us discuss possible operation modes of nanomachines based on relative motion of nanotube walls along line of thread. As we have shown above, in the case, when conditions $kT \ll U_1, U_2$ and $F_x \delta / 2 \ll kT$ are fulfilled, the relative motion of carbon nanotube walls is described by Fokker-Planck equation (12). The operation mode of nanomachine based on such a motion is called here Fokker-Planck operation mode. This mode is worthwhile to use in nanomachine if average distance $x_{dr} = BF_x t$ passed by a wall along a helical line of "thread" in result of drift is greater than average distance $x_{dif} = \sqrt{2Dt}$ passed by this wall in result of diffusion. This condition is fulfilled for displacements $x_{dr} \gg \delta$, that is, e.g., for tens of relative jumps of wall along a helical thread line between minima of the interwall potential $U(\mathbf{r})$. Such displacement along a helical line corresponds to less than one revolution of wall about the nanotube axis or displacement by

nanometers along this axis. Although Fokker-Planck operation mode does not allow the precise control of relative positions of walls, this mode can be used, for example, in perforating nanodril for perforation of layers with thickness less than average displacement x_{dr} of wall (that plays the role of auger) in result of drift.

For forces $F_x\delta/2 \gg kT$ the stochastic contribution in relative motion of walls can be neglected. In this case the relative motion of walls is accelerated and as it is discussed above equivalent to two-dimensional motion of one particle described by Eq. (7). The operation mode of nanomachine based on such a motion is called here the accelerating operation mode. In this mode the controlled relative displacement of walls along a helical line of "thread" for distance that is less than δ is possible. This mode can be used, for example, in variable nanoresistor.

For *intermediate* forces $F_x\delta/2 \approx kT$ the next terms of exponent expansion can be used. Then Fokker-Planck equation (12) takes the analogous form as for small forces

$$\frac{\partial n}{\partial t} = D' \frac{\partial^2 n}{\partial x^2} + \frac{\partial n}{\partial x} B' F_x \quad (15)$$

where the diffusion coefficient D' and the mobility B' are expressed in terms of diffusion coefficient D and mobility B , in the case of small forces, respectively.

$$D' = D \left(1 + \frac{F_x^2 \delta^2}{8k^2 T^2} \right) \quad (16)$$

$$B' = B \left(1 + \frac{F_x^2 \delta^2}{24k^2 T^2} \right) \quad (17)$$

Let us estimate the range of forces that can be used to control the relative motion of carbon nanotube walls in nanomachine operating in Fokker-Planck and in accelerating operation modes. Our estimations are made for nanotube (8,2)@(12,8). The ratio of barriers $\gamma = U_1/U_2$ of this nanotube conserves within the range 25-40 for all considered lengths of outer wall. The conditions $kT \ll U_1, U_2$ and $F_x\delta/2 \ll kT$ give the maximal force F_{FP} corresponding to Fokker-Planck mode $F_{FP} \ll 2U_1/\delta$, where

$$\delta = \frac{a_0}{2} \sqrt{\left(\frac{R_2}{R_1}\right)^2 \cos^2 \chi + \sin^2 \chi}, \quad (18)$$

Here R_1 and R_2 are radii of inner and outer wall, respectively, χ is the angle between helical line of "thread" and wall circumference.

For nanotube (8,2)@(12,8) we have: 1) value of χ equal to that of chiral angle $\theta = 10.89^\circ$ and 2) magnitude of $U_1 \approx 0.6$ meV corresponding to outer wall length that equals to the length of unit cell of the wall. In result we get $\delta = 1.86$ Å and $F_{FP} \ll 10^{-12}$ N.

The using of too high force controlling relative motion of walls at accelerating mode can give rise twist-off. The twist-off can occur only if the projection F_y of external controlling force on the direction normal to thread line will satisfy to the inequality

$$F_y > \left\langle \frac{\partial U(y)}{\partial y} \right\rangle_y \approx \frac{2U_2}{\delta_y} \quad (19)$$

where y is wall relative displacement in the direction normal to thread line and δ_y is the distance between neighbouring lines of "thread"

$$\delta_y = \frac{\sqrt{3}a_0}{2} \sqrt{\left(\frac{R_2}{R_1}\right)^2 \cos^2 \chi + \sin^2 \chi} \quad (20)$$

For controlling forces greater than $F_{ac} = 2U_2/\delta_y$ the relative motion of walls in the direction normal to thread line must be taken into account. For controlling forces less than F_{ac} it is sufficiently to consider the

relative motion of walls only along the thread line. For nanotube (8,2)@(12,8) on substituting in Eq. (19) $\delta_y = 2.23 \text{ \AA}$, $U_2 = 20 \text{ meV}$ and magnitude of χ equal to chiral angle θ we get $F_{ac} \approx 3 \cdot 10^{-11} \text{ N}$.

Acknowledgements

Yu.E.L. is grateful to S.V. Iordanskii and A.Ya. Vul for useful discussions. This work was supported by grants of Russian Foundation of Basic Researches and Ministry of Sciences.

References

- [1] T. Junno, K. Depent, L. Montelius, L. Samuelson, Appl. Phys. Lett. 66, 3627 (1995).
- [2] M. Porto, M. Urbakh, J. Klafter, Phys. Rev. Lett. 84, 6058 (2000).
- [3] M.F. Yu, O. Lourie, M.J. Dyer, K. Moloni, R.S. Ruoff, Science, 287, 5453, 637 (2000).
- [4] M.F. Yu, B.I. Yakobson, R.S. Ruoff, J. Phys. Chem. B 104, 37, 8764 (2000).
- [5] J. Cumings, A. Zettl, Science 289, 602 (2000).
- [6] P. Poncharat, Z.L. Wang, D. Ugarte, W.A. de Heer, Science 283, 1513 (1999).
- [7] R.E. Tuzun, D.W. Noid, B.G. Sumpter, Nanotechnology, 6, 52 (1995).
- [8] D.W. Srivastava, Nanotechnology, 8, 186 (1997).
- [9] L. Forro, Science, 289, 560 (2000).
- [10] Q. Zheng, Q. Jiang, Phys. Rev. Lett., 88, 045503 (2002).
- [11] C.T. White, D.H. Robertson, J.W. Mintmire, Phys. Rev. B, 47, 5485 (1993).
- [12] R. Saito, R. Matsuo, T. Kimura, G. Dresselhaus, M.S. Dresselhaus, Chem. Phys. Lett. 348, 187 (2001).
- [13] S. Iijima, Nature 354, 56 (1991).
- [14] Yu.E. Lozovik, A.M. Popov, Physics Uspekhi 40 (1997) 717.
- [15] J. Sloan, R.E. Dunin-Borkowski, J.L. Hutchison, K.S. Coleman, V.C. Williams, J.B. Claridge, A.P.E. York, C. Xu, S.R. Bailey, G. Brown, S. Friedrich, M.L.H. Green, Chem. Phys. Lett. 316, 191 (2000).
- [16] S. Bandow, M. Takizawa, K. Hirahara, M. Yadasako, S. Iijima, Chem. Phys. Lett. 316, 191 (2000).
- [17] R. Saito, M. Fujita, G. Dresselhaus, M.S. Dresselhaus, Appl. Phys. Lett. 60, 2204 (1992).
- [18] R.A. Jishi, M.S. Dresselhaus, G. Dresselhaus, Phys. Rev. B 47, 16671 (1993).
- [19] J.-C. Charlier, J.P. Michenaud, Phys. Rev. Lett., 70, 1858(1993).
- [20] Y.K. Kwon, D. Tomanek, Phys. Rev. B, 58, R16001, (1998).
- [21] A.N. Kolmogorov, V.H. Crespi, Phys. Rev. Lett., 85, 4727 (2000).
- [22] M. Damnjanovic, T. Vukovic and I. Milosevic, Eur. Phys. J. B, 25, 131 (2002).
- [23] M. Yoshida, E. Osawa, Full. Sc. & Tech., 1, 54 (1993).

- [24] Yu.E. Lozovik, A.M. Popov, Chem. Phys. Lett., 328, 355 (2000).
- [25] A. Burian, J.C. Dore, H.E. Fisher, J. Sloan, Phys. Rev. B, 59, 1665 (1999).
- [26] J.P. Lu, X.P. Li, R.M. Martin, Phys. Rev. Lett, 68, 1551 (1992).
- [27] M. Damnjanovic, I. Milosevic, T. Vukovic, R. Sredanovic, Phys. Rev. B, 60, 2728 (1999).
- [28] A.V. Belikov, Y.E. Lozovik, A.M. Popov, Physics of Solid State 45(7) (in print) (2003).
- [29] R. Guttierrez, G. Fagas, G. Cuniberti, F. Grossmann, R. Schmidt, K. Richter, Phys. Rev. B, 65 113410(2002).
- [30] Kim, D.H.; Chang, K.J. Phys. Rev. B, 65, 155402(2002).
- [31] Yu.E. Lozovik, (to be publ.).