

Implications of T_c variation in UBe_{13} for a possible Fulde-Ferrell-Larkin-Ovchinnikov phase

H.A. Radovan and R.J. Zieve

Physics Department, University of California at Davis, Davis, CA 95616

J.S. Kim and G.R. Stewart

Physics Department, University of Florida, Gainesville, FL 32661

We measure the heat capacity of UBe_{13} with an unusually low T_c for a polycrystal. We find an upturn in the upper critical field $H_{c2}(T)$ below about $T_c/2$, much as for higher- T_c samples. Comparing the critical fields in our sample and in samples with higher T_c 's shows that the low-temperature limit of H_{c2} is proportional to $T_c(H = 0)$, as expected if the upturn comes from an FFLO phase and strong coupling.

Although discovered in 1983, the heavy-fermion superconductor UBe_{13} [1] still has many incompletely understood properties. These include the splitting of the superconducting transition upon doping the U sites with thorium, and the power law temperature dependences of various quantities in the superconducting phase. Another issue is the temperature dependence of the upper critical field $H_{c2}(T)$. Unique among heavy fermion superconductors, UBe_{13} shows a clear upturn in $H_{c2}(T)$ at about half the superconducting transition temperature, with $H_{c2}(T = 0)$ far exceeding the Clogston paramagnetic limit [2]. Indeed, the only other material with similar H_{c2} behavior is the recently discovered UGe_2 , which superconducts under pressure [3].

The two most detailed explanations of the upturn involve a mixture of two representations in the order parameter [4] and an enhancement of the paramagnetic limit of $H_{c2}(T = 0)$ by strong coupling [5]. Here we show that the behavior of $H_{c2}(T)$ in samples of different T_c is consistent with the latter explanation. Thomas et al. [5] fit $H_{c2}(T)$ with three adjustable parameters: the slope $dH_{c2}/dT(T_c)$, which probes the orbital field limit; the gyromagnetic ratio g of the quasiparticles; and the strong coupling parameter λ . Matching the upturn requires the further assumption of a Fulde-Ferrell-Larkin-Ovchinnikov (FFLO) state [6, 7].

Several limits influence the low-temperature critical field. The orbital limit, $H_{c2}^{orb}(T) = H_{c2}^{orb}(0)(1 - (T/T_c)^2)$, determines the critical field in most superconductors. The huge effective masses in heavy fermion superconductors make spin effects far more important than usual, although the orbital influence continues to dominate very close to T_c . A second field is the paramagnetic limit H_{c2}^p , also known as the Clogston or Pauli limit. For spin singlet pairing, the superconducting condensation energy competes with the magnetic energy tending to align the quasiparticle spins. In a single-particle excitation model, this leads to an abrupt quenching of superconductivity when the applied field reaches the Clogston limit $H_{c2}^p(T) = \frac{\sqrt{2}\Delta(T)}{g\mu_B}$, where Δ is the superconducting energy gap and μ_B is the Bohr magneton. Yet the Clogston limit is not the final word on spin limitations of H_{c2} . At high magnetic fields and T less than about $T_c/2$, a Fulde-Ferrell-Larkin-Ovchinnikov (FFLO) state [6, 7] may appear in clean superconductors. H_{c2}^p is derived in a single excitation picture, but multiple excitations interact by reducing the energy gap. In the FFLO state pairs are broken over an entire portion of the Fermi surface, with the resulting quasiparticles aligned by

spin. The pairing over only part of the Fermi surface leads to an anisotropic energy gap with planar nodes perpendicular to the field. The energy difference between the spin-up and spin-down branches of the Fermi surface gives a finite center-of-mass pairing Q . Further energy considerations show that in fact the order parameter amplitude undergoes a real-space modulation. Since the FFLO state has partial spin alignment, its critical field H_{c2}^{FFLO} exceeds H_{c2}^p .

These low-temperature critical field behaviors have different dependence on the sample's transition temperature. The Clogston limit is proportional to the energy gap, leading to a proportionality to the zero-field transition temperature as well. The strong coupling parameter enters here through its effects on the gap. Similarly, the energetics of the FFLO state scale with the energy gap, and hence with T_c , so $H_{c2}^{FFLO}(t = T/T_c)$ should also be proportional to T_c . On the other hand, H_{c2}^{orb} depends on the coherence length ξ , and its scaling with T_c is not straightforward.

Fortunately, another unusual feature of UBe_{13} allows us to test this scaling. Reported values for the onset of the superconducting transition vary by more than 200 mK, with high-quality crystals (as judged by the transition width) at both extremes of the range. Langhammer et al. suggest that two types

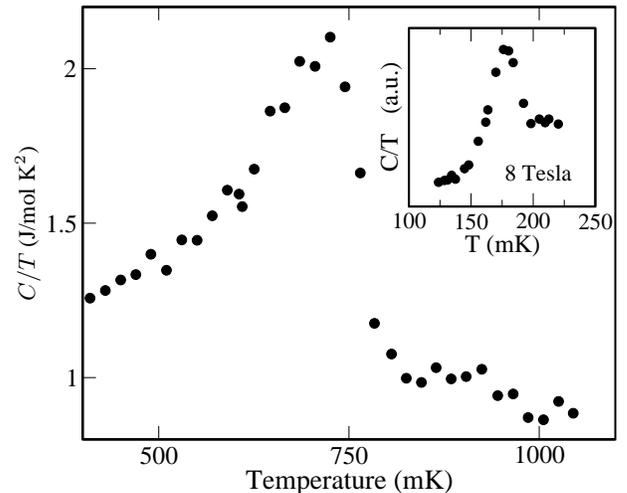


FIG. 1: Heat capacity of our UBe_{13} sample. The main figure is with no applied field, the inset at 8 Tesla.

of UBe_{13} exist: L(low)-type, with T_c around 750 mK; and H(high)-type, with T_c from 850 to 950 mK [8]. Furthermore, polycrystals are supposedly all H-type, while single crystals fall into both categories. Here we show the H_{c2} upturn in a polycrystal with a particularly low T_c . The only sample with such a low transition temperature previously studied had not shown the H_{c2} upturn [8]. Comparing the shape of the upturn in samples of different T_c supports the FFLO interpretation of the upturn.

Our sample was prepared by arc melting in an argon atmosphere and subsequent annealing at 1400° C for 1000 hours in a beryllium atmosphere [9]. It is polycrystalline with a typical grain size of 100 μm , as seen in a Philips CM-30 transmission electron microscope. We use a relaxation method to measure heat capacity $C(T)$, shown in Figure 1, from 100 mK to 900 mK. The superconducting transition width is small, about 50 mK, speaking to a high sample quality despite the low T_c .

The inset of Figure 1 shows heat capacity in our highest magnetic field, 8 Tesla, measured on a small piece cut from the same sample as that for the main figure. This piece is less than 20 microns thick and less than 1 mm in lateral dimensions. Because of its small size, the background heat capacity is significant but the transition remains clearly visible. The piece was made thin for irradiation with high-energy uranium ions to study the influence of lattice disorder on the superconducting phases [10]. Although the irradiation shows no measurable effects up to a density of 10^{15} tracks per square meter, we performed various measurements as a function of applied field while searching for matching effects at fields where the defect density equals the vortex density. The results presented here are from the irradiated sample which we studied in the most detail, with track density $5 \times 10^{13}/\text{m}^2$. This sample's zero-field T_c and transition width are identical to those of the unirradiated samples.

Figure 2 combines our own data with previous measurements on a higher- T_c sample [8]. Since the criterion for identifying T_c can change the curve shape of $H_{c2}(T)$ [5], both our data and the high- T_c comparison curve use T_c as the transition midpoint of heat capacity measurements. The transition widths of the two samples are also comparable. Both curves display the characteristic upturn in H_{c2} . The temperature of the upturn tracks the zero-field T_c , remaining near $T_c/2$. The shift we observe in the temperature of the upturn with T_c is consistent with an FFLO explanation.

Near T_c , resistance measurements at fields below 0.28 kG give $\frac{dH_{c2}}{dT}(T_c) = 6.5$ Tesla/K for our sample, much lower than the 42 Tesla/K found in UBe_{13} samples with T_c near 900 mK [11]. If orbital effects dominate near T_c , this slope is related to the zero-temperature orbital limit. The smaller value in the lower- T_c sample could indicate a smaller superconducting coherence length. It is not clear why $\frac{dH_{c2}}{dT}(T_c)$ depends so strongly on the sample's T_c , but we note that $\frac{dT_c}{dP}$ has a similar variation, with pressure affecting T_c far more strongly for a higher- T_c sample [12].

At low temperatures, the H_{c2} curves have a natural scaling, as shown in Figure 3. The circles and dotted line show the higher- T_c curve from Figure 2, as a function of $t = T/T_c$. The dashed line shows our measurements, again as a function

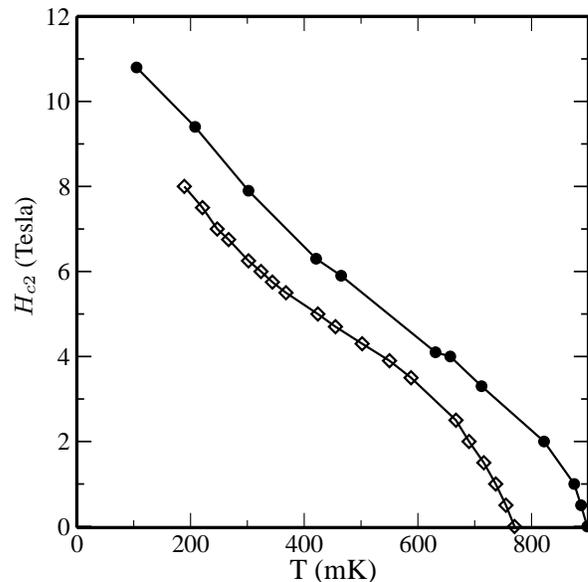


FIG. 2: Upper critical field as a function of temperature for our sample (diamonds) and from Reference [8] (circles).

of t , and with the field values also scaled by the ratio of the two transition temperatures, $h = H_{c2} * T_c(\text{high})/T_c(\text{ours})$. Since these two curves overlay for $t < 0.45$, the low-temperature critical fields for the samples scale with T_c . If this region is dominated by paramagnetic effects, including the FFLO enhancement, this scaling is expected. We find a different and unexplained scaling at intermediate temperatures. The solid curve of Figure 3 shows the same data as the dashed line, but with the scaling applied only to the temperature axis. From $t = 0.7$ to near 1, this curve coincides with the low- T_c data.

With respect to the H_{c2} upturn, Th-doped compounds behave quite differently from pure UBe_{13} . In the $\text{U}_{0.97}\text{Th}_{0.03}\text{Be}_{13}$, no upturn occurs in H_{c2} down to $t = 0.26$ [13]. This is consistent with the upturn indicating an FFLO phase, which is destroyed by disorder in thorium-doped material. Another possibility is that the upturn in pure UBe_{13} is a precursor for the second phase transition [14]. For example, the two upper critical fields in $\text{U}_{0.978}\text{Th}_{0.022}\text{Be}_{13}$ merge below about $t = 0.59$ [13]. Since $H_{c2}(T)$ has different slopes in the two phases, the boundary between normal and superconducting phases in the $H - T$ plane has an upturn much like that in pure UBe_{13} .

Because the wide range of T_c 's for samples with narrow transitions in UBe_{13} is so unusual, with its origin not well understood, we make a few further comments on our sample. Suggested causes [8] for the T_c variation include aluminum impurities, and variations in the beryllium content, which must be carefully monitored during the preparation process [9]. Previously only single crystals had been reported with such low transition temperatures, and explanations focused on differences between single crystal and polycrystal preparation. However, this seems to be a consequence of reporting T_c as the onset rather than midpoint of the transition.

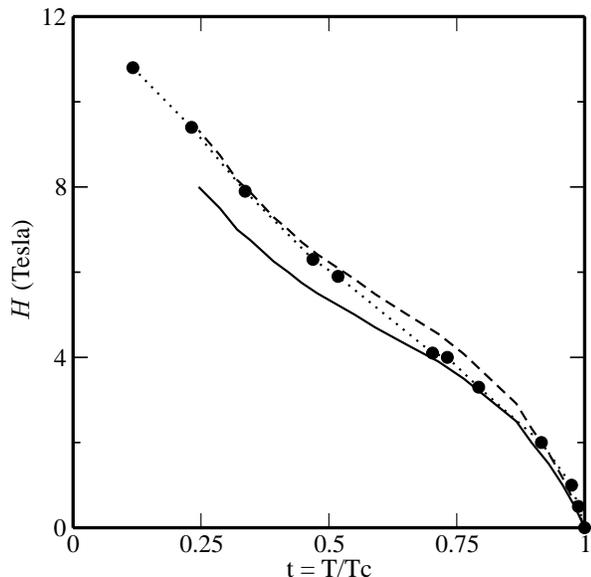


FIG. 3: Circles and dotted line: upper critical field from heat capacity on high- T_c sample. Solid line: our measurements. Dashed line: same as solid line, but with field scaled by the same factor as temperature.

In Table I we list both midpoints and onsets for our sample and for those from several previously published works. Except as otherwise noted, we extracted these numbers from heat capacity graphs in those papers. Resistive measurements generally yield slightly higher values, but the large span of T_c 's remains. We note that the transition *midpoints*, for both single crystals and polycrystals, are widely distributed between 725 mK and 930 mK. Since previous polycrystalline samples with low T_c 's also had wide transitions, the T_c *onsets* were all near 900 mK. In our sample, with its narrow transition, T_c is clearly much lower. Since the samples with the narrowest transitions do not have the highest onset temperatures, identifying the midpoint temperatures is reasonable.

We find an upturn in $H_{c2}(T)$ below about $T_c/2$, a feature previously seen only in UBe_{13} samples with T_c around 900 mK. Comparing the shape of $H_{c2}(T)$ for samples with differ-

ent T_c 's meshes well with interpreting the upturn as an FFLO state in a strong coupled superconductor. As T_c changes the paramagnetic limit for critical field scales with T_c , which we find for H_{c2} at low temperatures. The orbital limit depends on the superconducting coherence length and changes with T_c in a less straightforward way, in agreement with our measurements near T_c . Observing the critical field upturn in a low T_c sample does raise a question about the role of disorder in causing the wide T_c range. If the upturn indicates an FFLO phase, which requires a clean limit, then the upturn should be suppressed in low T_c samples, as it is in thorium-doped UBe_{13} . The resolution probably depends upon a better understanding of the T_c variation itself. Our measurements on a polycrystalline UBe_{13} sample with $T_c = 770$ mK and our compilation of past work present evidence for the existence of only one type of UBe_{13} with a range in T_c between 725 mK and 930

TABLE I: Transition temperatures of UBe_{13} measured by heat capacity for various samples. Both the midpoint and onset of the transition are given.

Midpoint (mK)	Onset (mK)	Width (mK)	Reference
Single crystals			
725	770	90	[15]
745	780	70	[16]
744	768	48	[8]
790	880	180	[1]
860	–	< 96	[17]
900	920	40	[5, 8]
907	950	86	[18]
Polycrystals			
765	790	50	This work
830	910	160	[19]
830	885	110	[20]
885	945	120	[14]
915	980	130	[16]
919	–	< 40	[17]
930	970	80	[21]

mK.

We thank R. Field for TEM measurements. This work was supported by NSF under DMR-9733898 (UCD) and by DOE under DE-FG05-86ER45268 (Florida).

[1] H.R. Ott, H. Rudigier, Z. Fisk, and J.L. Smith, "UBe₁₃: An unconventional actinide superconductor," *Phys. Rev. Lett.* **50**, 1595 (1983).
[2] L. Glemot, J.P. Brison, J. Flouquet, A.I. Buzdin, and D. Jaccard, "Strong coupling superconductivity in heavy fermion systems," *Physica* **C317-318**, 73 (1999).
[3] I Sheikin, A. Huxley, D. Braithwaite, J.P. Brison, S. Watanabe, K. Miyake, and J. Flouquet, "Anisotropy and pressure dependence of the upper critical field of the ferromagnetic superconductor UGe₂," *Phys. Rev.* **B64**, 220503 (2001).
[4] I.A. Fomin and J.P. Brison, "Subdominant interactions and H_{c2} in UBe₁₃," *J. Low Temp. Phys.* **119**, 627 (2000).
[5] F. Thomas *et al.*, "Strong coupling effects on the upper criti-

cal field of the heavy-fermion superconductor UBe₁₃," *J. Low Temp. Phys.* **102**, 117 (1996).
[6] P. Fulde and R.A. Ferrell, "Superconductivity in a strong spin-exchange field," *Phys. Rev.* **135**, A550 (1964).
[7] A.I. Larkin and Y.N. Ovchinnikov, "Inhomogeneous state of superconductors," *Sov. Phys. JETP* **20**, 762 (1965).
[8] C. Langhammer *et al.*, "Evidence for the existence of two variants of UBe₁₃," *J. Magn. Magn. Mat.* **177-181**, 443 (1998).
[9] J.S. Kim, B. Andraka, and G.R. Stewart, "Investigation of the second transition in U_{1-x}Th_xBe₁₃," *Phys. Rev.* **B44**, 6921 (1991).
[10] H.A. Radovan, R.J. Zieve, J.S. Kim, G.R. Stewart, W.-K. Kwok, and R.D. Field, "Heavy-ion irradiation of UBe super-

- conductors,” *J. Phys. Chem. Solids* **64** 1015 (2003).
- [11] M.B. Maple, J.W. Chen, S.E. Lambert, Z. Fisk, J.L. Smith, H.R. Ott, J.S. Brooks, and M.J. Naughton, “Upper critical magnetic field of the heavy-fermion superconductor UBe_{13} ,” *Phys. Rev. Lett.* **54**, 477 (1985).
- [12] C.F. Miclea, F.M. Grosche, J. Sichelschmidt, G.R. Stewart, G. Sparn, and F. Steglich, “Unconventional superconductivity in UBe_{13} probed by uniaxial stress,” *Physica* **B312** 97 (2002).
- [13] D.S. Jin, S.A. Carter, T.F. Rosenbaum, J.S. Kim, and G.R. Stewart, “ $H - T$ phase diagrams of the double transition in thoriated UBe_{13} ,” *Phys. Rev.* **B53**, 8549 (1996).
- [14] U. Rauchschwalbe, C.D. Bredl, F. Steglich, K. Maki, and P. Fulde, “Phase diagram of the superconducting states of $U_{1-x}Th_xBe_{13}$,” *Europhys. Lett.* **3**, 757 (1987).
- [15] P.H.P. Reinders, B. Wand, F. Steglich, G. Fraunberger, G.R. Stewart, and G. Adrian, “Specific-heat measurements on UBe_{13} under uniaxial pressure,” *Europhys. Lett.* **25**, 619 (1994).
- [16] A.P. Ramirez, C.M. Varma, Z. Fisk, and J.L. Smith, “Fermi-liquid renormalization in the superconducting state of UBe_{13} ,” *Phil. Mag. B* **79**, 111 (1999).
- [17] D.S. Jin, T.F. Rosenbaum, J.S. Kim, and G.R. Stewart, “Low-temperature specific heat of $U_{1-x}Th_xBe_{13}$,” *Phys. Rev.* **B49**, 1540 (1994).
- [18] Z. Fisk *et al.*, “Superconductivity of heavy-electron uranium compounds,” *Physica* **C153-155**, 1728 (1988).
- [19] R.H. Heffner *et al.*, “Thermodynamics and magnetism in $U_{1-x}Th_xBe_{13-y}B_y$,” *J. Appl. Phys.* **69**, 5481 (1991).
- [20] W.P. Beyermann *et al.*, “Effects of boron substitution on the superconducting state of UBe_{13} ,” *Phys. Rev.* **B51**, 404 (1995).
- [21] H.R. Ott, H. Rudigier, E. Felder, Z. Fisk, and J.L. Smith, “Influence of impurities and magnetic fields on the normal and superconducting states of UBe_{13} ,” *Phys. Rev.* **B33**, 126 (1986).