

Viscosity models for silicate melts

Jesper deClaville Christiansen

*Center for Nanotechnology, Aalborg University Fibigerstraede 16, DK-9220
Aalborg East, Denmark E-mail: i9ictus@iprod.auc.dk, Phone: +45 9635 8970*

Abstract

Rheology of silicates (melts or super cooled as glasses) is one of the most important fields to mankind, as geological activity largely influences life. In this paper, unifying empirical models for the Non-Newtonian shear viscosity and the extensional viscosity are proposed. The models have only one parameter, the zero shear viscosity (the Newtonian plateau), and are valid for a wide range of chemical compositions

Key words: Silicates, rheology, Non-Newtonian

1 Introduction

The field of geology attracts scientists from many areas. This scientific field has for obvious reasons a great importance to mankind. In geology, the study of silicate melts attracts the main focus because in nearly all igneous processes silicate melts does play a role. The importance of the field attract many researchers in the search for general models and physical origins to the behaviour of silicate melts. Due to the chemical complexity of silicates occurring in nature the area of rheology of silicates is not easiest field one can choose. Amongst the many studies [1,2,3,4,5,6,7,8,9,10,15,18,19] can be mentioned. The challenges in rheometry can be seen, when considering the need for temperature spans of more than 2000 C, and viscosities ranging from 10^{40} Pas [17] at room temperature to 10^{12} Pas at T_g and 10^{-4} Pas at supercritical conditions. Finally the melts are chemically very aggressive in the high temperature range. Rheometrical methods that have been used in the study of silicates are nearly all that we know: Concentric cylinder, cone/plate, "solid" bar oscillatory rheometry, ball indentation, fiber elongation, biaxial compression, ultrasonics and capillary rheometry. Many of these methods does not provide the accuracy that we normally are used to when doing rheometry under more pleasant environmental conditions. In this study an analysis have been made on experimental oscillatory data from [11,12] and on extensional data from [1,2].

2 Analysis of experiments

The raw data for the following analysis work was taken from [11] and [12]. In the first reference, N. Bagdassarov made oscillatory experiments for GLAFO, The Swedish Glass Research Institute, on an E-glass and a Rock wool composition, both below and above T_g . In the second reference, 9 different chemical compositions were measured by GLAFO on a Bohlin oscillatory rheometer, in both cases a "solid" bar type of instrument was used. An example of the raw data for 11 different temperatures for a glass fibre composition can be seen on Figure 1. On the right hand side of Figure 1, the data have been shifted to a master curve at 902 K, using IRIS [13].

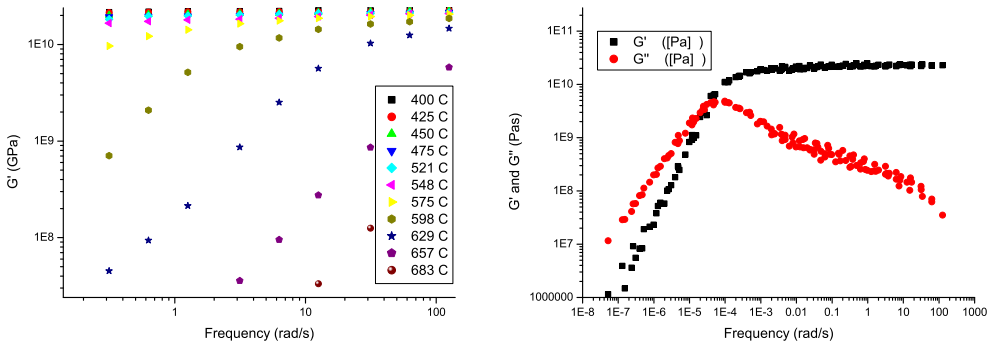


Fig. 1. Raw oscillatory data (673 K - 956 K) for the glass fibre composition and the master curve (902 K) obtained from time-temperatures superposition using IRIS [13].

The data falls quite nicely on a single master curve. Now it is possible to apply the Cox-Merz approximation [17] and obtain Figure 2. The Non-Newtonian onset corresponds to a Deborah number of approximately 0,7 when G is assumed constant 25 GPa no matter temperature and composition. The latter approximation is acceptable, as the viscosity can vary several decades, whereas G only varies a few percent, and remains in the same range even with different chemical compositions. When making this exercise for all the different chemical compositions and temperatures and plotting the Cox-Merz shear viscosity, a very interesting behaviour is observed: The Deborah number for the Non-Newtonian onset remains constant around 0,7. This observation agrees well with the discussion of Webb and Dingwell in [15].

Similar observations for the extensional viscosity were found by [1]. From the data from [1], the onset can be calculated to occur at a Deborah number approximately two decades lower than what was observed in this study. This difference is consistent with what one would expect, as an extensional flow is known to be much stronger in aligning structure than shear, thus the onset is lower in an extensional flow. What is really surprising in the study of the ex-

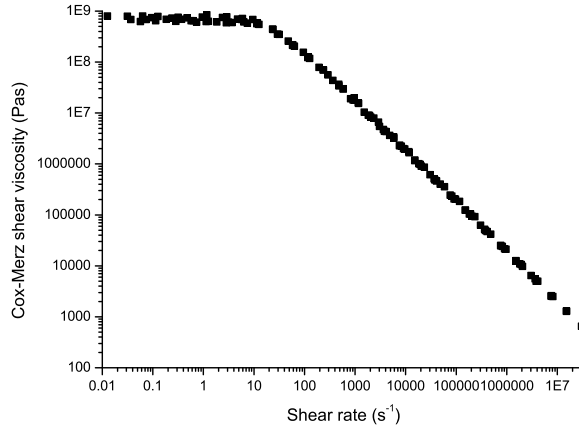


Fig. 2. The Cox-Merz shear viscosity as a function of shear rate, E-glass (902 K).

tensional properties in [1,2] is the fact, that silicates also in extension show an extensional thinning behaviour. But this can be explained from the extremely small size of structures in a silicate melt compared with e.g. polymers.

In the current study, it was observed from the shear viscosity plots that the slope of the graph in the shear thinning region is constant for all compositions. Thus it is possible to merge all shear viscosity curves of the different silicate melts to a single curve for the same Newtonian plateau. This is shown on Figure 3 for two compositions, the E-glas and the Rock wool, (only two in order to make the plot easy to read). In [1] the same was made for the extensional case, and in [14] for a single composition but different temperatures. A natural question that can be raised is the origin for this simplicity, when we do have a non-exponential nature of the relaxation (a pluralis of relaxation times). A good discussion have been made by Webb and Dingwell in [15].

3 A Non-Newtonian shear viscosity model for silicates

With the knowledge from Figure 3, it is now possible to propose a shear viscosity relation that fits all the chemical compositions used in this study. A viscosity model is just curve fit; the choice of a good mathematical model to fit experimental data. Many models are all ready available that represents various degrees of complexity depending on the number of parameters. For this study, a simple Carreau type of model was chosen.

$$\eta(\dot{\gamma}) = \frac{A_0}{(1 + (A_1\dot{\gamma})^2)^{A_2}} \quad (1)$$

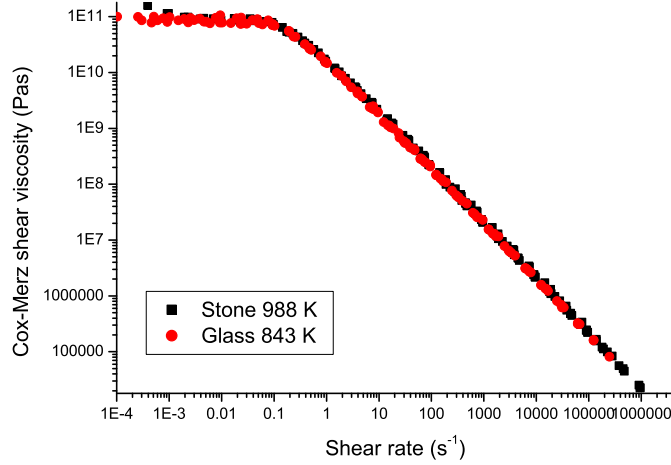


Fig. 3. The Cox-Merz shear viscosity for an E-glass (843 K) and a rock wool composition (988 K), with temperatures adjusted to provide the same zero-shear viscosity.

A_0 should be the Newtonian shear viscosity plateau at low shear rates. A_2 affects the slope of the curve in the Non-Newtonian region and was found from fitting experiments on the data sets to be 0,48. A_1 is the parameter that adjusts the Non-Newtonian onset. We know from the observations in this study, that the onset approximately occur at a Deborah number of 0,7. With this and the definition of the Deborah number [17], an onset shear rate can be defined:

$$\dot{\gamma}_{onset} = \frac{DeG_{\infty}}{\eta_0} \Rightarrow \quad (2)$$

$$\dot{\gamma}_{onset} = \frac{0.7G_{\infty}}{\eta_0} \quad (3)$$

A_1 is found to be the reciprocal to the onset shear rate. We now have a suggestion to a simple model for the shear viscosity for silicate melts

$$\eta(\dot{\gamma}) = \frac{\eta_0}{\left(1 + \left(\frac{\eta_0}{0.7G_{\infty}}\dot{\gamma}\right)^2\right)^{0.48}} \quad (4)$$

Figure 4 and Figure 5, show the comparison of experimental data and the prediction of this model on six different chemical compositions.

The quality of the fits on Figures 4 and Figures 5 depends on the quality of the oscillatory data as some datasets show mores scatter than others. The slight deviation of the data and the curve is due to this scatter in the lower shear region for some measurements, as the curve was drawn in Origin, using a Non-linear curve fit to provide the "best" fit. All together the model (4)

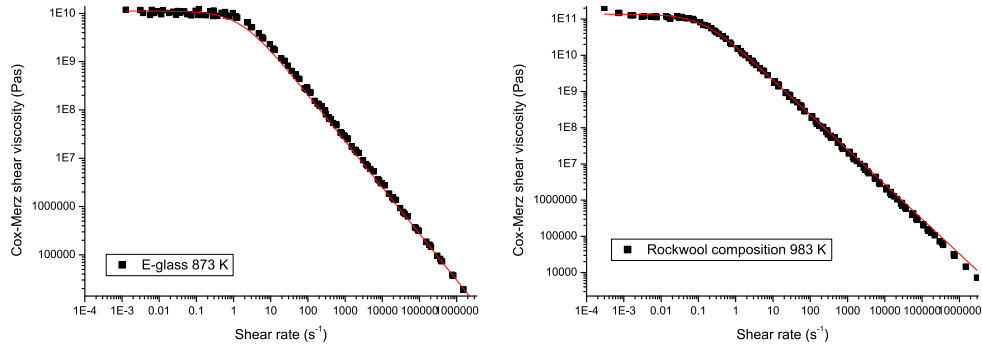


Fig. 4. The figure shows the Cox-Merz shear viscosity (points) for two different chemical compositions together with the prediction of the shear viscosity model proposed in this study. Analysis based on [11]

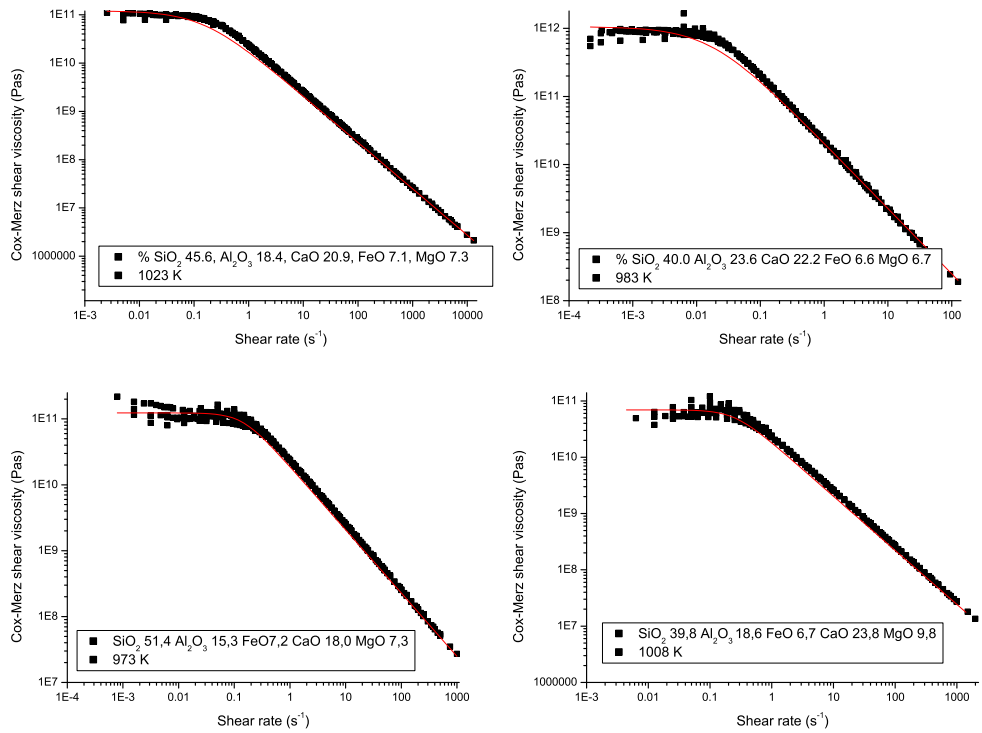


Fig. 5. The figure shows the Cox-Merz shear viscosity (points) for four different chemical compositions together with the prediction of the shear viscosity model proposed in this study. Analysis based on [12]

show a fair fit to the data.

4 Extensional viscosity

Knowing, that the zero-extensional viscosity is three times the zero-shear viscosity and having the data from the article of [1,2] a relation for the extensional viscosity can be proposed.

$$\eta_E(\dot{\epsilon}) = \frac{3\eta_0}{\left(1 + \left(\frac{3\eta_0}{De3G_\infty}\dot{\epsilon}\right)^2\right)^{A_2}} \Rightarrow \quad (5)$$

$$\eta_E(\dot{\epsilon}) = \frac{3\eta_0}{\left(1 + \left(\frac{\eta_0}{DeG_\infty}\dot{\epsilon}\right)^2\right)^{A_2}} \quad (6)$$

Here in equation (5) the three times the shear viscosity can be replaced by measured data from an extensional experiment and $3G$ with Youngs Modulus E if extensional data are available. From [1,2], the De number for the onset can be found to approximately 0,003. The lower De number for the onset corresponds well to the fact that extension is a structural stronger aligning flow than shear. Thus a first suggestion for an equation would be:

$$\eta_E(\dot{\epsilon}) = \frac{3\eta_0}{\left(1 + \left(\frac{\eta_0}{0.003G_\infty}\dot{\epsilon}\right)^2\right)^{0.48}} \quad (7)$$

This equation have been tested on the data from [1,2]. Results can be seen in Figure 6,7 and 8. The suggested model can be seen to represent a fair fit to the data. The model is almost identical to the model of [18,19], but it has the advantage, that it can be adjusted through the De number.

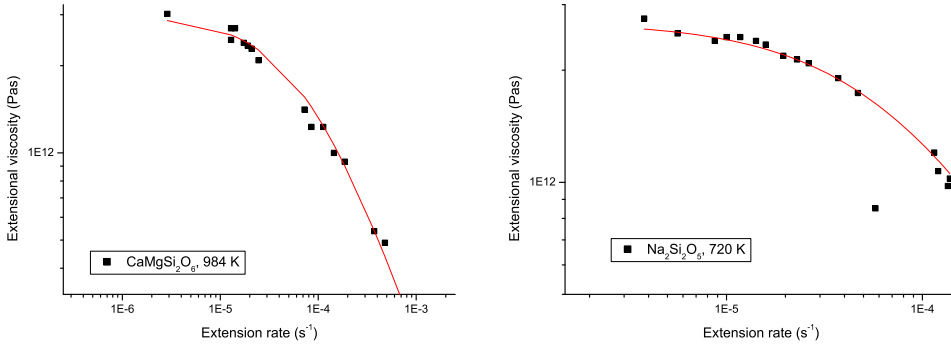


Fig. 6. Comparison between data from [1,2] and the model. The line represents the best fit of the model to the data (using Origin with only unknown η_0).

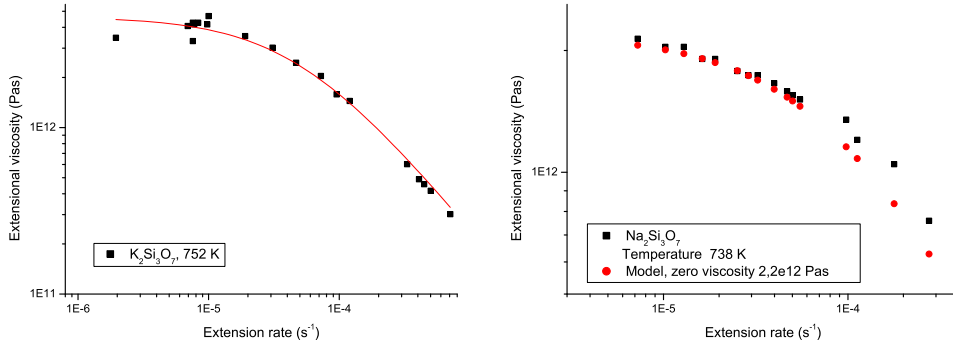


Fig. 7. Comparison between data from [1,2] and the model. The line (left figure) represents the best fit of the model to the data (using Origin). The points (right figure) were obtained by manually setting a value for the zero shear viscosity.

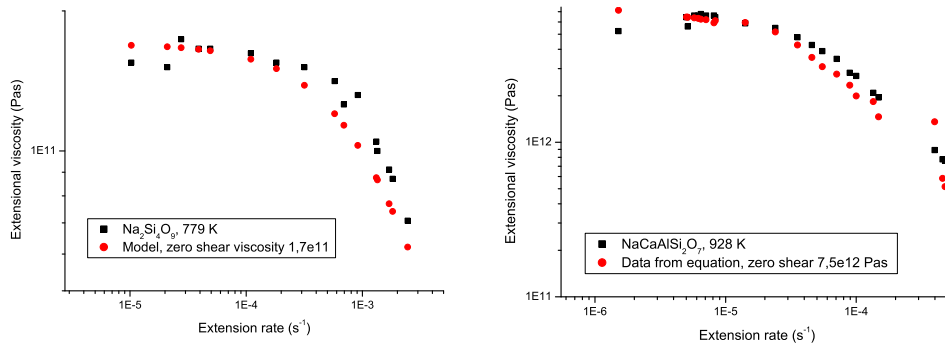


Fig. 8. Comparison between data from [1,2] and the model. The points were obtained by manually setting a value for the zero shear viscosity.

5 Discussion and conclusions

Oscillatory data from two different laboratories on 11 different chemical compositions have been analysed. Time-temperature superposition have been performed on all dataset, and the Cox-Merz shear viscosity plotted.

It is observed, that the onset to Non-Newtonian behaviour for all chemical compositions in shear occur in the order of a Deborah number of 0,7. All curves can be shifted to a master curve, when scaled to the same Newtonian plateau viscosity. Data was fitted using the Carreau model, and it was observed, that the parameters A_1 could be found as the reciprocal of the onset shear rate. The onset shear rate can be calculated from the Deborah number.

A_2 was found by fitting experiments to be approximately 0,48. A_0 is simply the zero-shear viscosity (Newtonian plateau).

Thus an empiric expression has been proposed, that allows an estimate of

the Non-Newtonian shear viscosity curve, and where the only variable is the Newtonian viscosity; an easily found parameter that can be estimated from the viscosity-temperature function that are available in literature [20] for many different chemical compositions. The model is in extension quite similar to the work of Simmons [18,19], but has the adjustable feature of a De number.

The applicability of such relations as proposed here are potentially very big. Geological processes involve variations in chemical composition, and phenomena like melt fracture occur in the Non Newtonian range.

The results reported here and the model proposed agree well with the observations of [1,2]. In fact it was possible to make a fair fit to the data from this work just modifying the shear equation to an extensional viscosity model with a $De=0,003$ to compensate for a stronger aligning flow. The other modifications made was straight forward: $E=3G$ and the zero-extensional viscosity equals three times the zero-shear viscosity. The model was demonstrated to fit extensional data from [1,2] very well.

The simple relation between [1,2] and shear is nice, as it strengthens the conclusion of the applicability of the Cox-Merz approximation after the Non-Newtonian onset and simplifies the models.

Though robust to chemical compositions future work is needed in order to verify the limits of this model regarding compositions. Adjustments to suggested values of Deborah number for the onset and the parameter A_2 would also be welcome. The Carreau model was chosen as a fit function, but others fit functions can be tested. The chosen value of G of 25 GPa is a minor approximation, as G varies slightly with composition, temperature and pressure.

6 Acknowledgements

The author would greatly like to acknowledge GLAFO, the Swedish Glass Research Institute, for making data available for the analysis. Also the author would like to thank Dr Erik Appel Jensen, Aalborg University and Dr. Søren Lund Jensen, Rockwool International for good discussions and Rockwool International A/S for financial support.

References

- [1] Webb, S.L. and Dingwell, D.B., The onset of non-Newtonian rheology of silicate melts. A fiber elongation study. *Phys Chem Minerals* **17(2)** (1990) 125-132

- [2] Webb, S.L. and Dingwell, D.B., Non-newtonian rheology of igneous melts at high stresses and strain rates; experimental results for rhyolite, andesite, basalt and nephelinite. *J Geophys Res* **95(B10)** (1990) 15695-15701
- [3] Bagdassarov, N. and Dorfman, A., Viscoelastic behavior of partially molten granites. *Tectonophysics* **290** (1998) 27-45
- [4] Bagdassarov, N. Dingwell, D.B and Webb, S.L. Viscoelasticity of crystal- and bubble-bearing rhyolite melts. *Physics of the Earth and Planetary Interiors* **83(2)** (1994) 83-99
- [5] Bagdassarov, N. and Dingwell, D.B., Frequency dependent rheology of vesicular rhyolite. *Journal of Geophysical Research* **98 (B4)** (1993) 6477-87
- [6] Stevenson, R.J., Dingwell, D.B., Bagdassarov, N. and Manley, C.R. Measurement and implication of "effective" viscosity for rhyolite flow emplacement. *Bull. Volcanol* **63** (2001) 227-237
- [7] Dingwell, D.B. Volcanic Dilemma: Flow or Blow? *Science* **273** (1996) 227-237
- [8] Gottsmann, J, Giordano D. and Dingwell, D.B., Predicting shear viscosity during volcanic processes at the glass transition: a calorimetric calibration *Earth and Planetary Science Letters* **198** (2002) 417-427
- [9] Bottinga, Y. Configurational entropy and the non-Newtonian rheology of homogenous silicate liquids. *Physical Review B* **49(1)** (1994) 95-99
- [10] Bottinga, Y., Sipp, A. and Richet, P. Time-dependent isothermal variations of silicate melt viscosity after sudden temperature or stress change. *Journal of Non-Crystalline Solids* **290** (2001) 129-144
- [11] GLAFO, The Glass Research Institute, Växjö Sweden. Oscillatory measurements on an E-glass and a rock wool composition, Measured by N. Bagdassarov, Germany (1999)
- [12] GLAFO,
The Glass Research Institute, Växjö Sweden. Oscillatory measurements on 9 different glasses, Measured by GLAFO (2001)
- [13] Winther, H.H. and Mours, M., Innovative Rheological Interface Software (IRIS) version 7.26 (2003)
- [14] Lund-Jensen, S., Analysis of torsional data, Internal working paper, Rockwool International A/S. (2000)
- [15] Stebbins, J.F. McMillan, P.F. and Dingwell, D.B., Structure, dynamics and properties of silicate melts *Reviews in Mineralogy* **3** (1995)
- [16] Christiansen, J. deC. and Drozdov, A.D. Rheology of silicate glasses *Rheology Bulletin* **71(2)** (2002) 5-13
- [17] Barnes, H.A., Hutton, J.F. and Walters, K. An Introduction to Rheology *Rheology series, Elsevier* **3** (1989)

- [18] Simmons, J.H., Simmons, C.J. Nonlinear viscous flow in glass forming *American Ceramic Society Bulletin* **68(11)** (1989) 1949-1955
- [19] Simmons, J.H. What is so exciting about non-linear viscous flow in glass, molecular dynamics simulations of brittle fracture and semiconductor-glass quantum composites. *Journal of Non-Crystalline Solids* **239** (1999) 1-15
- [20] Solvang, M. Rheological and Thermodynamic Response to Compositional Variation in High Aluminosilicate Melts. *PhD thesis, Aalborg University* (2003)