

# FINITE-SIZE SPIN-WAVE THEORY OF A COLLINEAR ANTIFERROMAGNET

LUCA CAPRIOTTI

*Kavly Institute for Theoretical Physics, University of California at Santa Barbara  
Santa Barbara CA 93106-4030, United States of America  
caprio@kitp.ucsb.edu*

Received Day Month Year  
Revised Day Month Year

The ground-state and low-energy properties of the two-dimensional  $J_1$ – $J_2$  Heisenberg model in the collinear phase are investigated using finite-size spin-wave theory [Q. F. Zhong and S. Sorella, *Europhys. Lett.* **21**, 629 (1993)], and Lanczos exact diagonalizations. For spin one-half – where the effects of quantization are the strongest – the spin-wave expansion turns out to be quantitatively accurate for  $J_2/J_1 \gtrsim 0.8$ . In this regime, both the magnetic structure factor and the spin susceptibility are very close to the spin-wave predictions. The spin-wave estimate of the order parameter in the collinear phase,  $m^\dagger \simeq 0.3$ , is in remarkable agreement with recent neutron scattering measurements on  $\text{Li}_2\text{VO}_2\text{SiO}_4$ .

*Keywords:* quantum antiferromagnets, spin-wave theory, exact diagonalizations

## 1. Introduction

The experimental realization of quasi-2d frustrated antiferromagnets,<sup>1</sup> such as  $\text{Li}_2\text{VO}_2\text{SiO}_4$ ,  $\text{Li}_2\text{VOGeO}_4$ , and  $\text{VOMoO}_4$  has recently generated a renewed interest in the physics of the so-called *collinear* antiferromagnets. In these compounds the relevant superexchange interactions involve  $s = 1/2$   $V^{4+}$  ions on weakly coupled stacked planes, and the magnetic behavior is likely to be described by the  $J_1$ – $J_2$  Heisenberg model on the square lattice,

$$\mathcal{H} = J_1 \sum_{n.n.} \mathbf{S}_i \cdot \mathbf{S}_j + J_2 \sum_{n.n.n.} \mathbf{S}_i \cdot \mathbf{S}_j, \quad (1)$$

where  $J_1$  and  $J_2$  are the (positive) nearest-neighbor (*n.n.*) and next-nearest-neighbor (*n.n.n.*) couplings, respectively. In the experimentally relevant case  $J_2 \gtrsim J_1$ , frustration is known to originate in the classical ( $s \rightarrow \infty$ ) limit a collinear low-temperature phase.<sup>2,3,4</sup> In fact, for  $J_2/J_1 > 0.5$ , the ground state for  $s \rightarrow \infty$  is a state where the spins are ferromagnetically aligned along one direction and antiferromagnetically in the other, corresponding to magnetic wave vectors  $Q = (\pi, 0)$  or  $Q = (0, \pi)$ . These two families of states break not only the  $\text{SU}(2)$  symmetry and the translational invariance of the Hamiltonian, as the conventional Néel state, but also its invariance under  $\pi/2$  real-space rotations. Interestingly, this additional two-fold degeneracy is

expected to generate non-trivial finite-temperature properties. In fact, an Ising-like order parameter can be defined in order to discriminate between the two classes of states which are connected by real space  $\pi/2$  rotations, and a finite-temperature second-order phase transition is expected.<sup>4</sup>

How these low-temperature properties are affected by quantum fluctuations, especially for the experimentally interesting  $s = 1/2$  case, is an open problem currently preventing a faithful comparison with the experiments.<sup>1,5,6</sup> In fact, due to numerical instabilities induced by frustration (*sign-problem*),<sup>7</sup> this issue cannot be investigated with the powerful stochastic numerical methods successfully employed for the  $n.n$  Heisenberg model<sup>8</sup>, so that approximate approaches have to be followed.<sup>7,5,6</sup>

In this paper, we address the reliability of the spin-wave (*sw*) theory as an analytical tool to give *quantitative* predictions on the low-energy properties of the  $J_1$ – $J_2$  Heisenberg model in the collinear phase. To this purpose, a previously introduced finite-size *sw* theory<sup>9</sup> is generalized to the collinear phase and a direct comparison with Lanczos exact diagonalization results<sup>10</sup> is performed for  $s = 1/2$ . This allows us to demonstrate the effectiveness of *sw* theory in describing the low-energy properties of the  $J_1$ – $J_2$  Heisenberg antiferromagnet in the experimentally relevant regime  $J_2 \gtrsim J_1$ .

## 2. Finite-size spin-wave theory

The finite-size *sw* theory of Zhong and Sorella,<sup>9</sup> is a rigorous generalization of the standard *sw* approach to finite clusters with  $N$  sites, which allows one to avoid the spurious Goldstone-mode divergences – related to the  $SU(2)$  symmetry breaking assumption – in a straightforward way, without imposing any *ad hoc* holonomic constraint on the sublattice magnetization.<sup>11</sup> In the collinear case, a systematic finite-size *sw* expansion can be derived for  $J_2/J_1 > 0.5$  considering as the approximated ground state the symmetric linear combination

$$|\psi_{sw}\rangle = (|\pi, 0\rangle + |0, \pi\rangle)/\sqrt{2}, \quad (2)$$

where  $|\pi, 0\rangle$  and  $|0, \pi\rangle$  are the (normalized) *sw* ground states obtained assuming the classical collinear order with  $Q = (\pi, 0)$ , and  $Q = (0, \pi)$ , respectively. Since on any finite size the ground state is expected to have all the spatial symmetries of the Hamiltonian it is important to consider the symmetric linear combination (2) in order to obtain an accurate description of its correlations. In addition, this is also crucial to generalize rigorously the finite-size *sw* theory to the collinear phase.

Both  $|\pi, 0\rangle$  and  $|0, \pi\rangle$  in Eq. (2) can be obtained according to the standard *sw* procedure. The first step is to apply the unitary transformation which defines a spatially varying reference frame pointing along the local direction of the spins in the classical state, assumed in the  $xy$  plane:  $\mathcal{U} = \exp[\pi/2 \sum_i (\cos Q \cdot r_i - 1) S_i^z]$ . Then, using the Holstein-Primakoff spin-boson transformation to first-order in  $1/s$ ,  $S^x = s - a^\dagger a$ ,  $S^y = \sqrt{\frac{s}{2}}(a^\dagger + a)$ ,  $S^z = i\sqrt{\frac{s}{2}}(a^\dagger - a)$ , and translational invariance,

the leading term of the Hamiltonian in the  $sw$  expansion reads

$$\mathcal{H}_{sw} = E_{cl} + 2J_1s \sum_k \left[ A_k a_k^\dagger a_k + \frac{1}{2} B_k (a_k^\dagger a_{-k}^\dagger + a_k a_{-k}) \right] \quad (3)$$

where  $E_{cl} = -2J_2Ns^2$  is the classical ground-state energy, and  $a_k^\dagger = 1/\sqrt{N} \sum_r \exp[-ik \cdot r] a_r^\dagger$ , with  $k = (k_x, k_y)$  varying in the first Brillouin zone of the lattice. Here  $A_k = 2J_2/J_1 + \cos k_x$  and  $B_k = -(\cos k_y + 2J_2/J_1 \cos k_x \cos k_y)$  for  $Q = (0, \pi)$  and with  $k_x \leftrightarrow k_y$  for  $Q = (\pi, 0)$ . Such leading part of the Hamiltonian, being bilinear in the Bose operators, can be diagonalized for  $k \neq (0, 0), (0, \pi), (\pi, 0), (\pi, \pi)$  using the well-known Bogoliubov transformation,  $a_k = u_k \alpha_k + v_k \alpha_{-k}^\dagger$ , with  $u_k = \sqrt{(A_k + \omega_k)/2\omega_k}$ ,  $v_k = -\text{sgn}(B_k) \sqrt{(A_k - \omega_k)/2\omega_k}$ ,  $\omega_k = \sqrt{A_k^2 - B_k^2}$  being the  $sw$  dispersion relation. In contrast, the Goldstone modes cannot be diagonalized by this transformation since  $u_k$  and  $v_k$  are not defined for the  $k$ -vectors for which  $\omega_k = 0$ . For infinite systems such divergences are integrable in two dimensions and do not lead to any contribution. On any finite-size system, instead, they are important and they must be treated independently.

To this end, it is possible to define a set of Hermitian operators commuting with each other and with the Hamiltonian:  $Q_k = i(a_k^\dagger - a_k)$  for  $k = (0, 0)$  and  $(\pi, \pi)$  and  $Q_k = (a_k^\dagger + a_k)$  for  $k = (0, \pi)$  and  $(\pi, 0)$ . With these definitions the Goldstone-mode contribution to (3) reads  $\mathcal{H}_{sm} = J_1s \sum_k^{sm} A_k [Q_k^2 - 1]$ , with the sum extended only to the four singular modes. This allows us to diagonalize the Hamiltonian for any finite size in a basis where the  $Q_k$ 's have definite quantum numbers. In particular, being  $A_k > 0$  for  $J_2/J_1 > 0.5$ ,  $\mathcal{H}_{sm}$  favors a ground state with  $Q_k = 0$  and it is easy to show that this implies to order  $1/s$   $S^y(0, 0) = S^z(0, 0) = 0$  and  $S^y(\pi, \pi) = S^z(\pi, \pi) = 0$  where  $S^\alpha(q) = \sum_r \langle S_0^\alpha S_r^\alpha \rangle e^{iq \cdot r}$  is the  $\alpha$  component of the magnetic structure factor. These relations together with the sum rules  $S^x(0, 0) = S^x(\pi, \pi) = 0$ , following from the translational invariance of the  $sw$  Hamiltonian, are consistent with a singlet ground-state with a zero value of the total spin on each sublattice. This is rigorously true according to the Lieb-Mattis theorem<sup>12</sup> for  $J_2/J_1 \rightarrow \infty$ . In fact, in this limit the system decouples into two independent *n.n.* Heisenberg models on the two sublattices. In general, a singlet ground state is also expected for the  $J_1 - J_2$  model on any finite size with an even number of sites and non-frustrating boundary conditions. The sum rules  $S^\alpha(\pi, \pi) = 0$ , instead, are not necessarily true on a finite size and for finite values of  $J_2/J_1$  but they turn out to be fulfilled with good approximation in the collinear phase (see below).

According to this procedure, the  $sw$  estimate of the ground-state energy reads,  $E_0 = E_{cl} + J_1s \sum_k [\omega_k - A_k]$ , and it turns out to be in remarkable agreement with the exact results for  $s = 1/2$  and  $N = 36$  in the whole range  $J_2/J_1 \gtrsim 0.7$  (Fig. 1), i.e., far enough from the classical critical point  $J_2/J_1 = 0.5$  separating the collinear from the Néel zero-temperature phases. In fact, in this strongly frustrated regime, a non-magnetic ground state of purely quantum mechanical nature is likely to be stabilized for  $s = 1/2$  (Ref. 13). It is therefore natural to expect  $sw$  theory to fail in describing its correlations. Indeed, approaching the fully frustrated point

$J_2/J_1 = 0.5$ , the  $sw$  expansion eventually breaks down leading to a zero value of the antiferromagnetic order parameter<sup>2</sup> and of the uniform susceptibility (see below).

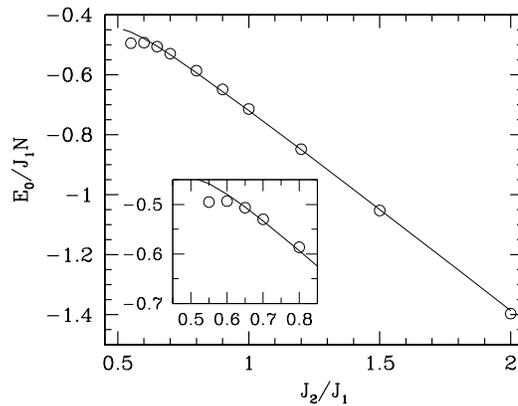


Fig. 1. Ground-state energy as a function of the frustration ratio  $J_2/J_1$ , for  $N = 36$ . The line is the finite-size spin-wave prediction and the empty circles are the exact diagonalization results. The inset is an enlargement of the strongly frustrated regime.

A little more involved calculation allows us also to access the spin-rotation invariant spin-spin correlation functions:  $C(r) = \langle \mathbf{S}_i \cdot \mathbf{S}_{i+r} \rangle$ . The different contributions coming from the two degenerate states in Eq. (2),  $C_Q(r)$ , can be found by adding to the Hamiltonian a term of the form  $\mathcal{H}(h_r) = J_2 h_r / 2 \sum_{i,\tau} \mathbf{S}_i \cdot \mathbf{S}_{i+\tau}$  where the vectors  $\tau$  are the  $z_\tau$  equivalent lattice vectors that can be reached from a site  $i$  with  $|\tau| = |r|$ . The resulting  $sw$  Hamiltonian has the same form of Eq. (3) with field-dependent coefficients and it can be diagonalized similarly to the zero-field case. Then, according to the Hellmann-Feynman theorem,<sup>14</sup> the spin-spin correlations can be obtained by differentiating the  $sw$  energy in presence of the perturbation with respect to  $h_r$ , after a careful treatment of the singular modes. In particular, in the collinear case, such rigorous treatment is possible only assuming for the ground state the symmetric form (2).

The resulting correlation functions have different expressions depending on the form of the vector  $r$ . In particular, for  $r$  connecting the same sublattice, they read:

$$C_Q(r) = s^2 + s\delta_{r,0} - \frac{2s}{N} \sum_k^{ns} (1 - \cos k \cdot r) v_k^2, \quad (4)$$

if  $e^{iQ \cdot r} = 1$ , and

$$C_Q(r) = -s^2 - \frac{4s}{N} + \frac{2s}{N} \sum_k^{ns} (v_k^2 - \cos k \cdot r u_k v_k) \quad (5)$$

if  $e^{iQ \cdot r} = -1$ , with the sums extended to all the non singular ( $ns$ )  $k$ 's. For  $r$  connecting different sublattices, instead, the spin-spin correlations are:

$$C_Q(r) = \frac{s}{N} \sum_k^{ns} (\tau_k v_k^2 - \tilde{\tau}_k u_k v_k), \quad (6)$$

where  $\tau_k = 1/z_\tau \sum_\tau \cos k \cdot \tau$  with  $e^{iQ \cdot \tau} = 1$ , and  $\tilde{\tau}_k = 1/z_\tau \sum_\tau \cos k \cdot \tau$  with  $e^{iQ \cdot \tau} = -1$ . The  $sw$  spin-spin correlation functions calculated as  $C(r) = (C_{(0,\pi)}(r) + C_{(\pi,0)}(r))/2$  are invariant under the symmetry operations of the lattice, as expected for the ground-state expectation values on any finite size. Using these expressions the spin-isotropic magnetic structure factor,  $S(q) = \sum_r C(r) e^{iq \cdot r}$ , can be also calculated. In addition, having obtained an ordered expansion in  $1/s$  for the spin-spin correlation functions,  $C(r) = s^2(e^{i(\pi,0) \cdot r} + e^{i(0,\pi) \cdot r})/2 + s\alpha(r)$ , the antiferromagnetic order parameter,  $m^\dagger = \sqrt{2/NS(Q)}$ ,<sup>15</sup> can be expanded as  $m^\dagger = s(1 + \hat{\alpha}/s)$  with  $\hat{\alpha} = 1/N \sum_r e^{iQ \cdot r} \alpha(r)$ , and it reads:

$$m^\dagger = s \left[ 1 + \frac{2}{Ns} - \frac{1}{Ns} \sum_k^{ns} v_k^2 \right]. \quad (7)$$

Note that for  $N \rightarrow \infty$  the known  $sw$  result<sup>2,3</sup> for the thermodynamic order parameter,  $m^\dagger = \sqrt{\langle 0, \pi | (S_i^x)^2 | 0, \pi \rangle}$ , is recovered. As shown in Fig. 2, the  $sw$  magnetic structure factor,  $S(q)$ , is in remarkable quantitative agreement with the exact diagonalization result for  $s = 1/2$  and  $J_2/J_1 = 1$  for all the wave vectors  $q$ , and the  $sw$  sum rule  $S(\pi, \pi) = 0$  is fulfilled almost exactly. In particular, the  $sw$  approach provides a very accurate estimate (within a few percent) of the antiferromagnetic order parameter in the whole range of  $J_2/J_1 \gtrsim 0.7$ .

The sharp drop of the order parameter at  $J_2/J_1 \simeq 0.7$  is suggestive of a first order transition between the gapped and the collinear phase, as also indicated by a recent variational study.<sup>16</sup> This leads in particular to a very fast saturation of the order parameter to the value of the *n.n.* Heisenberg model,<sup>17</sup> expected for  $J_2/J_1 \rightarrow \infty$ . Remarkably, the  $sw$  prediction for  $J_2/J_1 \gtrsim 1.0$  is in excellent agreement with the result of recent neutron scattering measurements<sup>18</sup> on  $\text{Li}_2\text{VOSiO}_4$ , giving  $m^\dagger = 0.31(2)$  in the zero temperature limit. This compound is known to have  $J_2 \gtrsim J_1$ , even if the precise value of the frustration ratio is presently much debated.<sup>1,6,19</sup> Unfortunately, the weak dependence of the order parameter on  $J_2/J_1$  for  $J_2/J_1 \gtrsim 1.0$  does not allow to use the  $sw$  prediction to determine more precisely this ratio.

Within the finite-size  $sw$  theory, it is also possible to study the structure of the low-energy spin excitation spectrum which is connected to the ground-state antiferromagnetic correlations and to the uniform susceptibility. Following Lavallo

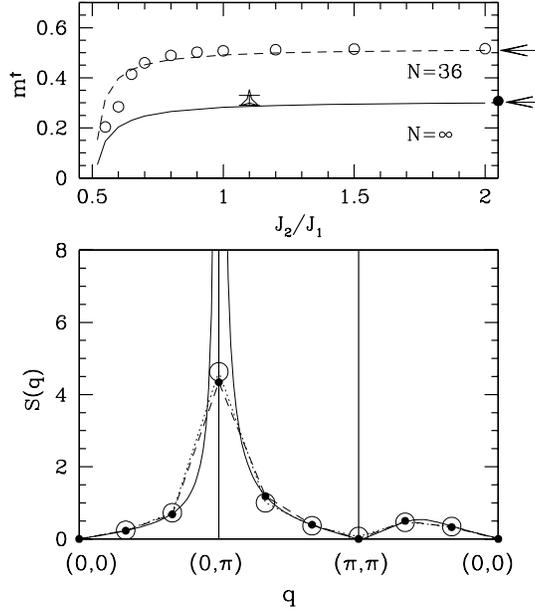


Fig. 2. Lower panel: magnetic structure factor for  $J_2/J_1 = 1$ , and  $N = 36$ . Spin-wave (full dots and dashed line), exact (empty circles and dotted line). Upper panel: antiferromagnetic order parameter at wave vector  $Q$  as a function of the frustration ratio  $J_2/J_1$ , for  $N = 36$ . Spin-wave (dashed line), exact (empty circles). The arrows and the full dot indicate the *sw* and the exact<sup>17</sup> results for the *n.n.* Heisenberg model, respectively, and the star is the experimental result for  $\text{Li}_2\text{VO}_4$ <sup>18</sup> which has a still undetermined  $J_2/J_1 \gtrsim 1$ .<sup>1,6,19</sup> The continuous lines in both panels are the spin-wave results in the thermodynamic limit.

*et al.*,<sup>20</sup> in order to stabilize an excitation of total spin  $S$ , a Zeeman term,  $\mathcal{H}(h) = -hs \sum_i S_i^z$ , is added to the spin Hamiltonian. Classically, for magnetic fields not large enough to induce a spin-flop transition, the classical solution is simply obtained by canting the spins of an angle  $\theta_h$  along the direction of the field  $h$  [ $\sin \theta_h = h/4J_1(1 + 2J_2/J_1)$ ]. After a new rotation of the reference frame in order to align it to the new directions of the spins, the finite-size *sw* expansion is straightforward and again it leads to a linearized Hamiltonian of the same form of Eq. (3) with field-dependent coefficients  $A_k^h = A_k + B_k \sin^2 \theta_h$ ,  $B_k^h = B_k(1 - \sin^2 \theta_h)$ , and classical energy. In this case, due to the reduced spin-rotation symmetry of the Hamiltonian only the  $(0,0)$  and the  $(\pi,\pi)$  modes are singular. The former favors a value of  $S^z(0,0) = N(s \sin \theta)^2$  consistent with the applied field, at the classical level, while the latter generates the usual approximated sum rule  $S^z(\pi,\pi) = 0$ , which is not affected by the uniform field along the  $z$  direction. The total spin  $S = N \langle S_i^z \rangle$  of the excitation can be related to the magnetic field  $h$  by means of the Hellmann-Feynman theorem

$$\langle S_i^z \rangle_h = -\frac{1}{Ns} \frac{\partial}{\partial h} E(h) = s \frac{h}{4J_1(1 + 2J_2/J_1)} \times$$

$$\left[ 1 - \frac{1}{2Ns(1+2J_2/J_1)} \sum_k^{ns} B_k \sqrt{\frac{A_k^h + B_k^h}{A_k^h - B_k^h}} \right], \quad (8)$$

where

$$E(h) = E_{cl} - (sh)^2 \frac{N}{8J_1(1+2J_2/J_1)} + J_1 s \sum_k [\omega_k^h - A_k^h], \quad (9)$$

and  $\omega_k^h = \sqrt{(A_k^h)^2 - (B_k^h)^2}$ . Using these expressions the energy spectrum  $E(S)$  can be calculated by means of a Legendre transform,  $E(S) = E(h) + hsS$ . Besides, the uniform susceptibility in the thermodynamic limit,  $\chi = -1/Ns^2 \partial^2 E(h)/\partial h^2|_{h=0}$ , can be obtained from Eq. (9) by direct derivation and it reads:

$$\chi/\chi_{cl} = 1 - \frac{1}{2s(1+2J_2/J_1)} \int \frac{d^2k}{(2\pi)^2} B_k \sqrt{\frac{A_k + B_k}{A_k - B_k}}. \quad (10)$$

where  $\chi_{cl} = 1/4J_1(1+2J_2/J_1)$  is the susceptibility in the classical limit.

Due to the discreteness of the energy spectrum, a direct comparison of the *sw* susceptibility with the exact diagonalization results is not possible on a finite size. However, in a quantum antiferromagnet with a long-range ordered ground state, the susceptibility is directly related to the properties of the low-energy spectrum and this can be exploited to establish the accuracy of the *sw* predictions. In fact, whenever long-range order is present in the thermodynamic limit, the low-lying spin excitations ( $S \ll \sqrt{N}$ ) order themselves as in the spectrum of a free quantum rotator,  $E(S) - E_0 = S(S+1)/2IN$ , where  $I$  is the so-called *momentum of inertia* per site. This definition is very close to the definition of the uniform spin susceptibility, which can be calculated by taking first the infinite-volume limit of the energy per site at fixed magnetization  $m = S/N$ ,  $e(m) = E(S)/N$ , and then letting  $m \rightarrow 0$ :  $e(m) = e_0 + m^2/(2\chi)$ . As it is known from the low-energy theory of a quantum antiferromagnet,<sup>21</sup> this allows for an identification between  $I$  and  $\chi/N$  so that the quantity  $[2\chi_S]^{-1} = N(E(S) - E_0)[S(S+1)]^{-1}$  approaches for infinite size the physical inverse susceptibility  $1/2\chi$ , for any spin-excitation  $S \ll N$ . This features are clearly verified by the *sw* scheme as it is illustrated in the lower panel of Fig. 3 for  $J_2/J_1 = 1$ , where  $1/2\chi_S$  is plotted for  $S = L \equiv \sqrt{N}$  and approaches the thermodynamic value calculated according to Eq. (10) ( $1/2\chi_{sw} \simeq 11.36$ ).

The comparison with the exact results of the *sw* spectrum  $E(S) - E_0$  vs  $S(S+1)$  (inset of Fig. 3), and, equivalently, of the quantity  $1/2\chi_{S=1}$  (upper panel of Fig. 3) demonstrates the accuracy of *sw* theory in estimating the spin susceptibility of the  $J_1$ - $J_2$  model in the collinear phase for  $J_2/J_1 \gtrsim 0.8$ . As it is shown in the same figure (upper panel), the classical uniform susceptibility is strongly renormalized by quantum fluctuations for  $s = 1/2$  at the *sw* level. As expected, approaching  $J_2/J_1 = 0.5$  such reduction is enhanced due to the increased frustration and it leads eventually to the vanishing of the susceptibility for  $J_2/J_1 \simeq 0.507$  and to the expected transition to a spin-gapped non-magnetic phase.<sup>7</sup> However, from the comparison with the exact diagonalization results for both the uniform susceptibility

and the order parameter, it appears clear that the effects of quantum fluctuations are underestimated by the *sw* expansion in the regime of strong frustration so that the transition to the non-magnetic region is likely to occur at slightly higher values of the  $J_2/J_1$  ratio ( $J_2/J_1 \simeq 0.6$ ).

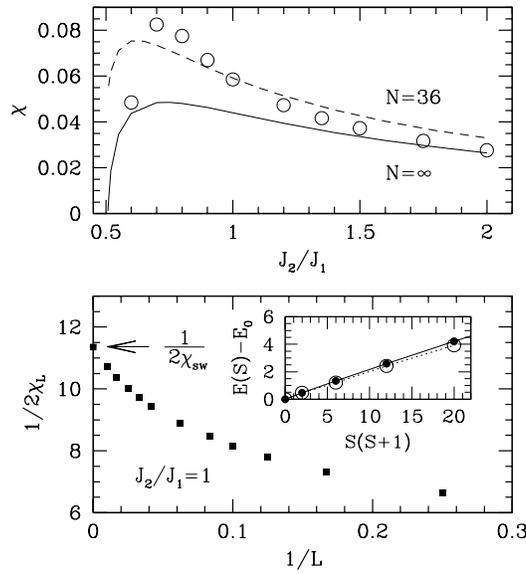


Fig. 3. Lower panel: size dependence of the spin-wave  $1/2\chi_L$  (see text) for  $J_2/J_1 = 1$ . Inset: spin-wave (full dots and continuous line) and exact (empty circles and dotted line) low-energy spectra as a function of  $|\mathbf{S}^2| = S(S+1)$  for  $N = 36$ , and  $J_2/J_1 = 1$ . Upper panel: uniform susceptibilities as a function of  $J_2/J_1$ . Dashed line: spin-wave  $\chi_{S=1}$  for  $N = 36$ . Empty circles: exact  $\chi_{S=1}$  for  $N = 36$ . Continuous line: thermodynamic spin-wave  $\chi$ .

### 3. Conclusions

In conclusion, we have presented a finite-size spin-wave study of the  $J_1 - J_2$  Heisenberg antiferromagnet in the collinear phase, focusing in particular on the ground-state spin-spin correlations and the low-energy excitations. For  $s = 1/2$ , the comparison with exact diagonalization results reveals a remarkable agreement for  $J_2/J_1 \gtrsim 0.8$ . In particular, both the antiferromagnetic structure factor and the spin susceptibility are very close to the spin-wave predictions. The accuracy of the results on finite sizes indicates that the spin-wave expansion provides a quantitatively reliable description of the ground state of the  $J_1 - J_2$  model in the experimentally relevant regime  $J_2 \gtrsim J_1$ . This is confirmed by recent neutron scattering measurements on  $\text{Li}_2\text{VO}_2\text{SiO}_4$ , providing a value of the order parameter in excellent agreement with the spin-wave prediction in the collinear phase,  $m^\dagger \simeq 0.3$ .

The accuracy of spin-wave theory in describing the low-energy excitations also suggests that theoretical approaches to the thermodynamics based on a Gaussian treatment of quantum fluctuations, such as effective Hamiltonian methods,<sup>22</sup> are likely to successfully describe the finite-temperature properties of the  $J_1$ – $J_2$  model in the collinear phase. Work on this line of research would allow to establish a closer contact between the frustrated Heisenberg model and the physical properties of the recently synthesized collinear antiferromagnets, helping in their precise characterization and in the determination of the actual frustration ratios.

I wish to thank Alberto Parola, Sandro Sorella, and Valerio Tognetti for their teachings, support, and continuous encouragement. Special thanks to Pietro Carretta for a very useful correspondence and for kindly communicating the experimental results on  $\text{Li}_2\text{VOSiO}_4$  before publication. Thanks to Federico Becca for help in performing the Lanczos calculations, and to Frederic Mila, and Doug Scalapino for many fruitful discussions. Special thanks also to Liz Osterberg for a careful reading of the manuscript. CPU time kindly provided by SISSA and INFM-Democritos is gratefully acknowledged. This work was supported by NSF under grant DMR-9817242.

## References

1. R. Melzi, P. Carretta, A. Lascialfari, M. Mambrini, M. Troyer, P. Millet, and F. Mila, *Phys. Rev. Lett.* **85**, 1318 (2000); R. Melzi, S. Aldovrandi, F. Tedoldi, P. Carretta, P. Millet, and F. Mila, *Phys. Rev.* **B64**, 024409 (2001). P. Carretta, R. Melzi, N. Papinutto, and P. Millet, *Phys. Rev. Lett.* **88**, 47601 (2002); P. Carretta, N. Papinutto, C. B. Azzoni, M.C. Mozzati, E. Pavarini, S. Gonthier, and P. Millet, cond-mat/0205092.
2. P. Chandra and B. Doucot, *Phys. Rev.* **B38**, 9335 (1988).
3. H. J. Schulz, T. A. L. Ziman, and D. Poilblanc, *J. Phys. I (France)* **6**, 675 (1996).
4. P. Chandra, P. Coleman, and A. I. Larkin, *Phys. Rev. Lett.* **64**, 88 (1990).
5. R. R. P. Singh, W. Zheng, J. Oitmaa, O. P. Sushkov, and C. J. Hamer, cond-mat/0303075.
6. G. Misguich, B. Bernu, and L. Pierre, cond-mat/0302583.
7. See for instance: L. Capriotti, *Int. J. Mod. Phys.* **B15**, 1799 (2001).
8. E. Manousakis, *Rev. Mod. Phys.* **63**, 1 (1991).
9. Q. F. Zhong and S. Sorella, *Europhys. Lett.* **21**, 629 (1993).
10. C. Lanczos, *J. Res. Nat. Bur. Stand.* **45**, 255. See also: W. D. Joubert in *Siam J. on Matrix Anal. and Appl.*, Volume 13, Number 3, July 1992.
11. M. Takahashi, *Phys. Rev.* **B40**, 2494 (1989); J. E. Hirsch and S. Tang, *Phys. Rev.* **B40**, 4769 (1989); H. Nishimori and Y. Saika, *J. Phys. Soc. Jpn.* **59**, 4454 (1990).
12. E. Lieb and D. Mattis, *J. Math. Phys.* **3**, 749 (1962).
13. The nature of the non-magnetic phase is presently a debated issue. See for instance: L. Capriotti, F. Becca, A. Parola, and S. Sorella, *Phys. Rev. Lett.* **87**, 097201 (2001); *Phys. Rev.* **B67**, 212402 (2003); V.N. Kotov, J. Oitmaa, O.P. Sushkov, and Z. Weihong, *Phil. Mag. B*, **80** 1483 (2000).
14. R.P. Feynman, *Phys. Rev.* **56**, 340 (1939).
15. The factor 2 appearing in this definition is related to the two-fold degeneracy of the  $(0, \pi)$  and  $(\pi, 0)$  states,<sup>3</sup> and allows one to recover the *n.n.* Heisenberg limit for  $J_2/J_1 \rightarrow \infty$ .
16. A. Parola, F. Becca, L. Capriotti, and S. Sorella, *J. Mag. Mag. Mat.*, to be published.

17. A.W. Sandvik, *Phys. Rev.* **B56**, 11678 (1997); M. Calandra Buonauro and S. Sorella, *Phys. Rev.* **B57**, 11446 (1998).
18. A. Bombardi, L. Paolasini, P. Carretta, J. Rodriguez-Carvajal, P. Millet, and R. Caciuffo, communicated by P. Carretta.
19. H. Rosner, R. R. P. Singh, W. H. Zheng, J. Oitmaa, S.-L. Drechsler, and W. E. Pickett, *Phys. Rev. Lett.* **88**, 186405 (2002).
20. C. Lavalle, S. Sorella and A. Parola, *Phys. Rev. Lett.* **80**, 1746 (1998).
21. S. Chakravarty, B.I. Halperin, and D.R. Nelson, *Phys. Rev. Lett.* **60**, 1057 (1988)
22. A. Cuccoli, V. Tognetti, R. Vaia, and P. Verrucchi, *Phys. Rev. Lett.* **77**, 3439 (1996).