

Strong electron-Boson coupling effect in the infrared spectra of $Tl_2Ba_2CaCu_2O_{8+\delta}$

N. L. Wang,* P. Zheng, J. L. Luo, and Z. J. Chen

*Key Laboratory of Extreme Conditions Physics, Institute of Physics,
Chinese Academy of Sciences, P. O. Box 603, Beijing 100080, P. R. China*

S. L. Yan, L. Fang, and Y. C. Ma

Department of Electronics, NanKai University, Tianjin 300071, P. R. China

We report on a study of the in-plane infrared response of a $Tl_2Ba_2CaCu_2O_{8+\delta}$ film with $T_c=108$ K. The fingerprint evidence for a strong electron-Boson coupling has been observed. The raw reflectance below T_c exhibits a knee structure at around 650 cm^{-1} and the ratio of the reflectances below and above T_c displays a pronounced minimum at around 1000 cm^{-1} . In particular, the features appear at higher energy scale than other bilayer cuprates with T_c around 90-95 K. The gap amplitude and the Boson mode energy were extracted from the analysis of the bosonic spectral function. In comparison with several other optimally doped high- T_c cuprates, we find that the gap size scales with T_c , but Boson mode energy has a tendency to decrease.

PACS numbers: 74.25.Gz, 74.72.Jt, 74.78.Bz

Superconductivity requires the electrons being glued together in pairs. In conventional superconductors the pairing is due to the coupling between electrons and phonons. Although the Boson responsible for mediating the pairing or the "glue" in high temperature superconducting cuprates (HTSC) remains elusive, evidence for strong electron-Boson coupling effects began to accumulate in various charge spectroscopies. In particular, many of them are suggestive of a magnetic mode to glue the charge carriers together. For example, the photoemission line shape near $(\pi,0)$ in many of the HTSC in the superconducting state is characterized by a sharp peak, followed at higher energy by a dip and broad hump.¹ As one moves towards the zone diagonal, a kink in the dispersion develops.^{2,3} The kink appears at the same energy scale as the dip.² These anomalies were widely believed to result from the interaction of electrons with a collective mode which appears below T_c . The inferred mode energy and its temperature dependence agree well with the magnetic resonance observed at (π,π) by neutron scattering.^{4,5,6} The coupling of the electrons with magnetic mode has also been indicated in the tunneling spectra of $Bi_2Sr_2CaCu_2O_{8+\delta}$ (Bi2212), where a sharp dip was observed at a voltage beyond the gap edge 2Δ .⁷

Study of electron-phonon coupling effects in infrared spectra of conventional superconductors began in early 1970's.⁸ Progresses have been made in recent years. Marsiglio *et al.*⁹ showed that the electron-phonon spectral function $\alpha^2F(\Omega)$ is closely related to the optical scattering rate

$$\frac{1}{\tau(\omega)} = \frac{\omega_p^2}{4\pi} Re \frac{1}{\sigma(\omega)} = \frac{\omega_p^2}{4\pi} \frac{\sigma_1(\omega)}{\sigma_1^2(\omega) + \sigma_2^2(\omega)}, \quad (1)$$

where ω_p is the plasma frequency. They found that

$$W(\omega) = \frac{1}{2\pi} \frac{d^2}{d\omega^2} \left[\omega \frac{1}{\tau(\omega)} \right] \quad (2)$$

is very close to $\alpha^2F(\Omega)$ in the phonon region with

additional wiggles beyond the phonon cutoff. However, no correlation between the structure in $W(\omega)$ and phonon density of states has been established for high- T_c cuprates. Instead, signature of the spin resonance mode in neutron experiment is also indicated in the in-plane infrared spectrum. Carbotte *et al.*¹⁰ analyzed optical conductivity $\sigma(\omega)$ in magnetically mediated d-wave superconductors and argued that $W(\omega)$ of equ.(2) still gives a good approximation to the charge-spin spectral density and that the spin resonance feature should show up in $W(\omega)$ as a result of coupling of the electrons to this magnetic mode. In particular, the peak in $W(\omega)$ below T_c is correlated to $\Delta + \Omega$, where Ω is the energy of the spin resonance mode.¹¹ In another theoretical study of optical conductivity in superconductors with quasiparticles strongly coupled to their own collective spin modes, Abanov *et al.*¹² emphasized that a deep minimum locating at $2\Delta + \Omega_s$ in $W(\omega)$ is more relevant to superconductivity. They also identified two weaker high frequency singularities at 4Δ and $2\Delta + 2\Omega$. More recently, Shulga¹³ pointed out that the minimum in the ratio of the raw reflectance $R_s(\omega)/R_n(\omega)$ is the key evidence for the Boson-mediated superconductivity. He showed that the minimum locates at frequency of $2\Delta + \Omega$, where the scattering rate displays a peak. Obviously, identifying these features in the infrared spectra represents the fingerprint evidence for the electron-Boson coupling in high- T_c cuprates.

In this paper, we report on a study of the in-plane infrared response of a $Tl_2Ba_2CaCu_2O_{8+\delta}$ (Tl2212) film with $T_c=108$ K. The above mentioned features in reflectance spectra are clearly observed, providing unambiguous evidence for the strong electron-Boson coupling effect in this bilayer cuprate with higher T_c . In particular, the features appear at higher energy scale than other bilayer cuprates with T_c around 90-95 K. We compared the results on Tl2212 with other high- T_c cuprates, and suggest that a magnetic resonance mode exists in this bilayer material.

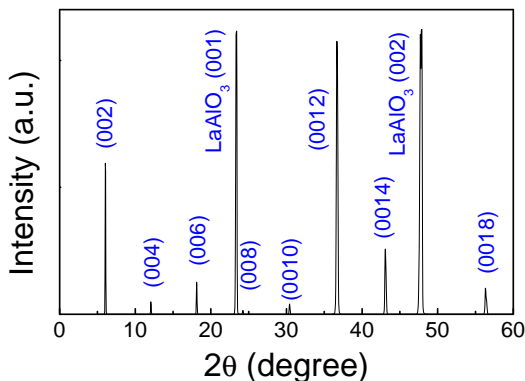


FIG. 1: The X-ray diffraction pattern for a Tl2212 film. All the sharp peaks can be assigned to the (00l) peaks of Tl2212 except those of LaAlO₃ substrate.

Epitaxial Tl₂Ba₂CaCu₂O_{8+δ} films were grown on LaAlO₃ substrates by dc magnetron sputtering and a post-annealing process. X-ray diffraction measurements confirm that the films were strongly textured with the c-axis parallel to the c-axis of the substrate, as shown in Fig. 1. Details of the film growth were described elsewhere.¹⁴ Optimally doped films with thickness of 4000 Å were used for optical reflectance measurements. The reflectance measurements from 50 to 25000 cm⁻¹ for **E** ∥ ab-plane were carried out on a Bruker 66v/S spectrometer with the samples mounted on optically black cones in a cold-finger flow cryostat using an *in situ* overcoating technique.¹⁵ The optical conductivity spectra were derived from the Kramers-Kronig transformation.

Figure 2 shows the temperature dependent resistivity of the Tl2212 film. The zero-resistance temperature T_{c0} is 108 K, which is much higher than other optimally doped bilayer cuprates with $T_{c0} \sim 90$ -95 K. The raw reflectances $R(\omega)$ from 50 to 2000 cm⁻¹ and the calculated optical conductivities $\sigma_1(\omega)$ at different temperatures are displayed in Fig. 3(a) and 3(b), respectively. It should be pointed out that the thickness of 4000 Å of our films appears sufficient to avoid signals from the substrate. For this purpose, we show, in the inset of Fig. 3(b), the far-infrared reflectance spectrum measured on LaAlO₃ substrate at room temperature. The spectrum is dominated by phonon peaks. However, no clear features at the energies corresponding to the phonon peaks could be detected in $R(\omega)$ of the Tl2212 film.

In the normal state, the reflectance spectra show roughly linear frequency dependence. With decreasing temperature, the low- ω $R(\omega)$ increases, being consistent with the metallic behavior of the sample. At 10 K in the superconducting state, $R(\omega)$ shows a knee structure at around 650 cm⁻¹. Above this frequency, the reflectance drops fast and becomes lower than the normal-state values at around 1000 cm⁻¹. $R(\omega)$ recovers the linear-frequency dependence at higher frequencies. Similar but weak behaviors were seen at 95 K, which is close to T_c . The change of the $R(\omega)$ in the superconducting state with respect to the normal state could be seen

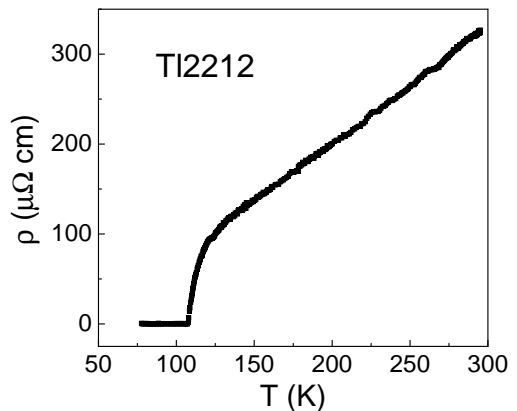


FIG. 2: The resistivity vs. temperature curve for the film with zero resistivity at 108 K

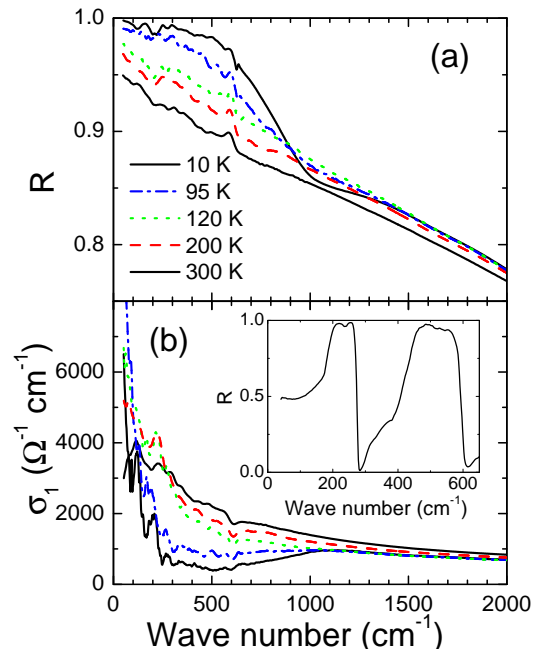


FIG. 3: ab-plane optical data from 50 to 2000 cm⁻¹ of the optimally doped Tl-2212 with $T_c=108$ K. (a) the temperature-dependent reflectance and (b) the temperature-dependent $\sigma_1(\omega)$. Inset: the far-infrared reflectance of the substrate LaAlO₃ at room temperature.

more clearly from the plot of the ratio of the reflectance below T_c over that above T_c . Fig. 4(a) shows the ratio of $R_{10K}(\omega)/R_{120K}(\omega)$ as a function of frequency. It becomes evident that a maximum at around 650 cm⁻¹ and a minimum at around 1000 cm⁻¹ exist in the plot. The scattering rate $1/\tau(\omega)$ spectra at 10 K and 120 K, extracted from equ. (1) with the use of plasma frequency of 1.6×10^3 cm⁻¹ determined by summarizing the optical conductivity up to 1 eV, are displayed in Fig. 4(b). We can see that, at frequencies corresponding to the maximum and minimum in the $R_{10K}(\omega)/R_{120K}(\omega)$ plot, the $1/\tau(\omega)$ at 10 K exhibits a rapid rise and a peak or a substantial overshoot of the normal state result, respectively.

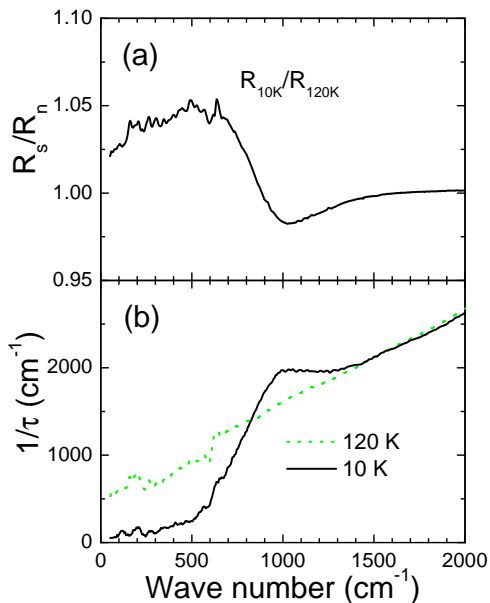


FIG. 4: (a) The reflectance ratio below and above T_c as a function of frequency. (b) The frequency-dependent scattering rate $1/\tau(\omega)$ spectra at 10 K and 120 K.

Obviously, the features caused by strong electron-Boson coupling as discussed by Shulga¹³ were observed in infrared spectra of the optimally doped $\text{Tl}_2\text{Ba}_2\text{CaCu}_2\text{O}_{8+\delta}$ with $T_{c0}=108$ K. The present work is very suggestive that a simple deviation or suppression from the linear-frequency dependence in $1/\tau(\omega)$, *i.e.* the so-called "pseudogap" feature in ab-plane optical response, may not be a direct indication for the Boson mode being coupled to the electronic spectra. The dip in the reflectance ratio R_s/R_n or the "overshoot" in $1/\tau(\omega)$ is more essential. We note that the overshoot feature was observed previously on optimally doped $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (YBCO) by Basov et al.¹⁶ and $\text{HgBa}_2\text{Ca}_2\text{Cu}_3\text{O}_{8+\delta}$ (Hg1223) by McGuire et al.¹⁷. The features in Bi2212 are weak, but a recent study by Tu et al.¹⁸ made it clear that those features exist. However, the "overshoot" behavior is absent in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_{4+\delta}$ (LSCO), although the suppression of low- ω scattering rate is still observed.¹⁹

Another remarkable observation here is that the "overshoot" feature in $1/\tau(\omega)$ appears at higher energy than the corresponding features in YBCO and Bi2212, which are in the range of about 800 - 900 cm^{-1} .^{16,18} We note that the feature in Hg1223 with $T_c=130$ K locates at even higher frequency beyond 1100 cm^{-1} .¹⁷ Therefore, there is a tendency that the energy of the feature scales with the superconducting transition temperature.

There are two different opinions about the origins of the Bosons seen in charge spectroscopies. One is phonon origin³ and the other the magnetic mode origin. We found that the phonon scenario is inconsistent with the present experiment, for the feature is seen only in the superconducting state, whereas phonons exist also in the

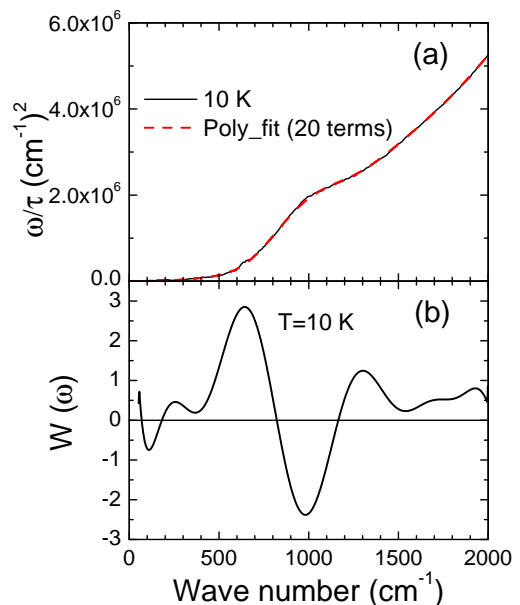


FIG. 5: (a) The experimental data of $\omega/\tau(\omega)$ at 10 K together with a 20-term polynomial fit. (b) The bosonic spectral function $W(\omega)$ vs. frequency derived from the polynomial fit curve.

normal state. Recent study on the oxygen isotope effect in the ab-plane optical properties of YBCO also ruled out the phonons as the main player.²⁰ By contrast, Tl2212 shares the same coupling behavior as the YBCO and Bi2212, where suggestions for the magnetic origin were proposed from the inversion of the ab-plane optical conductivity.^{10,18,21} Note that, neutron experiments revealed a main difference for the resonances in optimally doped YBCO and Bi2212: the resonance peak in the later material exhibits a considerable broadening in both energy and wave vector, which was interpreted to be caused by the intrinsic inhomogeneities in Bi2212.²² Therefore, We can ascribe the weak "dip" or "overshoot" features in Bi2212 to the broadening of the resonance peak. The absence of those features in LSCO might be related to the absence of the magnetic resonance. Since the "overshoot" feature in Tl2212 is prominent, like the case in YBCO, we suggest that a sharp magnetic resonance mode exists in this material.

The above discussion on the dip or "overshoot" behavior appears at frequency of $2\Delta + \Omega$, which contains the superconducting gap and a Boson mode. It would be much desired to separate the two different energy scales. This might be achieved from the analysis of the bosonic spectral function $W(\omega)$ defined in equ.(2). Since $W(\omega)$ is obtained by taking the second derivative of the function $\omega/\tau(\omega)$, a smoothing of the experimental data is required. Tu et al.¹⁸ suggested an unambiguous method to extract $W(\omega)$ by fitting the experimental measured quantity $\omega/\tau(\omega)$ with high-order polynomial. This method has been used in present analysis. In Fig. 5 (a), the $\omega/\tau(\omega)$ at 10 K is shown together with a 20-term polynomial fit. The resulting spectral function $W(\omega)$ vs. fre-

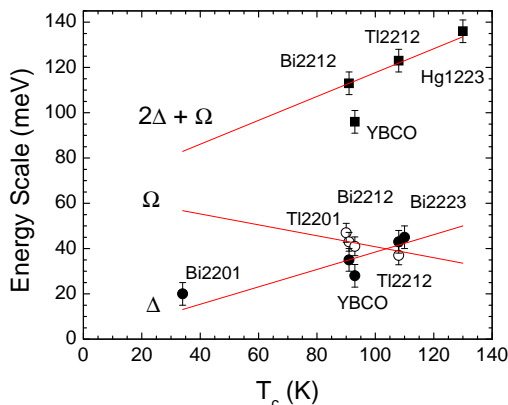


FIG. 6: Plots of Δ , Ω and the energy of overshoot ($2\Delta + \Omega$) versus T_c for several optimally doped cuprates. The data for Bi2212¹⁸ and YBCO¹⁰ are from inversion of optical spectra. The Δ values for Bi2201 and Bi2223 are from photoemission study (peak position gap).²³ Hg1223 data is from¹⁷. The Ω value for Tl2201 is from neutron experiment.²⁴ The straight lines are for eye guidance. We start to put straight lines for ($2\Delta + \Omega$) and Ω , the third one for Δ is then extracted.

quency is displayed in Fig.5 (b). We can see a large maximum at about 650 cm^{-1} , a deep negative minimum at 1000 cm^{-1} , and a weak maximum at around 1300 cm^{-1} . According to Carbotte et al.,¹⁰ the large maximum corresponds to $\Delta + \Omega$. In terms of Abanov et al.¹², the other two features correspond to $2\Delta + \Omega$ and $2\Delta + 2\Omega$, respectively. Then, we obtain $\Delta=350 \text{ cm}^{-1}$ (or 43 meV) and $\Omega=300 \text{ cm}^{-1}$ (or 37 meV) for $\text{Tl}_2\text{Ba}_2\text{CaCu}_2\text{O}_{8+\delta}$.

We find obviously that the extracted gap Δ is larger than the values for Bi2212 (35 meV) and YBCO (28 meV), but the Boson mode energy Ω is smaller than the corresponding values of 43 meV for Bi2212 and 41 meV for YBCO.^{10,18} Since the T_c of Tl2212 is very close to that of Bi2223, it would be interesting to compare the result with Bi2223. The gap amplitudes for $n=1, 2, 3$ compounds in Bi-based family have been studied in photoemission experiments by Feng et al.²³ They found that the leading-edge-midpoint (peak position) gap values are 10 (21), 24 (40), 30 (45) meV for $n=1, 2, 3$ systems, respectively. It is seen that the gap values for Bi2212 and Tl2212 extracted from in-plane optical data are more closer (but a bit smaller) to their peak position gap values for $n=2$ and 3 systems. In Fig.6, we plot Δ , Ω and the energy of "overshoot" ($2\Delta + \Omega$) versus T_c for several optimally doped cuprates where those data are available. We find that the gap increases with T_c , but the Boson mode energy has the tendency to decrease with T_c . In the figure, the data of YBCO appear to deviate substantially from the scaling behavior. The reason is not clear.

One possibility is that the existence of the Cu-O chains, which also become superconducting below T_c , helps to enhance T_c , even though its gap value is smaller than Bi2212 and Tl2201.

Earlier studies have established that the T_c in optimally doped cuprates is proportional to the condensed carrier density n_s . The present study shows that T_c is also correlated with the energy scale of the superconducting gap Δ . Within current understanding, both the n_s and Δ are important quantities characterizing superconducting state. Δ reflects the pairing strength, while n_s is an indication of the phase stiffness of the pairing.^{23,25} To achieve maximum T_c , both the superconducting gap and the condensate should be maximized.

Finally, we briefly comment on the two sizeable features at 600 cm^{-1} and 230 cm^{-1} , which are present in all measured temperatures. Since the frequencies are away from the phonon modes of the substrate,²⁶ they are not likely to come from the substrate due to the possible leakage of the film in the long wave length region. The high-frequency mode was seen in other high- T_c cuprates, e.g. Bi2212¹⁸ and YBCO^{16,20}, and was assigned to the transverse optic phonon (Cu-O stretching mode). The 230 cm^{-1} mode was also reported in earlier reflectance study on YBCO, where it was suggested to be of electronic origin for the spectral weight of the mode was found to be an order of magnitude larger than what is expected for a phonon.²⁷ Comparing the present data with those studies, we found that the high-frequency mode appears as an antiresonance rather than a peak in the conductivity spectra, and the strength of the 230 cm^{-1} mode is not weakened very much at high temperature, which is in contrast to the reported behavior in YBCO. Further studies are required to illustrate the difference.

In summary, we have presented a set of high-quality in-plane optical data for $\text{Tl}_2\text{Ba}_2\text{CaCu}_2\text{O}_{8+\delta}$ (Tl2212) with $T_c=108 \text{ K}$. The fingerprint evidence for strong electron-Boson coupling effect has been observed in reflectance spectra for this bilayer cuprate with higher T_c . In particular, the energy scale of the feature appears at higher energy than other bilayer cuprates with T_c around 90-95 K. The gap amplitude and the Boson mode energy were extracted from the analysis of the bosonic spectral function. It is found that the gap size scales with T_c for different cuprates. We discussed the origin of the Boson and compared the results on Tl2212 with other high- T_c cuprates.

This work is supported by National Science Foundation of China (No.10025418, 19974049), the Knowledge Innovation Project of Chinese Academy of Sciences.

* Electronic address: nlwang@aphy.iphy.ac.cn

¹ D. S. Dessau, B. O. Wells, Z.CX. Shen, W. E. Spicer, A. J. Arko, R. S. List, D. B. Mitzi and A. Kapitulnik, Phys.

Rev. Lett. **66**, 2160 (1991).

² A. Kaminski, M. Randeria, J. C. Campuzano, M. R. Norman, H. Fretwell, J. Mesot, T. Sato, T. Takahashi, and K.

- Kadowaki, Phys. Rev. Lett. **86**, 1070 (2001).
- ³ A. Lanzara, P. V. Bogdanov, X. J. Zhou, S. A. Keller, D. L. Feng, E. D. Lu, Y. Yoshida, A. Fujimori, K. Kishio, J.-I. Shimoyama, T. Noda, S. Uchida, Z. Hussain, and Z. X. Shen, Nature **412**, 510 (2001).
 - ⁴ H. Ding, A. F. Bellman, J. C. Campuzano, M. Randeria, M. R. Norman, T. Yokoya, T. Takahashi, H. Katayama-Yoshida, T. Mochiku, K. Kadowaki, G. Jennings, and G. P. Brivio, Phys. Rev. Lett. **76**, 1533 (1996).
 - ⁵ M. R. Norman, H. Ding, J. C. Campuzano, T. Takeuchi, M. Randeria, T. Yokoya, T. Takahashi, T. Mochiku, and K. Kadowaki, Phys. Rev. Lett. **79**, 3506 (1997).
 - ⁶ J. C. Campuzano, H. Ding, M. R. Norman, H. M. Fretwell, M. Randeria, A. Kaminski, J. Mesot, T. Takeuchi, T. Sato, T. Yokoya, T. Takahashi, T. Mochiku, K. Kadowaki, P. Guptasarma, D. G. Hinks, Z. Konstantinovic, Z. Z. Li, and H. Raffy, Phys. Rev. Lett. **83**, 3709 (1999).
 - ⁷ J. F. Zasadzinski, L. Ozyuzer, N. Miyakawa, K. E. Gray, D. G. Hinks, and C. Kendziora, Phys. Rev. Lett. **87**, 067005 (2001).
 - ⁸ R. R. Joyce and P. L. Richards, Phys. Rev. Lett. **24**, 1007 (1970); P. B. Allen, Phys. Rev. B **3**, 305 (1971); B. Farnworth and T. Timusk, Phys. Rev. B **10**, 2799 (1974).
 - ⁹ F. Marsiglio, T. Startseva, and J. P. Carbotte, Phys. Lett. A **245**, 172 (1998).
 - ¹⁰ J. P. Carbotte, E. Schachinger, and D. N. Basov, Nature (London) **401**, 354 (1999).
 - ¹¹ Ph. Bourges, Y. Sidis, H. F. Fong, B. Keimer, L. P. Regnault, J. Bossy, A. S. Ivanov, D. L. Milius, and I. A. Aksay, in *High Temperature Superconductivity*, edited by S. E. Barnes et al., AIP Conf. Proc. No. 483 (AIP, Woodbury, N. Y., 1999), pp. 207-212.
 - ¹² A. Abanov, A. V. Chubukov, and J. Schmalian, Phys. Rev. B **63**, 180510(R) (2001).
 - ¹³ S. V. Shulga, in *Material Science, Fundamental Properties and Future Electronic Applications of High-Tc Superconductors*, edited by S.-L. Drechsler and T. Mishonov (Kluwer Academic Publishers, Dordrecht, 2001), pp. 323-360.
 - ¹⁴ S. L. Yan, L. Fang, M. S. Si, H. L. Cao, Q. X. Song, J. Yan, X. D. Zhou, and J. M. Hao, Supercond. Sci. Technol. **7**, 681 (1994).
 - ¹⁵ C. C. Homes, M. Reedyk, D. A. Crandles, and T. Timusk, Appl. Opt. **32**, 2973 (1993).
 - ¹⁶ D. N. Basov, R. Liang, B. Dabrowski, D. A. Bonn, W. N. Hardy, and T. Timusk, Phys. Rev. Lett. **77**, 4090 (1996).
 - ¹⁷ J. J. McGuire, M. Windt, T. Startseva, T. Timusk, D. Colson and V. Viallet-Guillen, Phys. Rev. B **62**, 8711 (2000).
 - ¹⁸ J. J. Tu, C. C. Homes, G. D. Gu, D. N. Basov, and M. Strongin, Phys. Rev. B **66**, 144514 (2002).
 - ¹⁹ T. Startseva, T. Timusk, A. V. Puchkov, D. N. Basov, H. A. Mook, M. Okuya, T. Kimura, and K. Kishio, Phys. Rev. B **59**, 7184 (1999).
 - ²⁰ N. L. Wang, T. Timusk, J. P. Franck, P. Schweiss, M. Braden, and A. Erb, Phys. Rev. Lett. **89**, 087003 (2002).
 - ²¹ N. L. Wang and B. P. Clayman, Phys. Rev. B **63**, 052509 (2000).
 - ²² Ph. Bourges, B. Keimer, S. Pailhes, L. P. Regnault, Y. Sidis, and C. Ulrich, cond-mat/0211227, to be published in LT23 proceedings.
 - ²³ D. L. Feng, A. Damascelli, K. M. Shen, N. Motoyama, D. H. Lu, H. Eisaki, K. Shimizu, J.-i. Shimoyama, K. Kishio, N. Kaneko, M. Greven, G. D. Gu, X. J. Zhou, C. Kim, F. Ronning, N. P. Armitage, and Z.-X. Shen, Phys. Rev. Lett. **88**, 107001 (2002).
 - ²⁴ H. F. He, P. Bourges, Y. Sidis, C. Ulrich, L. P. Regnault, S. Pailhs, N. S. Berzigiarova, N. N. Kolesnikov, and B. Keimer, Science **295**, 1045 (2002).
 - ²⁵ V. J. Emery and S. A. Kivelson, Nature **374**, 434 (1995).
 - ²⁶ A Kramers-Kronig transformation of the reflectance of the substrate results in two strong phonon modes at frequencies of 486 cm^{-1} and 186 cm^{-1} .
 - ²⁷ C. Berhard, T. Holden, J. Humlicek, D. Munzar, A. Golnik, M. Klaser, Th. Wolf, L. Carr, C. Homes, B. Keimer, and M. Cardona, Solid State Communi. **121**, 93 (2002).