

# Cyclotron Resonance in Ferromagnetic InMnAs/(Al,Ga)Sb Heterostructures

G. A. Khodaparast and J. Kono\*

*Department of Electrical and Computer Engineering, Rice Quantum Institute,  
and Center for Nanoscale Science and Technology, Rice University, Houston, Texas 77005*

Y. H. Matsuda,<sup>†</sup> S. Ikeda, and N. Miura

*Institute for Solid State Physics, University of Tokyo, Kashiwa, Chiba 277-8581, Japan*

T. Slupinski,<sup>‡</sup> A. Oiwa,<sup>§</sup> and H. Munekata

*Imaging Science and Engineering Laboratory, Tokyo Institute of Technology, Yokohama, Kanazawa 226-8503,  
and Kanazawa Academy of Science and Technology, Kawasaki, Kanazawa 213-0012, Japan*

Y. Sun, F. V. Kyrychenko, G. D. Sanders, and C. J. Stanton

*Department of Physics, University of Florida, Box 118440, Gainesville, Florida 32611-8440*

(Dated: March 22, 2022)

We report the observation of hole cyclotron resonance (CR) in InMnAs/(Al,Ga)Sb heterostructures in a wide temperature range covering both the paramagnetic and ferromagnetic phases. We observed two pronounced resonances that exhibit drastic changes in position, linewidth, and intensity at a temperature higher than the Curie temperature, indicating possible local magnetic ordering or clustering. We attribute the two resonances to the fundamental CR transitions expected for delocalized valence-band holes in the quantum limit. Using an 8-band  $\mathbf{k}\cdot\mathbf{p}$  model, which incorporates ferromagnetism within a mean-field approximation, we show that the temperature-dependent CR peak shift is a direct measure of the carrier-Mn exchange interaction. Significant line narrowing was observed at low temperatures, which we interpret as the suppression of localized spin fluctuations.

The interaction of free carriers with localized spins plays an important role in a variety of physical situations in metals [1, 2, 3]. Carriers near a magnetic ion are spin-polarized, which can mediate an indirect exchange interaction between magnetic ions. The carrier-induced ferromagnetism realized in Mn-doped III-V semiconductors [4] has provided a novel system in which to study itinerant carriers interacting with localized spins in the dilute limit. Various mechanisms have been suggested but the microscopic origin of carrier-induced ferromagnetism is still controversial [5]. One of the unanswered questions is the nature of the carriers, i.e., whether they are in the impurity band ( $d$ -like), the delocalized valence bands ( $p$ -like), or some type of mixed states.

Here we report a clear observation of hole cyclotron resonance (CR) in ferromagnetic InMnAs/(Al,Ga)Sb, demonstrating the existence of delocalized  $p$ -like carriers. In addition, this is the first CR study in any ferromagnet covering temperatures ( $T$ 's) both below and above the Curie temperature ( $T_c$ ) [6]. CR is a direct method for determining carrier effective masses and therefore the nature of the carrier states. In all samples studied, we ob-

served two resonances, both of which exhibited unusual  $T$ -dependence in position, intensity, and width. The lower-field line showed an abrupt reduction in width with a concomitant decrease in resonance field above  $T_c$ . The higher-field line, which was absent at room  $T$ , suddenly appeared above  $T_c$ , rapidly grew with decreasing  $T$ , and became comparable to the lower-field resonance at low  $T$ . We ascribe these lines to the two fundamental CR transitions expected for delocalized holes in the valence band of a Zinc-Blende semiconductor in the magnetic quantum limit. We developed an 8-band  $\mathbf{k}\cdot\mathbf{p}$  theory, including full valence band complexities and treating ferromagnetism within a mean-field approximation. Results show that the  $T$ -dependent CR peak shift is a direct measure of the carrier-Mn exchange interaction.

TABLE I: Characteristics of the  $\text{In}_{1-x}\text{Mn}_x\text{As}/\text{Al}_y\text{Ga}_{1-y}\text{Sb}$  samples. Densities and mobilities are room  $T$  values.  $m_A$  and  $m_B$  are the low- $T$  cyclotron masses for the two lines (see Fig. 1).

| Sample No.                           | 1                    | 2                    | 3                    | 4                    |
|--------------------------------------|----------------------|----------------------|----------------------|----------------------|
| $T_c$ (K)                            | 55                   | 30                   | 40                   | 35                   |
| Mn content $x$                       | 0.09                 | 0.12                 | 0.09                 | 0.12                 |
| Al content $y$                       | 0                    | 0                    | 0                    | 1                    |
| Thickness (nm)                       | 25                   | 9                    | 31                   | 9                    |
| Density ( $\text{cm}^{-3}$ )         | $1.1 \times 10^{19}$ | $4.8 \times 10^{19}$ | $1.1 \times 10^{19}$ | $4.8 \times 10^{19}$ |
| Mobility ( $\text{cm}^2/\text{Vs}$ ) | 323                  | 371                  | 317                  | 384                  |
| $m_A/m_0$                            | 0.0508               | 0.0525               | 0.0515               | 0.0520               |
| $m_B/m_0$                            | 0.122                | 0.125                | 0.125                | 0.127                |

\*Author to whom correspondence should be addressed; Electronic address: kono@rice.edu

<sup>†</sup>Present address: Department of Physics, Faculty of Science, Okayama University, Okayama 700-8530, Japan.

<sup>‡</sup>Present address: Institute of Experimental Physics, Warsaw University, Hoza 69, 00-681 Warsaw, Poland.

<sup>§</sup>Present address: PRESTO, Japan Science and Technology Corporation, 4-1-8 Honcho, Kawaguchi, Saitama 332-0012, Japan.

The samples were  $\text{In}_{1-x}\text{Mn}_x\text{As}/\text{Al}_y\text{Ga}_{1-y}\text{Sb}$  single

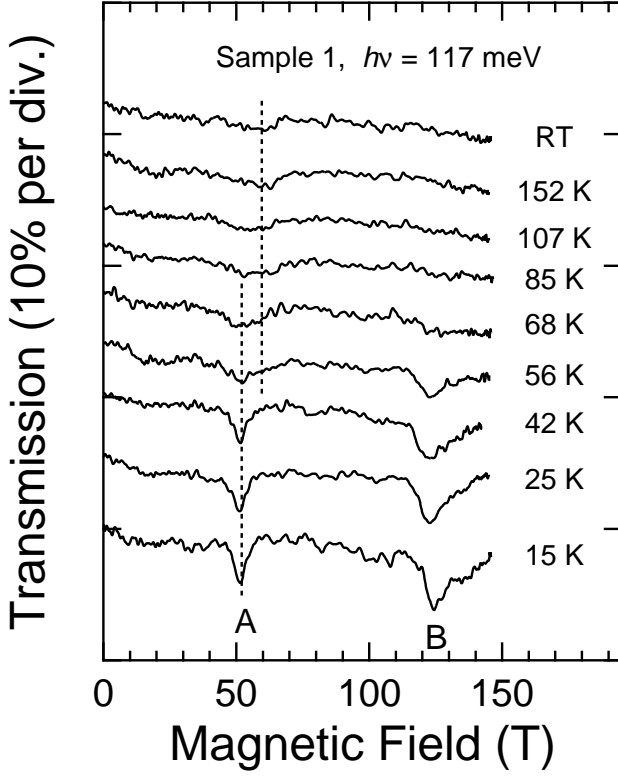


FIG. 1: CR spectra for sample 1. The transmission of hole-active circular polarized  $10.6 \mu\text{m}$  radiation is plotted vs. magnetic field at different temperatures.

heterostructures containing high densities ( $\sim 10^{19} \text{ cm}^{-3}$ ) of holes. They were grown by low temperature molecular beam epitaxy on GaAs (100) substrates [7]. Unlike the  $n$ - and  $p$ -type films we studied earlier [8, 9, 10, 11], the samples in the present work showed ferromagnetism. Sample characteristics are summarized in Table I. Sample 1 was annealed at  $250^\circ\text{C}$  after growth, which increased the  $T_c$  by  $\sim 10 \text{ K}$  [12]. We performed CR measurements using ultrahigh pulsed magnetic fields ( $B$ 's) generated by the single-turn coil technique [9, 13]. We used circularly-polarized radiation with wavelengths of  $10.6 \mu\text{m}$ ,  $10.2 \mu\text{m}$ ,  $9.25 \mu\text{m}$  ( $\text{CO}_2$  laser), and  $5.527 \mu\text{m}$  (CO laser), and the transmitted radiation was detected using a fast HgCdTe detector. A multi-channel digitizer recorded the signals from the pick-up coil and the detector.

Figure 1 shows the transmission of the  $10.6 \mu\text{m}$  beam through sample 1 at various  $T$ 's as a function of  $B$ . From room  $T$  down to slightly above  $T_c$ , a broad feature (labeled 'A') is observed with almost no change in intensity, position, and width with decreasing  $T$ . However, at  $\sim 68 \text{ K}$ , which is still above  $T_c$ , we observe quite abrupt and dramatic changes in the spectra. First, a significant reduction in linewidth and a sudden shift to a lower  $B$  occur simultaneously. Also, it increases in intensity rapidly with decreasing  $T$ . In addition, a second feature (labeled

'B') suddenly appears  $\sim 125 \text{ T}$ , which also rapidly grows in intensity with decreasing  $T$  and saturates, similar to feature A. Note that the temperature at which these unusual sudden CR changes occur ( $T_c^*$ ) is higher than  $T_c$ .

The observed unusual  $T$ -dependence is neither specific to this particular wavelength ( $\lambda$ ) used nor to the sample measured. We observed essentially the same  $T$ -dependent behavior in all the samples studied. Figure 2(a) shows low- $T$  CR traces for three samples at  $10.6 \mu\text{m}$ . Both features A and B are clearly observed but their intensities and linewidths vary from sample to sample. Figure 2(b) displays the  $\lambda$ -dependence of the CR spectra for sample 2. We can see that both lines shift to higher  $B$ 's with decreasing  $\lambda$  (i.e., increasing photon energy), as expected. Figures 2(c) and 2(d) show data at different  $T$ 's for sample 1 measured at  $9.25 \mu\text{m}$  and  $5.52 \mu\text{m}$ , respectively. The  $T$ -dependence observed at these shorter  $\lambda$ 's is similar to what was observed at  $10.6 \mu\text{m}$ . The observations of CR with essentially the same masses in samples with different buffer layers (GaSb or AlSb) exclude the possibility of hole CR in the buffer. We also confirmed the absence of CR in a control sample which consisted of only a GaSb layer grown on GaAs. All these facts confirm the universality of the effects we observed and their relevance to ferromagnetic order.

The clear observation of CR indicates that *at least* a fraction of the holes are delocalized. This is in agreement with our measurements on low- $T_c$  films [10, 11], which showed similar two resonance spectra although the resonances were much broader and  $T$ -dependence was much weaker. However, extensive earlier attempts to observe CR in GaMnAs [14] did not detect any sign of resonant absorption within the  $B$  and  $\lambda$  ranges in which both light hole (LH) and heavy hole (HH) CR in GaAs were expected. This fact indicates that the holes in GaMnAs are strongly localized, that the mixing of  $p$ - and  $d$ -like states makes the effective masses of holes extremely large, or that scattering is too strong to satisfy  $\omega_c\tau > 1$ . In any case, it appears that the carriers mediating the Mn-Mn exchange interaction are considerably more localized in GaMnAs than in InMnAs, consistent with recent optical conductivity [15] and photoemission experiments [16].

Feature A becomes strikingly narrow at low  $T$ 's. The estimated CR mobility is  $4\text{--}5 \times 10^3 \text{ cm}^2/\text{Vs}$ , which is one order of magnitude larger than the low- $T$  mobilities measured by the Hall effect (see Table I). We speculate that this is associated with the suppression of localized spin fluctuations at low  $T$ 's. A similar effect has been observed in (II,Mn)VI systems [17]. Spin fluctuations become important when a band carrier simultaneously interacts with a limited number of localized spins. This occurs, for example, for magnetic polarons and for electrons in (II,Mn)IV quantum dots. The strong in-plane localization by the magnetic field may also result in a reduction of the number of spins which a band carrier feels, thus increasing the role of spin fluctuations.

It is important to emphasize that the  $T$  at which the significant spectral changes start to appear ( $T_c^*$ ) is con-

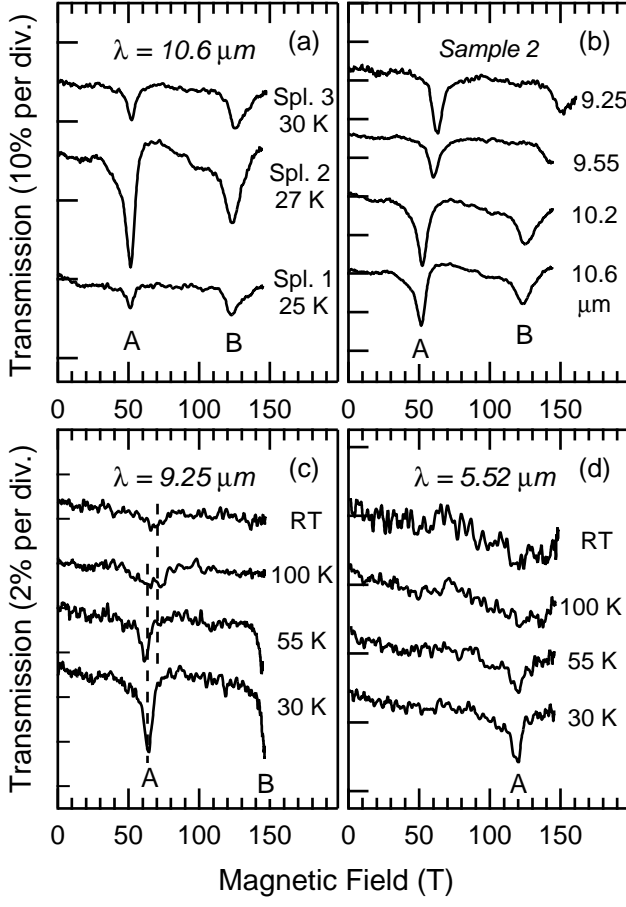


FIG. 2: (a) Low temperature CR spectra for three samples at  $10.6 \mu\text{m}$ . (b) Wavelength dependence of the CR spectra for sample 2 at 27 K. CR spectra for sample 1 at different temperatures at (c)  $9.25 \mu\text{m}$  and (d)  $5.52 \mu\text{m}$ .

sistently higher than  $T_c$  in all the samples. This fact may be explainable in light of a recent Monte Carlo study [18], which suggested that *short-range* magnetic order and finite *local* carrier spin polarization are present for temperatures substantially higher than  $T_c$ . A more recent theoretical study [19] explicitly predicts the existence of  $T_c^*$ , corresponding to *clustering*. Any such local order should result in modifications in band structure, which in turn modify CR spectra.

In order to further understand the effects of ferromagnetism on band structure, we used an  $8 \times 8$   $\mathbf{k} \cdot \mathbf{p}$  model with  $s(p)$ - $d$  exchange interaction taken into account [9, 20]. Each state is specified by two indices,  $(n, \nu)$ , where  $n$  is the Landau quantum number and  $\nu$  labels the eigenvectors within each Landau manifold. Peak A can be identified as the  $\text{HH}(-1,1) \rightarrow \text{HH}(0,2)$  transition [11, 21]. We attribute the  $T$ -dependent peak shift to the increase of carrier-Mn exchange interaction resulting from the increase of magnetic ordering at low  $T$ . Our calculated CR spectra are shown in Fig. 3(a) for

bulk  $\text{In}_{0.91}\text{Mn}_{0.09}\text{As}$  with only a minimal broadening of 4 meV. The figure shows the shift of peak A with decreasing  $T$ . Note that the peak in a bulk system occurs at room  $T$  at  $\sim 40$  T as opposed to the heterostructures where the resonance occurs at  $\sim 50$  T due to quantum confinement/strain.

It is easy to obtain an exact analytical expression for this shift since it involves only the lowest two manifolds in our model ( $n = -1$ , which is 1 dimensional, and  $n = 0$ , which factors into two  $2 \times 2$  matrices for  $k_z = 0$ ). Furthermore, to simplify the final expressions, we neglect the small terms arising from the interaction with remote bands. With these simplifications, the cyclotron energy (at the center of the Landau subbands) has the form:

$$E_{CR} = -\frac{E_g}{2} + \frac{1}{4}x\langle S_z \rangle(\alpha - \beta) + \sqrt{\left[\frac{E_g}{2} - \frac{1}{4}x\langle S_z \rangle(\alpha - \beta)\right]^2 + E_p\mu_B B}, \quad (1)$$

where  $E_g$  is the energy gap,  $E_p$  is related to the Kane momentum matrix element  $P$  as  $E_p = \frac{\hbar^2 P^2}{2m_0}$ ,  $\alpha$  and  $\beta$  are  $s$ - $d$  and  $p$ - $d$  exchange constants, and  $x\langle S_z \rangle$  is the magnetization per unit cell.

In the field range of our interest ( $\sim 40$  T),  $\sqrt{E_p\mu_B B}$  is in the same order as  $\frac{E_g}{2}$ , while the exchange interaction is much smaller even in the saturation limit. Expanding the square root in (1), we obtain the final expression

$$E_{CR} \approx \frac{E_g}{2} \left( \frac{1}{\delta} - 1 \right) + \frac{1}{4}x\langle S_z \rangle(\alpha - \beta)(1 - \delta), \quad (2)$$

where  $\delta = E_g / (E_g^2 + 4E_p\mu_B B)^{1/2}$ .

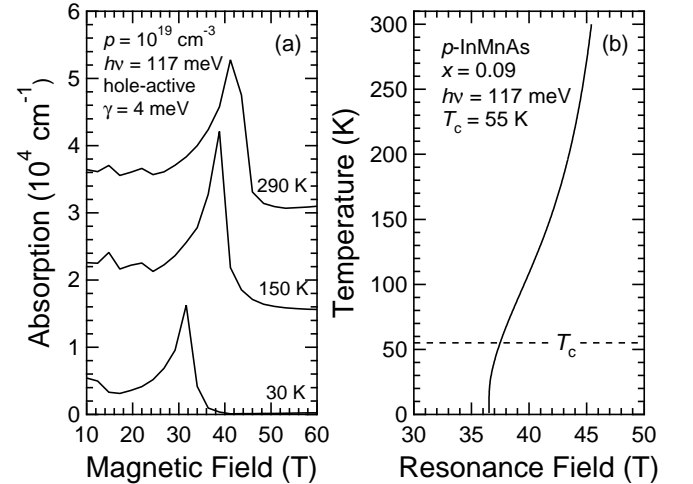


FIG. 3: (a) Theoretical CR spectra for sample 1 showing a shift of peak A with temperature. (b) Calculated temperature-dependence of the resonance field for peak A in sample 1.

If we assume that the  $T$ -dependence of  $E_g$  and  $E_p$  is small, it follows from Eq. (2) that the peak shift should follow the  $T$ -dependence of  $\langle S_z \rangle$ . This shift directly measures the carrier-Mn exchange interaction. To obtain quantitative agreement with the experiment, one should calculate  $\langle S_z \rangle$  by taking into account the possibility of short-range ordering, as discussed above [18, 19]. This effect could substantially modify the band structure at low  $B$ . At high  $B$ , however, this effect should be smoothed out by the field-induced magnetic ordering. In the following we neglect this effect and calculate  $\langle S_z \rangle$  via standard mean-field theory [22], solving the transcendental equation

$$\langle S_z \rangle = SB_S \left( \frac{gS}{kT} \left[ \mu_B B - \frac{3kT_c \langle S_z \rangle}{gS(S+1)} \right] \right), \quad (3)$$

where  $g$  is the free electron  $g$  factor,  $B_S$  is the Brillouin

function, and  $S = \frac{5}{2}$  is the spin of the magnetic ion.

The  $T$ -dependence of the resonance field, calculated using Eqs. (2)-(3), is presented in Fig. 3(b). Parameters used in the calculation are  $x = 0.09$ ,  $T_c = 55$  K,  $E_g = 0.4$  eV,  $E_p = 21$  eV, and  $\alpha - \beta = 1.5$  eV. It shows that from room temperature to 30 K the the resonance  $B$  decreases by  $\sim 20\%$ , approximately the result observed in the experiment. In addition, we find that the shift is nonlinear with  $T$  and the main shift occurs at  $T$ 's well above  $T_c$ , which is also consistent with the experiment.

We gratefully acknowledge support from NSF DMR-0134058 (CAREER) and DARPA MDA972-00-1-0034 (SPINS). CJS also acknowledges support from NSF DMR-9817828. We also thank A. H. MacDonald, S. J. Allen, and E. Dagotto for useful discussions.

- 
- [1] P. W. Anderson, Phys. Rev. **124**, 41 (1961).
  - [2] C. Kittel, *Indirect Exchange Interaction in Metals*, Solis State Physics **22**, 1 (1968).
  - [3] A. C. Hewson, *The Kondo Problem to Heavy Fermions* (Cambridge University Press, 1993).
  - [4] H. Munekata *et al.*, J. Cryst. Growth **111**, 1011 (1991); Appl. Phys. Lett. **63**, 2929 (1993); H. Ohno *et al.*, Appl. Phys. Lett. **69**, 363 (1996).
  - [5] E.g., T. Dietl *et al.*, Science **287**, 1019 (2000); J. König *et al.*, Phys. Rev. Lett. **84**, 5628 (2000); A. Kaminski and S. Das Sarma, *ibid.* **88**, 247202 (2002); G. Zarand and B. Jankó, *ibid.* **89**, 047201 (2002).
  - [6] For CR in ferromagnetic systems, see P. Goy and C. C. Grimes, Phys. Rev. B **7**, 299 (1973); A. K. Chin and A. J. Sievers, J. Appl. Phys. **52**, 7380 (1981).
  - [7] T. Slupinski, A. Oiwa, S. Yanagi, and H. Munekata, J. Cryst. Growth **237-239**, 1326 (2002).
  - [8] Y. H. Matsuda *et al.*, Physica E **10**, 219 (2001).
  - [9] M. A. Zudov *et al.*, Phys. Rev. B **66**, 161307(R) (2002).
  - [10] Y. H. Matsuda *et al.*, Proc. of the 10th Int. Conf. on Narrow Gap Semiconductors (The Institute of Pure and Applied Physics, Tokyo, 2001), pp. 93-95; G. A. Khodaparast *et al.*, J. Supercond. **16**, 107 (2003).
  - [11] G. D. Sanders *et al.*, J. Appl. Phys. **93**, 6897 (2003).
  - [12] T. Hayashi *et al.*, Appl. Phys. Lett. **78**, 1691 (2001); S. J. Potashnik *et al.*, *ibid.* **79**, 1495 (2001).
  - [13] K. Nakao *et al.*, J. Phys. E **18**, 1018 (1985).
  - [14] Y. H. Matsuda, H. Arimoto, N. Miura, H. Ohno, A. Shen, and F. Matsukura, 3rd Symp. on Phys. & Appl. of Spin-Related Phenomena in Semicond., 1997, pp. 42-44.
  - [15] K. Hirakawa *et al.*, Phys. Rev. B **65**, 193312 (2002); Physica E **10**, 215 (2001).
  - [16] J. Okabayashi *et al.*, Phys. Rev. B **65**, 161203 (2002).
  - [17] R. Brazis and J. Kossut, Solid State Commun. **122**, 73 (2002) and references cited therein.
  - [18] J. Schliemann, J. König, and A. H. MacDonald, Phys. Rev. B **64**, 165201 (2001).
  - [19] G. Alvarez, M. Mayr, and E. Dagotto, Phys. Rev. Lett. **89**, 277202 (2002).
  - [20] G. D. Sanders *et al.*, cond-mat/0304434.
  - [21] G. D. Sanders *et al.*, J. Supercond. **16**, 449 (2003).
  - [22] N. W. Ashcroft and N. D. Mermin, *Solid State Physics* (Saunders College, Philadelphia, 1976).