

# A symmetric Lineshape due to Inhomogeneous Broadening of the Crystal-Field Transitions in $Mn_{12}Ac$ Single Crystals

S. Vongtragool<sup>1</sup>, A. Mukhin<sup>1,2</sup>, B. Gorshunov<sup>1,2</sup>, and M. Dressel<sup>1</sup>

<sup>1</sup> 1. Physikalisches Institut, Universität Stuttgart, Pfaffenwaldring 57, 70550 Stuttgart, Germany

<sup>2</sup> General Physics Institute, Russian Academy of Sciences, Moscow, Russia

(dated: March 22, 2024)

The lineshape of crystal-field transitions in single crystals of  $Mn_{12}Ac$  molecular magnets is determined by the magnetic history. The absorption lines are symmetric and Gaussian for the non-magnetized state obtained by zero-field cooling (zfc). In the magnetized state which is reached when the sample is cooled in a magnetic field (fc), however, they are asymmetric even in the absence of an external magnetic field. These observations are quantitatively explained by inhomogeneous symmetric (Gaussian) broadening of the crystal-field transitions combined with a contribution of off-diagonal components of the magnetic susceptibility to the effective magnetic permeability.

PACS numbers: 75.50.Xx, 76.30.-v, 78.20.Ls

## I. INTRODUCTION

The high-spin magnetic cluster of  $Mn_{12}Ac$  (which stands for  $[Mn_{12}O_{12}(CH_3COO)_{16}(H_2O)_4] \cdot 2CH_3COOH \cdot 4H_2O$ ) is the prime example of single-molecule based magnets which reveal a number of interesting phenomena like mesoscopic quantum tunneling of the magnetization and quantum phase interference<sup>1,2,3,4,5,6</sup>. Over a wide range the properties of  $Mn_{12}Ac$  are determined by the splitting of the crystal field (CF) of the  $S = 10$  ground multiplet described by the spin Hamiltonian<sup>7,8,9,10</sup>

$$H = D S_z^2 + D_4 S_z^4 + B_4^4 (S_+^4 + S_-^4) = 2 g_B S H \quad (1)$$

where the first three terms represent the crystal field and the last one the Zeeman energy in a magnetic field  $H$ . The large single-ion anisotropy with an energy barrier of

65 K is produced mainly by the axial term  $D S_z^2$  with  $D < 0$ . The magnetization  $M$  of the cluster is stabilized along the fourth order  $C_4$  symmetry axis. At low temperatures resonant tunneling through the energy barrier is possible if the energy levels on both sides coincide<sup>3,4,5</sup>.

In the last years the structure of the energy levels of the ground state multiplet of  $Mn_{12}Ac$  and the parameters of the effective spin Hamiltonian (1) were studied by EPR measurements<sup>7,8</sup>, inelastic neutron scattering<sup>9</sup> and quasi-optical magnetic spectroscopy<sup>10,11,12</sup>. Currently much attention is devoted to the shape and width of the absorption lines (CF transitions) which may provide a deeper understanding of the mechanisms of quantum tunneling in real crystals of molecular magnets. The Gaussian lineshape found at zero field<sup>11,12</sup> directly indicates an inhomogeneous character of the line broadening due to a distribution of intra-crystalline interactions, in particular, magneto-dipolar and crystal fields. Detailed EPR investigations<sup>13,14,15,16</sup> of various contributions to the line broadening (distribution of the crystal fields, g-factors, dipolar fields) revealed an important role of the CF distribution coming from local strains (D-strain). In addition, the asymmetry of the EPR lines was attributed<sup>17</sup> to the distribution of the easy-axis

orientation. In particular, dislocations in real crystals were suggested to cause a distribution of crystal fields which strongly influences the mechanism of quantum tunneling<sup>18</sup>. We have applied a novel type of magnetic spectroscopy to study the influence of the inhomogeneous broadening on the lineshape of magneto-dipolar transitions in  $Mn_{12}Ac$  which allowed us to reveal new features and to advance an alternative explanation.

## II. EXPERIMENTAL RESULTS

A few dozen of  $Mn_{12}Ac$  single crystals of typically 1 to 2 mm in size were aligned to a mosaic of about 0.5 mm thickness and  $7 \times 7 \text{ mm}^2$  area such that the  $C_4$  axes of the crystals lay in the plane of the plate and were parallel to each other (to an accuracy better than  $3^\circ$ ). Using a frequency-domain magnetic spectroscopy<sup>19</sup>, we studied the magnetic absorption by measuring the optical transmission coefficient in the frequency range from 8 to  $18 \text{ cm}^{-1}$ . The experiments were performed at temperatures  $T = 2.33 \text{ K}$  in a magnetic field  $H$  up to 7 Tesla which was oriented perpendicular to the magnetic field vector  $h$  of the radiation propagating with the wavevector  $q$  along the  $y$ -direction (Voigt geometry:  $h \parallel x, q \parallel y, H \parallel z \parallel C_4$ ).

The two transmission spectra plotted in Fig. 1 show the  $j = 10 \rightarrow j = 9$  transition measured at  $T = 2.33 \text{ K}$  with no external field present:  $H = 0$ ; note that this corresponds to a real zero-field EPR experiment. In one case (non-magnetized, zfc state) the sample is cooled down without applied magnetic field, in the second case (magnetized, fc state) the crystals are cooled from 40 K in a field of 1 T (parallel to  $C_4$ ) which was subsequently switched off. In fc crystals the resonance frequency is shifted up by  $0.1 \text{ cm}^{-1}$  and the lineshape is significantly asymmetric, with the slope smoother on the left (low-frequency) side. Applying a magnetic field parallel to the  $C_4$  axis of the fc crystals increases the transition frequency as displayed in Fig. 2; the lineshape remains asymmetric similar to the  $H = 0$  case.

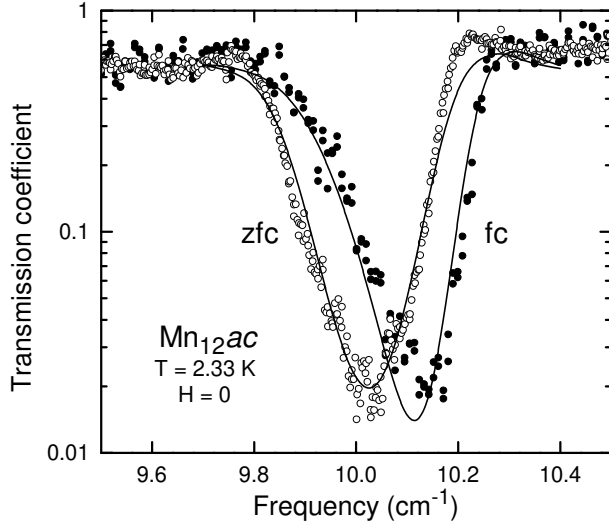


FIG. 1: Magnetic absorption due to the  $j = 10 \rightarrow j = 9$  crystal-field transition of  $\text{Mn}_{12}\text{ac}$  single crystals as observed in the transmission spectra at  $T = 2.33$  K without external magnetic field. In one case (zfc) the sample is cooled down without applied magnetic field, in the other case (fc) it is cooled in a magnetic field of 1 T which was subsequently switched off. The solid lines represent the calculations using a single Gaussian line and an effective susceptibility as described in the text.

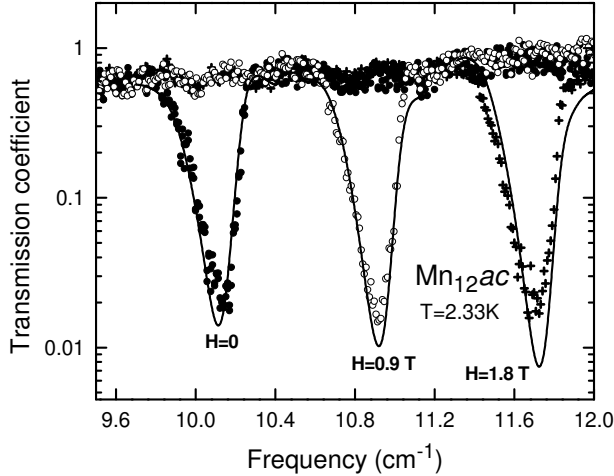


FIG. 2: Absorption of the  $j = 10 \rightarrow j = 9$  crystal-field transition in  $\text{Mn}_{12}\text{ac}$  single crystals at  $T = 2.33$  K measured by transmission at different magnetic fields. The lines represent the calculations using a single Gaussian term and an effective susceptibility.

### III. ANALYSIS

For a quantitative description of the spectra we have to consider the radiation propagating along  $z$  axis through a transversely magnetized medium ( $\mathbf{h}_x; \mathbf{e}_y$ ), whose optical response is determined by an effective magnetic

perm eability<sup>20</sup>

$$\epsilon_{\text{eff}}(\omega) = \epsilon_{xx}(\omega) \quad \epsilon_{xy}(\omega) \quad \epsilon_{yx}(\omega) = \epsilon_{yy}(\omega); \quad (2)$$

and thus depends on both diagonal and off-diagonal components of the magnetic perm eability  $\epsilon_{ij}(\omega)$  or susceptibility  $\chi_{ik}(\omega)$  ( $\chi_{ik}(\omega) = 1 + 4\chi_{ik}(\omega)$ ), where the latter are sensitive to the magnetic state of the sample (fc or zfc). For low temperatures only transitions from the ground state to the first excited state  $j = 10 \rightarrow j = 9$  contribute to the susceptibility

$$\chi_{xx,yy}(\omega) = \chi'(\omega) = \frac{1}{2}(\chi_{10} + \chi_{-10}) + \frac{1}{2}(\chi_{10} - \chi_{-10}); \quad (3)$$

$$\chi_{xy}(\omega) = \chi_{yx}(\omega) = \frac{1}{2}(\chi_{10} - \chi_{-10}) = \frac{1}{2}(\chi_{10} - \chi_{-10}); \quad (4)$$

where  $\hbar\omega_{10} = E_9 - E_{10} = \hbar\omega_{10}^0 - g_B H_z$  are the transition frequencies between the corresponding states on one (+) or another (-) side of an isotropy barrier. Here  $\hbar\omega_{10}^0 = 19[D + D_4(10^2 + 9^2)]$  is the zero-field frequency and  $\omega_{10} = 2N(g_B \hbar \omega_{10}^0 \beta_x \beta_y)^2 (\omega_{10}^0 - g_B H_z) = \hbar\omega_{10}$  are the contributions to the magnetic susceptibility due to the corresponding transitions,  $N$  is the particle density, and  $m$  is the population of the energy levels  $E_m$  which are given by the Boltzmann factor  $m = \exp(-E_m/k_B T) / \sum \exp(-E_n/k_B T)$  in an equilibrium state. The lineshape functions  $R_{10}(\omega) = R_m(\omega)$  may be either Lorentzian  $R_m(\omega) = \frac{1}{2} / (\frac{1}{2}(\omega - \omega_m)^2 + \frac{1}{2})$ , or Gaussian<sup>11</sup> with the imaginary part

$$R_m^{\text{G}}(\omega) = (\frac{1}{2})^{1/2} (\frac{1}{2}) \exp[-(\frac{1}{2}(\omega - \omega_m)^2 + \frac{1}{2})] + \exp[-(\frac{1}{2}(\omega + \omega_m)^2 + \frac{1}{2})]; \quad (5)$$

and the real one determined via the Kramers-Kronig relation  $R_m^{\text{R}}(\omega) = (2\pi)^{-1} \int_{-\infty}^{\infty} R_m^{\text{G}}(\omega_1) (\frac{1}{\omega - \omega_1}) d\omega_1$ .

In a nonmagnetized state, when the population is the same on both sides of the barrier,  $\chi_{10} = \chi_{-10}$ , and the off-diagonal components of the susceptibility vanish  $\chi_{xy, yx}(\omega) = 0$ , the effective perm eability is given by

$$\epsilon_{\text{eff}}^{\text{zfc}}(\omega) = \epsilon_{xx}(\omega) = 1 + 4\chi'(\omega); \quad (6)$$

where the diagonal susceptibility component  $\chi'(\omega)$  is determined by Eq. (3) for  $\chi_{10} = \chi_{-10}$  and  $R_{10} = R_{-10}$ . In a magnetized state ( $\chi_{10} \neq \chi_{-10}$ )

$$\epsilon_{\text{eff}}^{\text{fc}}(\omega) = 1 + \frac{4\chi'(\omega)[1 + 4\chi'(\omega)(\frac{1}{2}(\omega - \omega_m)^2 + \frac{1}{2})]}{1 + 4\chi'(\omega)} + \frac{4\chi''(\omega)}{1 + 4\chi'(\omega)}; \quad (7)$$

where  $\chi'(\omega) = \frac{1}{2}(\chi_{10} + \chi_{-10})$ . For  $H = 0$  the functions  $\chi'(\omega)$  in the Eqs. (6) and (7) coincide and the difference between zfc and fc perm eability is mainly determined by the denominator  $1 + 4\chi'(\omega)$  in Eq. (7).

As shown in Fig. 1 by the solid lines, we can nicely fit our experimental results for both the fc and zfc states

by using the expressions for the transmission coefficient of a plane-parallel layer<sup>21</sup> and a Gaussian lineshape entering for  $R(\omega)$  in  $\chi''(\omega)$ . The main parameters, the CF resonance frequency  $\omega_0 = 10.002 \text{ cm}^{-1}$ , the Gaussian linewidth  $\omega_{10} = 0.095 \text{ cm}^{-1}$  (corresponding full width at the half of maximum  $\omega_{10} = 2 \sqrt{2 \ln 2} \omega_{10} = 0.224 \text{ cm}^{-1}$ ), and the contribution to the permeability  $\chi_{10} = 4 \chi_0 = 0.076$ , were found by fitting only the zfc data<sup>22</sup>. The calculated spectra reproduce both, the upward shift of the resonance frequency and the asymmetry of the lineshape in the fc state. The increase of the resonant frequency from the value  $\omega_0$  in zfc state to  $\omega_{e10} (1 + \chi_{10})$  in the fc state is mainly due to the change of the effective permeability since the off-diagonal term of the susceptibility becomes significant. A slight renormalization of the resonance frequency  $\hbar\omega_{e10} = \hbar\omega_0 + g_B \mu_B M_0$  in the fc state is caused by the weak internal dipolar magnetic field; from our two we obtain  $\mu_B M_0 = 265 \text{ Oe}$  (i.e.  $g_B \mu_B M_0 = 0.024 \text{ cm}^{-1}$ ), where  $M_0$  is the magnetization<sup>23</sup>. The above statement concerning the shift of the resonance frequency in the fc state is true both for Lorentzian and Gaussian lineshape. For the change of the shape, however, it is essential that the lines are inhomogeneously broadened and have to be described by Gaussian lines.

In Fig. 3 the imaginary part of the permeability spectrum  $\chi''(\omega)$  (which describes the magnetic absorption) in the fc state is calculated assuming a Gaussian and a Lorentzian lineshape  $R_m(\omega)$ . It is clearly seen that the line becomes asymmetric only in the case of the Gaussian lineshape while for the Lorentzian case it remains symmetric. This important result is connected to the fact that for a Lorentzian lineshape  $R_m(\omega)$  in the Eq. (7) only the resonant frequency and the contribution ("strength") are renormalized, while the overall frequency dependence of  $\chi''(\omega)$  remains unchanged, i.e. Lorentzian<sup>24</sup>. In the

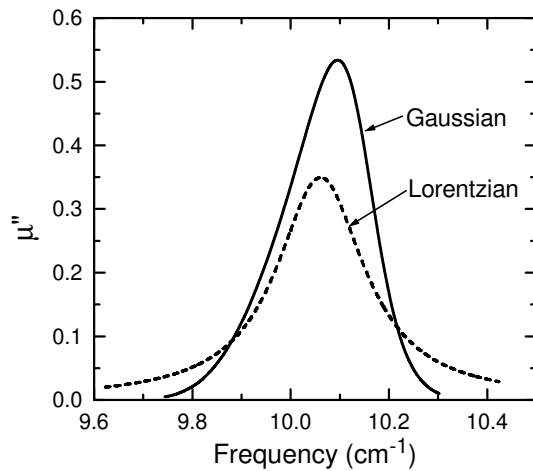


FIG. 3: Magnetic absorption spectra  $\chi''$  at zero magnetic field ( $H = 0$ ) for the field-cooled (fc) state of  $\text{Mn}_{12}\text{Ac}$ . The calculation compares Gaussian with Lorentzian lineshapes of the  $j = 10 \rightarrow j = 9$  crystal-field transition.

case of inhomogeneously broadened (Gaussian) lines, their shape is disturbed<sup>25</sup>. Our approach also explains the asymmetric lineshape for finite magnetic fields, as demonstrated in Fig. 2 where the solid lines correspond to calculations using  $g = 1.93$  and the aforementioned parameters.

#### IV. DISCUSSION

An asymmetric EPR lineshape of  $\text{Mn}_{12}\text{Ac}$  magneto-dipolar transitions was reported in<sup>16</sup> and was explained subsequently<sup>17</sup> by random distributions not only of the  $D$  parameter of the crystal field but also of the easy-axis orientation. In this case, however, the asymmetry should vanish in zero magnetic field which is in contradiction to our present observations. Hence, the asymmetry of the lineshape can in principle not be connected with the distribution of the easy axis but rather is determined by a distribution of the zero-field resonance frequencies. It should be noted that the experimental measurement geometry (Voigt configuration) is of crucial importance<sup>25</sup>. Since regular EPR experiments are performed at fixed frequencies as a function of applied magnetic field (in contrast to our experiments which are conducted at fixed (finite or zero) magnetic field as a function of frequency) the smaller slope is found on the right (high-field) side relative to the resonance field as reported by Hillet al.<sup>16</sup>. Assuming that the main contribution to the observed linewidth is given by the dispersion of the crystal field  $D$  and taking into account that  $\omega_0 = \omega_0 + D = (D + 181D_4)$   $D = D$ , we obtain  $D = 0.01D$  which is half the value estimated in<sup>16</sup>.

Recently it was shown<sup>26</sup> that a disorder of the acetic acids of crystallization induces different CF distortions at the  $\text{Mn}^{3+}$  ions positions; as a result six different isomers can be found. The estimated CF parameters  $D(n)$  for the most populated isomers are  $-0.769 \text{ K}$ ,  $-0.778 \text{ K}$  and  $-0.788 \text{ K}$  for  $n = 1; 2; 3$ , respectively<sup>26</sup>. The relative differences  $D(2) - D(1) = 0.0115$  and  $D(3) - D(2) = 0.0128$  agree very well with the CF distribution obtained from the linewidth. A simulation of the observed fc and zfc spectra by three narrower Gaussians lines, corresponding to the three isomers with the given concentrations, provides an excellent description of the whole lineshape (not shown). According to Comia et al.<sup>26</sup> the CF distortions in the  $\text{Mn}_{12}\text{Ac}$  isomers are accompanied by an appearance of a second-order transverse CF term  $E(S_x^2 - S_y^2)$  which is responsible for the tunnel splitting and increase of the relaxation rate. The correlation between  $D$  and  $E$  terms opens a possibility to observe an inhomogeneous relaxation of the spectra inside the line in a long-living non-equilibrium state created by magnetic field inversion<sup>27</sup>.

In summary, using high-frequency magnetic spectroscopy we discovered a dependence of the frequency and lineshape of the magneto-dipolar transitions in  $\text{Mn}_{12}\text{Ac}$  on the magnetic history of the sample. Zero-field

cooled samples show a symmetrical Gaussian lineshape of the  $S = 10$  ground multiplet transition  $|j = 10, i = j - 9\rangle$ . If the sample was previously cooled in magnetic field, the line becomes asymmetric and shifts up in frequency by about  $0.1 \text{ cm}^{-1}$  even for  $H = 0$ . These observations are explained by an inhomogeneous (Gaussian) distribution of the resonant frequencies taking into account the effective susceptibility of the transversely magnetized medium which includes off-diagonal components and the internal magnetic field. We quantitatively describe the absorption seen in the transmission spectra for both  $H = 0$  and  $H \neq 0$  and determined the main characteristics of

interactions in the system.

#### Acknowledgments

We thank the Prof. N. Karl and the Materials Lab for synthesizing the  $Mn_{12}ac$  single crystals. We acknowledge helpful discussions with N. S. Dalal and J. Tejada. This work was supported by the Deutsche Forschungsgemeinschaft (DFG) and by RFBR (No. 02-02-16597).

- <sup>1</sup> R. Sessoli, D. Gatteschi, A. Caneschi, and H. A. Novak, *Nature* 356, 141 (1993).
- <sup>2</sup> D. Gatteschi, A. Caneschi, L. Pardi, and R. Sessoli, *Science* 265, 1054 (1994).
- <sup>3</sup> J. R. Friedman, M. P. Sarachik, J. Tejada, and R. Ziob, *Phys. Rev. Lett.* 76, 3830 (1996).
- <sup>4</sup> B. Barbara, L. Thomas, F. Lioni, I. Chioresu, and A. Sulpice, *J. Magn. Magn. Mat.* 200, 167 (1999).
- <sup>5</sup> A. Caneschi, D. Gatteschi, C. Sangregorio, R. Sessoli, L. Sorace, A. Corina, M. N. Novak, C. Paulsen, and W. Wemsdorfer, *J. Magn. Magn. Mat.* 200, 182 (1999).
- <sup>6</sup> W. Wemsdorfer and R. Sessoli, *Science* 284, 133 (1999).
- <sup>7</sup> A. L. Barra, D. Gatteschi, and R. Sessoli, *Phys. Rev. B* 56, 8192 (1997).
- <sup>8</sup> S. Hill, J. A. J. Perenboom, N. S. Dalal, T. Hathaway, T. Stalcup, and J. S. Brooks, *Phys. Rev. Lett.* 80, 2453 (1997).
- <sup>9</sup> M. Hennion, L. Pardi, I. Mirebeau, E. Suard, R. Sessoli, and A. Caneschi, *Phys. Rev. B* 56, 8819 (1997); I. Mirebeau, M. Hennion, H. Casalta, H. Andres, H. J. Gudel, A. V. Irodova, and A. Caneschi, *Phys. Rev. Lett.* 83, 628 (1999).
- <sup>10</sup> A. A. Mukhin, V. D. Travkin, A. K. Zvezdin, S. P. Lebedev, A. Caneschi, and D. Gatteschi, *Europhys. Lett.* 44, 778 (1998).
- <sup>11</sup> A. A. Mukhin, B. Gorshunov, M. Dressel, C. Sangregorio, and D. Gatteschi, *Phys. Rev. B* 63, 214411 (2001).
- <sup>12</sup> A. A. Mukhin, A. S. Prokhorov, B. Gorshunov, A. K. Zvezdin, V. D. Travkin, and M. Dressel, *Physics Uspekhi* 34, 1306 (2002).
- <sup>13</sup> S. Hill, R. S. Edwards, S. I. Jones, N. S. Dalal, and J. M. North, *Phys. Rev. Lett.* 90, 217204 (2003).
- <sup>14</sup> B. Parks, J. Loomis, E. Rumberger, D. N. Hendrickson, and G. Christou, *Phys. Rev. B*, 64, 184426 (2001).
- <sup>15</sup> K. Park, M. A. Novotny, N. S. Dalal, S. Hill, and P. A. Rikvold, *Phys. Rev. B* 65, 014426 (2002).
- <sup>16</sup> S. Hill, S. Maccagnano, K. Park, R. M. Achey, J. M. North, and N. S. Dalal, *Phys. Rev. B* 65, 224410 (2002).
- <sup>17</sup> K. Park, M. A. Novotny, N. S. Dalal, and P. A. Rikvold, *J. Appl. Phys.* 91, 7167 (2002); K. Park, M. A. Novotny, and N. S. Dalal, *J. Chem. Phys.* 117, No. 24 (2002).
- <sup>18</sup> E. M. Chudnovsky and D. A. Garanin, *Phys. Rev. Lett.* 87, 187203 (2001); D. A. Garanin and E. M. Chudnovsky, *Phys. Rev. B* 65, 094423 (2002); F. Torres, J. M. Hernandez, E. Molins, A. Garcia-Santiago, and J. Tejada, *cond-mat/0110538*.
- <sup>19</sup> G. V. Kozlov and A. A. Volkov, *Millimeter and Submillimeter Wave Spectroscopy of Solids*, ed. by G. Gruner (Springer, Berlin, 1998), p. 51.
- <sup>20</sup> See for example: B. Lax and K. J. Button, *Microwave ferrites and ferrimagnets* (McGraw-Hill, New York, 1962).
- <sup>21</sup> M. Dressel and G. Gruner, *Electrodynamics of Solids* (Cambridge Univ. Press, Cambridge, 2002).
- <sup>22</sup> The linewidth agrees well with the one obtained in polycrystalline  $Mn_{12}ac$ <sup>10,11,12</sup>. The found value of  $\gamma_{10}$  is slightly smaller than the theoretical value 0.0109 obtained by  $N = N_A / M_{Mn_{12}}$  using the reported density  $\rho = 1.84 \text{ g/cm}^3$  with  $N_A$  the Avogadro number and  $M_{Mn_{12}}$  the mass of the  $Mn_{12}ac$  molecule. The reason may be the mosaic structure of the sample used in our experiments.
- <sup>23</sup> Strictly speaking, also the transverse internal dipolar fields  $\gamma_{\perp} M_{\perp}$  may become important when the magnetization deviates from the easy axis during oscillations; in general, this effect could lead to a renormalization of  $\gamma_{\perp}(\omega)$ . However, our simulation shows that this effect is not relevant in our case.
- <sup>24</sup> It can be easily checked by a direct substitution of  $\gamma_{\perp}(\omega) = \gamma_{10} R + \gamma_{10}(\omega)$  in Eq. (7).
- <sup>25</sup> In Faraday geometry for a circular polarization the inhomogeneously broadened lines stay symmetric due to another kind of effective permeability. These experiments are in progress.
- <sup>26</sup> A. Comia, R. Sessoli, L. Sorace, D. Gatteschi, A. L. Barra, and C. Daguebonne, *Phys. Rev. Lett.* 89, 257201 (2002).
- <sup>27</sup> M. Dressel, B. Gorshunov, K. Rajagopal, S. Vongtragoon, and A. A. Mukhin, *Phys. Rev. B* 67, 060405(R) (2003).