

Surface contribution to the superconducting properties of MgB_2 single crystals

A. Rydh,^{*} U. Welp, J. M. Hiller, A. Koshlev, W. K. Kwok, and G. W. Crabtree
Materials Science Division, Argonne National Laboratory, 9700 S. Cass Ave., Argonne, IL 60439, USA

K. H. P. Kim, C. U. Jung, H.-S. Lee, B. Kang, and S.-I. Lee
NCRICS and Dept. of Physics, Pohang University of Science and Technology, Pohang 790-784, Republic of Korea
 (Dated: March 22, 2022)

We demonstrate direct evidence of possible surface superconductivity on small, well-shaped MgB_2 single crystals. Transport measurements in the range $H < 1.6H_{c2}^c$, where H_{c2}^c is the bulk upper critical field for the c axis, show non-Ohmic and strongly angular dependent resistivity. Studies of the alignment of \mathbf{H} with selected crystal surfaces, transport and specific heat measurements on the same crystal, and a physical sculpturing of the crystal surfaces using a focused ion beam all support the conclusion. Similar, albeit less pronounced results are obtained for fields in the basal plane.

PACS numbers: 74.25.Dw, 74.25.Fy, 74.25.Op, 74.25.Qt

Keywords: surface superconductivity, transport, specific heat, phase diagram, FIB, peak effect

The binary MgB_2 compound has been subject of intense studies since the discovery of its superconducting properties at temperatures up to 39 K [1]. The superconductor has been found to be of phonon-mediated BCS type but with a multitude of novel properties, mainly arising from its complex, two-band (π and σ) Fermi surface [2, 3]. In particular, MgB_2 is the first example of a superconductor showing two distinct superconducting gaps [4]. The two-gap nature is revealed in the macroscopic properties of MgB_2 through a pronounced temperature dependence of the anisotropy of the upper critical field [5, 6, 7, 8]. The effect of the two-gap structure on vortex dynamics is presently under intense investigation. Although STM [9] and specific heat measurements [10] indicate a rapid suppression of the π gap with increasing magnetic field its effect on magneto-transport properties remains controversial. In particular, a pronounced broadening of the resistive transitions in magnetic fields applied along the c axis has been observed. Whether this broadening is related to the two superconducting gaps [11] or other phenomena such as vortex dissipation and vortex lattice melting [12], surface barriers [13], superconducting fluctuations [13], or surface superconductivity [6, 7, 8] remains to be settled.

In this Letter we present definitive indications of a surface superconducting state in well-shaped MgB_2 single crystals. From angular dependent transport and specific heat measurements, we demonstrate that the broadening of the resistive transitions for $\mathbf{H} \parallel \mathbf{c}$ as well as for $\mathbf{H} \parallel \mathbf{ab}$ occurs *above* the bulk upper critical field, while there is virtually no broadening of the transitions in the mixed state. The result is confirmed by directly modifying the crystal surface geometry using a focused ion beam (FIB).

MgB_2 crystals with typical maximum dimensions of 50 μm were obtained through a high pressure heat treatment of a mixture of Mg and B in excess Mg [14]. The resulting crystals were well shaped with smooth, hexagonal facets. Scanning electron microscopy (SEM) and high-

resolution transmission electron microscopy confirmed the absence of grain boundaries or other correlated defects [15]. The crystals had $T_c \approx 36$ K, $\Delta T_c \approx 0.15$ K (at low current), and a bulk $H_{c2}^c(0) \approx 3.5$ T. Transport measurements were performed using standard DC and AC techniques. A total of five crystals were studied, all showing similar behavior with slight variations in the exact shape of the resistive transition. We present results on two of these crystals.

Figures 1a and 1b show the resistive transitions in various fields around the c axis and around the basal (ab) plane, respectively. The transitions broaden significantly with increasing field around c as reported earlier [7, 8, 11, 12, 13]. This broadening evolves in a characteristic two stage fashion with a gradual onset at T_{on} and a steep drop at lower temperature, which we are going to identify with $T_{c2}(H)$. The gradual onset broadens in increasing field, while the steep drop at $T_{c2}(H)$ stays sharp. In addition to a strong current dependence the broadening is also strongly angular dependent. As the applied field is tilted away from the c axis the gradual resistive onset is rapidly suppressed and the steep resistive drop becomes more pronounced. The gradual onset is largely eliminated at angles around 40° (in 1.5 T). Similar behavior is seen for fields applied along the ab plane (Fig. 1b).

For exact field alignment with the ab plane, the gradual resistive onset becomes more pronounced with increasing fields, but is readily suppressed by a tilt as small as 0.7° . The strong angular dependence is clearly seen in angular scans shown in Fig. 2 for both the c axis (main panel) and the ab plane (inset). The angular dependence around the c axis depends on the direction in which the field is tilted. If the field is tilted across the vertical side faces (the direction marked as “ \perp ” in the schematic inset of Fig. 1a) the resistance increases rapidly in a cusp-like fashion. At high angles the resistance decreases again due to the super-imposed, intrinsic, superconducting anisotropy. If

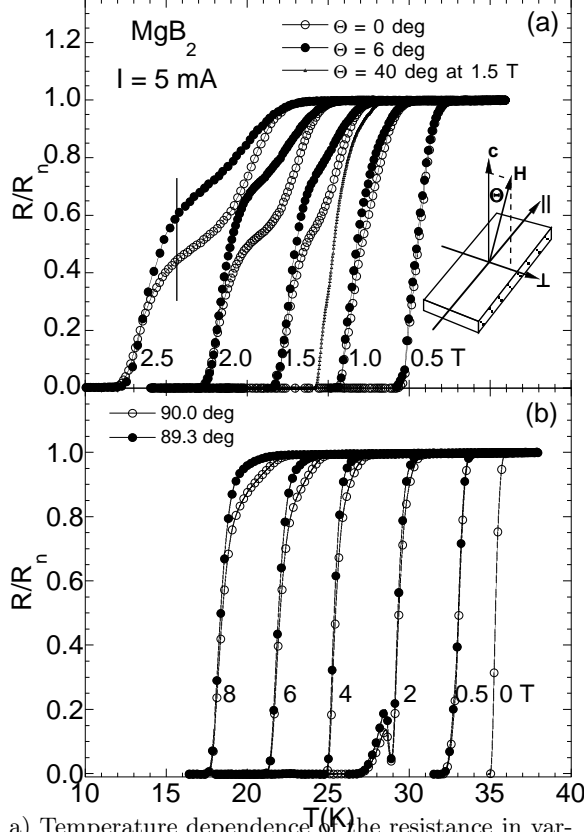


FIG. 1: a) Temperature dependence of the resistance in various fields directed along and at 6° off the c axis. At 1.5 T data for an angle of 40° are also included. The inset defines the geometry. b) Similar data for fields applied around the ab plane. For clarity only 2% of the data points are displayed.

the field is tilted in such a way that it stays parallel to the side surfaces (marked as “||” in Fig.1a) the resistance remains at a low level. As a direct proof that the resistive behavior shown in Fig. 1 is associated with the sample surfaces, we artificially modified the side faces of a crystal. A trapezoidal cross-section was cut into the sample between the voltage contacts (see insets of Fig. 2) using a focused ion beam (FIB). As a consequence, two new dips appeared near -7° and $+16^\circ$ (solid symbols in Fig. 2) corresponding to the orientation of the newly formed surfaces. These results demonstrate that the observed features in the transport properties indeed originate from the crystal surfaces, and not from possible planar, crystallographic defects that are aligned with the side surfaces.

It is important to note that the angular dependent, gradual, superconducting onset at T_{on} in Figs. 1 and 2 occurs *well above* the bulk upper critical field. Figure 3 shows the specific heat signature of T_{c2} together with the resistive transition of the *same crystal* measured at various currents in a field of 1.5 T \parallel c . The step in $\Delta C_p/T$, which corresponds to the bulk superconducting

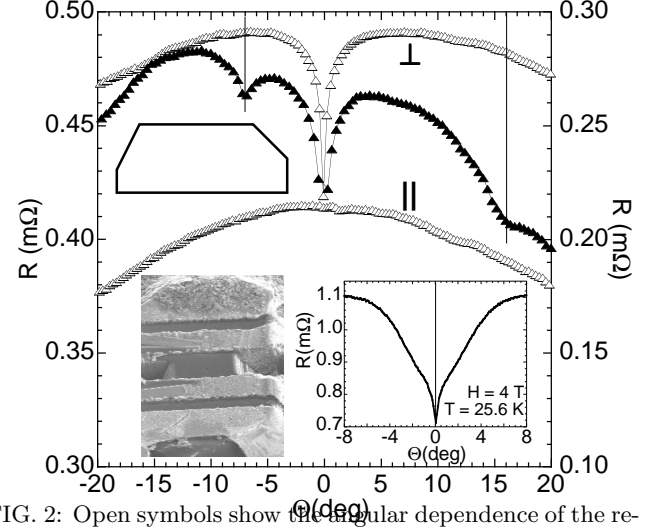


FIG. 2: Open symbols show the angular dependence of the resistance when tilting the applied field across (“⊥”) and within (“||”) the side face. The solid symbols show the appearance of new dips after reshaping the crystal side surfaces with an FIB. The data are taken at 2.5 T and 5 mA. The insets on the left display a schematic cross section and an SEM image of the FIB-milled crystal. The inset on the right shows the cusp-like angular dependence around the ab plane.

transition, occurs about 5 K below T_{on} (for $H = 1.5$ T) but coincides well with the steep drop to zero resistance seen at high enough currents. This indicates that the transport behavior is caused neither by a conventional surface barrier effect [13], nor by a transition in the vortex system [12] for which the sample has to be in the mixed state, i.e., below H_{c2} . Instead, the normalconducting bulk is covered by a superconducting sheath in places where the field is aligned with the surface.

The field – temperature (H – T) phase diagram resulting from the data of Figs. 1 and 3 and similar data is shown in Fig. 4, and is in agreement with previous reports [5, 6, 7, 8]. Shown are the bulk upper critical fields, as determined from specific heat measurements and resistive drops, as well as the onsets of angular and current depend transport. We notice that the onsets are enhanced with respect to the bulk H_{c2} by a coefficient of about 1.6 for $\mathbf{H} \parallel \mathbf{c}$ and 1.4 for $\mathbf{H} \parallel \mathbf{ab}$. This behavior is reminiscent of the development of a surface superconducting state. A superconducting surface sheath with a thickness given by the Ginzburg–Landau coherence length, $\xi(T)$, nucleates at an enhanced field of $H_{c3} = 1.69H_{c2}$ when a magnetic field is applied parallel to the flat (infinite) surface of an isotropic superconductor [16]. The exact value of the enhancement factor may depend on clean-limit corrections [17], on the shape of the sample and its intrinsic

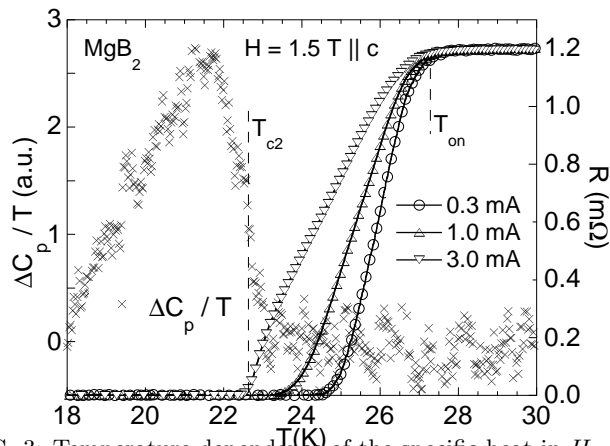


FIG. 3: Temperature dependence of the specific heat in $H = 1.5 \text{ T} \parallel c$ and of the resistance at various currents measured on the same crystal. The temperatures T_{c2} and T_{on} are indicated.

anisotropy [18], and on the surface quality [20].

The results presented here can be accounted for in a model of surface superconductivity. It has been shown that the surface superconducting state is rapidly suppressed in a cusp-like fashion when the applied field has a normal component to the surface [19], exactly the behavior observed when the field is tilted across the side face (see Figs. 1 and 2). Similarly, when the field is tilted within the side faces the surface superconducting state is not suppressed, and the only observed angular dependence arises from the intrinsic anisotropy of MgB_2 . Furthermore, non-Ohmic transport properties above the bulk upper critical field are expected due to the presence of a surface critical current, I_{sc} , [20]. If the applied current is smaller than I_{sc} then the resistance will go to zero above H_{c2} (T_{c2}), see Fig. 3. At higher current a finite, current dependent resistance arises signaling current sharing between the surface sheath and the normal core of the sample. At H_{c2} the core of the sample goes superconducting, and the resistance drops to zero. We also note that (for macroscopic samples) the contribution of the superconducting surface sheath has a negligible contribution to the specific heat.

Figure 1 and 3 suggest the surprising result that the surface superconducting state is more pronounced and (as function of angle) more robust for $\mathbf{H} \parallel c$ than for $\mathbf{H} \parallel ab$, implying that surface supercurrents on the narrow side faces (shaded in Fig. 1a) are stronger than those on the wide top and bottom faces. A similar observation has recently been reported for NbSe_2 [22] for which indications of surface superconductivity were obtained for $\mathbf{H} \parallel c$ but not for $\mathbf{H} \parallel ab$. Several factors may contribute to this behavior. The top and bottom surfaces appear very smooth indicating that the surface critical currents are weak. This is consistent with the broader angular

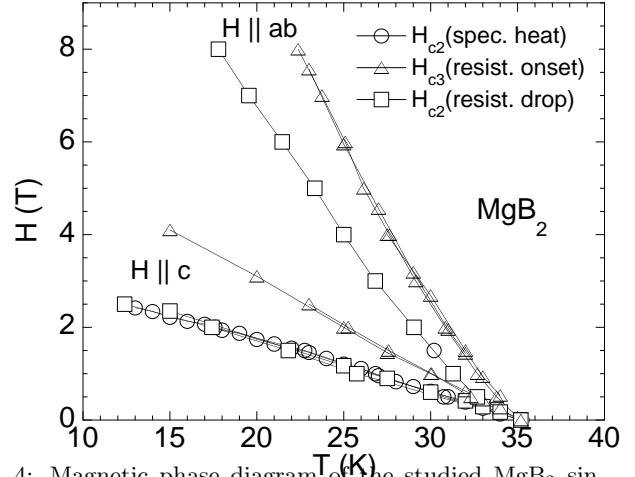


FIG. 4: Magnetic phase diagram of the studied MgB_2 single crystals. The bulk upper critical fields for the two main axes are consistently obtained from specific heat and transport measurements of the peak effect (which develops at the location of the sharp resistive drop at high enough currents [7]). Onsets of transport nonlinearities and deviations from the normal state resistivity are found at $\sim 1.6H_{c2}^c$ for the c axis and $\sim 1.4H_{c2}^{ab}$ for the basal plane.

dependence for field around the c axis and studies on PbTl films and ribbons [20] that have shown that the angular dependence is sharper for smooth surfaces. In addition, due to the anisotropy of the coherence length, the thickness of the current carrying layer at the top and bottom faces is about four times smaller than along the side faces.

To complete the picture, we studied the influence of the angle between the magnetic field and the current direction on the transport properties, for \mathbf{H} aligned with the basal plane. Figure 5 shows the field dependence of the resistance for $\mathbf{H} \perp \mathbf{I}$ and $\mathbf{H} \parallel \mathbf{I}$. A distinct orientational dependence is observed, reminiscent of the Lorentz force effect on a vortex system. In the parallel case the transitions are featureless, while for $\mathbf{H} \perp \mathbf{I}$ the location of H_{c2} is revealed by the already described, steep drop of the resistance and the appearance of a peak effect at high enough currents. The angular dependence clearly persists to fields well above H_{c2} . In considering the surface superconductivity description, the angular-dependence behavior arises because the mutual orientation of \mathbf{H} and \mathbf{I} affects the distribution of the superconducting order parameter near the surface [23]. For $\mathbf{H} \perp \mathbf{I}$ the superconducting order parameter is displaced with respect to the surface [24] whereas for $\mathbf{H} \parallel \mathbf{I}$ it acquires an additional phase analogous to the force free configuration in thin, superconducting wires. As a result there is an intrinsic anisotropy of the superconducting phase stiffness and, consequently, of the maximum (depairing) critical current $I_c^\perp/I_c^\parallel = 0.6$ which can account for our data.

Surface superconductivity as discussed here is a con-

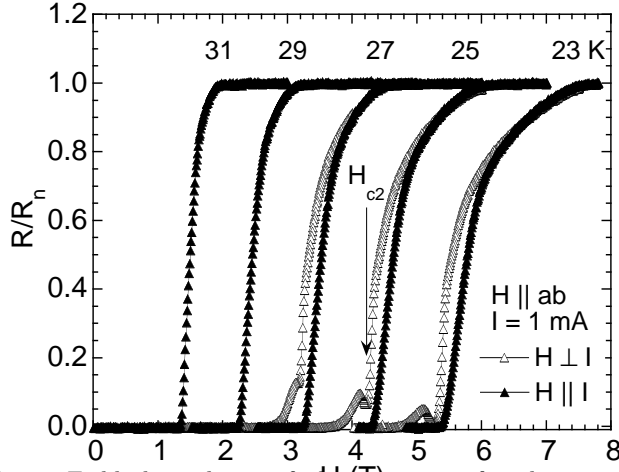


FIG. 5: Field dependence of the resistance for the zero Lorentz force ($\mathbf{H} \parallel \mathbf{I}$) and maximum Lorentz force ($\mathbf{H} \perp \mathbf{I}$) configurations.

sequence of the boundary conditions at the free surface of an otherwise unperturbed sample. In the case of MgB_2 , ARPES experiments [25] show that the very existence of the surface induces modifications of the electronic structure at Mg- and B-terminated surfaces. Various band structure calculations [26] indicate that these surface electronic states could either locally enhance or suppress the superconducting properties. However, increasing the surface area by pulverizing single crystals has not given any indication for enhanced T_c [27]. In addition, the sample surfaces could be modified due to exposure to oxygen and humidity. Although the value of T_c has proven remarkably insensitive to modest amounts of disorder [28], there could arise a shell of enhanced (dirty) upper critical field giving rise to the observed transport behavior. However, our experiments on the freshly cut surfaces seem to rule out such a possibility. Furthermore, the observation of the general features shown here with enhancement factors consistently in the range of 1.5 to 2 on a large number of crystals from various sources indicates an intrinsic nature of the surface effects.

In summary, we have shown that the surfaces of well-shaped MgB_2 single crystals possess locally enhanced superconducting properties in magnetic fields aligned to the surfaces. The surface superconductivity is more pronounced for fields along the c axis and is found to display a field-induced anisotropy for fields in the basal plane. Further studies could address the possible significance of the two-band structure for the exact mechanism behind the observations.

This work was supported through the Fulbright program and the Sweden-America Foundation (A.R.), by the Ministry of Science and Technology of Korea, and by the U.S. Department of Energy, Basic Energy Sciences, under Contract No. W-31-109-ENG-38. Work with the FIB was carried out in the Center for Microanalysis of

Materials, University of Illinois, which is partially supported by the U.S. Department of Energy under grant DEFG02-91-ER45439.

* Also at Solid State Physics, Royal Institute of Technology (KTH), Stockholm-Kista, Sweden; Electronic address: rydh@anl.gov

- [1] J. Nagamatsu *et al.*, Nature (London) **410**, 63 (2001). For extensive reviews see *Special Edition on MgB₂*, Physica (Amsterdam) **385C** (2003).
- [2] H. J. Choi *et al.*, Nature (London) **418**, 758 (2002).
- [3] A. Y. Liu *et al.*, Phys. Rev. Lett. **87**, 087005 (2001).
- [4] F. Bouquet *et al.*, Phys. Rev. Lett. **87**, 047001 (2001); P. Szabo *et al.*, *ibid* **87**, 137005 (2001); F. Giubileo *et al.*, *ibid* **87**, 177008 (2001); H. Schmidt *et al.*, *ibid* **88**, 127002 (2002); M. Iavarone *et al.*, *ibid* **89**, 187002 (2002).
- [5] M. Angst *et al.*, Phys. Rev. Lett. **88**, 167004 (2002); S. L. Budko *et al.*, Phys. Rev. B **64**, 180506 (2001); M. Zehetmayer *et al.*, *ibid* **66**, 052505 (2002); Y. Machida *et al.*, *ibid* **67**, 094507 (2003).
- [6] L. Lyard *et al.*, Phys. Rev. B **66**, 180502 (2002).
- [7] U. Welp *et al.*, Phys. Rev. B **67**, 012505 (2003).
- [8] A. V. Sologubenko *et al.*, Phys. Rev. B **65**, 180505 (2002).
- [9] M. Eskildsen *et al.*, Phys. Rev. Lett. **89**, 187003 (2002).
- [10] F. Bouquet *et al.*, Phys. Rev. Lett. **89**, 257001 (2002).
- [11] A. K. Pradhan *et al.*, Phys. Rev. B **65**, 144513 (2002); Yu. Eltsev, Physica (Amsterdam) **385C**, 162 (2003).
- [12] Yu. Eltsev *et al.*, Physica (Amsterdam) **378–381C**, 61 (2002); Yu. Eltsev *et al.*, Phys. Rev. B **65**, 140501 (2002).
- [13] T. Masui *et al.*, cond-mat/0210358.
- [14] C. U. Jung *et al.*, Phys. Rev. B **66**, 184519 (2002).
- [15] K. H. Kim *et al.*, Phys. Rev. B **65**, 100510 (2002).
- [16] D. Saint-James and P. G. de Gennes, Phys. Rev. Lett. **7**, 306 (1963); A. A. Abrikosov, Sov. Phys. JETP **20**, 480 (1965); H. J. Fink, Phys. Rev. Lett. **14**, 309 (1965).
- [17] C.-R. Hu and V. Korenman, Phys. Rev. **178**, 684 (1969); Phys. Rev. B **6**, 1 (1972).
- [18] V. G. Kogan *et al.*, Phys. Rev. B **65**, 094514 (2002).
- [19] C. Hempstead and Y. Kim, Phys. Rev. Lett. **12**, 145 (1964); W. J. Tomasch and A. S. Joseph, Phys. Rev. Lett. **12**, 148 (1964); R. S. Thompson, Sov. Phys. JETP **42**, 1144 (1976).
- [20] H. R. Hart, Jr., and P. S. Swartz, Phys. Rev. **156**, 403 (1967).
- [21] I. O. Kulik, Soviet Phys. JETP **28**, 461 (1969).
- [22] G. D'Anna *et al.*, Phys. Rev. B **54**, 6583 (1996).
- [23] H. Schmidt and H. J. Mikeska, J. Low Temp. Phys. **3**, 123 (1970); A. E. Koshelev, to be published.
- [24] This effect predicts rectification as seen, for example, in P. S. Swartz and H. R. Hart, Jr., Phys. Rev. **156**, 412 (1967). We could not observe any such effects here, however, possibly due to the contact arrangement.
- [25] H. Uchiyama *et al.*, Phys. Rev. Lett. **88**, 157002 (2002); S. Souma *et al.*, Nature **423**, 65 (2003).
- [26] I. G. Kim *et al.*, Phys. Rev. B **64**, 020508 (2001); V. M. Silkin *et al.*, *ibid* 172512; E. Bascones and F. Guinea, *ibid* 214508; Z. Li *et al.*, Phys. Rev. B **65**, 100507 (2002); V. D. Seredio *et al.*, Phys. Rev. B **66**, 140502 (2002); G. Profeta *et al.*, *ibid* 184517.
- [27] J. Karpinski, private communication.

- [28] I. I. Mazin *et al.*, Phys. Rev. Lett. **89**, 107002 (2002).