

Electric Field Effects on the Diffuse Scattering in PZN-8%PT

P. M. Gehring,¹ K. Ohwada,² and G. Shirane³

¹NIST Center for Neutron Research, National Institute of Standards and Technology, Gaithersburg, Maryland 20899-8562

²Synchrotron Radiation Research Center (at SPRING 8),

Japan Atomic Energy Research Institute, Sayo-gun Hyogo 679-5148, Japan and

³Department of Physics, Brookhaven National Laboratory, Upton, New York 11973-5000

(Dated: April 14, 2024)

We report measurements of the neutron diffuse scattering from a single crystal of the relaxor ferroelectric $\text{Pb}(\text{Zn}_{1/3}\text{Nb}_{2/3}\text{O}_3)$ doped with 8% PbTiO_3 (PZN-8%PT) for temperatures 100 K \leq T \leq 530 K and electric fields 0 kV/cm \leq E \leq 10 kV/cm. The diffuse scattering is strongly suppressed transverse to the (003) Bragg peak at 400 K for E = 2 kV/cm applied along the [001] direction. However, no change in the diffuse scattering is observed transverse to (300), even for field strengths up to 10 kV/cm. Thus the application of an external electric field in the tetragonal phase does not produce a macroscopically polarized state. This unusual behavior can be understood within the context of the Hirota et al. phase-shifted polar nanoregion (PNR) model of the relaxor diffuse scattering, since an electric field E oriented parallel to [001] would remove the shift of the nanoregions along [001] while preserving those along the orthogonal [100] direction.

PACS numbers: 61.12.-q, 77.65.-j, 77.84.Dy

I. INTRODUCTION

The shape, size, density, and orientation of the polar nanoregions (PNR) that form below the Burns temperature T_d ¹ in the lead-oxide class of relaxors $\text{Pb}(\text{Zn}_{1/3}\text{Nb}_{2/3}\text{O}_3)$ and $\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3}\text{O}_3)$ doped with PbTiO_3 (PZN-xPT and PMN-xPT, respectively) are key parameters of interest to many researchers attempting to clarify the various mechanisms responsible for the exceptional piezoelectric properties exhibited by these materials.² First identified through optical measurements of the index of refraction by Burns and Dacol,¹ the presence of PNR have been correlated with the onset of neutron diffuse scattering in PMN,³ a saturation of the unit cell volume below T_d ,⁴ and the overdamping of long-wavelength phonon modes in PZN and PZN-8%PT.^{5,6} More recently an important model concerning the relationship between the PNR and the surrounding cubic lattice was presented by Hirota et al.⁷ Based on neutron time-of-flight measurements of the diffuse scattering in PMN at 300 K performed by Vakhrushev et al.,⁸ Hirota et al. noticed that the corresponding ionic displacements could be decomposed into a scalar shift (displacement) common to all atoms, and a pattern of shifts that satisfies a center-of-mass condition.⁹ It was further shown that these center-of-mass shifts are consistent with neutron inelastic measurements of the soft TO phonon intensity in PMN above T_d , thus providing compelling evidence that the polar nanoregions result from the condensation of a soft mode at the Burns temperature.

Subsequent measurements on PZN-8%PT using neutron diffraction techniques by Ohwada et al. demonstrate that the zero-field cooled structure at low temperature is not rhombohedral as had been previously believed.¹⁰ Instead, surprising evidence of a new phase, called phase X, was found that exhibits an average cubic unit cell structure. These findings motivated the high-

energy x-ray study by Xu et al. on pure PZN,¹¹ and the high-resolution neutron study by Gehring et al. on PMN-10%PT.¹² Both of these studies revealed a low-temperature bulk phase that is not rhombohedral, but rather consistent with the phase X observed by Ohwada et al. in PZN-8%PT. It has been suggested that the phase-shifted nature of the PNR could be responsible for stabilizing phase X at low temperatures as the uniform shift of the PNR would present a natural energy barrier in the system against the formation of a uniform polar state.

To shed more light on this idea, we have performed a study of the PNR in PZN-8%PT by measuring the response of the neutron diffuse scattering below the cubic-to-tetragonal phase transition temperature T_c = 470 K to an external electric field E. As is well known, a classic ferroelectric system will break into many domains below T_c , and the application of an electric field can produce a nearly uniform polar state by aligning all of the domains via domain wall motion. In the case of the relaxor ferroelectric PZN-8%PT, however, our data show that for E oriented parallel to the [001] direction, only the diffuse scattering transverse to the (003) reciprocal lattice point decreases. The diffuse scattering transverse to the orthogonal (300) position is unaffected. Thus a macroscopic uniformly polarized state is not achieved. The model of phase-shifted PNR provides a possible explanation for these findings, as an electric field along [001] would remove the PNR shift along [001] while preserving that along [100].

II. EXPERIMENTAL DETAILS

The neutron scattering data presented here were obtained on the BT9 triple-axis spectrometer located at the NIST Center for Neutron Research. The diffuse scatter-

ing near the reciprocal lattice points (300) and (003) was measured at a fixed neutron energy $E_i = E_f = 14.7 \text{ meV}$ ($\lambda = 2.36 \text{ \AA}$) using the (002) reflection of highly-oriented crystals of pyrolytic graphite (HOPG) as monochromator and analyzer. Horizontal beam collimations were $40^\circ\text{--}46^\circ\text{--}S\text{--}40^\circ\text{--}80^\circ$ ($S = \text{sample}$).

The high-quality single crystal of PZN-8%PT used in this study was grown by the flux solution method³ at the Pennsylvania State University. It is a sister crystal to the one used by Ohwada et al. in an earlier study, some results from which are presented in this paper.¹⁰ The crystal weighs 1.1 gm (0.15 cm^3), and is a rectangular block with 100 faces and dimensions $7.2 \times 6.9 \times 3.0 \text{ mm}^3$. Gold electrodes were plated onto the two largest surfaces of the crystal to which thin gauge copper wires were attached using a red-on silver conductive adhesive epoxy cured at 100°C for 2 hours. In this geometry the field is always applied along a cubic [001] axis. These wires were twisted and soldered onto leads connected to a high voltage power supply. Tests were performed both before and after the experiment to verify that the voltage set by the power supply appeared across the sample. The difference between the set and measured voltage drop was always less than 1%.

The crystal was mounted onto an electrically insulating boron nitride post using boron nitride paste to provide a strain-free environment for the sample. The crystal [010] axis was oriented vertically, giving access to reflections of the form $(h0l)$. The sample holder assembly was then mounted inside the vacuum space of a high-temperature closed-cycle ^3He refrigerator, which was subsequently positioned and fixed onto the goniometer of the BT9 spectrometer.

III. DIFFUSE SCATTERING

The PZN-8%PT phase E-T diagram has been mapped out by Ohwada et al., and is shown in Fig. 1.¹⁰ The data presented in the top panel were taken while cooling in a constant electric field, whereas those shown in the bottom panel were taken with increasing field at fixed temperature after first cooling in zero field. The electric field acts to stabilize the tetragonal phase as can be seen from the slope of the tetragonal (T) to cubic (C) phase boundary in Fig. 1(a), where the transition temperature increases with field. The transition temperatures, represented by the circles in Fig. 1, were determined from measurements of the lattice constants (Bragg peaks). But while this relaxor compound clearly exhibits a tetragonally-distorted structure, the precise nature of the polar order is still unknown.

Important information can be obtained about the polar order in the tetragonal phase of PZN-8%PT through measurements of the diffuse scattering. Fig. 2 shows neutron scattering measurements taken by Ohwada et al. (on a different PZN-8%PT single crystal, but grown using the same technique) near the (003) reciprocal lattice

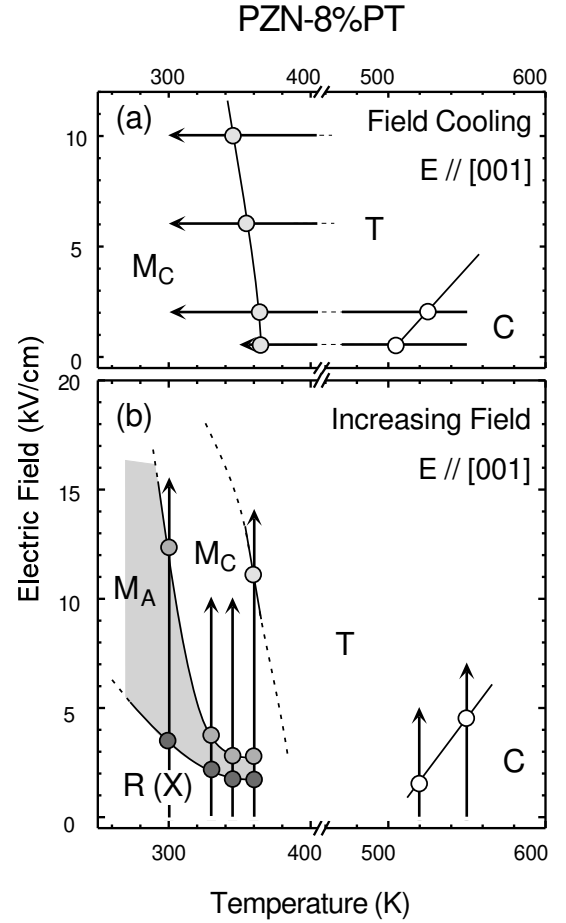


FIG. 1: The E-T phase diagram of PZN-8%PT determined by Ohwada et al.¹⁰ The notations C, T, M, and R refer to cubic, tetragonal, monoclinic, and rhombohedral phases, respectively. The arrows point in the scan direction, while the length of the arrows correspond to the scan range. The circles denote the transition temperatures determined from each scan.

position, for which the diffuse scattering structure factor is known to be strong.¹⁰ The intensity at $Q = (0.04, 0.3)$ is shown as a function of temperature at $E = 0 \text{ kV/cm}$ (solid circles) and 3 kV/cm (open circles), with the field applied along the [001] direction. In the cubic phase at high temperature ($T > 520 \text{ K}$) the diffuse scattering intensities are equal, indicating no field dependence. However at lower temperatures, in the tetragonal phase, the diffuse scattering is strongly suppressed by the field while the zero-field diffuse scattering intensity remains strong and increases with cooling. For purposes of comparison, the integrated Bragg intensity measured at (002) in zero-field is shown (scale on the right-hand side of Fig. 2). The Bragg intensity increases sharply below 500 K , which is consistent with the slope of the T-C phase boundary in Fig. 1.

The data in Fig. 2 were obtained at a fixed Q value at two different field values. Information about the geometry of the diffuse scattering is presented in Fig. 3,

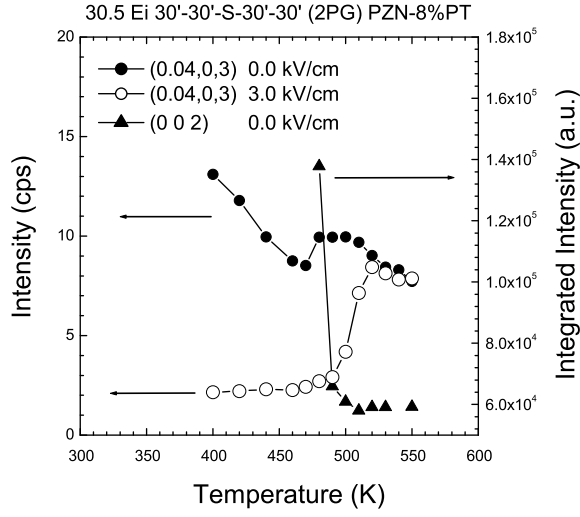


FIG. 2: Temperature dependence of the neutron diffraction scattering at $Q = (0.04, 0.3)$ in zero field (solid circles) and $E = 3 \text{ kV/cm}$ // $[001]$ (open circles). The zero-field Bragg intensity measured at (002) is shown as a function of temperature by the solid triangles. These data were taken by Ohwada et al. on a different single crystal of PZN-8%PT.

which compares the diffraction scattering intensity measured at several different reciprocal lattice points at a fixed field strength of 2 kV/cm oriented along the $[001]$ axis. The intensities measured around the (003) position (open circles) decrease upon cooling in field in agreement with the data of Fig. 2. However the striking behavior revealed in this figure is the that the diffraction intensities measured around the orthogonal (300) position remain high, much like the zero-field data shown in Fig. 2. The vertical arrows in this figure indicate the phase transition temperatures T_{M-T} and T_{T-C} between the monoclinic and tetragonal, and tetragonal and cubic phases, respectively.

To clarify this behavior wide scans were made of the scattered neutron intensity as a function of the reduced momentum transfer q transverse to both the (300) and (003) Bragg positions as a function of field and temperature. The resulting data are plotted on a log-intensity scale in Fig. 4. The top two panels display transverse q -scans in zero field, and the bottom two panels show the same scans taken after cooling the sample in a 2 kV/cm field. In the cubic phase at 500 K we observe diffraction scattering of roughly equal intensity in zero field along directions transverse to both $Q = (300)$ and (003) . This scattering does not change when an external electric field of 2 kV/cm is applied along the $[001]$ direction. In the tetragonal phase at 400 K the diffraction scattering in zero field increases slightly, becoming somewhat stronger around (003) compared to (300) . Then when the sample is field cooled, the diffraction scattering transverse to (003) is reduced substantially, as is suggested by the data shown in Fig. 3. Remarkably, however, the diffraction scattering transverse to (300) is unaffected. This latter result indicates that the application of a 2 kV/cm field is insu-

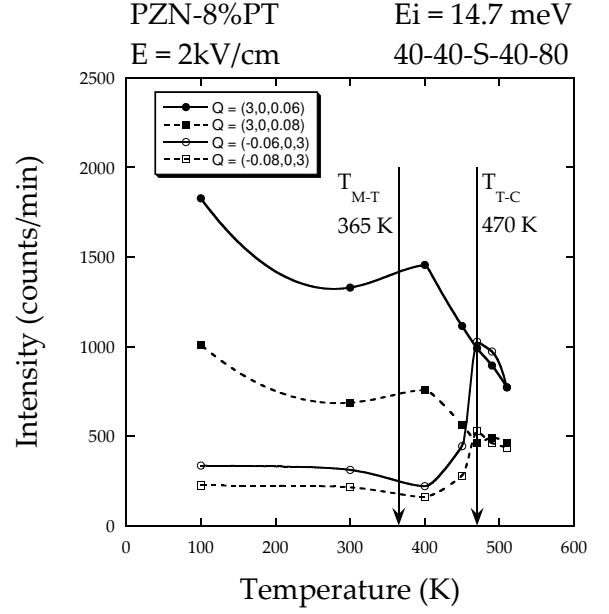


FIG. 3: Comparison of the diffraction scattering intensities measured near (300) (solid symbols) and (003) (open symbols) as a function of temperature in a field of 2 kV/cm applied along $[001]$.

cient to produce a uniform polarization in the tetragonal phase. The dotted line in the lower left panel of Fig. 4 indicates the measured instrumental (Gaussian) resolution function. Although data are not shown, the same behavior was observed at 300 K in the monoclinic phase of PZN-8%PT as in the tetragonal phase at 400 K .

An effort was made to determine the field strength E_c at which the diffraction scattering transverse to (300) begins to decrease. Fig. 5 shows the diffraction scattering intensity measured at $Q = (3, 0, -0.06)$ at 450 K , still in the tetragonal phase, from zero to 10 kV/cm . All of these data were taken as a function of increasing electric field strength after first field cooling from 520 K in a field of 2 kV/cm except for the zero-field data point, which was obtained after zero-field cooling. The solid and open circles are successive measurements at the same temperature and Q . The solid square shows the diffraction scattering intensity at 450 K at $E = 2 \text{ kV/cm}$. These data clearly reveal the inability of even a strong external electric field to diminish the diffraction scattering orthogonal to the field direction. Hence the underlying mechanism responsible for the diffraction scattering in PZN-8%PT must have an energy barrier that is sufficiently large in order to stabilize it against external fields of at least 10 kV/cm .

IV. DISCUSSION

The results on PZN-8%PT presented here are significant not because the diffraction scattering measured transverse to (003) is suppressed by an external electric field,

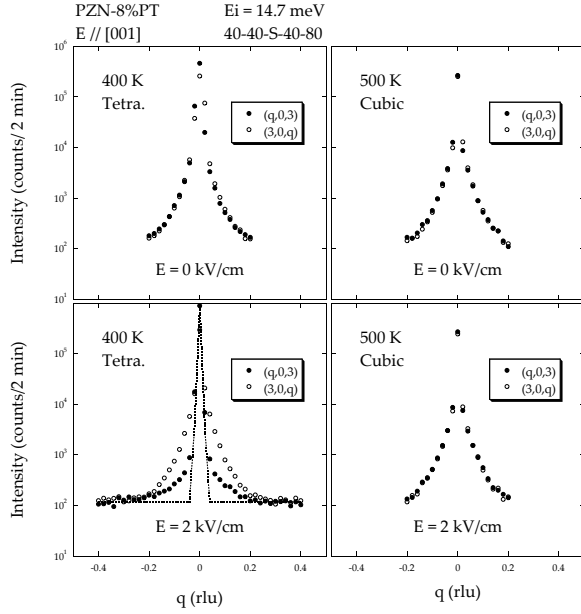


FIG. 4: A log-scale comparison of the diffuse scattering intensities measured transverse to the (300) (open circles) and (003) (solid circles) reciprocal lattice positions at 400 K (tetragonal phase) and 500 K (cubic phase). The top panels show data in zero field, and the bottom panels show data in an electric field of 2 kV/cm (bottom panels) applied along [001]. The dashed line in the lower left panel represents the instrumental transverse q -resolution.

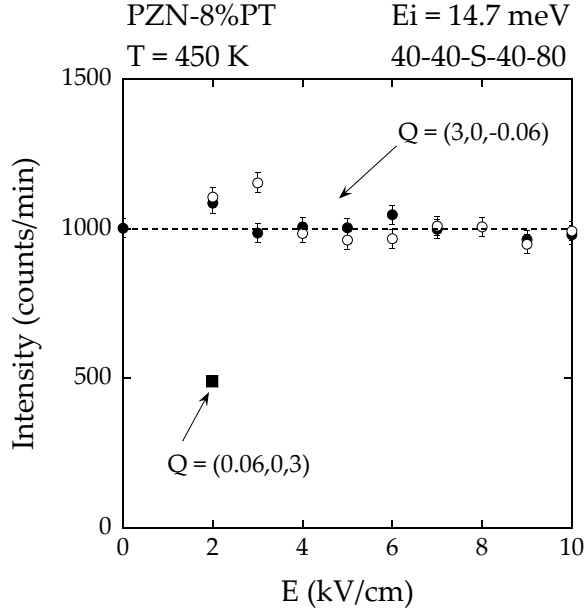


FIG. 5: Plot of the diffuse scattering intensity measured in the tetragonal phase at $(3,0,-0.06)$ at 450 K as a function of increasing field strength applied along the [001] direction. The open and solid circles represent independent measurements. The solid square corresponds to the diffuse scattering intensity at 2 kV/cm at $(0.06,0,3)$ for comparison.

but rather because the diffuse scattering measured transverse to (300) is not. Independent of any model, our data provide unambiguous evidence that the field-induced polar state in this important relaxor material is not macroscopically uniform. This unusual finding must therefore be explained by any model that purports to address the fundamental properties of these lead-oxide relaxor compounds. While not unique, we believe that the concept of the phase-shifted polar nanoregions provides a natural explanation for the observed field and Q -dependence of the diffuse scattering in PZN-8%PT. This phase shift, or uniform displacement, of the PNR occurs with respect to the surrounding cubic lattice at the Burns temperature T_d where the PNR condense from the soft TO phonon mode (see the top panel in Fig. 6). This soft TO mode is in fact coupled to the TA mode as first shown by Naberezhnov et al., and later studied by Wakimoto et al.^{3,14} The uniform phase shift is believed to result from the fact that the soft TO mode is actually a soft-coupled mode that contains a significant transverse acoustic component, an idea originally proposed by Yamada and Takakura.¹⁵

The results of our study can be explained quite simply on the basis of the shifted nature of the PNR, as illustrated by the three-panel schematic diagram shown in Fig. 6. In the top panel, the system is in the cubic phase, below the Burns temperature. The white squares represent the non-polar regions of the lattice (note that these are not individual unit cells), while the PNR are shown as the red hatched regions (corresponding to something of the order of 10 unit cells), which are slightly displaced in different directions from the cubic lattice. The arrows represent the direction and size of the uniform shift, which occurs in the direction of the PNR polarization. In the tetragonal phase ($T < T_c$) the lattice develops its own polarization as indicated by the red dotted shading, while the uniform shift of the PNR remains intact (see the upper left panel of Fig. 4). Under the application of an external electric field, the shifts antiparallel to E are removed, thereby reducing the local disorder, and in turn suppressing the diffuse scattering. (As it is unclear how much of the diffuse scattering transverse to the (003) reciprocal lattice position remains (see the lower left-hand panel of Fig. 4), we can only speculate that parallel shifts may be unaffected.) But the orthogonal PNR shifts are unaffected, and hence the corresponding diffuse scattering is also unaffected. Thus a macroscopically ordered polar phase is not achieved in this system, even under applied electric field strengths up to 10 kV/cm.

Interesting high- q resolution studies in zero field have now been performed by Gehring et al. on PMN-10%PT, and Xu et al. on PMN-20%PT and PMN-27%PT.^{12,16} These studies have examined the low-temperature phase in the PMN- x PT system, and document the existence of phase X up to PbTiO₃ concentrations as high as 20%. The 27% sample naturally exhibits the expected rhombohedral phase. The stability of this new phase X against the formation of a global rhombohedral polar phase at

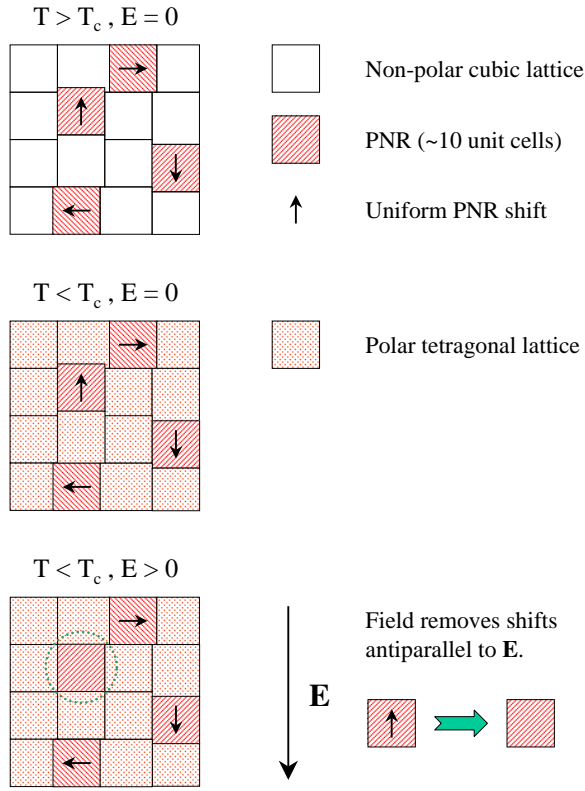


FIG. 6: Top panel: Phase-shifted PNR embedded in a non-polar cubic lattice for $T > T_c$. Middle panel: Below T_c the lattice achieves a polarization of its own, but the phase shift remains. Bottom panel: An applied electric field removes shifts along E , while preserving those that are orthogonal.

temperatures below T_c can also be understood in terms of the phase-shifted PNR model. The latter study by Xu et al. in particular demonstrates that phase X is both undistorted and rhombohedrally polarized.

V. ACKNOWLEDGMENTS

We would like to thank R. Erwin, Y. Fujii, K. Hirota, C. Stock, and S. Wakimoto, for stimulating discussions, and P. W. Rehrig for supplying the high quality PZN-8% PT single crystal. We acknowledge financial support from the U.S. Dept. of Energy under contract No. DE-AC02-98CH10886. We also acknowledge the U.S. Dept. of Commerce, NIST Center for Neutron Research, for providing the neutron scattering facilities used in this study.

- ¹ G. Burns and F. H. Dacol, Solid State Commun. 48, 853 (1983); *ibid*, Phys. Rev. B 28, 2527 (1983).
- ² S.-E. Park and T. R. Shrout, J. Appl. Phys. 82, 1804 (1997).
- ³ A. Naberezhnov, S. B. Vakhrushev, B. Domer, and H. Moudén, Eur. Phys. J. B 11, 13 (1999).
- ⁴ J. Zhao, A. E. Glazounov, Q. M. Zhang, and B. Toby, Appl. Phys. Lett. 72, 1048 (1998).
- ⁵ P. M. Gehring, S.-E. Park, and G. Shirane, Phys. Rev. B 63, 224109 (2001).
- ⁶ P. M. Gehring, S.-E. Park, and G. Shirane, Phys. Rev. Lett. 84, 5216 (2000).
- ⁷ K. Hirota, Z.-G. Ye, S. Wakimoto, P. M. Gehring, and G. Shirane, Phys. Rev. B 65, 104105 (2002).
- ⁸ S. B. Vakhrushev, B. E. Kvyatkovsky, A. A. Naberezhnov, N. M. Okuneva, and B. Toperverg, Ferroelectrics 90, 173 (1989).

- ⁹ J. Harada, J. D. Axe, and G. Shirane, Phys. Rev. B 4, 155 (1971).
- ¹⁰ K. Ohwada, K. Hirota, P. W. Rehrig, Y. Fujii, and G. Shirane, Phys. Rev. B 67, 094111 (2003).
- ¹¹ G. Xu, Z. Zhong, Y. Bing, Z.-G. Ye, C. Stock, and G. Shirane, Phys. Rev. B 67, 104102 (2003).
- ¹² P. M. Gehring, W. Chen, Z.-G. Ye, and G. Shirane, cond-mat/0304289.
- ¹³ M.-L. Mulvihill, S.-E. Park, G. Risch, Z. Li, K. Uchino, and T. R. Shrout, Jpn. J. Appl. Phys. 35, 3984 (1996).
- ¹⁴ S. Wakimoto, C. Stock, Z.-G. Ye, W. Chen, P. M. Gehring, and G. Shirane, Phys. Rev. B 66, 224102 (2002).
- ¹⁵ Y. Yamada and T. Takakura, cond-mat/0209573.
- ¹⁶ G. Xu, D. Viehland, J. Li, P. M. Gehring, and G. Shirane, cond-mat/0307144.