

Electronic structures of $\text{Zn}_{1-x}\text{Co}_x\text{O}$ using photoemission and x-ray absorption spectroscopy

S. C. Wi, J.-S. Kang, J. H. Kim, S.-B. Cho, B. J. Kim, S. Yoon, and B. J. Suh
Department of Physics, The Catholic University of Korea, Puchon 420-743, Korea

S. W. Han and K. H. Kim
Department of Physics, Gyeongsang National University, Chinju 660-701, Korea

K. J. Kim, B. S. Kim, H. J. Song, and H. J. Shin
Pohang Accelerator Laboratory (PAL), POSTECH, Pohang 790-784, Korea

J. H. Shim and B. I. Min
Department of Physics, POSTECH, Pohang 790-784, Korea
(Dated: April 14, 2024)

Electronic structures of $\text{Zn}_{1-x}\text{Co}_x\text{O}$ have been investigated using photoemission spectroscopy (PES) and x-ray absorption spectroscopy (XAS). The Co 3d states are found to lie near the top of the O 2p valence band, with a peak around 3 eV binding energy. The Co 2p XAS spectrum provides evidence that the Co ions in $\text{Zn}_{1-x}\text{Co}_x\text{O}$ are in the divalent Co^{2+} (d^7) states under the tetrahedral symmetry. Our finding indicates that the properly substituted Co ions for Zn sites will not produce the diluted ferromagnetic semiconductor property.

PACS numbers:

Diluted magnetic semiconductors (DMs) are considered as good candidates for spintronics materials because of the possibility of incorporating the spin degree of freedom in traditional semiconductors^{1,2}. Motivated by the recent theoretical calculations by Dietlet al.³ which predicted room-temperature ferromagnetism in Mn-doped ZnO , $\text{Zn}_{1-x}\text{T}_x\text{O}$ systems (T = 3d transition-metal atom) have been investigated extensively. Indeed there were reports that $\text{Zn}_{1-x}\text{Mn}_x\text{O}$ epitaxial thin films exhibited ferromagnetic properties^{4,5} and that $\text{Zn}_{1-x}\text{Co}_x\text{O}$ films showed ferromagnetism with the Curie temperature $T_C \sim 300\text{ K}$ ⁶. However, the reproducibility is somewhat questionable, and there are contradicting reports on Co-doped ZnO ^{6,7,8}. Technologically ZnO -based DMs of $\text{Zn}_{1-x}\text{T}_x\text{O}$ attract much attention due to the cheapness and abundance of ZnO , and the easy solubility of T atoms in ZnO up to several ten %^{4,9}. In addition, since ZnO has a wide band gap energy of 3.4 eV, ZnO -based DMs would be useful for short wavelength magneto-optical applications.

In order to understand the magnetic interaction in $\text{Zn}_{1-x}\text{T}_x\text{O}$, it is essential to understand the electronic structure of the doped 3d T impurities in $\text{Zn}_{1-x}\text{T}_x\text{O}$. Photoemission spectroscopy (PES) is one of the powerful experimental methods for providing direct information on the electronic structures of solids. To our knowledge, only a few PES studies have been reported on $\text{Zn}_{1-x}\text{T}_x\text{O}$: the PES study on $\text{Zn}_{1-x}\text{Mn}_x\text{O}$ ¹⁰ and the Co 2p core-level PES spectra for $\text{Zn}_{1-x}\text{Co}_x\text{O}$ ⁸.

In this study we have investigated the electronic structure of homogeneous bulk samples of $\text{Zn}_{1-x}\text{Co}_x\text{O}$ using PES and x-ray absorption spectroscopy (XAS). Differently from previously reported films⁶, magnetic properties of our bulk $\text{Zn}_{1-x}\text{Co}_x\text{O}$ samples revealed that

the Co-Co magnetic interaction is dominated by the antiferromagnetic coupling¹¹. Magnetic susceptibility at high temperature exhibits a typical Curie-Weiss behavior with negative T_C and the magnetization of Co ion is reduced with increasing the Co ion concentration reflecting an increase in average antiferromagnetic interaction between Co ions. Hence the present bulk sample is not a diluted ferromagnetic semiconductor.

Polycrystalline $\text{Zn}_{1-x}\text{Co}_x\text{O}$ samples ($x = 0.01$) were synthesized using the standard solid-state reaction method. $\text{Zn}_{1-x}\text{Co}_x\text{O}$ samples were obtained by sintering a mixed powder of $(1-x)\text{ZnO} + x\text{CoO}$ at $T = 1400^\circ\text{C}$ for 2 hours followed by the furnace cooling in air. The x-ray diffraction (XRD) analysis showed that all the samples have the single phase of the wurtzite structure with no impurity phase. Valence-band PES, XAS and Co 2p 3d resonant photoemission spectroscopy (RPES) measurements were performed at the 2B1 and 8A1 beamlines of the PAL. Samples were cleaned in situ by repeated scraping with a diamond file and the data were obtained at room temperature with the pressure better than 4×10^{-10} Torr. The Fermi level E_F ¹² and the overall instrumental resolution (FWHM) of the system were determined from the valence-band spectrum of a sputtered Au foil in electrical contact with a sample. The FWHM was about 0.1–0.6 eV between a photon energy $h\nu = 30\text{ eV}$ and $h\nu = 600\text{ eV}$. All the spectra were normalized to the mesh current. The XAS spectra were obtained by employing the total electron yield method. The experimental energy resolution for the XAS data was set to 0.2 eV at the Co 2p absorption threshold ($h\nu = 700\text{ eV}$). Core-level spectra and the valence-band spectrum with $h\nu = 1486.6\text{ eV}$ were obtained by using the monochromatized Al K α radiation with a FWHM of 0.6 eV.

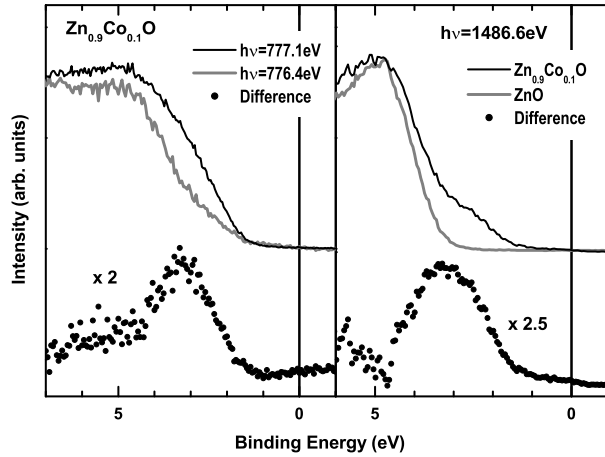


FIG. 1: Left: Comparison of the Co $2p_{3/2} \rightarrow 3d$ on-resonance spectrum ($h\nu = 777.1$ eV) and the off-resonance spectrum ($h\nu = 776.4$ eV) for $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$, scaled at 7 eV BE. Right: Comparison of the valence-band spectrum of ZnO and that of $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$, obtained with $h\nu = 1486.6$ eV. For both cases, the difference curves are shown at the bottom.

We have measured the valence-band PES spectra of $\text{Zn}_{1-x}\text{Co}_x\text{O}$ ($x = 0; 0.1$) over a wide several photon energy range 25 eV $h\nu = 1486.6$ eV, which includes the Co $2p \rightarrow 3d$ RPES energies (see Fig. 2). Our valence-band PES spectrum of ZnO agrees with the existing data in the literature¹³. Valence-band spectra for ZnO and $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$ were rather similar, showing two large structures, one sharp peak around 11 eV binding energy (BE), and the other broad band between 3 eV and 7 eV BE. The former and latter peaks are assigned as the Zn 3d and O 2p emissions, respectively. They also reveal negligible emission near E_F , reflecting that both ZnO and $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$ are insulating.

The left panel of Fig. 1 compares the on-resonance ($h\nu = 777.1$ eV) and off-resonance ($h\nu = 776.4$ eV) spectra for $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$ in the Co $2p_{3/2} \rightarrow 3d$ RPES, which are scaled to each other at 7 eV BE. The difference between on-resonance and off-resonance can be considered as representing the Co 3d partial spectral weight distribution (PSW)¹⁴. The right panel of Fig. 1 compares the valence-band spectrum of $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$ to that of ZnO, obtained with $h\nu = 1486.6$ eV. The differences between $x = 0$ and $x = 0.1$ also reflect the effect of the Co 3d states. In both cases the differences are shown at the bottom, which are very similar to each other, showing a peak around 3 eV BE and negligible emission near E_F ¹⁵. These results provide evidence that the Co 3d states in $\text{Zn}_{1-x}\text{Co}_x\text{O}$ are located near the top of the O 2p valence band.

The extracted Co 3d PSW reveals almost no emission between E_F and 2 eV BE. This feature does not agree with the calculated Co 3d PDOS (partial density of states), obtained from the LSDA (local spin-density

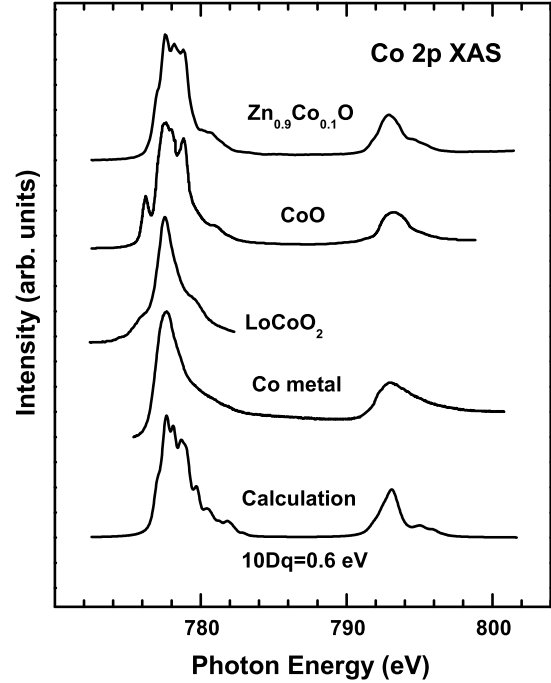


FIG. 2: The Co 2p XAS spectrum of $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$ in comparison to those of CoO (Co^{2+}) [Ref.¹⁸], LiCoO_2 (Co^{3+}) [Ref.¹⁹], and Co metal [Ref.¹⁸]. The data for CoO, LiCoO_2 , and Co metal were shifted by +0.1 eV, 3.64 eV and 0.1 eV, respectively. The calculated Co 2p XAS spectrum for low-spin Co^{2+} under the T_d symmetry is presented at the bottom.

approximation) band structure calculation¹⁶. The calculated Co 3d PDOS for $\text{Zn}_{0.75}\text{Co}_{0.25}\text{O}$ shows a sharp e_g^2 peak near E_F . To resolve this discrepancy, more elaborate calculations such as LSDA+U incorporating the Coulomb correlation U between Co 3d electrons will be required because it is well known that the LSDA calculation does not properly describe the electronic structures of insulators with strongly correlated electrons¹⁷.

Figure 2 compares the Co 2p XAS spectrum of $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$ with those of reference Co oxides, having the formal Co valences of 2+ (CoO, Ref.¹⁸) and 3+ (LiCoO_2 , Ref.¹⁹), and that of Co metal (Ref.¹⁸). Note that Co ions both in CoO and LiCoO_2 are located at the octahedron (O_h) centers. The peak positions and the line shape of the Co 2p XAS spectrum depend on the local electronic structure of the Co ion, providing the information about the valence state and the ground state symmetry of the Co ion^{20,21,22}. The Co $2p_{3/2}$ and $2p_{1/2}$ spectral parts are clearly separated by the large 2p core-hole spin-orbit interaction, and the core-hole lifetime broadening is small, resulting in the sharp multiplet structures. The Co 2p XAS spectrum of $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$ looks similar to that of CoO except for the absence of the low-energy shoulder ($h\nu = 776$ eV), but quite different from those of LiCoO_2 and Co metal. This observation indicates that Co ions in

$\text{Zn}_{1-x}\text{Co}_x\text{O}$ might be in the divalent Co^{2+} valence states, but not in the trivalent Co^{3+} valence states, and that the formation of the Co metal cluster in our $\text{Zn}_{1-x}\text{Co}_x\text{O}$ samples can be ruled out.

In order to estimate the valence state of Co ions in the ground states, we have analyzed the Co 2p XAS spectrum of $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$ within the cluster model where the effects of the multiplet interaction, the crystal field, and the hybridization with the O p ligands are included²¹. The calculated XAS spectrum is shown at the bottom of Fig. 2. We have found that including only one configuration, corresponding to Co^{2+} (d^7), and the tetrahedral (T_d) crystal field energy of $10Dq = 0.6$ eV yields a good fit for the measured 2p XAS spectrum²³. The analysis shows that it is not necessary to include the charge-transfer configuration, $d^{n+1}\bar{L}^1$ (\bar{L} : a ligand hole), indicating that the hybridization between Co 3d and O p orbitals is small, in contrast to Mn-doped ZnO case¹⁰. We have checked that small changes in the parameters do not affect the overall spectral shape including the prominent peak positions. Based on the calculated XAS spectrum, one can conclude that the doped-Co ions in $\text{Zn}_{1-x}\text{Co}_x\text{O}$ are divalent in the ground states, i.e., Co^{2+} ($S = 3$) under the T_d symmetry with a small crystal field energy²⁴. Our finding

suggests that, in our samples, Co ions substitute properly for the Zn sites with Co^{2+} valence states. In view of no long range ferromagnetic order in our samples, the reported DM S properties in some Co-doped ZnO^{6,8} are likely to be extrinsic, that is, to originate from Co cluster or other impurity phases.

In conclusion, the electronic structures of bulk $\text{Zn}_{1-x}\text{Co}_x\text{O}$ samples have been investigated by employing PES and XAS. According to the Co 2p \rightarrow 3d RPES and the careful comparison between $x = 0$ and $x = 0.1$, the Co 3d states in $\text{Zn}_{1-x}\text{Co}_x\text{O}$ are found to lie near the top of the O 2p valence band with a peak around 3 eV BE. The measured Co 2p XAS spectrum shows that the ground states of Co ions in $\text{Zn}_{1-x}\text{Co}_x\text{O}$ are the divalent Co^{2+} states under the T_d symmetry corresponding to the total spin of $S = 3$ per Co ion. Our finding suggests that the properly substituted Co ions in Co-doped ZnO do not produce the DM S property with the long range ferromagnetic order.

Acknowledgments This work was supported by the KRF (KRF-2002-070-C00038) and by the KOSEF through the CSCMR at SNU and the eSSC at POSTECH. The PAL is supported by the MOST and POSCO in Korea.

-
- * Author to whom all correspondence should be addressed: kangj@ catholic.ac.kr
- ¹ J. K. Furdyna, J. Appl. Phys. 64, R29 (1988).
 - ² S. A. Wolf, D. D. Awschalom, R. A. Buhrman, J. M. Daughton, S. von Molnar, M. L. Roukes, A. Y. Chitchelekanova, and D. M. Treger, Science 294, 1488 (2001).
 - ³ T. Dietl, H. Ohno, F. Matsukura, J. Cibert, and D. Ferrand, Science 287, 1019 (2000).
 - ⁴ T. Fukumura, Z. Jin, A. Ohtomo, H. Koinuma, M. Kawasaki, Appl. Phys. Lett. 75, 3366 (1999).
 - ⁵ S. W. Jung, S.-J. An, G. C. Yi, C. U. Jung, S. I. Lee, and S. Cho, Appl. Phys. Lett. 80, 4561 (2002).
 - ⁶ K. Ueda, H. Tabata, and T. Kawai, Appl. Phys. Lett. 79, 988 (2001).
 - ⁷ J. H. Kim, H. K. Kim, D. K. Kim, Y. E. Ihm, and W. K. Choo, J. Appl. Phys. 92, 6066 (2002).
 - ⁸ H. J. Lee, S. Y. Jeong, C. R. Cho, and C. H. Park, Appl. Phys. Lett. 81, 4020 (2002).
 - ⁹ Z. Jin, M. Murakami, T. Fukumura, Y. Matsumoto, A. Ohtomo, M. Kawasaki, and H. Koinuma, J. Crystal Growth 214/215, 55 (2000).
 - ¹⁰ T. Mizokawa, T. Nambu, A. Fujimori, T. Fukumura, and M. Kawasaki, Phys. Rev. B 65, 085209 (2002).
 - ¹¹ S. W. Yoon, S.-B. Cho, S. C. Wi, S. Yoon, B. J. Suh, H. K. Song, and Y. J. Shin, J. Appl. Phys. 93, 7879 (2003).
 - ¹² Since $\text{Zn}_{1-x}\text{Co}_x\text{O}$ samples are insulating, there is some ambiguity in determining E_F . However, the charging did not distort the valence-band lineshape with time.
 - ¹³ M. Ruckh, D. Schmid, and H. W. Schock, J. Appl. Phys. 76, 5945 (1994).
 - ¹⁴ J.-S. Kang, J. H. Kim, A. Sekiyama, S. Kasai, S. Suga, S. W. Han, K. H. Kim, T. Muro, Y. Saitoh, C. Hwang, C. G. Olson, B. J. Park, B. W. Lee, J. H. Shim, J. H. Park, and

- B. I. M in Phys. Rev. B 66, 113105 (2002).
- ¹⁵ When the difference is obtained with the on-resonance and off-resonance spectra being scaled at the Zn 3d peak, we get another broad feature between 4 eV and 8 eV BE. This feature is ascribed to the Co 3d-O 2p hybridized states. Here we focus on the resonating feature which has rather pure Co 3d electron character.
- ¹⁶ K. Sato and H. K. Yoshida, Semicond. Sci. Technol. 17, 367 (2002).
- ¹⁷ J. H. Park, S. K. Kwon, and B. I. M in, Physica B 281-282, 703 (2000).
- ¹⁸ T. J. Regan, H. Ohldag, C. Stamm, F. Nolting, J. Luning, J. Stohr, and R. L. White, Phys. Rev. B 64, 214422 (2001).
- ¹⁹ J. van Elp, J. L. Wieldand, H. Eskes, P. Kuiper, G. A. Sawatzky, F. M. F. de Groot, and T. S. Tumer, Phys. Rev. B 44, 6090 (1991).
- ²⁰ F. M. F. de Groot, J. C. Fuggle, B. T. Thole, and G. A. Sawatzky, Phys. Rev. B 42, 5459 (1990).
- ²¹ G. van der Laan and I. W. Kirkman, J. Phys.: Condens. Matter 4, 4189 (1992).
- ²² J.-Y. Kim, J. H. Park, B.-G. Park, H.-J. Noh, S.-J. Oh, J. S. Yang, D.-H. Kim, S. D. Bu, T.-W. Noh, H.-J. Lin, H.-H. Sieh, and C. T. Chen, Phys. Rev. Lett. 90, 017401 (2003).
- ²³ The fitting parameters are scaled by 80% of the atomic Slater integrals ($F(\text{dd})$; $F(\text{pd})$, and $G(\text{pd})$).
- ²⁴ In the T_d symmetry for Co ions, one cannot distinguish between the low-spin (LS) and high-spin (HS) divalent Co^{2+} states because the e_g states are located below the t_{2g} states. This results in the same total spin $S = 3$ for both the small (the so-called LS state) and high (the so-called HS state) values of $10Dq$.