

Anomalous elasticity of nematic and critically soft elastomers

Olof Stenull and T. C. Lubensky
Department of Physics and Astronomy
University of Pennsylvania
Philadelphia, PA 19104
USA

(Dated: January 2, 2022)

Uniaxial elastomers are characterized by d elastic constants. If their elastic modulus C_5 describing the energy of shear strains in planes containing the anisotropy axis vanishes, they are said to be soft. In spatial dimensions d less than or equal to 3, soft elastomers exhibit anomalous elasticity with certain length-scale dependent bending moduli that diverge and shear moduli that vanish at large length-scales. Using renormalized field theory at $d = 3$ and to first order in $\epsilon = 3 - d$, we calculate critical exponents and other properties characterizing the anomalous elasticity of two soft systems: (i) nematic elastomers in which softness is a manifestation of a Goldstone mode induced by the spontaneous symmetry breaking associated with a transition from an isotropic state to a nematic state and (ii) a particular version of what we call a critically soft elastomer in which $C_5 = 0$ corresponds to a critical point terminating the stability regime of a uniaxial elastomer with $C_5 > 0$.

PACS numbers: 61.41.+e, 64.60.Fr, 64.60.Ak

I. INTRODUCTION

Liquid-crystalline elastomers [1, 2, 3] are elastic media with the macroscopic symmetry properties of liquid crystals [4, 5]. They consist of weakly crosslinked polymeric networks with mesogenic units. The existence of the rubbery crosslinked network has apparently little impact on liquid crystalline phase behavior. In fact, the usual thermotropic liquid crystal phases, i.e., the nematic, cholesteric, smectic-A, and smectic-C phases have their elastomeric counterparts [3, 6]. However, because liquid-crystalline elastomers cannot flow, they have mechanical properties that differ significantly from standard liquid crystals. Usually, liquid-crystalline elastomers are prepared by crosslinking side-chain [10] or main-chain [7] polymers. Alternative methods of synthesis include the polymerization of monomeric solutes in a liquid-crystalline solvent [8] or the conignment of a conventional liquid crystal in a dilute flexible matrix such as aerosil [9].

The main subject of this paper are nematic liquid-crystalline elastomers, or briefly, nematic elastomers (NEs). For recent reviews on NEs see Refs. [10, 11]. These materials have unique properties that make them candidates for device applications. Temperature change [12] or illumination [13] can alter the orientational order and cause the elastomer to extend or contract as much as 400% [14]. This qualifies nematic elastomers as contestants for use in artificial muscles [15, 16]. Another striking property of nematic elastomers is their soft elasticity [17, 19, 20, 21] characterized by vanishing shear stresses for a range of longitudinal strains applied perpendicular to the uniaxial direction.

The origin of soft elasticity in NEs is the spontaneous breaking of rotational symmetry of the isotropic state induced by the development of orientational order in the nematic state [17, 18]. This spontaneous symme-

try breaking has the consequence that NEs are not like conventional uniaxial elastomers characterized by d independent shear moduli. Rather, the elastic constant associated with shear in planes containing the anisotropy axis (customarily called C_5) vanishes in NEs.

Though we are primarily interested in NEs, we also study a particular version of another class of soft uniaxial elastomers in which the elastic constant C_5 simply vanishes for energetic or entropic reasons. In this case, $C_5 = 0$ is a critical point marking the boundary between the high-symmetry uniaxial phase with $C_5 > 0$ and a low-symmetry sheared phase with $C_5 < 0$. In other words, C_5 acts like the temperature variable in a standard thermal phase transition. A complete model of this critical point requires the introduction of third and fourth order terms in the nonlinear strains to stabilize the system when $C_5 < 0$. Since this complete model is characterized by a large number of parameters, it is quite complex. Rather than analyze this full model, we consider simpler model systems, which we call critically soft elastomers or CSEs, defined by simply setting $C_5 = 0$ in the standard elastic energy of a uniaxial medium containing only quadratic terms in nonlinear strains. Remarkably, CSEs exhibit well-defined anomalous elasticity much like that of the more physical NEs even though they lack the nonlinear terms needed to stabilize their low-symmetry phase. CSEs are simpler in many ways than NEs, and the analysis of their anomalous behavior provides a useful and instructive tutorial prelude to the analysis of NEs.

On the level of mean-field theory, the elastic energies of NEs and CSEs coincide. Therefore, their respective elastic properties are equivalent above their mutual upper critical dimension 3. For dimensions $d \leq 3$, however, fluctuations become important. These fluctuations lead to Ginzburg-Pelcovits [22] type renormalizations culminating in anomalous elasticity, i.e., in a length-scale dependence of certain elastic constants, with different uni-

universality classes for NEs and CSEs.

In the present paper we explore the anomalous elasticity of NEs and CSEs by carrying out a renormalization group (RG) analysis. Using the methods of renormalized field theory [23] we examine the scaling behavior of the elastic constants in $d = 3$ as well as in $d = 3 - \epsilon$ dimensions. A brief account of our work on NEs appears in Ref. [24]. Our work on CSEs has not been reported hitherto. We will treat only systems in which random stresses are not important. Random stresses lead to a different universality class with anomalous behavior [17, 25] below $d = 3$ rather than three dimensions.

The plan of presentation is as follows: In Sec. II we give a brief summary of our main results. In Sec. III we discuss CSEs. In Sec. IIIA we briefly review some elements of the Lagrangian theory of elasticity and then set up a Landau-Ginzburg-Wilson elastic energy functional (Hamiltonian) for CSEs. As a prelude to the subsequent RG analysis we analyze the symmetry contents of this Hamiltonian. Section IIIB contains the core of our renormalized field theory of CSEs. We explain our diagrammatic perturbation calculation and its renormalization. By solving the appropriate RG equation, we ascertain the scaling behavior of displacement correlation functions and ultimately that of the relevant elastic moduli. We conclude Sec. III by making contact with conventional uniaxial elastomers by incorporating a small but nonvanishing C_5 , which leads to semi-soft elasticity. Section IV deals with NEs and has an outline similar to that of Sec. III. In Sec. IVA we derive a Landau-Ginzburg-Wilson minimal model for NEs in form of a field theoretic Hamiltonian. Our renormalized field theory for this model is presented in Sec. IVB. The main part of this paper concludes with Sec. V, where we give concluding remarks. There are five Appendices. In Appendices A, B and C we derive Ward identities for CSEs and NEs. An alternative RG approach to NEs is sketched in Appendix D. Appendix E contains details on the calculation of Feynman diagrams.

II. SUMMARY OF RESULTS

For the convenience of the reader we now summarize our main results before we get into details of our work.

A. Critically soft elastomers

The elastic constants of CSEs are defined via the model elastic energy

$$H = \frac{1}{2} \int d^d x \left[C_1 u_{dd}^2 + K r^2 u_d^2 + 2C_2 u_{dd} u_{aa} + C_3 u_{aa}^2 + 2C_4 u_{ab} u_{ab} + C_5 u_{ad} u_{ad} \right] \quad (2.1)$$

where u_d and u_a , $a = 1, \dots, d-1$, are, respectively, the directions parallel and perpendicular to the nematic order

and u_{dd} , u_{ab} , and u_{ad} are components of the Lagrangian nonlinear strain tensor [26, 27]. The elastic constant C_1 describes longitudinal shear along the anisotropy. C_2 couples strains along the anisotropy axis to shears in the plane perpendicular to the anisotropy axis. The elastic constants C_3 and C_4 are associated with shear purely in the plane perpendicular to the distinguished direction. K is a bending modulus. The pure CSE system with soft elasticity is characterized by $C_5 = 0$. The coupling C_5 plays a role similar to that of the temperature in a thermal phase transition. When $C_5 > 0$, the system displays conventional uniaxial elasticity. When $C_5 < 0$, the system is unstable with respect to the formation of a lower-symmetry (sheared) elastic state. $C_5 = 0$ marks the transition between the two phases. At this point, the system shows critical behavior analogous to critical behavior at a thermal phase transition. Our simple CSE model does not include higher order terms in the strain to stabilize the sheared phase. We expect, however, that the full model with these terms included will have the same structure as our CSE model, at least for $C_5 = 0$.

The inverse displacement correlation functions (vertex functions) obey scaling forms that can be expressed for $d < 3$ as

$$\hat{\chi}_{dd}(q_\perp; q_\parallel) = \frac{K}{T} L_\perp^{4-\nu_d-\kappa} \quad (2.2a)$$

$$\hat{\chi}_{dd}(q_\perp; q_\parallel) \sim \frac{L_\perp q_\perp}{\nu_d}; \frac{L_d q_\parallel}{\nu_d}; \frac{C_5}{K} \frac{L_\perp^2}{\nu_d-5};$$

$$\hat{\chi}_{ad}(q_\perp; q_\parallel) = \frac{C_2}{T} L_\perp^{1-\nu_d-1-\nu_2+\nu_+} \quad (2.2b)$$

$$\hat{\chi}_{ad}(q_\perp; q_\parallel) \sim \frac{L_\perp q_\perp}{\nu_d}; \frac{L_d q_\parallel}{\nu_d}; \frac{C_5}{K} \frac{L_\perp^2}{\nu_d-5};$$

$$\hat{\chi}_{ab}(q_\perp; q_\parallel) = \frac{C_4}{T} L_\perp^{2-\nu_d-\nu_2-\nu_c} \quad (2.2c)$$

$$\hat{\chi}_{ab}(q_\perp; q_\parallel) \sim \frac{L_\perp q_\perp}{\nu_d}; \frac{L_d q_\parallel}{\nu_d}; \frac{C_5}{K} \frac{L_\perp^2}{\nu_d-5};$$

where $q_\parallel$ and $q_\perp$ are, respectively, wavenumbers (or momenta) parallel and perpendicular to the anisotropy axis.

$$\kappa = 4-\epsilon; \quad \nu_c = \epsilon; \quad \nu_2 = \epsilon; \quad (2.3a)$$

$$\nu_5 = 1-2\epsilon; \quad \nu_d = (4-\kappa)=2; \quad (2.3b)$$

where $\epsilon = 3-d$, are scaling exponents. In principle, the exponents ν_d and ν_2 could be independent of the other exponents. For the CSE model, however, they are not at least to first order in ϵ . The scaling functions $\hat{\chi}_{dd}(q_\perp; q_\parallel; e)$, $\hat{\chi}_{ad}(q_\perp; q_\parallel; e)$, and $\hat{\chi}_{ab}(q_\perp; q_\parallel; e)$ are respectively proportional to $q_\perp^4 + q_\parallel^2 + e q_\perp^2$, $q_\perp q_\parallel$ and $q_\perp^2$ in the long-wavelength limit in mean-field theory. $\hat{\chi}_{ab}$ also has a term proportional to $q_\parallel^4$, but its coefficient is irrelevant and we will not be concerned with it here. The boundary between scaling and Gaussian behavior is

marked by the non-linear length scales

$$L_2 = \frac{h_p}{C_1 K^3} = (C_4 T)^{1/2}; \quad (2.4a)$$

$$L_d = \frac{p}{C_1 K} = L_2^2; \quad (2.4b)$$

where T is the temperature measured in units so that the Boltzmann constant is equal to 1.

The above scaling forms imply the following scaling for the elastic constants:

$$\begin{aligned} C_2 &= \frac{C_3}{8} = \frac{C_4}{8} \\ &< (L_2 \tilde{q}_2 \tilde{q})^c \quad \text{if } \tilde{q}_2 \tilde{q} = 1; q_1 = 0 \\ &= (L_d q_1)^c = \quad \text{if } \tilde{q}_2 \tilde{q}_d = L_2^{-1}; q_2 = 0 \\ &: (L_2 \tilde{q}_2^{-1})^c \quad \text{if } (q_2; q_1) = (0; 0) \end{aligned} \quad (2.5)$$

and

$$\begin{aligned} &< (L_2 \tilde{q}_2 \tilde{q})^K \quad \text{if } \tilde{q}_2 \tilde{q} = 1; q_1 = 0 \\ &K : (L_d q_1)^K = \quad \text{if } \tilde{q}_2 \tilde{q}_d = L_2^{-1}; q_2 = 0 \\ &: (L_2 \tilde{q}_2^{-1})^K \quad \text{if } (q_2; q_1) = (0; 0) \end{aligned} \quad (2.6)$$

where $\tilde{q}_2$ is a correlation length given by

$$\tilde{q}_2 = L_2 (L_2^2 C_5 = K)^{-1/5}; \quad (2.7)$$

The elastic constant C_1 is not renormalized and it is not singular in either the wavenumbers or $\tilde{q}_2$. When C_5 is nonzero, $\tilde{q}_2 \propto C_5^{-1/5} q_2^{-2/5} + K q_2^{-4/5}$ at small q , where $\tilde{q}_2 = (2^{-1/5} K)^{-1/5}$ and K is given by the last expression in Eq. (2.6).

At exactly three dimensions the above power law singularities become logarithmic singularities

$$C_2 = C_3 = C_4 = \ln(\tilde{q}_2 \tilde{q})^{1/7}; \quad (2.8a)$$

$$K = \ln(\tilde{q}_2 \tilde{q})^{4/7}; \quad (2.8b)$$

where $\tilde{q}_2$ is a wavenumber scale. This logarithmic anomaly can be observed for $\tilde{q}_2 \tilde{q} \approx 1$, where

$$\tilde{q}_2 = \frac{h_p}{2 \exp 32} \frac{p}{C_1 K^3} = (7 T C_4)^{-1/2}; \quad (2.9)$$

In the critical regime at small C_5 , we find the following universal Poisson ratios:

$$C_2^2 = (C_1 C_4) = 0 \quad \text{and} \quad C_3 = C_4 = 1/2; \quad (2.10)$$

B. Nematic elastomers

At the transition from the isotropic to the nematic phase, liquid-crystalline elastomers undergo an anisotropic stretch relative to their isotropic reference state of a factor α_{jj} along the nematic axis and $\alpha_{\perp}$ perpendicular to it. In the absence of explicit uniaxial terms such as

$$\frac{1}{2} \int d^3x \frac{1}{d} u_{ii}; \quad (2.11)$$

the elastic energy of the nematic phase that forms spontaneously from an isotropic phase is soft, i.e., the elastic constant C_5 for shears in the uniaxial plane vanishes. After rescaling lengths measured relative to the anisotropic nematic reference state and displacements according to $x_a \rightarrow x_a, x_d \rightarrow \frac{1}{r} x_d, u_a \rightarrow u_a$ and $u_d \rightarrow \frac{1}{r} u_d$, where $r = \frac{2}{\alpha_{jj}} = \frac{2}{\alpha_{\perp}}$, the relevant parts of the elastic energy can be written when uniaxial terms are present and small as

$$\begin{aligned} H = & \frac{1}{2} \int d^3x \frac{1}{2} dx_d C_1 v_{dd}^2 + K \int d^3x \frac{1}{2} u_d^2 \\ & + 2 C_2 v_{dd} v_{aa} + C_3 v_{aa}^2 + 2 C_4 v_{ab}^2 + C_5 v_{ad}^2; \end{aligned} \quad (2.12)$$

with nonstandard strains $v_{ab} = \frac{1}{2} (\partial_a u_b + \partial_b u_a - \partial_a u_d \partial_b u_d)$, $v_{dd} = \partial_d u_d + \frac{1}{2} \partial_a u_d \partial_b u_d$ and $v_{ad} = \frac{1}{2} \partial_a u_d$ and where C_5 goes linearly to zero with h or the magnitude of other uniaxial terms.

The scaling of the inverse displacement correlation functions of NEs is similar to but not identical to that of the CSE model:

$$\chi_{dd}(q_2; q_1) = \frac{K}{T} L_2^{-4} \tilde{q}_2^{-K} \quad (2.13a)$$

$$\propto \frac{L_2 q_2}{\tilde{q}_d}; \frac{L_d q_1}{\tilde{q}_d}; \frac{C_5 L_2^2}{K \tilde{q}_d^{1/5}}; \frac{C_1}{C_4} \frac{1}{\tilde{q}_c};$$

$$\chi_{ad}(q_2; q_1) = \frac{C_2}{T} L_2^{-1} L_d^{-1} \tilde{q}_d^{-1} \quad (2.13b)$$

$$\propto \frac{L_2 q_2}{\tilde{q}_d}; \frac{L_d q_1}{\tilde{q}_d}; \frac{C_5 L_2^2}{K \tilde{q}_d^{1/5}};$$

$$\chi_{ab}(q_2; q_1) = \frac{C_3}{T} L_2^{-2} \tilde{q}_d^{-2} \quad (2.13c)$$

$$\propto \frac{L_2 q_2}{\tilde{q}_d}; \frac{L_d q_1}{\tilde{q}_d}; \frac{C_5 L_2^2}{K \tilde{q}_d^{1/5}}; \frac{C_4}{C_3} \tilde{q}_c^{-1};$$

where, to first order in "

$$K = 38/59; \quad \tilde{q}_c = 4/59; \quad (2.14a)$$

$$= 2^{-21/59}; \quad \tilde{q}_h = 1/2 + 9/108; \quad (2.14b)$$

and

$$L_2 = \frac{h_p}{K^3} = (C_4 T^2)^{1/2}; \quad (2.15a)$$

$$L_d = \frac{p}{C_4 K} = L_2^2; \quad (2.15b)$$

Note that four independent scaling exponents, K , $\tilde{q}_c$, $\tilde{q}_h$, and $\tilde{q}_h$ are required to describe NEs with a small uniaxial energy. In the above, lengths, displacements and q -vectors are measured in rescaled units.

The above scaling forms predict that C_1 , C_2 , and C_3 are unrenormalized and that

$$\begin{aligned} &< (L_2 \tilde{q}_2 \tilde{q})^c \quad \text{if } \tilde{q}_2 \tilde{q} = 1; q_1 = 0 \\ C_4 : & (L_d q_1)^c = \quad \text{if } \tilde{q}_2 \tilde{q}_d = L_2^{-1}; q_2 = 0 \\ &: (L_2 \tilde{q}_2^{-1})^c \quad \text{if } (q_2; q_1) = (0; 0) \end{aligned} \quad (2.16)$$

as well as

$$K = \begin{cases} (L_2 \mathcal{H}_2 \mathcal{J})^K & \text{if } h_2 \mathcal{H}_2 \mathcal{J} = 1; q_1 = 0 \\ (L_d q_1)^K & \text{if } h_2 \mathcal{H}_2 \mathcal{J}_d = L_2 \quad 1; q_2 = 0 \\ (L_2 h_1)^K & \text{if } (q_2; q_1) = (0; 0) \end{cases} \quad (2.17)$$

with h_1 given by

$$h_1 = L_2 (L_2^2 h = K) h_1 : \quad (2.18)$$

At small but nonzero h_1 , $h_1 q_2^2 + K q_2^4$ at small q_2 , where $h_1 = (2 h_1) h_1$ and K is given by the last expression in Eq. (2.17).

At exactly three dimensions the above power laws become

$$C_4 = j \ln(j_2 j_2) j^{4=59}; \quad (2.19a)$$

$$K = j \ln(j_2 j_2) j^{38=59}; \quad (2.19b)$$

The length scale that marks the crossover from harmonic to logarithmic behavior is

$$\eta = \frac{1}{\exp} \frac{h}{64} \frac{P}{K^3} = \frac{P}{(7^6 C_4 T)} : \quad (2.20)$$

Provided that C_5 is small, the critical regime entails four independent Poisson ratios:

$$C_2=C_1 = 1; C_3=C_1 = 1; C_4=C_1 = 0; \quad (2.21a)$$

$$(2C_2 - C_3 - C_1) = C_4 = 1=2; \quad (2.21b)$$

III. CRITICALLY SOFT ELASTOMERS

A. The model

We start by setting up a field theoretic minimal model for CSEs that is suitable for our subsequent RG analysis. We find it convenient to use the Lagrangian formulation of elasticity [26, 27]. In this formulation the mass points of the equilibrium undistorted medium are labeled by their position vectors x in d -dimensional (reference) space. When the medium is distorted, a mass point originally at x is mapped to a new point $R(x)$ in d -dimensional (target) space. Since $R(x) = x$ when there is no distortion, it is customary to introduce the phonon variable $u(x) = R(x) - x$ that measures the deviation of $R(x)$ from x .

Suppose for a moment the medium is distorted solely by stretching. The energy of the distorted state relative to the reference state depends on the relative amount of stretching $dR^2 = dx^2 = 2u_{ij} dx_i dx_j$, where

$$u_{ij} = \frac{1}{2} f @_i u_j + @_j u_i + @_i u_k @_j u_k g \quad (3.1)$$

with $i, j, k = 1; \dots; d$ [28] are the components of the familiar nonlinear Lagrangian strain tensor $\underline{u}$. Note that $\underline{u}$ is invariant under arbitrary rotations in target space.

This feature makes the Lagrangian strain tensor an adequate variable for formulating elastic energies because all elastic media are rotationally invariant in target space. This invariance is easy to understand: different physical orientations of the same sample have the same energy [29]. As customary, the reference state, relative to which $\underline{u}$ is defined, is taken to be in mechanical equilibrium, and hence no terms linear in u_{ij} appear in the stretching energy. To lowest order, the stretching energy is then of the form

$$H_{st} = \frac{1}{2} \int d^d x K_{ijkl} u_{ij} u_{kl}; \quad (3.2)$$

where K_{ijkl} is an elastic constant tensor. For media isotropic in the reference space, for example, there are only two independent elastic constants in K_{ijkl} that are known as the Lamé coefficients and ν . Media with uniaxial symmetry in the reference space are characterized in general by five independent elastic constants. Assuming that the anisotropy axis is in the $\hat{e}_d = (0; \dots; 1)$ direction we may write the stretching energy as

$$H_{st} = \frac{1}{2} \int d^d x \left[\sum_{d=1}^d dx_d C_1 u_{dd}^2 + 2C_2 u_{dd} u_{aa} + C_3 u_{aa}^2 + 2C_4 u_{ab}^2 + C_5 u_{ad}^2 \right] \quad (3.3)$$

with $d_2 = d - 1$ and $a, b = 1; \dots; d_2$.

Now suppose that the elastic constant C_5 vanishes. Rewriting H_{st} in Fourier space one sees easily that the stretching energy cost is zero for phonon displacements $\mathbf{a}(q)$ perpendicular to $\hat{e}_d$ with momentum q parallel to $\hat{e}_d$ and for $\mathbf{a}(q)$ parallel to $\hat{e}_d$ with q perpendicular to $\hat{e}_d$. In other words: CSEs are soft elastic materials.

For many elastic systems it is justified to neglect energetic contributions, such as bending, that are associated with higher derivatives of the displacements. That is, because bending is unimportant compared to stretching at small momenta. Due to the soft elasticity, however, the stretching energy of CSEs can vanish, and hence, bending is important.

For the moment, we set aside the uniaxial term proportional to C_5 and concentrate on the pure soft case. The effects of a small but non-vanishing C_5 will be included later on. Taking into account stretching and bending, the CSE model is defined by the Hamiltonian

$$H = \frac{1}{2} \int d^d x \left[\sum_{d=1}^d dx_d C_1 u_{dd}^2 + K \sum_{d=1}^d r_d^2 u_d^2 + 2C_2 u_{dd} u_{aa} + C_3 u_{aa}^2 + 2C_4 u_{ab} u_{ab} \right]; \quad (3.4)$$

where K is a bending modulus. All other bending terms allowed by symmetry turn out to be irrelevant in the sense of the renormalization group. Also, not all parts of the strains are relevant. Discarding any parts of the strains that lead to irrelevant contributions to the Hamiltonian, as discussed further below, leaves us with

$$u_{ab} = \frac{1}{2} f @_a u_b + @_b u_a + @_a u_d @_b u_d g \quad (3.5a)$$

and

$$u_{dd} = \partial_d u_d : \quad (3.5b)$$

In principle we could use H as it stands in Eq. (3.4) for our RG analysis. We find it convenient, however, to reduce the number of constants featured in H at the onset. To this end, we rescale $u_a \rightarrow (K=C_4)u_a$, $u_d \rightarrow \frac{1}{K}u_d$, and $x_d \rightarrow (C_4=K^{-2})x_d$. Then the Hamiltonian takes on the form

$$H = \frac{1}{2} \int d^d x \int dx_d \left[u_{dd}^2 + r \frac{1}{2} u_d^2 + 2g u_{dd} u_{aa} + f u_{aa}^2 + 2u_{ab} u_{ab} \right] ; \quad (3.6)$$

where

$$r = C_1 K^3 = C_4^2 ; \quad g = C_2 (K=C_4)^{3=2} ; \quad f = C_3 = C_4 : \quad (3.7)$$

At this stage we would like to point out that we explicitly keep the temperature T in the Boltzmann weight $\exp(-H/T)$ governing our field theoretic calculations. In what follows we carry out a perturbation expansion in the temperature, i.e., T serves as our expansion parameter. As a consequence, not only the constants and fields featured in H but also the temperature will require renormalization.

An effective Hamiltonian for u_d alone can be obtained by integrating out the transverse variable u_a from the full CSE Hamiltonian of Eq. (3.4). When $C_4 = 1$, this process leads to the Hamiltonian for a smectic-A liquid crystal whose anomalous elasticity was analyzed by Grinstein and Pelcovits [22]. Our rescaling of variables to obtain Eq. (3.6) with the coefficients of both $(r \frac{1}{2} u_d^2)$ and $2u_{ab}u_{ab}$ set to unity is not ideally suited to taking the $C_4 = 1$ limit. Our primary interest is the anomalous elasticity unique to soft uniaxial systems for which the parametrization of Eq. (3.6) is appropriate. We will not give further consideration to the Grinstein-Pelcovits limit of our model.

As a further step towards our RG analysis, we now discuss the scaling symmetries of our model. First, under a global rescaling of the coordinates $x_a \rightarrow \lambda^{-1} x_a$ and $x_d \rightarrow \lambda^{-2} x_d$, we find a scaling invariant theory provided that $u_a \rightarrow \lambda^{-1} u_a$ and $T \rightarrow \lambda^{-3+d} T$ (invariance). Viewing as an inverse length scale, this means that the field u_a has a naive dimension 1 and that the naive dimension of T is $[T] = 3 - d$. The field u_d and the remaining parameters in H have a vanishing naive dimension. Above $d = 3$ dimensions the naive dimension of T is negative and T is irrelevant whereas it is relevant below $d = 3$. Hence, we identify $d_c = 3$ as the upper critical dimension of the CSE model.

At this point we take a short detour and catch up on justifying the truncation of the strains as stated in Eqs. (3.5). Applying the λ -rescaling to the original full strains leads to

$$u_{ab} \rightarrow \frac{1}{2} \left[\partial_a u_b + \partial_b u_a + \partial_a u_d \partial_b u_d + \frac{1}{2} \partial_a u_c \partial_b u_c \right] \quad (3.8a)$$

and

$$u_{dd} \rightarrow \frac{1}{2} \left[\partial_d u_d + \frac{1}{2} (\partial_d u_d)^2 + \frac{1}{2} \partial_d u_c \partial_d u_c \right] \quad (3.8b)$$

The terms carrying extra powers of λ do not contribute to the leading behavior in the limit $\lambda \rightarrow 0$. Hence, they can be neglected in studying the long length scale behavior at leading order, i.e., they are irrelevant in the sense of the RG.

Second, due to the anisotropy of the model, we may rescale the longitudinal coordinate alone: $x_d \rightarrow \lambda x_d$. Scale invariance is retained if $\lambda^{-2} r$, $g \rightarrow g$, and $T \rightarrow T$ (invariance). Note that the composed couplings

$$r = g^2 = 1 ; \quad g = f ; \quad \text{and } t = \frac{P}{T} \quad (3.9)$$

are invariant under the longitudinal rescaling. The factor $\frac{P}{T}$ is included in the definition of t to render it, like r and g , dimensionless. As we go along, we will see that r , g , and t emerge quite naturally in perturbation theory. Third, H is invariant under the rescaling $u_d \rightarrow u_d + f_d(x_d)$, where f_d is an arbitrary function of the transversal coordinate x_d . Fourth, rescaling $u_a \rightarrow u_a + f_a(x_d) + M_{ab} x_b$ leaves H invariant if the matrix constituted by the M_{ab} is antisymmetric and f_a is a function of the longitudinal coordinate only. Finally, H is invariant under the transformation $u_a \rightarrow u_a + \lambda u_d$ and $u_d \rightarrow u_d - \lambda x_a$ provided that the λ 's are small. Note that this transformation mixes the longitudinal and the transversal fields (mixing invariance). It can be viewed as a remnant of the rotational invariance of the original theory in target space. This mixing transformation will be valuable for us because it leads to Ward identities that reduce the number of vertex functions to be calculated in perturbation theory. These Ward identities will be derived in Appendix A.

B. Renormalization group analysis

In this section we determine the scaling behavior of the correlation function of the fields $u_a(x)$ and $u_d(x)$ by using perturbation theory augmented by renormalization group methods. As usual, we analyze vertex functions that require renormalization due to the presence of ultraviolet (UV) divergences in Feynman diagrams. Our main tools in this section will be dimensional regularization and minimal subtraction. To avoid infrared (IR) singularities in the Feynman diagrams, we supplement our Hamiltonian with a mass term,

$$H \rightarrow H + \frac{1}{2} \int d^d x \int dx_d u_d^2 : \quad (3.10)$$

At the appropriate stage of the calculations we then sent to zero to recover the original situation.

1. Diagrammatic expansion

In order to set up a diagrammatic perturbation expansion we have to determine its constituting elements. First, we have the Gaussian propagator $\underline{G}$ that has the form of a $d \times d$ matrix. The elements of its inverse $\underline{G}^{-1}$ are readily collected from the Hamiltonian:

$$G_{dd} = T^{-1} + !q_d^2 + q_d^4; \quad (3.11a)$$

$$G_{ad} = T^{-1} g q_a q_d; \quad (3.11b)$$

$$G_{ab} = T^{-1} (f+1) q_a q_b + ab q_a^2 q_b^2; \quad (3.11c)$$

Inverting $\underline{G}^{-1}$ we find that the Gaussian propagator has the elements

$$G_{dd} = T \frac{B}{B + A q_d^2 + B q_d^4}; \quad (3.12a)$$

$$G_{ad} = T \frac{g}{B + A q_d^2 + B q_d^4} \frac{q_a q_d}{q_d^2}; \quad (3.12b)$$

$$G_{ab} = T \frac{ab}{q_a^2 q_b^2} \frac{D + C q_d^2 + D q_d^4}{B + A q_d^2 + B q_d^4} \frac{q_a q_b}{q_d^4}; \quad (3.12c)$$

where we have used the shorthand notations $A = ! (f+2) g^2$, $B = f+2$, $C = ! (f+1) g^2$, and $D = f+1$. Second, our diagrammatic expansion features the 4 vertices

$$i \frac{g}{2T} q_a^{(1)} q_b^{(2)} q_b^{(3)}; \quad (3.13a)$$

$$i \frac{f}{2T} q_a^{(1)} q_b^{(2)} q_b^{(3)}; \quad (3.13b)$$

$$i \frac{1}{T} q_a^{(2)} q_b^{(1)} q_b^{(3)}; \quad (3.13c)$$

$$\frac{f+2}{8T} q_a^{(1)} q_a^{(2)} q_b^{(3)} q_b^{(4)}; \quad (3.13d)$$

It is understood that the sum of the momenta has to vanish at each vertex.

Next, we need to determine which of the vertex functions $\Gamma^{(M,N)}$ with M external u_a -legs and N external u_d -legs are supercially UV divergent. Analyzing their topology, we find that the supercial degree of divergence

of our diagrams is given at the upper critical dimension by $\Delta = 4 - M - 2D_k - D_?$, where D_k ($D_?$) is the number of longitudinal (transversal) derivatives on the external legs. Thus, the only vertex functions containing supercially divergent diagrams are $\Gamma_d^{(0;1)}$, $\Gamma_a^{(1;0)}$, $\Gamma_{dd}^{(0;2)}$, $\Gamma_{ad}^{(1;1)}$, $\Gamma_{ab}^{(2;0)}$, $\Gamma_{ddd}^{(0;3)}$, $\Gamma_{add}^{(1;2)}$, and $\Gamma_{dddd}^{(0;4)}$. All these vertex functions have to be taken into account in the renormalization procedure. By virtue of the mixing invariance, however, there exist several relations between the vertex functions in form of Ward identities. These are derived and stated in Appendix A. Due to these Ward identities it is sufficient for our purposes to actually calculate the two-point functions $\Gamma_{dd}^{(0;2)}$, $\Gamma_{ad}^{(1;1)}$, and $\Gamma_{ab}^{(2;0)}$. Once the equations of state $\Gamma_d^{(0;1)} = 0$ and $\Gamma_a^{(1;0)} = 0$ are satisfied and the 2-point functions are renormalized, the Ward

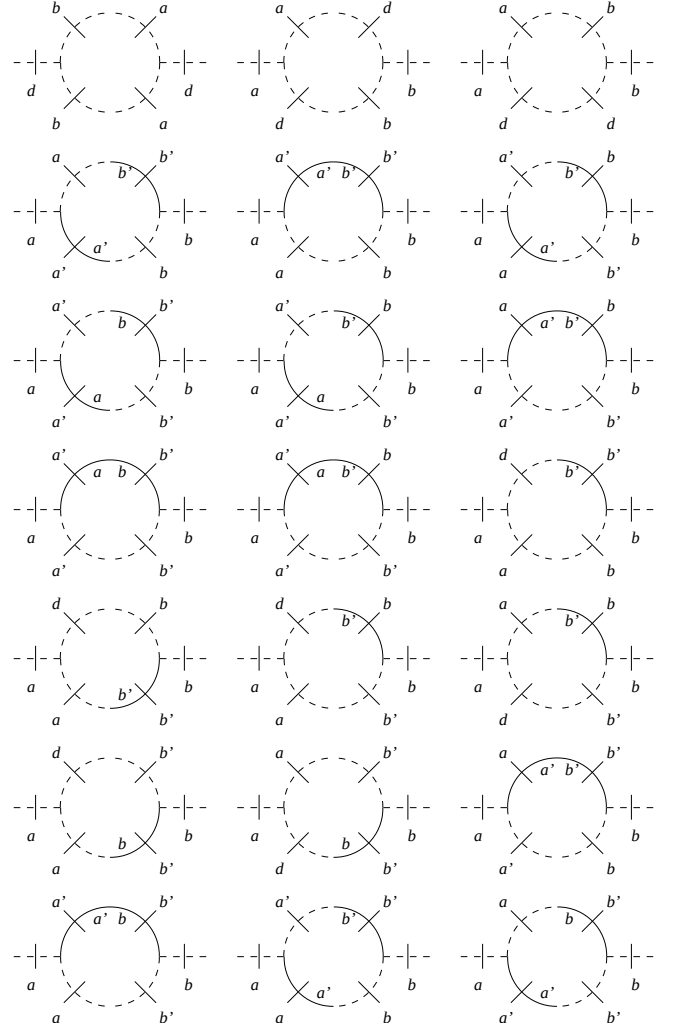


FIG. 1: Feynman diagrams contributing to G_{dd} . The dashed lines symbolize the element G_{dd} of the Gaussian propagator. Lines half dashed and half solid with an index, say a , stand for G_{ad} . Solid lines with 2 indices, say a and b , visualize G_{ab} . The ticks indicate derivatives with respect to the reference space coordinate with an index specifying the component.

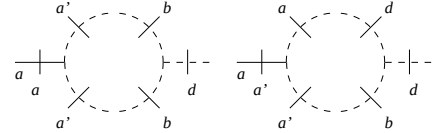


FIG. 2: Feynman diagrams contributing to G_{ad} . The meaning of the symbols is the same as in Fig. 1.

identities guarantee that the remaining vertex functions are cured of their UV divergences.

We calculate the two-point vertex functions to one-loop order using dimensional regularization. The Feynman diagrams entering this calculation are listed in Figs. 1 to 3. Details on computing the diagrams can be found in Appendix E. Our results for the 2-point functions read

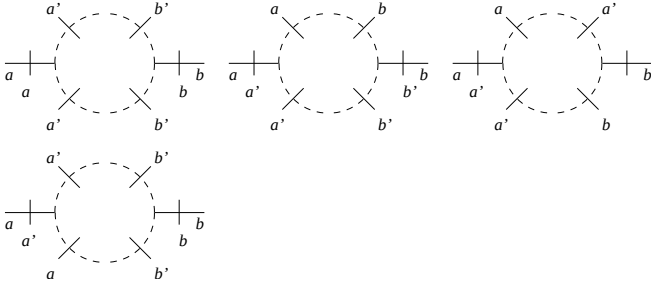


FIG. 3: Feynman diagrams contributing to Γ_{ab} . The meaning of the symbols is the same as in Fig. 1.

$$\Gamma_{dd}^{(0;2)} = T^{-1} \left[\frac{1}{16} \frac{p^2}{g^2 + (2+f)!} + \frac{1}{16} \frac{p^2}{g^2 + (2+f)!} \right] \quad (3.14a)$$

$$\frac{3(1+f)q_d^4}{8} \frac{p^2}{g^2 + (2+f)!} \quad (3.14b)$$

$$\Gamma_{ad}^{(1;1)} = T^{-1} g q_a q_d \frac{p^2}{g^2 + (2+f)!} \quad (3.14b)$$

$$\Gamma_{ab}^{(2;0)} = T^{-1} \left[\frac{(f+1)q_a q_b}{32} + \frac{q_{ab}^2}{32} \right] \frac{p^2}{g^2 + (2+f)!} \quad (3.14c)$$

As already indicated by the vertex functions' superficial degree of divergence, higher order terms in the momentum expansion are convergent and hence can be neglected for our purposes. Likewise, contributions proportional to the mass are convergent. Thus, Γ_{ab} does not require renormalization and consequently its scaling dimension is identical to its naive dimension four. At this stage of the calculation Γ_{ab} has fulfilled its purpose, viz. it prevented IR singularities from producing spurious ϵ poles. In conjunction with the ϵ expansion we now can safely send to zero.

2. Renormalization

The UV divergences have their manifestation in the ϵ poles appearing in Eqs. (3.14). We eliminate these poles by employing the renormalization scheme

$$u_d \rightarrow u_d = Z^{1/2} u_d; \quad (3.15a)$$

$$u_a \rightarrow u_a = Z u_a; \quad (3.15b)$$

$$T \rightarrow T = Z Z_T^{-1} T; \quad (3.15c)$$

$$I \rightarrow I = Z_T^{-1} I; \quad (3.15d)$$

$$g \rightarrow g = Z^{-1/2} Z_T^{-1} Z_g g; \quad (3.15e)$$

$$f \rightarrow f = Z^{-1} Z_T^{-1} Z_f f; \quad (3.15f)$$

where the Γ indicates unrenormalized quantities. Our scheme is chosen so that the Hamiltonian retains its original

structure:

$$\frac{H}{T} = \frac{1}{2T} \int d^d x \left[\frac{1}{2} \partial_\mu \phi \partial^\mu \phi + \frac{1}{2} \phi^2 + \frac{1}{2} \phi^4 + \frac{1}{2} \phi^6 + \frac{1}{2} \phi^8 + \frac{1}{2} \phi^{10} + \frac{1}{2} \phi^{12} + \frac{1}{2} \phi^{14} + \frac{1}{2} \phi^{16} + \frac{1}{2} \phi^{18} + \frac{1}{2} \phi^{20} + \frac{1}{2} \phi^{22} + \frac{1}{2} \phi^{24} + \frac{1}{2} \phi^{26} + \frac{1}{2} \phi^{28} + \frac{1}{2} \phi^{30} + \frac{1}{2} \phi^{32} + \frac{1}{2} \phi^{34} + \frac{1}{2} \phi^{36} + \frac{1}{2} \phi^{38} + \frac{1}{2} \phi^{40} + \frac{1}{2} \phi^{42} + \frac{1}{2} \phi^{44} + \frac{1}{2} \phi^{46} + \frac{1}{2} \phi^{48} + \frac{1}{2} \phi^{50} + \frac{1}{2} \phi^{52} + \frac{1}{2} \phi^{54} + \frac{1}{2} \phi^{56} + \frac{1}{2} \phi^{58} + \frac{1}{2} \phi^{60} + \frac{1}{2} \phi^{62} + \frac{1}{2} \phi^{64} + \frac{1}{2} \phi^{66} + \frac{1}{2} \phi^{68} + \frac{1}{2} \phi^{70} + \frac{1}{2} \phi^{72} + \frac{1}{2} \phi^{74} + \frac{1}{2} \phi^{76} + \frac{1}{2} \phi^{78} + \frac{1}{2} \phi^{80} + \frac{1}{2} \phi^{82} + \frac{1}{2} \phi^{84} + \frac{1}{2} \phi^{86} + \frac{1}{2} \phi^{88} + \frac{1}{2} \phi^{90} + \frac{1}{2} \phi^{92} + \frac{1}{2} \phi^{94} + \frac{1}{2} \phi^{96} + \frac{1}{2} \phi^{98} + \frac{1}{2} \phi^{100} \right] \quad (3.16)$$

The simplest way of determining the renormalization Z -factors is minimal subtraction. In this procedure the Z -factors are chosen so that they solely cancel the ϵ poles and otherwise leave the vertex functions unchanged. Expressed in terms of the effective couplings introduced in Sec. III A our Z -factors are of the structure

$$Z \dots(t; g; f) = 1 + \sum_{m=1}^{\infty} \frac{X^{(m)}(t; g; f)}{m!} \quad (3.17)$$

The $X^{(m)}(t; g; f)$ are expansions in the effective temperature t beginning with the power t^m . It is a fundamental fact of renormalization theory, cf. Ref. [23], that this procedure is suitable to eliminate all the UV-divergences (not only the superficial ones) from any vertex function order by order in perturbation theory. To one-loop order we find that our Z factors are given by

$$Z = 1 + t \frac{14 + 13}{32} \frac{p^2}{g^2 + (2+f)!} \quad (3.18a)$$

$$Z_T = 1 - t \frac{3(1+f)}{8} \frac{p^2}{g^2 + (2+f)!} \quad (3.18b)$$

$$Z_I = 1 + t \frac{1}{16} \frac{p^2}{g^2 + (2+f)!} \quad (3.18c)$$

$$Z_g = 1 + t \frac{2 + (1+f)}{8} \frac{p^2}{g^2 + (2+f)!} \quad (3.18d)$$

$$Z_f = 1 + t \frac{2 + (1 + 4 + 2^2)}{32} \frac{p^2}{g^2 + (2+f)!} \quad (3.18e)$$

3. Scaling 1: RG equation and its solution

Next, we infer the scaling behavior of vertex function from a RG equation. This RG equation is a manifestation of the fact that the unrenormalized theory has to be independent of the arbitrary length scale Λ^{-1} introduced by renormalization. By virtue of this independence, the unrenormalized vertex functions satisfy the identity

$$\frac{\partial}{\partial \Lambda} \Gamma^{(M;N)}(q; g; f; T; g; f) = 0 \quad (3.19)$$

The identity (3.19) translates via the Wilson functions [31]

$$\gamma_{\phi} = \frac{\partial}{\partial t} \ln Z_{\phi} ; \quad (3.20a)$$

$$\gamma_{\phi} = \frac{\partial \ln \Gamma}{\partial t} = \Gamma ; \quad (3.20b)$$

$$\gamma_{\phi} = \frac{\partial \Gamma}{\partial t} = \Gamma + \frac{1}{2} \Gamma + \frac{1}{2} \Gamma ; \quad (3.20c)$$

$$\gamma_{\phi} = \frac{\partial}{\partial t} = (\Gamma + \Gamma + \Gamma - 2g) ; \quad (3.20d)$$

$$\gamma_{\phi} = \frac{\partial}{\partial t} = (\Gamma + \Gamma - f) \quad (3.20e)$$

into the Gell-Mann-Low RG equation

$$D \quad M + \frac{N}{2} \quad (M, N) (f q_2 ; q_1 g ; ! ; t ; ; ;) = 0 : \quad (3.21)$$

Here we have used the shorthand notation

$$D = \frac{\partial}{\partial t} + ! \frac{\partial}{\partial !} + t \frac{\partial}{\partial t} + \frac{\partial}{\partial t} + \frac{\partial}{\partial t} : \quad (3.22)$$

The Wilson- γ -functions are easily gathered from the renormalization factors stated in Eqs. (3.18) upon re-expressing $\frac{\partial}{\partial t}$ as $t \frac{\partial}{\partial t}$. Because the Wilson functions must be finite, one then immediately gets

$$\gamma_{\phi}(t ; ;) = t X^{(1)}(t ; ;) ; \quad (3.23)$$

where $X^{(1)}$ is defined in Eq. (3.17). Since we will need them to determine the fixed points of the RG flow, we state the Wilson- γ -functions explicitly:

$$\gamma_{\phi} = t + t^2 \frac{20 + 19}{32} \frac{p^2}{2 + p^2} ; \quad (3.24a)$$

$$= t \frac{p^2}{32} \frac{(3 + 4 \frac{p^2}{2 + p^2})}{2 + p^2} ; \quad (3.24b)$$

$$= t \frac{2 + 7 \frac{p^2}{2 + p^2} + 7 \frac{p^2}{2 + p^2} + 2 \frac{p^3}{2 + p^2}}{32} : \quad (3.24c)$$

To solve the RG equation we employ the method of characteristics. We introduce a flow parameter λ and look for functions $\gamma(\lambda), Z(\lambda), !(\lambda), t(\lambda), \Gamma(\lambda)$, and $f(\lambda)$ determined by the characteristic equations

$$\frac{\partial \gamma(\lambda)}{\partial \lambda} = \gamma ; \quad \Gamma(1) = \Gamma ; \quad (3.25a)$$

$$\frac{\partial}{\partial \lambda} \ln Z(\lambda) = \Gamma(\lambda) ; \quad \Gamma(\lambda) ; \quad \Gamma(\lambda) ; \quad Z(1) = 1 ; \quad (3.25b)$$

$$\frac{\partial}{\partial \lambda} \ln \Gamma(\lambda) = \Gamma(\lambda) ; \quad \Gamma(\lambda) ; \quad \Gamma(\lambda) ; \quad \Gamma(1) = \Gamma ; \quad (3.25c)$$

$$\frac{\partial}{\partial \lambda} t(\lambda) = t(\Gamma(\lambda) ; \Gamma(\lambda) ; \Gamma(\lambda)) ; \quad t(1) = t ; \quad (3.25d)$$

$$\frac{\partial}{\partial \lambda} \Gamma(\lambda) = (\Gamma(\lambda) ; \Gamma(\lambda) ; \Gamma(\lambda)) ; \quad \Gamma(1) = \Gamma ; \quad (3.25e)$$

$$\frac{\partial}{\partial \lambda} f(\lambda) = (f(\lambda) ; \Gamma(\lambda) ; \Gamma(\lambda)) ; \quad \Gamma(1) = f ; \quad (3.25f)$$

These characteristics describe how the parameters transform if we change the momentum scale according to $\lambda \rightarrow \lambda' = \lambda e^{\lambda}$. Being interested in the IR behavior of the theory, we focus on the limit $\lambda \rightarrow 0$. In this IR limit we find that the set of coupling constants $(\Gamma(\lambda) ; \Gamma(\lambda) ; \Gamma(\lambda))$ flows to a stable fixed point

$$(t ; ;) = \frac{32}{7} ; 0 ; \frac{1}{2} \quad (3.26)$$

satisfying $t(t ; ;) = (t ; ;) = (t ; ;) = 0$. Recalling that $\Gamma = g^2$ and $f = f$, we learn that the stable fixed point implies two universal ratios of the elastic moduli (Poisson ratios):

$$C_2^2 = (C_1 C_4) = 0 \quad \text{and} \quad C_3 = C_4 = 1/2 : \quad (3.27)$$

Note that the longitudinal and the transversal directions are effectively decoupled at the IR stable fixed point. In addition to the stable fixed point there are 4 unstable fixed points, viz. the zero temperature fixed point $t = 0$ as well as $(32 ; 0 ; 1)$, $(64 ; 2/3 ; 1/3, 1/2 ; 1/2)$, and $(32 ; 2/3 ; 1/2 ; 1)$.

With help of the characteristics the RGE is readily solved, at least formally:

$$(M, N) (f q_2 ; q_1 g ; ! ; t ; ; ;) = Z(\lambda)^{(M+N=2)} \quad (M, N) (f q_2 ; q_1 g ; !(\lambda) t(\lambda) ; \Gamma(\lambda) ; \Gamma(\lambda) ; \lambda) : \quad (3.28)$$

As it stands, Eq. (3.28) does not account for the naive dimensions of its ingredients. Recalling the invariance of the Hamiltonian H it is straightforward to check that

$$(M, N) (f q_2 ; q_1 g ; ! ; t ; ; ;) = (d+1) + dM + (d+1)N \quad (M, N) \frac{q_2}{\lambda} ; \frac{q_1}{\lambda} ; ! ; t ; ; ; 1 : \quad (3.29)$$

Moreover, the invariance tells us that

$$(M, N) (f q_2 ; q_1 g ; ! ; t ; ; ;) = (M+N-1) (M, N) q_2 ; \frac{q_1}{\lambda} ; ! ; t ; ; ; = !^{(M+N-1)=2} (M, N) q_2 ; !^{1=2} q_1 ; 1 ; t ; ; ; : \quad (3.30)$$

where the last line reflects our freedom to choose $\lambda = !^{1=2}$. Combining Eqs. (3.28), (3.29) we find that the scaling behavior of the vertex functions is described by

$$(M, N) (f q_2 ; q_1 g ; ! ; t ; ; ;) = (\lambda)^{(d+1)+dM+(d+1)N} Z(\lambda)^{(M+N=2)} (M, N) \frac{q_2}{\lambda} ; \frac{q_1}{(\lambda)^2} ; !(\lambda) t(\lambda) ; \Gamma(\lambda) ; \Gamma(\lambda) ; \lambda : \quad (3.31)$$

Due to Eq. (3.30) we may also write

$$(M, N) (f q_2 ; q_1 g ; ! ; t ; ; ;) = (\lambda)^{(d+1)+dM+(d+1)N} Z(\lambda)^{(M+N=2)} !(\lambda)^{(M+N-1)=2} (M, N) \frac{q_2}{\lambda} ; \frac{!(\lambda)^{1=2} q_1}{(\lambda)^2} ; 1 ; t(\lambda) ; \Gamma(\lambda) ; \Gamma(\lambda) ; \lambda : \quad (3.32)$$

We have to mention that Eqs. (3.31) and (3.32) do not correctly describe $\chi_{ab}^{(2;0)}$ at $q_? = 0$ because we omitted a dangerous irrelevant bending of the type $K_d q_d^4$. Without such a term, Eqs. (3.31) and (3.32) unphysically suggest that the leading scaling behavior of $\chi_{ab}^{(2;0)}$ is independent of q_d for $q_? = 0$. In other words, K_d is dangerous irrelevant as far as the leading behavior of $\chi_{ab}^{(2;0)}$ at $q_? = 0$ is concerned. Because K_d is irrelevant its omission has no impact on the leading behavior of the relevant elastic constants and hence does not affect our main results. Of course one could and it would be interesting to investigate the scaling behavior of K_d . One has to keep in mind, however, that irrelevant terms tend to mix under renormalization with a whole bunch of other irrelevant terms, making a proper RG analysis a tedious endeavour. This will be left to future work.

4. Scaling 2: Physical quantities

The variables we considered so far in our RG analysis had the benefit of being convenient. The upside of this convenience is, however, that the featured quantities have no direct physical meaning. Now we recast our results so that their physical content becomes pronounced.

To have a clear distinction between physical variables and the scaled variables we used in our calculations we mark the latter in the remainder of this section with a hat, i.e., we denote

$$\hat{q}_i = \frac{C_4}{K^2} q_i; \hat{u}_a = \frac{C_4}{K} u_a; \hat{u}_d = \frac{C_4}{K} u_d; \quad (3.33)$$

It is not difficult to see that the relation between the physical vertex functions and the vertex functions in the scaled variables is given by

$$\chi_{ab}^{(M;N)}(f q_?; q_i g; !; t; ; ;) \quad (3.34)$$

$$= K^{M+3N=2} C_4^{1-N=2} \chi_{ab}^{(M;N)}(f q_?; \hat{q}_i g; !; t; ; ;) :$$

Blending Eq. (3.34) and our findings of Sec. II B 3 we now obtain

$$\chi_{ab}^{(M;N)}(f q_?; q_i g; !; t; ; ;) = \frac{1}{T} C_1^{(M+N-2)=2} C_4^{(2M+N-2)=2} K^{(M-2)=2} L_?^{2(d-1)+dM+(d+1)N} \times$$

$$\times \frac{p}{\sqrt{2}} \frac{!^{(N)=!}}{!^{(N)=!}} L_d q_d^{(M+N-1)=2} Z(\gamma)^{(M+N=2)} \times$$

$$\chi_{ab}^{(M;N)} \frac{L_? q_?}{\sqrt{2}}; \frac{!^{(N)=!}}{\sqrt{2}} L_d q_d; \quad ;$$

$$1; t(\gamma); (\gamma); (\gamma); 1; \quad (3.35)$$

where we introduced the susceptibilities

$$\chi_{ab}^{(M;N)} = t \chi_{ab}^{(M;N)} \quad (3.36)$$

to make explicit that the vertex functions are proportional to the inverse temperature. Moreover, we introduced the length scales

$$L_? = \frac{1}{\sqrt{2}}; \quad (3.37a)$$

$$L_d = \frac{C_4}{K^2} \frac{p}{\sqrt{2}} = \frac{C_1}{K} L_?^2; \quad (3.37b)$$

At this stage, $L_?$ and L_d are still arbitrary. Further below we will fix these length scales so that they acquire a physical meaning, viz. the borderline between harmonic and scaling behavior. Note that the result (3.35) is general in the sense that it holds in the harmonic as well as in the scaling limit. When $t(l) \rightarrow 0$, the system behaves approximately like a harmonic system. When l is small, behavior is determined by the fixed point with $t \rightarrow 0$.

Now to our main goal, viz. the behavior of the elastic constants. The sought after behavior can be inferred without much effort from result (3.35). As an example, we consider the case $M = 0, N = 2$ in some detail. In addition to the information contained in Eq. (3.35) we need some knowledge on the concrete form of the scaling function $\chi_{dd}^{(0;2)}$. Since t is of order l^2 it is reasonable to assume that $\chi_{dd}^{(0;2)}$ can be approximated by its Gaussian form [cf. Eq. (3.11)] even in the scaling limit. Hence, we write

$$\chi_{dd}^{(0;2)} \frac{L_? q_?}{\sqrt{2}}; \frac{!^{(N)=!}}{\sqrt{2}} L_d q_d; 1; t(\gamma); (\gamma); (\gamma); 1$$

$$= \frac{p}{\sqrt{2}} \frac{!^{(N)=!}}{!^{(N)=!}} L_d q_d^{1/2} + \frac{L_? q_?^4}{\sqrt{2}}; \quad (3.38)$$

Merging Eqs. (3.38) and (3.35) we obtain the physical vertex function

$$\chi_{dd}^{(0;2)}(q_?; q_i) = T^{-1} C_1(\gamma) q_d^2 + K(\gamma) q_i^4 \quad (3.39)$$

with

$$K(\gamma) = K \sqrt{2} Z(\gamma)^{-1} [t(\gamma)=t]^{-1} [!^{(N)=!}]^{1=2}; \quad (3.40a)$$

$$C_1(\gamma) = C_1 \sqrt{2} Z(\gamma)^{-1} [t(\gamma)=t]^{-1} [!^{(N)=!}]^{1=2}; \quad (3.40b)$$

In the case of the bending modulus we cannot finalize our conclusions without solving the characteristics, i.e. without knowing $Z(\gamma)$ and so on. For C_1 , however, we observe without further information the following:

$$\frac{\partial}{\partial \gamma} C_1(\gamma) = - \frac{t}{t} + \frac{1}{2} = 0; \quad (3.41)$$

Since $!$ is proportional to t it vanishes at the stable fixed point. Hence, C_1 is independent of γ . In other words, C_1 is normal. Of course, we cannot tell from our analysis if this stays true beyond 1-loop order. Nevertheless, this may well be the case.

The behavior of the remaining elastic constants can be extracted by similar means from the other 2-leg vertex functions. We find

$$\chi_{ad}^{(1;1)}(q_2; q_1) = T^{-1} C_2(\nu) q_a q_b; \quad (3.42a)$$

$$\chi_{ab}^{(2;0)}(q_2; q_1) = T^{-1} [C_3(\nu) q_a q_b + C_4(\nu) (q_a q_b + \chi_{ab}^{(2;0)}(q_2, q_1))] : (3.42b)$$

with the anomalous elastic constants

$$C_2(\nu) = C_2 \nu^{-2} Z(\nu)^{3=2} [t(\nu)=t]^{-1} [\nu]=\nu^{-2}; \quad (3.43a)$$

$$C_3(\nu) = C_3 \nu^{-2} Z(\nu)^2 [t(\nu)=t]^{-1} [\nu]=\nu^{-1=2}; \quad (3.43b)$$

$$C_4(\nu) = C_4 \nu^{-2}; \quad (3.43c)$$

To obtain the equation for $C_2(\nu)$ we used the fact that it must be proportional to C_2 and thus to ν^{-2} . Note that ν affects the leading behavior of C_2 despite owing to zero. In other words: ν is a dangerous irrelevant variable. Similar arguments for C_3 imply that $C_3(\nu)$ must be proportional to ν^{-1} which reaches a non-zero fixed point value. There are, therefore, no contributions to the scaling of C_3 from dangerous irrelevant variables.

5. Behavior of the elastic constants in $d < 3$

For $\nu > 0$ we can assign a physical meaning to the hitherto arbitrary length scale L_2 via the definition of our dimensionless temperature t , viz.

$$L_2 = \frac{P \overline{C_1 K^3} t^{-1}}{C_4 T} : \quad (3.44)$$

Of course, this choice also affects the length scale L_d , cf. Eq. (3.37b). The length scales L_2 and L_d mark the borderline between harmonic and critical behavior.

Below 3 dimensions the solutions to the characteristics are for ν^{-1} governed by the IR-stable fixed point. Readily, one finds the power laws

$$Z(\nu) = \nu^{-2}; \quad (3.45a)$$

$$t(\nu) = t \nu^{-1}; \quad (3.45b)$$

where

$$t = (t; \nu; \nu) = \nu^{-5=7}; \quad (3.45c)$$

$$t = (t; \nu; \nu) = \nu^{-4=7}; \quad (3.45d)$$

From our discussion above it is clear that we cannot simply set ν equal to its fixed point value $\nu = 0$ because ν is a dangerous irrelevant variable that affects the scaling behavior of C_2 at leading order. The vanishing of ν is described by

$$\nu = \nu_0 \exp \left(-\frac{w}{T} \right); \quad (3.45e)$$

with a Wegner exponent $w = \nu^{-7}$ corresponding to the smallest eigenvalue of the Hessian of the flow near $(t; \nu; \nu)$.

Combining the formal scaling form of Eq. (3.35) with the power laws of Eq. (3.45) for $Z(\nu)$, $t(\nu)=t$ and $\nu=0$ and the crossover length scales as given in Eqs. (3.44) and (3.37b), we obtain a complete picture of the scaling behavior of the displacement vertex functions in $d < 3$. In particular we obtain Eqs. (2.2) for the 2-point functions $\chi_{dd}^{(0;2)}$, $\chi_{ad}^{(1;1)}$ and $\chi_{ab}^{(2;0)}$ with $C_5 = 0$ featuring the scaling exponents

$$\kappa = \nu^{-2} + \nu^{-2} = 2 = 4 = 7; \quad (3.46a)$$

$$c = \nu^{-2} = 2 = 7; \quad (3.46b)$$

$$2 = \nu^{-3} = 2 + w = 2 = 7 = c; \quad (3.46c)$$

$$= 2 = 2 = 2 = 7 = (4 - \kappa) = 2 : (3.46d)$$

Thus, even though there are three independent exponents κ , c and w the scaling behavior of the 2-point functions is determined, at least to first order in ν , by only two exponents, say κ and c . Upon inserting the power laws (3.45) into Eqs. (3.43) and (3.40a) we obtain the scaling expressions for C_2, C_3, C_4 and K stated in Eqs. (2.5) and (2.6) the review section. Note that K diverges at long length scales whereas C_2, C_3 , and C_4 vanish in this limit.

6. Logarithmic behavior in $d = 3$

Since ν vanishes in $d = 3$ the solutions to the characteristic equations are no longer of power law type. The flow of the temperature, for example, is described at leading order, i.e., for $\nu = 0$ and $\nu = 0$, by

$$\frac{d}{d\nu} t(\nu) = \frac{7}{32} t(\nu)^2 : \quad (3.47)$$

This differential equation is readily solved with the result

$$t(\nu) = t = 1 - \frac{7t}{32} \ln(\nu) : \quad (3.48)$$

Similarly, we find $Z(\nu) = t(\nu) = t \nu^{-\frac{5}{7}}$, $t(\nu) = t \nu^{-\frac{4}{7}}$ and $\nu = t(\nu) = t \nu^{-\frac{1}{7}}$ at leading order. Inserting these logarithmic solutions into Eqs. (3.40a) and (3.43) we find that

$$K(q_2) = K^{-1} \frac{7t}{32} \ln(L_2 \chi_2) : \quad (3.49a)$$

$$C_2(q_2) = C_2^{-1} \frac{7t}{32} \ln(L_2 \chi_2) : \quad (3.49b)$$

$$C_3(q_2) = C_4(q_2) = C_2(q_2) : \quad (3.49c)$$

Of course, C_1 is normal as it was in $d < 3$. Once more, K diverges at long length scales and C_2, C_3 , and C_4 vanish in this limit.

Note that Eqs. (3.49) imply the existence of a nonlinear crossover length scale, viz.

$$\xi = L_2 \exp \left(-\frac{32}{7t} \right) = L_2 \exp \left(-\frac{32}{7T C_4} \frac{P \overline{C_1 K^3}}{C_4} \right) : (3.50)$$

For $\gamma_j \rightarrow 1$ the anomalous elastic constants are approximately harmonic whereas one has clearly anomalous behavior for $\gamma_j \rightarrow 1$.

7. C_5 as a relevant perturbation { semi-soft elasticity

Up to this point we have excluded a term proportional to C_5 , cf. Eqs. (2.1) and (3.3), from the elastic energy of CSEs because such a term destroys the soft elasticity. Now we establish contact to more conventional uniaxial elastomers by incorporating a small but nonvanishing C_5 . As a consequence, we find semi-soft behavior.

Technically, we treat C_5 as a perturbation to the CSE model. It turns out that this perturbation is relevant in the sense of the RG. This situation is analogous to the ϵ model where a deviation from the critical temperature represents a relevant perturbation. Our central task will be to determine the scaling exponent that governs the departure of C_5 from zero.

Our analysis here is based on the full Hamiltonian (2.1). Carrying out the rescaling it is straightforward to see that not the entire strain u_{ad} is relevant and that it is sufficient to keep

$$u_{ad} = \frac{1}{2} \epsilon_a u_d : \quad (3.51)$$

Applying the rescaling that led us from Eq. (3.4) to (3.6) we obtain

$$H_e = H + \frac{e}{2} \int d^d x \int dx_d \epsilon_a u_d \epsilon_a u_d ; \quad (3.52)$$

with H as stated in Eq. (3.6) and where $e = C_5 = (4K)$. Note that $e \sim L^2$, i.e., the naive dimension of e is 2 and hence e is clearly relevant.

The Gaussian part of H_e has an extra term compared to H and hence the Gaussian propagator of H_e is different from that of H . Here, any q_4^4 in Eqs. (3.12) has to be replaced by $q_4^4 + e q_2^2$. The non-Gaussian terms of H_e and H are identical and hence we still have the 4 vertices stated in Eqs. (3.13).

To investigate the departure of e from zero we expand the propagator to linear order in e . Then this expanded propagator is used in our diagrammatic calculation. Of course, at zeroth order in e we retrieve our vertex functions (3.14). The first order in the expansion leads to an extra divergent term in $\Gamma_{dd}^{(0;2)}$ that is proportional to $e q_2^2$. To remove the extra divergence we introduce an additional renormalization factor via setting

$$e \rightarrow e = Z_T^{-1} Z_e e : \quad (3.53)$$

From the diagrams depicted in Fig. 1 we extract that

$$Z_e = 1 - \frac{t}{16} \frac{6+5}{2+} \frac{+}{2+} : \quad (3.54)$$

The RGE for the vertex functions expanded to linear order in e reads

$$D + e \epsilon_e = M + \frac{N}{2} \quad (M, N) (f q_2; q_4; !; t; ; ; e;) = 0 \quad (3.55)$$

with D as stated in Eq. (3.22) and

$$= \epsilon \ln e_j = T_e : \quad (3.56)$$

Setting up a characteristic for e ,

$$\frac{\partial}{\partial \lambda} \ln e(\lambda) = t(\lambda); (\lambda); (\lambda); \quad e(1) = e; \quad (3.57)$$

we find that this coupling flows in $d < 3$ as

$$e(\lambda) = e \lambda^{-\epsilon}; \quad (3.58)$$

where $\epsilon = (t; ;) = 7$. Now, the solution to the RGE (3.55) in conjunction with dimensional analysis tells us that the scaling behavior of $\Gamma_{dd}^{(0;2)}$ expanded to linear order in e is given by

$$\Gamma_{dd}^{(0;2)}(q_2; q_4; !; t; ; ; e;) = (\lambda)^4 Z(\lambda)^{-1} \quad (3.59)$$

$$\Gamma_{dd}^{(0;2)} = \frac{q_2}{\lambda}; \frac{q_4}{(\lambda)^2}; !(\lambda) t(\lambda); (\lambda); (\lambda) \frac{e(\lambda)}{(\lambda)^2}; 1 : \quad (3.60)$$

Next we switch back to physical variables. By performing much the same steps as in Secs. (IIIB 5) and (IIIB 4) we obtain for $d < 3$

$$\Gamma_{dd}^{(0;2)}(q_2; q_4; e) = \frac{K}{T} L_2^{-4} \lambda^{4-\epsilon} \quad (3.60)$$

$$\wedge \Gamma_{dd}^{(0;2)} = \frac{L_2 q_2}{\lambda}; \frac{L_d q_4}{\lambda}; \frac{L_2^2 e}{\lambda^{1-\epsilon}} ; \quad (3.61)$$

where we have dropped several arguments for notational simplicity and where

$$\epsilon = (2) = 1 = 2 \quad \epsilon = 28 : \quad (3.61)$$

Thus, C_5 plays the same role in this problem as temperature plays in a traditional thermodynamic phase transition. As in the thermodynamic case, it is useful to introduce a correlation length

$$\xi = L_2 (e L_2^2)^{-\epsilon} = C_5^{-\epsilon} : \quad (3.62)$$

There are two interesting limits we can now consider: $\gamma_j \rightarrow 1$ and $\gamma_j \rightarrow 1$. In the first case, $\Gamma_{dd}^{(0;2)}$ must be proportional to q_2^2 when $q_4 = 0$ and to q_4^2 when $q_2 = 0$. Thus, we obtain by choosing $\lambda = (\xi = L_2)^{-\epsilon}$ from Eq. (3.60):

$$\Gamma_{dd}^{(0;2)}(q_2; q_4; e) \quad (3.63)$$

$$\frac{1}{T} K L_2^{-\epsilon} \xi^{(2-\epsilon)} q_2^2 = C_5^{-\epsilon} q_2^2 \quad \text{if } q_4 = 0$$

$$\frac{1}{T} C_1 q_4^2 \quad \text{if } q_2 = 0$$

where

$$\epsilon = \epsilon (2 - \kappa) = 1 - 5 = 14 : \quad (3.64)$$

The second limit $\epsilon \rightarrow 1$ corresponds $C_5 \rightarrow 0$, and we must obtain the same scaling forms as we obtained for $C_5 = 0$ with a correction term that vanishes with $(\epsilon \rightarrow 1)^{1-\epsilon}$.

As we stated earlier, we have not included nonlinear terms in our model Hamiltonian [Eq. (3.4)] that are needed to stabilize the system when $C_5 < 0$. In particular, we have not included terms $(u_{ad}u_{ad})^2$, $(\partial_a u_d \partial_a u_d)^2$, $u_{aa}u_{bd}u_{bd}$, $u_{ab}u_{ad}u_{bd}$, $u_{aa}^2 u_{bd}u_{bd}$, $u_{ab}^2 u_{cd}u_{cd}$, and $u_{aa}u_{bc}u_{bd}u_{cd}$, all of which have the same naive scaling dimension as the harmonic terms in nonlinear strain that we retained in Eq. (3.4). Our expectation is that the general theory in which these terms are included will have the same general form as the present theory with, however, a different stable fixed point with in particular a nonzero value of the coefficient of $(u_{ad}u_{ad})^2$. At such a fixed point, $h_a u_d$ will develop a nonzero value at negative C_5 that scales as $(-C_5)^{\frac{1}{2}}$ where $\frac{1}{2} = (1 + \frac{1}{4})^{-1}$. This result can be obtained by observing that Eq. (3.35) for $(0;2)$ implies $\partial_a^2 G_{dd}(x_d; x_a; C_5) = l^{2+} = 2 \partial_a^2 G_{dd}(l^{2+} = 2 x_d; l x_a; l^{-5} C_5)$, where ∂_a^0 is a derivative with respect to $l x_a$, and that $G_{dd}(x_d; x_a; C_5) \sim h_a u_d$ as $x \rightarrow 1$.

IV. NEMATIC ELASTOMERS

Usual NEs are either crosslinked in the isotropic or in the nematic phase. If synthesized in the isotropic phase, the uniaxial anisotropy arises via a spontaneous symmetry breaking at the isotropic to nematic transition and is associated with soft elasticity. Crosslinking in the nematic phase, on the other hand, permanently imprints the uniaxial anisotropy into the material and leads to semi-soft behavior. We will start by studying the soft case. Further below, we will include the effects of an imprinted uniaxial anisotropy to investigate the semi-soft case.

A. The model

Since the spontaneous symmetry axis of soft NEs can point in any direction, their elastic energy has to be rotationally invariant not only in target space but also in reference space. Both invariances are taken into account by writing the stretching energy as

$$\begin{aligned} H_{st} = & \int d^d x \frac{1}{2} \text{tr} \underline{\underline{u}}^2 + \text{tr} \underline{\underline{u}}^2 + A_1 \text{tr} \underline{\underline{u}}^3 \\ & + A_2 \text{tr} \underline{\underline{u}} \text{tr} \underline{\underline{u}}^2 + A_3 \text{tr} \underline{\underline{u}}^3 + B_1 \text{tr} \underline{\underline{u}}^4 + B_2 \text{tr} \underline{\underline{u}}^2 \text{tr} \underline{\underline{u}}^2 \\ & + B_3 \text{tr} \underline{\underline{u}}^2 \text{tr} \underline{\underline{u}}^2 + B_4 \text{tr} \underline{\underline{u}} \text{tr} \underline{\underline{u}}^3 + B_5 \text{tr} \underline{\underline{u}}^4 ; \quad (4.1) \end{aligned}$$

with the first two expansion coefficients being the usual Lamé coefficients. Of course, terms of higher than fourth order are allowed by the symmetries of the system. However, these higher-order terms turn out to be irrelevant in the RG sense and are hence neglected.

Suppose that the spontaneously uniaxially ordered elastomer is described in equilibrium by an equilibrium strain tensor $\underline{\underline{u}}_0$. Without loss of generality we may assume that the anisotropy axis lies in the $\hat{e}_d$ direction and that $\underline{\underline{u}}_0$ is a diagonal matrix with the diagonal elements $u_{0aa} = u_0$ and $u_{0dd} = u_{0k}$. To describe deviations from the equilibrium configuration, we introduce the relative strain

$$\underline{\underline{w}} = \underline{\underline{u}} - \underline{\underline{u}}_0 \quad (4.2)$$

and to expand H in terms of $\underline{\underline{w}}$. By dropping terms that depend only on $\underline{\underline{u}}_0$ we find

$$\begin{aligned} H_{st} = & \int d^d x \left[a_1 w_{dd} + a_2 w_{aa} + b_1 w_{dd}^2 \right. \\ & + b_2 w_{dd} w_{aa} + b_3 w_{aa}^2 + b_4 w_{ab}^2 + b_5 w_{ad}^2 + c_1 w_{dd} w_{ad}^2 \\ & \left. + c_2 w_{aa} w_{bd}^2 + c_3 w_{ab} w_{ad} w_{bd} + d_1 w_{ad}^2 w_{bd}^2 \right] ; \quad (4.3) \end{aligned}$$

where we have discarded terms that turn out to be irrelevant. The new coefficients a_1, a_2, b_1 , and so on, depend on the old coefficients, and so forth, as well as on u_{0k} and u_0 .

By virtue of the rotational invariance in reference space there exists a set W and identities relating the vertex functions implicit in (4.3). We derive these identities in Appendix B. At zero-loop or mean-field level these W and identities correspond to relations between the elastic constants in (4.3),

$$a_1 - a_2 - s b_3 = 0 ; \quad (4.4a)$$

$$b_2 - 2 b_3 - s c_1 = 0 ; \quad b_2 + b_5 - 2 b_4 + s c_1 = 0 ; \quad (4.4b)$$

$$b_5 - 2 b_4 - s c_3 = 0 ; \quad c_1 - c_2 - c_3 - 2 s d_1 = 0 ; \quad (4.4c)$$

where s is an abbreviation for $u_{0k} - u_0$. Since $\underline{\underline{w}}$ describes deviations from the equilibrium $\underline{\underline{u}}_0$ its thermodynamic average $h \underline{\underline{w}} i$ has to vanish. At zero temperature, where the mean-field approximation becomes exact, this means that the coefficients of the linear terms in (4.3) must be zero. Equation (4.4a) then leads to the observation that $b_3 = 0$ for $u_{0k} \notin u_0$. At finite temperatures thermal fluctuations become important and loop corrections renormalize the elastic constants including a_1, a_2 and b_5 . For $h \underline{\underline{w}} i$ to vanish the renormalized versions of a_1 and a_2 have to satisfy equations of state to which $a_1 = 0$ and $a_2 = 0$ are the mean-field approximations. In the following we will assume that we have chosen a_1 and a_2 appropriately so that their respective equations of state are satisfied. In other words: we assume that we expand about the true equilibrium state. Then, the W and identity (B11) generalizing (4.4a) guarantees that the renormalized b_3 vanishes for $u_{0k} \notin u_0$. The vanishing of the elastic constant b_3 is the origin of the softness of NEs as can easily be seen by

rewriting the nonvanishing terms of the Hamiltonian at leading order in small deformations in Fourier space.

In what follows we assume that $a_1 = a_2 = b_3 = 0$. Exploiting the relations (4.4) we rewrite the stretching energy as

$$H_{st} = \frac{1}{2} \int d^3x \left[\frac{1}{2} \text{tr}(\underline{\underline{v}}_{dd}^2) + \frac{1}{2} \text{tr}(\underline{\underline{v}}_{dd} \underline{\underline{v}}_{aa}) + \frac{1}{2} \text{tr}(\underline{\underline{v}}_{aa}^2) + \frac{1}{2} \text{tr}(\underline{\underline{v}}_{ab}^2) \right]; \quad (4.5)$$

where we have introduced the non-standard strains

$$\underline{\underline{v}}_{ab} = \underline{\underline{w}}_{ab} - \frac{1}{2} \underline{\underline{w}}_{ad} \underline{\underline{w}}_{bd}; \quad (4.6a)$$

$$\underline{\underline{v}}_{dd} = \underline{\underline{w}}_{dd} + \frac{1}{2} \underline{\underline{w}}_{ad} \underline{\underline{w}}_{ad}; \quad (4.6b)$$

Next we cast $\underline{\underline{v}}_{ab}$ and $\underline{\underline{v}}_{dd}$ into a more familiar form. Recall that the relative strain $\underline{\underline{w}}$ depends upon the displacement $\underline{\underline{u}}$ relative to the original isotropic state measured in the original reference space coordinate $\underline{\underline{x}}$. It is more convenient, however, to work with a relative strain $\underline{\underline{u}}^0$ that depends on the displacement $\underline{\underline{u}}^0$ relative to the equilibrium state of the NE measured in the coordinate $\underline{\underline{x}}^0$ of the corresponding uniaxial reference state. The tensors $\underline{\underline{w}}$ and $\underline{\underline{u}}^0$ are related via (see, e.g., Ref. [11])

$$\underline{\underline{w}} = \frac{1}{2} \underline{\underline{u}}^0 \underline{\underline{u}}^0; \quad (4.7)$$

where $\underline{\underline{u}}^0$ is the so-called Cauchy deformation tensor of the uniaxial equilibrium state. $\underline{\underline{u}}^0$ and $\underline{\underline{u}}_0$ provide equivalent descriptions of this state and they are related via

$$\underline{\underline{u}}_0 = \frac{1}{2} \underline{\underline{u}}^0 \underline{\underline{u}}^0 = \underline{\underline{1}}; \quad (4.8)$$

where $\underline{\underline{1}}$ denotes the d -dimensional unit matrix. Substituting the relation (4.7) into Eqs. (4.6) we obtain

$$\underline{\underline{v}}_{ab} = \frac{1}{2} \left(\underline{\underline{u}}_a^0 \underline{\underline{u}}_b^0 + \underline{\underline{u}}_b^0 \underline{\underline{u}}_a^0 - \frac{1}{r} \underline{\underline{u}}_a^0 \underline{\underline{u}}_d^0 \underline{\underline{u}}_d^0 \underline{\underline{u}}_b^0 \right); \quad (4.9a)$$

$$\underline{\underline{v}}_{dd} = \frac{1}{2} \left(\underline{\underline{u}}_d^0 \underline{\underline{u}}_d^0 + \frac{1}{r} \underline{\underline{u}}_a^0 \underline{\underline{u}}_a^0 \underline{\underline{u}}_d^0 \underline{\underline{u}}_d^0 \right); \quad (4.9b)$$

where we have used Eqs. (3.5) and (3.51) to express $\underline{\underline{u}}^0$. $r = \frac{2}{0k} = \frac{2}{0?}$ is the usual anisotropy ratio that characterizes the anisotropy of the uniaxial equilibrium state. In the steps leading to Eqs. (4.9) we have exploited that $s = \frac{2}{0?} (r - 1) = 2$. A glance at Eqs. (4.9) shows that we can write $\underline{\underline{v}}$ in a simpler and more traditional form by rescaling $\underline{\underline{x}}_a^0 \rightarrow \underline{\underline{x}}_a$, $\underline{\underline{x}}_d^0 \rightarrow \underline{\underline{x}}_d$, $\underline{\underline{u}}_a^0 \rightarrow \underline{\underline{u}}_a$ and $\underline{\underline{u}}_d^0 \rightarrow \underline{\underline{u}}_d$. Incorporating bending, we eventually arrive at the Hamiltonian

$$H = \frac{1}{2} \int d^3x \left[\frac{1}{2} \text{tr}(\underline{\underline{v}}_{dd}^2) + K \frac{1}{r} \underline{\underline{u}}_d^2 + 2C_2 \text{tr}(\underline{\underline{v}}_{dd} \underline{\underline{v}}_{aa}) + C_3 \text{tr}(\underline{\underline{v}}_{aa}^2) + 2C_4 \text{tr}(\underline{\underline{v}}_{ab}^2) \right]; \quad (4.10)$$

with the non-standard strains

$$\underline{\underline{v}}_{ab} = \frac{1}{2} (\underline{\underline{u}}_a \underline{\underline{u}}_b + \underline{\underline{u}}_b \underline{\underline{u}}_a - \underline{\underline{u}}_d \underline{\underline{u}}_d \underline{\underline{u}}_a \underline{\underline{u}}_b); \quad (4.11a)$$

$$\underline{\underline{v}}_{dd} = \underline{\underline{u}}_d \underline{\underline{u}}_d + \frac{1}{2} \underline{\underline{u}}_a \underline{\underline{u}}_a \underline{\underline{u}}_d \underline{\underline{u}}_d; \quad (4.11b)$$

Here, we exclusively retained the only bending term that is relevant in the RG sense. The new elastic constants $C_{\dots}$ are proportional to the $b_{\dots}$ in (4.5): $C_1 = \frac{2b_1}{r} \frac{1}{0?} r^2 \frac{1}{r-1}$, $C_2 = \frac{b_2}{r} \frac{1}{0?} r^2 \frac{1}{r-1}$, $C_3 = \frac{2b_3}{r} \frac{1}{0?} r^2 \frac{1}{r-1}$ and $C_4 = \frac{b_4}{r} \frac{1}{0?} r^2 \frac{1}{r-1}$.

A comment regarding the rescaling of $\underline{\underline{x}}$ is called for. Our rescalings $\underline{\underline{x}}_d^0 \rightarrow \underline{\underline{x}}_d$ and $\underline{\underline{u}}_d^0 \rightarrow \underline{\underline{u}}_d$ only make sense if $r > 1$. We have assumed that the nematic phase is characterized by $r > 1$. Nematic phases with $r < 1$ are also possible. In this case, our rescalings would be different. At a second-order phase transition, $r \rightarrow 1$ will tend to zero. The transition from the isotropic to the nematic elastomer phase is first order in all dimensions above 2. The order of the transition in two dimensions has not yet been established. A second-order transition would have unusual properties since the coefficients of the nonlinear contributions to the nonlinear strain of Eqs. (4.9) diverge as $r \rightarrow 0$.

Instead of using the Hamiltonian (3.4) or our RG analysis we find it convenient to reduce the number of constants featured in the statistical weight $\exp(-H/T)$ by rescaling $T \rightarrow K^3 = C_4 T$, $\underline{\underline{x}}_d \rightarrow \underline{\underline{x}}_d$, $\underline{\underline{u}}_d \rightarrow \underline{\underline{u}}_d$, $K = C_4 \underline{\underline{u}}_d$ and $\underline{\underline{u}}_a \rightarrow (K = C_4) \underline{\underline{u}}_a$. This gives us finally

$$\frac{H}{T} = \frac{1}{2T} \int d^3x \left[\frac{1}{2} \text{tr}(\underline{\underline{v}}_{dd}^2) + \frac{1}{r} \underline{\underline{u}}_d^2 + 2g \text{tr}(\underline{\underline{v}}_{dd} \underline{\underline{v}}_{aa}) + f \text{tr}(\underline{\underline{v}}_{aa}^2) + 2v \text{tr}(\underline{\underline{v}}_{ab}^2) \right]; \quad (4.12)$$

where

$$! = C_1 = C_4; \quad g = C_2 = C_4; \quad f = C_3 = C_4; \quad (4.13)$$

Like the parametrization of Eq. (3.6) of the Hamiltonian for CSEs, the parametrization of Eq. (4.12) is not appropriate for taking the $C_4 \rightarrow 1$ limit to obtain a smectic-A Hamiltonian. As was the case for CSEs, we are interested in properties unique to NEs, and we will not consider the Ginzburg-Pelcovits limit of our model.

Formally, the Hamiltonians (3.6) and (4.12) look very similar. One has to bear in mind, however, that the strains $\underline{\underline{u}}$ and $\underline{\underline{w}}$ are different. In fact, the scaling symmetries of (3.6) and (4.12) are quite different except for the invariance. The naive dimensions of the fields, the temperature and the coupling constants are the same for the two models. In particular, NEs and CSEs have a mutual upper critical dimension $d_c = 3$. Though both systems possess a mixing invariance the specific forms of these invariances are distinct: the NE Hamiltonian is invariant under the transformation $\underline{\underline{u}}_a(\underline{\underline{x}}_c; \underline{\underline{x}}_d) \rightarrow \underline{\underline{u}}_a(\underline{\underline{x}}_c - \underline{\underline{c}} \underline{\underline{x}}_d; \underline{\underline{x}}_d) + \underline{\underline{u}}_a \underline{\underline{u}}_d(\underline{\underline{x}}_c; \underline{\underline{x}}_d)$ and $\underline{\underline{u}}_d(\underline{\underline{x}}_c; \underline{\underline{x}}_d) \rightarrow \underline{\underline{u}}_d(\underline{\underline{x}}_c - \underline{\underline{c}} \underline{\underline{x}}_d; \underline{\underline{x}}_d) + \underline{\underline{u}}_a \underline{\underline{u}}_d$ provided that the $\underline{\underline{c}}$'s are small. This mixing invariance is reminiscent of the original reference space rotation symmetry. In our current approach to NEs, the $\underline{\underline{c}}$ -invariance of CSEs has counterpart. However, in Appendix D we present an alternative formulation that features a $\underline{\underline{c}}$ -invariance at the cost of having an extra scaling parameter. Due to the different forms of the strains, the remaining symmetries stated at the end of Sec. IIIA have no analog in NEs.

B. Renormalization group analysis

The diagrammatic perturbation expansions for CSEs and NEs are similar. Instead of repeating the details we will highlight the differences. In contrast, the RG behavior of CSEs and NEs is quite different due to the varying scaling symmetries.

1. Diagrammatic expansion

It is not difficult to see that the Gaussian propagator for NEs coincides with that for CSEs, see Eqs. (3.12). The differences between $\underline{u}$ and $\underline{v}$, however, lead to different vertices. For NEs we have

$$i \frac{!}{2T} g q_a^{(1)} q_b^{(2)} q_c^{(3)} ; \quad (4.14a)$$

$$i \frac{g}{2T} f q_a^{(1)} q_b^{(2)} q_c^{(3)} ; \quad (4.14b)$$

$$i \frac{1}{T} q_a^{(2)} q_b^{(1)} q_c^{(3)} ; \quad (4.14c)$$

$$\frac{!}{8T} 2g + f + 2 q_a^{(1)} q_b^{(2)} q_c^{(3)} q_d^{(4)} : \quad (4.14d)$$

Of course the sum of the momenta has to vanish at each vertex. Note that the vertices (3.13) and (4.14) are of the same structure. Merely the coupling constants appear in different combination. Hence, the Feynman diagrams for both models have the same topology, or in other words, the 2-leg diagrams for both models can be drawn as in Figs. 1 to 3. Moreover, the same type of vertex functions are supercially divergent. By virtue of the NE mixing invariance, there exists a set of Ward identities relating the NE vertex functions. These identities are derived and stated in Appendix C. They guarantee that we merely have to calculate the 2-point functions. Appendix E describes details if the reader makes the appropriate changes in the vertices. Our results for the 2-point functions read

$$\begin{aligned} \chi_{dd}^{(0;2)} &= T^{-1} + ! q_a^2 + q_d^4 \\ &= \frac{!}{16} \frac{p^{\frac{2+f}{2}} (g + !)^2 q_a^2}{g^2 + (2+f)!} \quad " = 4 ; \end{aligned} \quad (4.15a)$$

$$\frac{4g + g^2}{32} \frac{p^{\frac{2+f}{2}} (2(6+!) f (12+!) q_d^4}{g^2 + (2+f)!} \quad " = 4 ;$$

$$\begin{aligned} \chi_{ad}^{(1;1)} &= T^{-1} g q_a q_d \\ &= \frac{!}{16} \frac{p^{\frac{2+f}{2}} (1+f g) (g + !) q_a q_d}{g^2 + (2+f)!} \quad " = 4 ; \end{aligned} \quad (4.15b)$$

$$\begin{aligned} \chi_{ab}^{(2;0)} &= T^{-1} (f+1) q_a q_b + ab q_d^2 \\ &= \frac{!}{32} \frac{p^{\frac{2+f}{2}} [2(1+f g^2) q_a q_b + ab q_d^2]}{g^2 + (2+f)!} \quad " = 4 ; \end{aligned} \quad (4.15c)$$

2. Renormalization

We eliminate the " poles from the NE vertex functions by employing the renormalization scheme

$$x_d ! x_d = Z^{-1=2} x_d ; \quad (4.16a)$$

$$u_d ! u_d = Z^{-1=2} u_d ; \quad (4.16b)$$

$$u_a ! u_a = Z u_a ; \quad (4.16c)$$

$$T ! T = Z^{-1=2} Z_T^{-1} t ; \quad (4.16d)$$

$$! ! ! = Z^{-1} Z_T^{-1} Z ! ! ; \quad (4.16e)$$

$$g ! g = Z^{-1} Z_T^{-1} Z_g g ; \quad (4.16f)$$

$$f ! f = Z^{-1} Z_T^{-1} Z_f f ; \quad (4.16g)$$

Our renormalizations are devised so that the strains v_{ab} and v_{dd} as well as our Hamiltonian remain invariant in form ,

$$\begin{aligned} \frac{H}{T} ! &= \frac{1}{2T} \int d^d x \int dx_d Z ! v_{dd}^2 + Z_T \int r^2 u_d^2 \\ &+ 2Z_g g v_{dd} u_{aa} + Z_f f v_{aa}^2 + 2Z_T Z v_{ab} v_{ab} ; \end{aligned} \quad (4.17)$$

The scheme (4.16) follows closely the approach developed by Grinstein and Pelcovitz [22]. Of course, other reparameterizations are conceivable. In Appendix D we present an alternative formulation with a different renormalization scheme in which neither the elastic displacement nor x_d is renormalized.

In our current formulation, there remains no scaling invariance of the Hamiltonian that can be exploited to further reduce the number of coupling constants. Hence, the renormalization factors are functions of the original dimensionless parameters $t, !, g$ and f rather than of a reduced number of effective couplings. The structure of the NE renormalization factors is

$$Z_{:::}(t; !; g; f) = 1 + \sum_{m=1}^{\infty} \frac{X_{:::}^{(m)}(t; !; g; f)}{m} ; \quad (4.18)$$

with $X_{:::}^{(m)}(t; !; g; f)$ being a power series in the effective temperature t beginning with the power t^m . To 1-loop order we find from (4.15) via minimal subtraction

$$Z = 1 + t \frac{4g + g^2}{32} \frac{p^{\frac{2+f}{2}} (2(7+!) f (13+!))}{g^2 + (2+f)!} ; \quad (4.19a)$$

$$Z_T = 1 + t \frac{4g + g^2}{32} \frac{p^{\frac{2+f}{2}} (2(6+!) f (12+!))}{g^2 + (2+f)!} ; \quad (4.19b)$$

$$Z ! = 1 + t \frac{!}{16} \frac{p^{\frac{2+f}{2}} (g + !)^2}{g^2 + (2+f)!} ; \quad (4.19c)$$

$$Z_g = 1 + t \frac{!}{16} \frac{p^{\frac{2+f}{2}} (1+f g) (g + !)}{g^2 + (2+f)!} ; \quad (4.19d)$$

$$Z_f = 1 + t \frac{!}{32} \frac{p^{\frac{2+f}{2}} [1 + 4(f g) + 2(f g^2)]}{g^2 + (2+f)!} ; \quad (4.19e)$$

3. Scaling 1: RG equation and its solution

The RGE for the NE vertex functions follows as usual from the fact that the unrenormalized theory has to be independent of the arbitrary length scale l introduced by renormalization. Instead of working with the original parameters g , f and λ we prefer to switch to

$$g = g_l = C_2 C_1; \quad f = f_l = C_3 C_1; \quad (4.20a)$$

$$\lambda = \lambda_l = C_4 C_1; \quad (4.20b)$$

This step turns out to be helpful in studying the RG flow because some of the original parameters tend to infinity. We will see shortly that, on the other hand, g , f , and λ flow to finite values. Our RGE reads

$$D \left(M + \frac{N}{2} \right) (f q_2; q_1 g; t; \lambda; \lambda) = 0 \quad (4.21)$$

with the RG differential operator

$$D = \partial_t - \frac{1}{2} q_1 \partial_{q_1} + t \partial_t + \lambda \partial_\lambda + \lambda \partial_\lambda : \quad (4.22)$$

The Wilson- β -functions, from which we determine the fixed points of the RG flow, are given in terms of the Wilson- β -functions

$$\beta_t = \frac{\partial}{\partial t} \ln Z : : :_0 : \quad (4.23)$$

by

$$t = t(\lambda + \frac{1}{2} = 2); \quad (4.24a)$$

$$g = g(\lambda + \frac{1}{2} = 2); \quad (4.24b)$$

$$f = f(\lambda + \frac{1}{2} = 2); \quad (4.24c)$$

$$\lambda = \lambda(\lambda + \frac{1}{2} = 2); \quad (4.24d)$$

The Wilson- β -functions are readily extracted from the renormalization factors with the result

$$\beta_t = t(X : : : (t; g; f)); \quad (4.25)$$

Switching to the parameters defined in Eqs. (4.20) we obtain

$$t = t'' \quad (4.26a)$$

$$t'' = \frac{3^2 + 12}{64} \frac{2(3 + 19)}{2 + \frac{1}{2}} \frac{(3 + 37)}{2};$$

$$= t \frac{p}{2 + \frac{1}{2}} \frac{(1 + \frac{1}{2})}{2}; \quad (4.26b)$$

$$= t \frac{p}{32} \frac{1}{2 + \frac{1}{2}}; \quad (4.26c)$$

$$= t \frac{2^2 (1 + \frac{1}{2}) + 2^2 \cdot 4 + 2 + (4 - 2)}{32} \frac{(2 + 4 \frac{2^2 + 1}{2})}{2}; \quad (4.26d)$$

For solving the RGE we introduce the characteristics

$$\frac{\partial}{\partial \lambda} (\lambda) = \quad ; \quad (1) = \quad ; \quad (4.27a)$$

$$\frac{\partial}{\partial \lambda} \ln Z(\lambda) = (t(\lambda); g(\lambda); f(\lambda); \lambda); Z(1) = 1 \quad (4.27b)$$

$$\frac{\partial}{\partial \lambda} t(\lambda) = t(t(\lambda); g(\lambda); f(\lambda); \lambda); t(1) = t; \quad (4.27c)$$

$$\frac{\partial}{\partial \lambda} g(\lambda) = (t(\lambda); g(\lambda); f(\lambda); \lambda); g(1) = g; \quad (4.27d)$$

$$\frac{\partial}{\partial \lambda} f(\lambda) = (t(\lambda); g(\lambda); f(\lambda); \lambda); f(1) = f; \quad (4.27e)$$

$$\frac{\partial}{\partial \lambda} \lambda(\lambda) = (t(\lambda); g(\lambda); f(\lambda); \lambda); \lambda(1) = \lambda; \quad (4.27f)$$

In contrast to the CSE model we have to look for fixed points in a 4 dimensional parameter space. We find that the quadruple of coupling constants $(t(\lambda); g(\lambda); f(\lambda); \lambda(\lambda))$ flows to the IR stable fixed point

$$(t; g; f; \lambda) = \left(\frac{64p}{59}, \frac{1}{6}, \frac{1}{6}, 0 \right); \quad (4.28)$$

This fixed point is characterized by $C_2 = C_1 = \frac{1}{6}$ and $C_3 = C_1 = \frac{1}{6}$. It turns out that the leading scaling behavior of physical quantities depends not only on the fixed point but also on the approach to the fixed point described by the dangerous irrelevant variable λ . Paths to the fixed point decay quickly to the line described by

$$\lambda = (a + 2 + 1 = 4) \quad (4.29a)$$

and

$$\lambda = a \quad (4.29b)$$

for small λ , where a is an arbitrary constant. In addition to the stable fixed point, there is the unstable Gaussian fixed point $t = 0$ and there are two unstable fixed lines which can be parameterized as $(t(\lambda); g(\lambda); f(\lambda); \lambda)$ with

$$t(\lambda) = \frac{64 \lambda^2 \frac{p}{2 + \frac{1}{2}} \frac{p}{2 + \frac{1}{2}} + 3}{3136 \frac{p}{2 + \frac{1}{2}} \frac{p}{2 + \frac{1}{2}} + 1521 \frac{p}{2 + \frac{1}{2}} \frac{p}{2 + \frac{1}{2}}}; \quad (4.30a)$$

$$g(\lambda) = 1 \frac{p}{2 + \frac{1}{2}} = 2; \quad (4.30b)$$

$$f(\lambda) = 1 \frac{p}{2 + \frac{1}{2}} = 2 \quad (4.30c)$$

and

$$t(\lambda) = \frac{64 \lambda^2 \frac{p}{2 + \frac{1}{2}} \frac{p}{2 + \frac{1}{2}} + 3}{3136 \frac{p}{2 + \frac{1}{2}} \frac{p}{2 + \frac{1}{2}} + 1521 \frac{p}{2 + \frac{1}{2}} \frac{p}{2 + \frac{1}{2}}}; \quad (4.31a)$$

$$g(\lambda) = 1 + \frac{p}{2 + \frac{1}{2}} = 2; \quad (4.31b)$$

$$f(\lambda) = 1 + \frac{p}{2 + \frac{1}{2}} = 2; \quad (4.31c)$$

With help of the characteristics a formal solution to the RGE is easily obtained,

$$\begin{aligned} (M, N) (f q_2; q_1 g; t; ; ; ;) &= Z(\gamma)^{(M+1)=2} \quad (4.32) \\ (M, N) q_2; Z(\gamma)^{1=2} q_1; t(\gamma); (\gamma); (\gamma); (\gamma); \gamma & \end{aligned}$$

Dimensional analysis gives

$$\begin{aligned} (M, N) (f q_2; q_1 g; t; ; ; ;) &= (d+1)+dM+(d+1)N \\ (M, N) \frac{q_2}{\gamma}; \frac{q_1}{\gamma}; t; ; ; ; 1 & : \quad (4.33) \end{aligned}$$

Equation (4.32) in conjunction with (4.33) finally reveals the scaling behavior of the vertex functions:

$$\begin{aligned} (M, N) (f q_2; q_1 g; t; ; ; ;) & \\ = (\gamma)^{(d+1)+dM+(d+1)N} Z(\gamma)^{(M+1)=2} & \quad (4.34) \\ (M, N) \frac{q_2}{\gamma}; \frac{q_1}{(\gamma)^2 Z(\gamma)^{1=2}}; & \\ t(\gamma); (\gamma); (\gamma); (\gamma); \gamma & \end{aligned}$$

4. Scaling 2: physical quantities

Now we switch back from the convenient scaled variables that we used in our calculations to the original variables in which we formulated our Hamiltonian (4.10). Once more, we mark rescaled variables as well as vertex functions of the rescaled variables with hats. Recalling our manipulations leading to Eq. (4.12) we write

$$\hat{T} = \frac{C_4}{K^3} T; \hat{t} = \frac{C_4}{K^3} t; \quad (4.35a)$$

$$\hat{q}_1 = \frac{C_4}{K} q_1; \hat{u}_a = \frac{C_4}{K} u_a; \hat{u}_d = \frac{C_4}{K} u_d : \quad (4.35b)$$

The relation between the physical vertex functions and the vertex functions in the scaled variables is given by

$$\begin{aligned} (M, N) (f q_2; q_1 g; t; ; ; ;) & \\ = K^{M+3N=2} C_4^{1-N=2} Z(\gamma)^{2(d+1)+dM+(d+1)N} & \\ \wedge (M, N) f q_2; q_1 g; \hat{t}; ; ; ; : & \quad (4.36) \end{aligned}$$

Equation (4.36) in conjunction with Eq. (4.34) gives

$$\begin{aligned} (M, N) (f q_2; q_1 g; t; ; ; ;) & \quad (4.37) \\ = \frac{1}{T} K^{M+3N=2} C_4^{1-N=2} Z(\gamma)^{2(d+1)+dM+(d+1)N} & \\ \wedge (d+1)+dM+(d+1)N [t(\gamma)=t]^{-1} Z(\gamma)^{(M+1)=2} & \\ \wedge (M, N) \frac{L_2 q_2}{\gamma}; \frac{L_d q_1}{Z(\gamma)^{1=2} \gamma}; & \\ \frac{C_4}{K^3} t(\gamma); (\gamma); (\gamma); (\gamma); 1; & \end{aligned}$$

where we introduced the susceptibilities

$$\wedge (M, N) = \hat{t} \wedge (M, N) \quad (4.38)$$

and where we switched from γ to the length scales

$$L_2 = \frac{1}{r}; \quad (4.39a)$$

$$L_d = \frac{C_4}{K} \gamma^2 = \frac{C_4}{K} L_2^2 : \quad (4.39b)$$

The behavior of the elastic moduli is now easily extracted from the 2-point vertex functions. Upon specializing Eq. (4.37) to $N = 2$ and $M = 0$ etc. we obtain

$$K(\gamma) = K \gamma^{-2} Z(\gamma)^{1=2} [t(\gamma)=t]^{-1}; \quad (4.40a)$$

$$C_1(\gamma) = C_1 \gamma^{-2} Z(\gamma)^{3=2} [t(\gamma)=t]^{-1} [\gamma]^{-1}; \quad (4.40b)$$

$$C_4(\gamma) = C_4 \gamma^{-2} Z(\gamma)^{3=2} [t(\gamma)=t]^{-1}; \quad (4.40c)$$

$$C_2(\gamma) = C_3(\gamma) = C_1(\gamma); \quad (4.40d)$$

For C_1 , C_2 and C_3 we can draw our final conclusions without solving the characteristics. Taking the derivative with respect to the flow parameter we find, for example,

$$\frac{\partial}{\partial \gamma} C_1(\gamma) = -\frac{3}{2} \frac{t}{\gamma} = -\frac{1}{2} : \quad (4.41)$$

Upon expressing γ in terms of $\hat{\gamma}$, $\hat{t}$, and $\hat{\gamma}$ and by taking into account Eqs. (4.29) we see that

$$\frac{\partial}{\partial \hat{\gamma}} C_1(\hat{\gamma}) = -\frac{1}{2} \quad (4.42)$$

in the vicinity of the IR-stable fixed point. Hence, γ vanishes in the scaling limit. Consequently, C_1 , C_2 and C_3 are normal.

5. Behavior of the elastic constants for $d < 3$

For $d < 3$ we can assign physical content to the length scale L_2 by exploiting the definition of the rescaled dimensionless temperature $\hat{t}$. This provides us with

$$L_2 = \frac{K^{3=2} \hat{t}^{-1}}{C_4^{1=2} T} \quad (4.43)$$

as the transversal length scale associated with the onset of scaling behavior. The corresponding longitudinal length scale can be inferred from Eq. (4.39b).

As solutions to the characteristics we obtain the power laws

$$Z(\gamma) = \gamma^{-2}; \quad (4.44a)$$

$$(\gamma) = \gamma^{-2}; \quad (4.44b)$$

where

$$= (t; ; ;) = -42 = -59 \quad (4.44c)$$

and

$$w = -4 = -59 \quad (4.44d)$$

is a Wegner exponent corresponding to the smallest eigenvalue of the Hessian at the stable fixed point.

Equation (4.37) in conjunction with the power-law behavior of $Z(\ell)$ and $\chi(\ell) = \chi_2$ along with Eqs. (4.43) and (4.39b) for the crossover-lengths L_2 and L_d provide us with a complete scaling picture of our vertex functions in $d < 3$. This picture is summarized in Eqs. (2.13) with

$$\chi_K = \chi_2 + \chi_2 = 38 = 59; \quad (4.45a)$$

$$\chi_C = \chi_2 + 3\chi_2 = 4 = 59 = w; \quad (4.45b)$$

$$\chi = 2 + \chi_2 = 2 + 21 = 59; \quad (4.45c)$$

Finally, the power-laws (4.44) along with Eqs. (4.40) result in the scaling forms for the elastic constants summarized in Eqs. (2.16) and (2.17). Note that K diverges at long length scales. C_4 , on the other hand, vanishes in this regime.

6. Logarithmic behavior in $d = 3$

In 3 dimensions the solutions to the characteristics that we need to determine the behavior of the elastic moduli are given at leading order by

$$t(\ell) = t_0 - \frac{7}{64} \frac{p}{6t} \ln(\ell) \quad (4.46)$$

and $Z(\ell) = t_0 - \frac{42}{59} \ln(\ell)$. Inserting these logarithmic solutions into Eqs. (4.40) we obtain

$$K(q_2) = K_0 - \frac{7}{64} \frac{p}{6t} \ln(L_2 \chi_2 \chi_j) \quad ; \quad (4.47a)$$

$$C_4(q_2) = C_4 - \frac{7}{64} \frac{p}{6t} \ln(L_2 \chi_2 \chi_j) \quad : \quad (4.47b)$$

Using $t(\ell) = t_0 - \frac{42}{59} \ln(\ell)$ one can check explicitly that C_1 , C_2 , and C_3 are normal. K and C_4 diverge and vanish, respectively, for $L_2 \chi_2 \chi_j \rightarrow 0$. Note that Eqs. (4.47) imply the existence of the crossover-length scale

$$\ell_2 = L_2 \exp \frac{64}{7 \frac{p}{6t}} = L_2 \exp \frac{64}{7 \frac{p}{6C_4 T}} \quad : \quad (4.48)$$

7. Poisson ratios

Since the momentum dependence of the anomalous elastic moduli is logarithmic in 3 dimensions it will be difficult to observe the anomalous elasticity of NEs upon measuring these moduli directly. However, our analysis reveals the existence of several Poisson ratios of the elastic moduli that should be conveniently accessible by experiments.

The IR stable fixed point values of χ , χ_2 and χ_j directly imply the Poisson ratios $\nu_2 = C_2 = C_1 = 1$, $\nu_3 = C_3 = C_1 = 1$ and

$\nu_4 = C_4 = 0$. Remarkably, not only the stable fixed point but also the approach to it contains information on relations between the elastic moduli. From Eqs. (4.29) it follows that $\nu_1 = \nu_2 = 2$ for small flow parameter ℓ . Switching back to the original elastic constants we find the Poisson ratio

$$\frac{2C_2 - C_3 - C_1}{C_4} = \frac{1}{2} \quad (4.49)$$

Note that Eq. (4.49) implies the Poisson ratio $\nu_L = 8$ found by Xing and Radzihovsky [24], where ν_L and ν_T are longitudinal and transverse shear moduli, respectively [32].

8. Semi-soft elasticity

So far we considered soft elastic NEs synthesized by crosslinking in the isotropic phase. If a NE is crosslinked in the nematic phase, a memory of the anisotropy at the time of crosslinking is locked in, or in other words, the rotational symmetry in the reference space is broken. The simplest way of modeling this symmetry breaking is by introducing an aligning external field, or more precisely, an aligning external stress. In this spirit we supplement the elastic energy (4.1) with the term stated in Eq. (2.11). Next, we switch to the relative strain (4.2) and exploit a Ward identity that corresponds at 0-loop order to

$$h = 2sb_5 \quad (4.50)$$

By virtue of this Ward identity, which is derived Appendix B, we can study the effects of the external aligning stress via studying the RG behavior of b_5 featured in Eq. (4.3).

Before embarking on a perturbation calculation we recall the rescalings that led from Eq. (4.3) to our final NE Hamiltonian (4.12). By applying these rescalings to Eq. (4.3) with now $b_5 = h/s$ instead of $b_5 = 0$, by incorporating bending and by dropping irrelevant terms we derive the model Hamiltonian

$$\frac{H_e}{T} = \frac{H}{T} + \frac{e}{2T} \int d^d x \chi_2 \chi_j \chi_d \partial_a u_d \partial_a u_d \quad ; \quad (4.51)$$

with $H = T$ given by Eq. (4.12). The coupling constant e is defined as

$$e = \frac{h}{4K(1 - 2s)} \quad (4.52)$$

Being interested in semi-soft behavior we assume that h is small. Hence, we treat e as a relevant perturbation.

Our diagrammatic calculation proceeds in much the same way as the one outlined in Sec. IIIB 7. The only difference is that we here have to replace the vertices (3.13) by the NE vertices (4.14). Expansion of the diagrams to

first order in e leads to an ℓ pole in $\chi_{dd}^{(0;2)}$ that is proportional to $e q_2^2$. We remove the divergence by letting

$$e \rightarrow e = Z_T^{-1} Z_e e \quad (4.53)$$

with

$$Z_e = 1 - \frac{p}{16} \frac{(3+f-2g+!)}{g^2 + (2+f)!} : \quad (4.54)$$

The appropriate RGE here reads

$$D + e \partial_e M + \frac{N}{2} \quad (M, N) (f q_? ; q_d g ; t ; ; ; e ;) = 0 \quad (4.55)$$

where it is understood the vertex functions are expanded to first order in e . The RG differential operator is D is stated in Eq. (4.22) and

$$= \partial \ln e_j = \tau_e : \quad (4.56)$$

In $d < 3$ the characteristic for e ,

$$\frac{\partial}{\partial e} \ln e(\gamma) = \tau(\gamma); (\gamma); (\gamma); (\gamma); e(1) = e; \quad (4.57)$$

has the fixed point solution

$$e(\gamma) = e^* ; \quad (4.58)$$

with $\tau = \tau(t; ; ;) = 18^\circ = 59$. Supplementing the solution to the RGE (4.55) with a dimensional analysis and switching to original variables yields for the physical vertex function $\Gamma_{dd}^{(0;2)}$ the scaling form

$$\Gamma_{dd}^{(0;2)}(q_? ; q_d ; e) = \frac{K}{T} L_?^{-4} \sqrt[4]{\kappa} \quad (4.59)$$

$$\wedge_{dd}^{(0;2)} \frac{L_? q_?}{\sqrt{\kappa}} ; \frac{L_d q_d}{\sqrt{\kappa}} ; \frac{L_?^2 e}{\sqrt[4]{\kappa}} ;$$

where we have simplified the notation by dropping several arguments and where

$$h = (2)^\kappa = 1 = 2 + 9^\circ = 108 : \quad (4.60)$$

We emphasize the different roles played by C_5 and h in the CSE model and in NEs, respectively. C_5 corresponds to a temperature whereas h corresponds to an external magnetic field. Nevertheless, it is useful to introduce a length scale

$$h = L_? (e L_?^2)^{-h} h^{-h} \quad (4.61)$$

at this point. In the limit $h \rightarrow 1$ we obtain upon choosing $\gamma = (h = L_?)^{-h}$ that

$$\Gamma_{dd}^{(0;2)}(q_? ; q_d ; e) \quad (4.62)$$

$$\frac{1}{T} \frac{K L_?^{-\kappa}}{C_1 q_d^2} h^{(2-\kappa)} q_?^2 \quad h^{-h} q_?^2 \quad \text{if } q_d = 0$$

$$\frac{1}{T} \frac{K L_?^{-\kappa}}{C_1 q_d^2} \quad \text{if } q_? = 0$$

where

$$h = h(2 - \kappa) = 1 - 10^\circ = 59 : \quad (4.63)$$

In the limit $h \rightarrow 1$, corresponding to the limit $h \rightarrow 0$, we retrieve essentially the scaling form that we had for $h = 0$. Now, however, there is an additional correction term that vanishes as $(h \rightarrow 1)^{1-h}$. Physically, this correction term modifies the behavior from soft to semi-soft. For a review of the complete scaling results, see Eqs. (2.13), (2.16) and (2.17).

V. CONCLUDING REMARKS

In this paper, we have explored the anomalous elasticity of two models for soft uniaxial elastomers, both of which are characterized by the vanishing of the shear modulus C_5 for shears in planes containing the anisotropy axis. The first model, which we refer to as a critically soft elastomer (CSE), describes a uniaxial system at a simplified critical point separating a true uniaxial elastic phase characterized by finite elastic moduli and a lower symmetry phase produced by shearing the uniaxial solid. The second model describes nematic elastomers (NEs) formed via spontaneous symmetry breaking from an anisotropic state. In the CSE model, a bending modulus diverges, and three of the four elastic moduli vanish as power-laws in wavenumber at long wavelength below spatial dimension $d = 3$ and logarithmically at $d = 3$. In the NE model, the relevant bending modulus diverges, but only one elastic constant exhibits singular behavior. In both models, we studied the effect of turning on couplings that take them from soft to true uniaxial elastomers. These fields act like temperature or external fields at a thermal critical point, respectively, and introduce coherence lengths that diverge as a power law as the fully soft state is approached.

The logarithmic corrections that we predict will be very difficult to measure. Our universal Poisson ratios, on the other hand, should be observable in experiments on three-dimensional soft elastomers. The anomalous elasticity will be more important in 2 than in 3 dimensions. It would be interesting to find a two-dimensional realization of nematic elastomers, say in a crosslinked membrane confined to a substrate which inhibits height fluctuations [33]. Another two-dimensional system belonging to the NE universality class would be a tethered nematic membrane that orients in a plane perpendicular to an external aligning field.

Our analysis exemplifies the power and the beauty of the renormalization group. The renormalization group handles the rotational invariances of nematic elastomers in two distinct spaces quite naturally. Though the constraints imposed by these invariances lead to almost baroque complicated formulae at intermediate stages of the analysis, our final results have a surprisingly clear and simple stature.

Acknowledgments

We gratefully acknowledge financial support by the Emmy Noether-Program of the Deutsche Forschungsgemeinschaft (DFG) and the National Science Foundation (TCL, grant DMR-00-96531). We thank H.K. Janssen and J. Toner for fruitful discussions. We are particularly grateful for discussions with X. Xing, and L. Radzihovsky, who have also studied this problem.

APPENDIX A : WARD IDENTITIES FOR CRITICALLY SOFT ELASTOMERS

By virtue of the mixing invariance discussed at the end of Sec. III A there exist several Ward identities for CSEs. In this Appendix we derive these identities.

To facilitate our derivation, we introduce external elds via

$$H = H_h = H \int d^d x h_a u_a + h_d u_d ; \quad (A1)$$

where $\int d^d x = \int d^d x_h \int d^d x_d$. As usual, the external elds allow us to exploit the free energy

$$F[h_a; h_d] = -T \ln Z[h_a; h_d]; \quad (A2)$$

where the partition function is given by

$$Z[h_a; h_d] = \int D u_a D u_d \exp(-H_h/T); \quad (A3)$$

as a generating function for the order parameters

$$m_a(x) = \langle u_a(x) \rangle = \frac{F}{h_a(x)}; \quad (A4)$$

$$m_d(x) = \langle u_d(x) \rangle = \frac{F}{h_d(x)}; \quad (A5)$$

As a consequence of the mixing invariance, the free energy obeys the relation

$$F[h_a; h_d] = \int d^d x x_a h_d + F[h_a; h_d^0]; \quad (A6)$$

where $h_d^0 = h_d + \int d^d x x_a h_a$. Because the right hand side of Eq. (A6) is independent of the x_a , we obtain

$$\begin{aligned} L_a &= \frac{\partial F}{\partial h_a} = \int d^d x x_a h_d(x) + \int d^d x m_d(x) h_a(x) \\ &= 0; \end{aligned} \quad (A7)$$

Now we adopt the usual strategy and take various derivatives. We start with

$$\begin{aligned} \frac{\partial^2 L_a}{\partial h_d(y) \partial h_b(z)} &= \int d^d x x_a \frac{\partial^2 h_d(x)}{\partial h_d(y) \partial h_b(z)} \\ &+ \frac{\partial h_a(y)}{\partial h_b(z)} + \int d^d x m_d(x) \frac{\partial^2 h_a(x)}{\partial h_d(y) \partial h_b(z)} = 0 \end{aligned} \quad (A8)$$

In equilibrium, the order parameters vanish for vanishing external elds, $h_a = h_d = 0$. Hence, we get the Ward identity

$$\int d^d x x_a \frac{\partial^2}{\partial h_b \partial h_d} \langle x; y; z \rangle = \frac{\partial^2}{\partial h_b \partial h_d} \langle y; z \rangle; \quad (A9)$$

In Fourier space, identity (A9) takes the form

$$\frac{\partial}{\partial p_a^{(1)}} \frac{\partial^2}{\partial h_b \partial h_d} p^{(1)} p^{(2)} p^{(3)} \Big|_{p^{(1)}=0} = \frac{\partial^2}{\partial h_b \partial h_d} p^{(2)} p^{(3)} \quad (A10)$$

with $p^{(2)} + p^{(3)} = 0$. Another Ward identity can be found by taking the second functional derivative of L_a with respect to $m_d(y)$ and $m_d(z)$. This leads in Fourier space to

$$\begin{aligned} \frac{\partial}{\partial p_a^{(1)}} \frac{\partial^3}{\partial h_d \partial h_d} p^{(1)} p^{(2)} p^{(3)} \Big|_{p^{(1)}=0} \\ = \frac{\partial^3}{\partial h_d \partial h_d} p^{(2)} p^{(3)} + \frac{\partial^3}{\partial h_d \partial h_d} p^{(3)} p^{(2)}; \end{aligned} \quad (A11)$$

An identity for the four point vertex function $\frac{\partial^4}{\partial h_d \partial h_d \partial h_d \partial h_d}$ follows in a similar manner upon taking a third order functional derivative of L_a with respect to, say, $m_d(y)$, $m_d(z)$, and $m_d(w)$. The result can be stated as

$$\begin{aligned} \frac{\partial}{\partial p_a^{(1)}} \frac{\partial^4}{\partial h_d \partial h_d \partial h_d \partial h_d} p^{(1)} p^{(2)} p^{(3)} p^{(4)} \Big|_{p^{(1)}=0} \\ = \frac{\partial^4}{\partial h_d \partial h_d \partial h_d \partial h_d} p^{(2)} p^{(3)} p^{(4)} + \frac{\partial^4}{\partial h_d \partial h_d \partial h_d \partial h_d} p^{(4)} p^{(2)} p^{(3)} \\ + \frac{\partial^4}{\partial h_d \partial h_d \partial h_d \partial h_d} p^{(3)} p^{(4)} p^{(2)}; \end{aligned} \quad (A12)$$

Of course, our Ward identities should hold to arbitrary order in perturbation theory. At zero loop order, the consistency of the Ward identities can be checked without much effort. We carried out this check and found our identities confirmed.

APPENDIX B : WARD IDENTITIES FOR NEMATIC ELASTOMERS I

Here we derive the Ward identities that follow from the reference space rotation invariance of the NE Hamiltonian (4.1). One of these Ward identities can be viewed as the origin of the soft elasticity characterizing NEs crosslinked in the isotropic phase. In addition, we consider semi-soft NEs where the reference space rotation invariance is broken by an aligning external stress.

1. The soft case

To make our arguments more intuitive we work directly in $d = 3$ dimensions. Without loss of generality we assume rotations about the x axis which we parameterize by a rotation angle θ . For small θ these rotations are described by the orthogonal matrix

$$\underline{\underline{O}}_R = \begin{pmatrix} 0 & 1 & 0 \\ 1 & 0 & 0 \\ 0 & 0 & 1 \end{pmatrix} \theta + \underline{\underline{A}}; \quad (B1)$$

Such a rotation takes the strain $\underline{u}$ to $\underline{u}^0 = \underline{\underline{O}}_R \underline{u} \underline{\underline{O}}_R^T$, where $\underline{\underline{O}}_R^T$ is the transposed of $\underline{\underline{O}}_R$. The relative strain $\underline{w} = \underline{u} - \underline{u}_0$ is taken by the rotation to

$$\underline{w}^0 = \underline{\underline{O}}_R \underline{u} \underline{\underline{O}}_R^T - \underline{u}_0 + \underline{\underline{O}}_R \underline{w} \underline{\underline{O}}_R^T; \quad (B2)$$

We introduce an external symmetric stress $\underline{\sigma}$ into our model via

$$H \rightarrow H = H + \int d^d x \, \sigma_{ij} w_{ij}; \quad (B 3)$$

where H is the elastic energy of Eq. (4.3) supplemented with the relevant bending term. Then, the free energy

$$F = -T \ln Z; \quad (B 4)$$

with the partition function

$$Z = \int \mathcal{D}\underline{w} \exp(-H/T); \quad (B 5)$$

is a generating function for the tensor order parameter

$$m_{ij}(\mathbf{x}) = \langle w_{ij}(\mathbf{x}) \rangle = \frac{F}{\int d^d x} : \quad (B 6)$$

Owing to the rotation invariance of the Hamiltonian (4.3) without external stress the free energy satisfies

$$F = \int d^d x \, [\sigma_{23} + \sigma_{32}] + F^0; \quad (B 7)$$

with the elements of the symmetric tensor σ^0 given by

$$\sigma_{11}^0 = \sigma_{11}; \quad (B 8a)$$

$$\sigma_{12}^0 = \sigma_{12} + \sigma_{13}; \quad (B 8b)$$

$$\sigma_{13}^0 = \sigma_{13} + \sigma_{12}; \quad (B 8c)$$

$$\sigma_{22}^0 = \sigma_{22} + (\sigma_{23} + \sigma_{32}); \quad (B 8d)$$

$$\sigma_{23}^0 = \sigma_{23} + (\sigma_{22} + \sigma_{33}); \quad (B 8e)$$

$$\sigma_{33}^0 = \sigma_{33} + (\sigma_{23} + \sigma_{32}); \quad (B 8f)$$

Evidently, the left hand side of the identity (B 7) is independent of the rotation angle. Hence, the quantity

$$L = \frac{\partial F}{\partial \sigma} = \int d^d x \, [\sigma_{23}(\mathbf{x}) + m_{12} + m_{13}(\mathbf{x}) + m_{13} + m_{12}(\mathbf{x}) + 2m_{23}[\sigma_{22}(\mathbf{x}) + \sigma_{33}(\mathbf{x})] + m_{33}(\mathbf{x}) + m_{22}(\mathbf{x}) + \sigma_{23}(\mathbf{x})] \quad (B 9)$$

vanishes identically. In this expression, we used the facts that $m_{ij}(\mathbf{x})$ and σ_{ij} are symmetric tensors and that $\sigma_{ij}(\mathbf{x}) = 2F = m_{ij}(\mathbf{x})$ for $i \neq j$ (we use only $i < j$) and $\sigma_{ii}(\mathbf{x}) = F = m_{ii}(\mathbf{x})$ for all i (no Einstein convention). Now we are in the position to extract the sought after Ward identities simply by taking functional derivatives of L with respect to the order parameter. For example, differentiating with respect to $m_{23}(\mathbf{y})$ and setting $m_{ij} = 0$, we obtain the Ward identity,

$$\frac{L}{m_{23}(\mathbf{y})} = \int d^d x \, [\sigma_{2323}(\mathbf{x}; \mathbf{y}) - 2[\sigma_{22}(\mathbf{y}) + \sigma_{33}(\mathbf{y})]] = 0; \quad (B 10)$$

which in Fourier space is

$$\sigma_{2323}(0;0) + 2[\sigma_{22}(0) + \sigma_{33}(0)] = 0; \quad (B 11)$$

This Ward identity is particularly important because it is the origin of the soft elasticity of NEs. Taking the appropriate derivatives of the free energy in Eq. (4.3), it is straightforward to show that $\sigma_{2323}(0;0) = 2b_5$, $\sigma_{33}(0;0) = a_1$, and $\sigma_{22}(0;0) = a_2$ and thus that Eq. (B 11) reduces relation (4.4a) at 0-loop order.

The derivation of the other Ward identities that generalize the remaining relations stated in Eqs. (4.4) is a similar exercise. We restrict ourselves to stating the final results

$$\sigma_{232311}(0; \mathbf{p}; \mathbf{p}) - 2\sigma_{2211}(\mathbf{p}; \mathbf{p}) + 2\sigma_{3311}(\mathbf{p}; \mathbf{p}) = 0; \quad (B 12a)$$

$$\sigma_{232333}(0; \mathbf{p}; \mathbf{p}) - 2\sigma_{2233}(\mathbf{p}; \mathbf{p}) + 2\sigma_{3333}(\mathbf{p}; \mathbf{p}) - \sigma_{2323}(\mathbf{p}; \mathbf{p}) = 0 \quad (B 12b)$$

$$\sigma_{231312}(0; \mathbf{p}; \mathbf{p}) - 2\sigma_{1212}(\mathbf{p}; \mathbf{p}) + 2\sigma_{1313}(\mathbf{p}; \mathbf{p}) = 0; \quad (B 12c)$$

$$\sigma_{23231313}(0; \mathbf{p}^{(1)}; \mathbf{p}^{(2)}; \mathbf{p}^{(3)}) - 2\sigma_{221313}(\mathbf{p}^{(1)}; \mathbf{p}^{(2)}; \mathbf{p}^{(3)}) + 2\sigma_{331313}(\mathbf{p}^{(1)}; \mathbf{p}^{(2)}; \mathbf{p}^{(3)}) - 2\sigma_{122313}(\mathbf{p}^{(2)}; \mathbf{p}^{(1)}; \mathbf{p}^{(3)}) - 2\sigma_{122313}(\mathbf{p}^{(3)}; \mathbf{p}^{(1)}; \mathbf{p}^{(2)}) = 0; \quad (B 12d)$$

2. The semi-soft case

Now we consider semi-soft NEs modeled by the elastic energy (4.1) supplemented with the explicit uniaxial term (2.11). The aligning stress $\mathbf{h}$ breaks the reference space rotation symmetry in much the same way as the stress $\underline{\sigma}$ utilized in Appendix B 1. Thus, we basically just have to repeat the steps carried out in Appendix B 1 with

$$H \rightarrow H_h = H + \int d^d x \, \mathbf{h}_{ij} w_{ij} = H + \int d^d x \, \mathbf{h}_{ij} w_{ij}; \quad (B 13)$$

where

$$\mathbf{h}_{ij} = \sigma_{ij} + \frac{h}{d} (\sigma_{11} \delta_{j1} + \sigma_{12} \delta_{j2}) - \frac{(d-1)h}{d} \sigma_{13} \delta_{j3}; \quad (B 14)$$

This analysis leads in Fourier space to the Ward identity

$$\sigma_{2323}(0;0) - h = 0 \quad (B 15)$$

provided that the equations of state $\sigma_{22}(0) = 0$ and $\sigma_{33}(0) = 0$ are satisfied. At 0-loop level the identity (B 15) reduced to the relation between h and b_5 stated in Eq. (4.50).

APPENDIX C : WARD IDENTITIES FOR NEMATIC ELASTOMERS II

The mixing invariance of NEs leads to Ward identities analogous to those for CSEs derived in Appendix A. Since the derivation of the 2 sets of identities is similar and Appendix A is fairly detailed we restrict ourselves here to mention differences in the derivations and to list results.

Introducing external fields via the step A1 we find that the free energy of NEs satisfies the identity

$$F[h_a(x); h_d(x)] = \int_a d^d x x_a h_d(x) \quad (C1)$$

$$+ F[h_a(x_c + c x_d; x_d); h_d(x_c + c x_d; x_d) + a h_a(x)]:$$

Thus, the quantity $L_a = \partial F / \partial a$ obeys the equation

$$\begin{aligned} L_a &= \int_a d^d x x_a h_d(x) + \int_a d^d x m_d(x) h_a(x) \\ &+ \int_a d^d x m_c(x) \frac{\partial h_c(x)}{\partial x_a} x_d + \int_a d^d x m_d(x) \frac{\partial h_d(x)}{\partial x_a} x_d \\ &= 0: \end{aligned} \quad (C2)$$

By taking the appropriate functional derivatives with respect to the order parameter, we obtain the Ward identities

$$\begin{aligned} i \frac{\partial}{\partial p_a^{(1)}} \frac{(1;2)}{ddb} p^{(1)}; p^{(2)}; p^{(3)}_{p^{(1)}=0} &= \frac{(2;0)}{ab} p^{(2)}; p^{(3)} \\ \frac{\partial}{\partial p_d^{(2)}} \frac{(1;1)}{bd} p^{(2)}; p^{(3)} p_a^{(2)} & \\ \frac{\partial}{\partial p_d^{(3)}} \frac{(1;1)}{bd} p^{(2)}; p^{(3)} p_a^{(3)}; & \end{aligned} \quad (C3a)$$

$$\begin{aligned} i \frac{\partial}{\partial p_a^{(1)}} \frac{(0;3)}{ddd} p^{(1)}; p^{(2)}; p^{(3)}_{p^{(1)}=0} & \\ = \frac{(1;1)}{ad} p^{(2)}; p^{(3)} + \frac{(1;1)}{ad} p^{(3)}; p^{(2)} & \\ \frac{\partial}{\partial p_d^{(2)}} \frac{(0;2)}{dd} p^{(2)}; p^{(3)} p_a^{(2)} & \\ \frac{\partial}{\partial p_d^{(3)}} \frac{(0;2)}{dd} p^{(2)}; p^{(3)} p_a^{(3)}; & \end{aligned} \quad (C3b)$$

$$\begin{aligned} i \frac{\partial}{\partial p_a^{(1)}} \frac{(0;4)}{dddd} p^{(1)}; p^{(2)}; p^{(3)}; p^{(4)}_{p^{(1)}=0} & \\ = \frac{(1;2)}{add} p^{(2)}; p^{(3)}; p^{(4)} + \frac{(1;2)}{add} p^{(3)}; p^{(2)}; p^{(4)} & \\ + \frac{(1;2)}{add} p^{(4)}; p^{(2)}; p^{(3)} & \\ \frac{\partial}{\partial p_d^{(2)}} \frac{(0;3)}{ddd} p^{(2)}; p^{(3)}; p^{(4)} p_a^{(2)} & \\ \frac{\partial}{\partial p_d^{(3)}} \frac{(0;3)}{ddd} p^{(2)}; p^{(3)}; p^{(4)} p_a^{(3)} & \\ \frac{\partial}{\partial p_d^{(4)}} \frac{(0;3)}{ddd} p^{(2)}; p^{(3)}; p^{(4)} p_a^{(4)}: & \end{aligned} \quad (C3c)$$

APPENDIX D : ALTERNATIVE RENORMALIZATION SCHEME FOR NEMATIC ELASTOMERS

Our renormalization scheme (4.16) which involves a reparameterization of the coordinate x_d follows closely the approach developed by Grinstein and Pelcovitz [22]. Though this approach has been established for more than 2 decades now, it is not clear how the known strategies of proving renormalizability apply to it. In this appendix we briefly present an alternative renormalization scheme for NEs that does not entail a reparameterization of x_d . We demonstrate that the alternative formulation leads exactly to the same results as our original approach.

Let us revisit our Hamiltonian (4.10) as a starting point. To reduce the number of scaling variables we set $T = TK$. This step yields

$$\begin{aligned} \frac{H}{T} &= \frac{1}{2T} \int d^d x \left[\frac{1}{2} \partial_\mu x_d \partial_\mu x_d + \frac{1}{2} v_{dd}^2 + \frac{1}{2} r_d^2 u_d^2 \right. \\ &\left. + 2g v_{dd} v_{aa} + f v_{aa}^2 + 2h v_{ab}^2 \right]; \end{aligned} \quad (D1)$$

where $! = C_1 = K$, $g = C_2 = K$, $f = C_3 = K$ and $h = C_4 = K$. Note that h has no counterpart in Eq. (4.12) and that we thus have an additional parameter in comparison to Eq. (4.12). Due to this additional parameter, the Hamiltonian (D1) has an additional invariance, viz. it is invariant in form under the rescaling $x_d \rightarrow \lambda^{1/2} x_d$, $u_d \rightarrow \lambda^{1/2} u_d$, $u_a \rightarrow \lambda^{1/2} u_a$, $T \rightarrow \lambda^{1/2} T$, $! \rightarrow \lambda^{1/2} !$, $g \rightarrow \lambda^{1/2} g$, $f \rightarrow \lambda^{1/2} f$ and $h \rightarrow \lambda^{1/2} h$ (rescaling). This scaling invariance implies that the vertex functions obey the scaling from

$$\begin{aligned} (M;N) \quad f q; q; g; T; !; g; f; h &= (M+1;N+2) \\ (M;N) \quad q; \lambda^{1/2} q; \lambda^{1/2} T; \lambda^{1/2} !; \lambda^{1/2} g; \lambda^{1/2} f; \lambda^{1/2} h &: \end{aligned} \quad (D2)$$

Equation (D2) suggest to introduce composite parameters that are invariant under the rescaling. Among various possibilities we choose

$$t = \frac{h^{1/2} T}{C_4 = K^3}; \quad (D3a)$$

$$! = !h = C_1 = C_4; \quad (D3b)$$

$$g = gh = C_2 = C_4; \quad (D3c)$$

$$f = fh = C_3 = C_4; \quad (D3d)$$

Note that these composite parameters are identical to the parameters we introduced by switching from Eq. (4.10) to (4.12).

After this prelude we specify our alternative renormalization scheme,

$$T \rightarrow T = Z_T T; \quad (D4a)$$

$$! \rightarrow ! = Z_T^{-1} Z_! !; \quad (D4b)$$

$$g \rightarrow g = Z_T^{-1} Z_g g; \quad (D4c)$$

$$f \rightarrow f = Z_T^{-1} Z_h f; \quad (D4d)$$

$$h \rightarrow h = Z_T^{-1} Z_h h; \quad (D4e)$$

2. Parameter integrals

Many of the 2-leg diagrams can be expressed in terms of the parameter integral

$$M_{\ln}^{(1)} = \frac{Z}{k} \frac{k_2^1}{B + A k_d^2 + B k_2^4} : \quad (E 7)$$

The calculation of this integral can be simplified by rescaling the momenta,

$$M_{\ln}^{(1)} = A^{1=2} B^{(d+1/2)=4} \frac{Z}{k} \frac{k_2^1}{B + k_d^2 + k_2^4} : \quad (E 8)$$

Next, we employ Schwinger representation,

$$M_{\ln}^{(1)} = \frac{A^{1=2} B^{(d+1/2)=4}}{(2)^d (n)} \frac{Z}{Z^0} \int_0^1 ds s^{n-1} \exp(-sB) \int d^d k_2 k_2^1 \exp(-s k_2^4) \int d^d k_d \exp(-s k_d^2) : \quad (E 9)$$

Now the momentum integrations are straightforward. We obtain

$$M_{\ln}^{(1)} = \frac{A^{1=2} B^{(d+1/2)=4}}{2 (4)^{d=2} (n)} \frac{(\frac{d+1/2}{4})}{(\frac{d-1/2}{2})} \int_0^1 ds \exp(-sB) s^{1+\frac{4n-1-d-1}{4}} : \quad (E 10)$$

Carrying out the remaining integration over the Schwinger parameters gives finally

$$M_{\ln}^{(1)} = \frac{A^{1=2} B^{(2n-1)=2} (\frac{2+1/n}{4})}{2 (4)^{d=2} (n) (\frac{2-n}{2})} \frac{4n-1}{4} \frac{4+n}{4} \frac{4n-1}{4} \frac{4+n}{4} : \quad (E 11)$$

In addition to $M_{\ln}^{(1)}$ it turns out to be convenient to introduce a second parameter integral, viz.

$$M_{\ln}^{(2)} = \frac{Z}{k} \frac{k_d^2 k_2^1}{B + A k_d^2 + B k_2^4} : \quad (E 12)$$

This integral can be calculated by the same means as $M_{\ln}^{(1)}$. We obtain the result

$$M_{\ln}^{(2)} = \frac{A^{3=2} B^{(2n-3)=2} (\frac{2+1/n}{4})}{4 (4)^{d=2} (n) (\frac{2-n}{2})} \frac{4n-1}{4} \frac{8+n}{4} \frac{4n-1}{4} \frac{8+n}{4} : \quad (E 13)$$

-
- [1] H. Finkelmann, H. J. Koch, and G. Rehage, *Makromol. Chem. Rapid Commun.* 2, 317 (1981).
- [2] P. G. de Gennes in *Liquid Crystals of One and Two-Dimensional Order*, p. 231, edited by W. Helfrich and G. Heppke (Springer, New York, 1980).
- [3] E. M. Terentjev, *J. Phys. Cond. Mat.* 11, R239 (1999).
- [4] P. G. de Gennes and J. Prost, *The Physics of Liquid Crystals* (Clarendon Press, Oxford, 1993).
- [5] S. Chandrasekhar, *Liquid Crystals* (Cambridge University Press, Cambridge, 1992).
- [6] S. T. Kim and H. Finkelmann, *Makromol. Rapid Commun.* 22, 429 (2001).
- [7] R. Zentel, *Angew. Chem. Adv. Mater.* 101, 1437 (1989).
- [8] C. N. Bowman and C. A. Guymon, *MRS Bulletin*, 15 (1997).
- [9] *Liquid Crystals in Complex Geometries*, edited by G. P. Crawford and S. Zumer (Taylor and Francis, London, 1996).
- [10] M. Wamer and E. M. Terentjev, *Prog. Poly. Science* 21, 853 (1996).
- [11] T. C. Lubensky, R. Mukhopadhyay, L. Radzihovsky, and X. Xing, *Phys. Rev. E* 66, 011702 (2002).
- [12] J. Kupfer and H. Finkelmann, *Makromol. Chem. Phys.* 195, 1353 (1994).
- [13] H. Finkelmann, E. Nishikawa, G. G. Pereira, and M. Wamer, *Phys. Rev. Lett.* 87, 015501 (2001).
- [14] H. Finkelmann and H. Wemter, *Polym. Mater. Sci. Eng.* 82, 319 (2000).
- [15] M. Hebert, R. Kant, and P. G. de Gennes, *J. Phys. I France* 7, 909 (1997).
- [16] D. L. T. III, P. Keller, J. Naciri, R. Pink, H. Jeon, D. Shenoy, and B. Ratna, *Makromolecules* 34, 5868 (2001).
- [17] L. Golubovic and T. C. Lubensky, *Phys. Rev. Lett.* 63, 1082 (1989).
- [18] Peter D. Onsted, *J. Phys. II (France)*, 4, 2215 (1994).
- [19] H. Finkelmann, I. Kundler, E. M. Terentjev, and M. Wamer, *J. Phys. II (France)* 7, 1059 (1997).
- [20] G. C. Verwey, M. Wamer, and E. M. Terentjev, *J. Phys. II (France)* 6, 1273-1290 (1996).
- [21] M. Wamer, *J. Mech. Phys. Solids* 47, 1355 (1999).
- [22] G. G. Ginzburg and R. A. Pelcovits, *Phys. Rev. Lett.* 47, 856 (1981); *Phys. Rev. A* 26, 915 (1982).
- [23] See, e.g., D. J. Amit, *Field Theory, the Renormalization Group, and Critical Phenomena* (World Scientific, Singapore, 1984); J. Zinn-Justin, *Quantum Field Theory and Critical Phenomena* (Clarendon, Oxford, 1989).
- [24] O. Stenull and T. C. Lubensky, *Europhys. Lett.* 61, 776 (2003). See also, X. Xing and L. Radzihovsky, *Europhys. Lett.* 61, 769 (2003).
- [25] X. Xing and L. Radzihovsky, *Phys. Rev. Lett.* 90, 168301 (2003).
- [26] L. D. Landau and E. M. Lifshitz, *Theory of Elasticity*, 3rd edition (Pergamon, New York, 1986).
- [27] P. M. Chaikin and T. C. Lubensky, *Principles of Condensed Matter Physics*, (Cambridge University Press, Cambridge, 1995).
- [28] Here and in the following we adopt Einstein's summation

convention.

[29] Provided, of course, there are no aligning fields.

[30] For convenience, we set the Boltzmann constant equal to one.

[31] The j indicates that bare quantities are kept fixed while taking the derivatives.

[32] In our notation these shear moduli are given by $\mu_L = (1 + f + 2\alpha + 2g)/4$ and $\mu_T = 1$.

[33] X. Xing, R. Mukhopadhyay, T. C. Lubensky, and R. Radzihovsky, e-print: cond-mat/0302006.