

Superconductivity in carbon nanotube ropes: Ginzburg-Landau approach and the role of quantum phase slips

A. De Martino and R. Egger

Institut für Theoretische Physik, Heinrich-Heine-Universität, D-40225 Düsseldorf, Germany

(Dated: December 27, 2021)

We derive and analyze the low-energy theory of superconductivity in carbon nanotube ropes. A rope is modelled as an array of ballistic metallic nanotubes, taking into account phonon-mediated plus Coulomb interactions, and Josephson coupling between adjacent tubes. We construct the Ginzburg-Landau action including quantum fluctuations. Quantum phase slips are shown to cause a depression of the critical temperature T_c below the mean-field value, and a temperature-dependent resistance below T_c .

PACS numbers: 73.63.Fg, 72.10.-d, 74.25.Kc

Over the past decade, the unique mechanical, electrical, and optical properties of carbon nanotubes, including the potential for useful technological applications, have created a lot of excitement. While many of these properties are well understood by now, the experimental observation of intrinsic [1, 2, 3] and anomalously strong proximity-induced [4, 5] superconductivity continues to pose open questions to theoretical understanding. In this paper we analyze 1D superconductivity found in ropes of carbon nanotubes [1, 3], starting from a microscopic model of the rope in terms of an array of individual clean single-wall nanotubes (SWNTs), with attractive phonon-mediated on-tube interactions and inter-tube nearest-neighbor Josephson couplings. Then the Luttinger interaction parameter g_c and the Josephson coupling λ describing transfer of Cooper pairs are crucial microscopic parameters, which, fortunately, can be estimated rather accurately [6, 7, 8]. The coupled-chain problem corresponding to superconducting nanotube ropes, where typically less than hundred metallic SWNTs are present [1, 3], does neither permit classical Ginzburg-Landau (GL) theory nor a standard self-consistent BCS approach, in contrast to the situation encountered in, e.g., quasi-1D organic superconductors [9]. At this time, nanotube ropes represent wires with the smallest number of transverse channels showing intrinsic superconductivity, even when compared to the amorphous MoGe wires of diameter ≈ 10 nm studied in Ref. [10], where still several thousand channels are available. Based on a microscopic derivation of the quantum GL action, we show that quantum phase slips (QPS's) [11, 12, 13, 14] are crucial for an understanding of experimental results [1, 3]. First, they cause a depression of the transition temperature T_c below the mean-field critical temperature T_c^0 . Furthermore, for $T < T_c$, a finite resistance $R(T)$ due to QPS's appears, which exhibits approximate power-law scaling. Below we determine the full temperature dependence of $R(T < T_c)$ for arbitrary rope length.

We consider a rope consisting of N metallic SWNTs, where disorder is assumed to be negligible [25]. The validity of modelling the rope as an array of ballistic 1D quantum wires has recently been discussed in Ref. [3]. Since the K point degeneracy is inessential here, an in-

dividual SWNT can be described as a spin-1/2 Luttinger liquid, where the combined effects of Coulomb and phonon-mediated interactions lead to an interaction parameter g_c [8], where $g_c = 1$ refers to the noninteracting case and $g_c > 1$ ($g_c < 1$) signals effectively attractive (repulsive) interactions. We mention in passing that lattice commensurabilities and electron-electron backscattering can be neglected in the intrinsically doped SWNTs encountered in practice [15, 16]. In a thick rope, Coulomb interactions are expected to be largely screened off, and $g_c > 1$ due to breathing-phonon exchange [8]. The only weak screening in the thinnest ropes studied in Refs. [1, 3] is probably linked to the absence of superconductivity in these samples. To probe superconductivity in ultrathin ropes, it is necessary to externally screen Coulomb interactions. In principle, three different inter-tube coupling mechanisms should now be taken into account, namely (i) direct Coulomb interactions, (ii) Josephson coupling (Cooper pair hopping), and (iii) single-electron hopping. The last process is strongly suppressed due to the generally different chirality of adjacent tubes [17], and, in addition, for $g_c > 1$, inter-SWNT Coulomb interactions can be neglected [9]. Therefore the most relevant mechanism is Josephson coupling between adjacent SWNTs.

In the (idealized) rope crystal, (metallic) SWNTs of radius R are arranged on a trigonal lattice with lattice constant $a = 2R + b$, where $b = 0.34$ nm [17]. Choosing the x -axis parallel to the rope, and numbering the SWNTs by $j = 1, \dots, N$, with center at $\vec{r}_j = (y_j, z_j) = n_1 \vec{a}_1 + n_2 \vec{a}_2$, where $\vec{a}_1 = a(1, 0)$ and $\vec{a}_2 = a(1/2, \sqrt{3}/2)$ span the trigonal lattice, allowed indices (n_1, n_2) corresponding to j follow from the condition $|\vec{r}_j| \leq R_{\text{rope}}$. A given rope radius R_{rope} then fixes the number of tubes N . The Josephson coupling matrix Λ_{ij} is nonzero only for nearest-neighbor pairs (i, j) , where $\Lambda_{ij} = \lambda$. Only singlet pairing of electrons on the same tube is important [8], leading to the on-tube order parameter $\mathcal{O}_j(x, \tau) = \sum_{r\sigma} \sigma \psi_{r\sigma j} \psi_{-r, -\sigma j}$, where $\psi_{r\sigma j}(x, \tau)$ is the electron operator for a right- or left-moving electron ($r = \pm$) with spin $\sigma = \pm$ on the j th SWNT, and $0 \leq \tau < 1/T$ is imaginary time (we put $\hbar = k_B = 1$). In bosonized language [15],

$$\mathcal{O}_j = (\pi a_0)^{-1} \exp \left[i\sqrt{2\pi}\theta_{c,j} \right] \cos \left[\sqrt{2\pi}\varphi_{s,j} \right], \quad (1)$$

where $a_0 = 0.246$ nm is the SWNT lattice spacing, $\varphi_{c/s,j}(x, \tau)$ denotes the charge/spin boson field on the j th SWNT, and $\theta_{c/s,j}$ is the dual field to $\varphi_{c/s,j}$. The Euclidean action is

$$S = \sum_{j=1}^N S_{\text{LL}}[\theta_{c,j}, \varphi_{s,j}] - \sum_{jk} \Lambda_{jk} \int dx d\tau \mathcal{O}_j^\dagger \mathcal{O}_k, \quad (2)$$

where the on-tube fluctuations are governed by an effective Luttinger liquid action [8, 15, 16],

$$S_{\text{LL}}[\theta_c, \varphi_s] = \int dx d\tau \left\{ \frac{v_c g_c}{2} [(\partial_\tau \theta_c / v_c)^2 + (\partial_x \theta_c)^2] + \frac{v_s}{2g_s} [(\partial_\tau \varphi_s / v_s)^2 + (\partial_x \varphi_s)^2] \right\},$$

with $v_{c/s} = v_F / g_{c/s}$ for Fermi velocity $v_F = 8 \times 10^5$ m/sec, and $g_s = 1$ due to spin $SU(2)$ invariance. Note that the model (2) and our results below apply beyond the specific system under study here, see also Refs. [9, 18].

Next we employ a Hubbard-Stratonovich transformation in order to decouple the Josephson term in Eq. (2), using the complex-valued order parameter field $\Delta_j(x, \tau)$. This allows to write the partition function as

$$Z = \int \mathcal{D}\Delta \exp \left(- \sum_j S_0[\Delta_j] - \int dx d\tau \sum_{jk} \Delta_j^* D_{jk} \Delta_k \right), \quad (3)$$

where Δ^* is the complex conjugate field. The $N \times N$ matrix D denotes the positive definite part of Λ^{-1} , since order parameter modes corresponding to negative eigenvalues of Λ can never become critical. Integration over the on-tube boson field fluctuations then leads to

$$S_0[\Delta] = - \ln \int \mathcal{D}\theta_c \mathcal{D}\varphi_s e^{-S_{\text{LL}}[\theta_c, \varphi_s] - \int dx d\tau (\Delta^* \mathcal{O} + \Delta \mathcal{O}^\dagger)}. \quad (4)$$

The expectation value of Eq. (1) can be computed as $\langle \mathcal{O}_j \rangle = \sum_k D_{jk} \langle \Delta_k \rangle$, where $\langle \Delta_k \rangle$ is averaged using the action corresponding to Eq. (3).

Assuming a spin gap, taking $T = 0$, and allowing only static homogeneous configurations $\Delta_j(x, \tau) = \Delta_0$, Eq. (4) can be evaluated explicitly [19]. Saddle-point analysis then yields a relation between the mean-field critical temperature and the $T = 0$ superconducting gap, see Ref. [18]. For general order parameter $\Delta_j(x, \tau)$ or arbitrary temperature, however, integration over the Luttinger phase fields in Eq. (4) is impossible. To make progress, it is instructive to construct the GL action [13, 20], where it is crucial to include quantum fluctuations. A systematic approach proceeds via cumulant expansion of Eq. (4) up to quartic order in the expansion parameter $|\Delta|/2\pi T$ [20]. We stress that this expansion is carried out for the single-chain problem, and is *not* restricted to $N \gg 1$. Assuming slowly varying configurations $\Delta_j(x, \tau)$, gradient expansion yields the Lagrangian

in Eqs. (3) and (4) as

$$L = \sum_{jk} V_{jk} \Delta_j^* \Delta_k + \sum_j \left([W_1^{-1} - A] |\Delta_j|^2 + B |\Delta_j|^4 + C [|\partial_x \Delta_j|^2 + c_s^{-2} |\partial_\tau \Delta_j|^2] \right), \quad (5)$$

with the Mooij-Schön plasma velocity [21], $c_s = v_c \sqrt{\tilde{C}/\tilde{D}}$, and $V_{jk} = \sum_\alpha (W_\alpha^{-1} - W_1^{-1}) \langle j|\alpha \rangle \langle \alpha|k \rangle$, where W_α denote the eigenvalues of Λ in descending order ($\alpha = 1, \dots, N$), with eigenvectors $|\alpha\rangle$, and the α -summation extends over $W_\alpha > 0$ only. Furthermore, the positive coefficients A, B, C are with $\gamma = v_c/v_s$ given by

$$\begin{aligned} A &= \frac{\gamma^{g_s}}{2\pi^2 v_c} (\pi a_0 T / v_c)^{g_c^{-1} + g_s - 2} \tilde{A}, \\ B &= \frac{a_0^2 \gamma^{2g_s}}{32\pi^4 v_c^3} (\pi a_0 T / v_c)^{2g_c^{-1} + 2g_s - 6} \tilde{B}, \\ C &= \frac{a_0^2 \gamma^{g_s}}{4\pi^2 v_c} (\pi a_0 T / v_c)^{g_c^{-1} + g_s - 4} \tilde{C}. \end{aligned} \quad (6)$$

Putting $g_s = 1$, dimensionless g_c -dependent numbers are defined as

$$\tilde{C} = \int dz \frac{w^2}{f_c(z) f_s(z)}, \quad (7)$$

where we use the notations $z = (w, u)$,

$$f_c(z) = |\sinh(w + iu)|^{1/g_c}, \quad f_s(z) = |\sinh(\gamma w + iu)|,$$

and $\int dz \equiv \int_0^\pi du \int_{-\infty}^\infty dw$. Here $\tilde{A}(\tilde{D})$ is given by Eq. (7) with $w^2 \rightarrow 1$ ($w^2 \rightarrow u^2$), and

$$\begin{aligned} \tilde{B} &= \int \frac{dz_1 dz_2 dz_3}{f_c(z_2) f_c(z_{13})} \left[\frac{4}{f_s(z_2) f_s(z_{13})} - \frac{f_c(z_1) f_c(z_{23})}{f_c(z_3) f_c(z_{12})} \right. \\ &\times \left. \left(\frac{f_s(z_1) f_s(z_{23})}{f_s(z_2) f_s(z_{13}) f_s(z_3) f_s(z_{12})} + (1 \leftrightarrow 2) + (1 \leftrightarrow 3) \right) \right], \end{aligned}$$

with $z_{ij} = (w_i - w_j, u_i - u_j)$. The quantity \tilde{B} is evaluated using the Monte Carlo method, see also Ref. [18]. For $g_c = 1$, we first numerically reproduced the exact result $\tilde{B} = 8\pi^2 \tilde{C}$ with $\tilde{C} = 7\pi\zeta(3)/4$ [20]. Numerical values can then be obtained for arbitrary g_c . From Eq. (5), previous GL results for the infinite 2D array of coupled 1D chains are recovered [9, 18]. In that case, the V_{ij} term in Eq. (5) leads to transverse gradients because α corresponds to transverse momentum \vec{k}_\perp , with $W_\alpha^{-1} - W_1^{-1} \propto \vec{k}_\perp^2$. Note that Eq. (5) additionally includes quantum fluctuations and allows to describe the case of arbitrary N .

From Eq. (5), we obtain the mean-field critical temperature

$$T_c^0 = \frac{v_c}{\pi a_0} \left(\frac{\tilde{A} W_1}{2\pi^2 v_F} \right)^{g_c/(g_c-1)}. \quad (8)$$

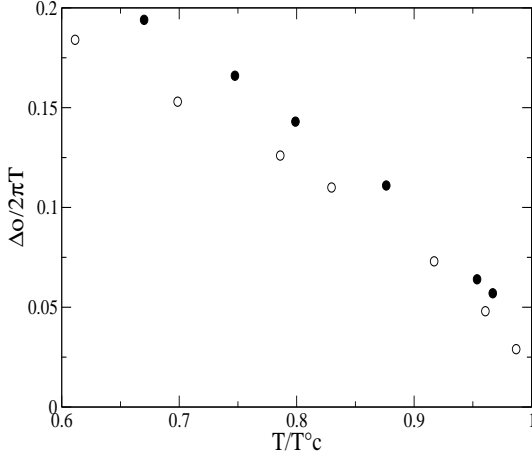


FIG. 1: Temperature dependence of $\Delta_0/2\pi T$ versus T/T_c^0 for $N = 31$ (open) and $N = 253$ (filled circles).

Assuming sufficiently thick ropes such that Coulomb interactions can be neglected, in concrete estimates we shall put $g_c = 1.3$ [8], with Josephson coupling $\lambda/v_F = 0.02$ [7]. Numerical evaluation yields

$$\tilde{A} \simeq 30.72, \quad \tilde{B} \simeq 293.1, \quad \tilde{C} \simeq 12.12, \quad \tilde{D} \simeq 7.78. \quad (9)$$

Equation (8) then predicts, e.g., $T_c^0 = 2.3$ K for $N = 31$, which is slightly above reported experimental values [1, 3]. In what follows, we focus on temperatures below T_c^0 . Writing $\Delta_j = |\Delta_j| \exp\{i\phi_j(x, \tau)\}$, the amplitudes $|\Delta_j|$ are finite, with a gap for fluctuations around the mean-field value. At not too low temperatures, they are found from the saddle point equation

$$\sum_j V_{ij} |\Delta_j| + (W_1^{-1} - A) |\Delta_i| + 2B |\Delta_i|^3 = 0, \quad (10)$$

whose numerical solution (via a Newton-Raphson root finding scheme) yields the transverse order parameter profile and $\Delta_0 = \sum_j |\Delta_j|/N$. Typical results for $\Delta_0/2\pi T$ are shown in Fig. 1, which demonstrates that GL theory quantitatively holds down to $T \approx T_c^0/2$. In our discussion below, it is useful even down to $T = 0$. Fixing the amplitudes $|\Delta_j|$ at their mean-field values, the resulting Lagrangian governing the massless phase fluctuations (Goldstone modes) is

$$L = \sum_j \frac{\mu_j}{2\pi} [c_s(\partial_x \phi_j)^2 + c_s^{-1}(\partial_\tau \phi_j)^2] + \sum_{i>j} 2V_{ij} |\Delta_i| |\Delta_j| \cos(\phi_i - \phi_j), \quad (11)$$

with dimensionless quantities $\mu_j = 2\pi C |\Delta_j|^2 / c_s$. Electromagnetic potentials can then be coupled in by standard Peierls substitution rules [20], e.g. allowing to describe the Meissner effect. Furthermore, dissipative effects can be included following Ref. [14].

In the 1D situation encountered here, superconductivity can be destroyed by thermally activated or quantum

phase slips [13]. Following arguments similar to the ones of Ref. [11], we find that only QPS's play a role. Numerical evaluation of Eq. (10) shows that well below T_c^0 , transverse fluctuations are heavily suppressed [22], and therefore QPS's can be described using the action

$$S = \frac{\mu}{2\pi} \int dx d\tau [c_s^{-1}(\partial_\tau \phi)^2 + c_s(\partial_x \phi)^2], \quad (12)$$

where $\mu = \sum_j \mu_j$ is a dimensionless rigidity. For not too low temperature, and neglecting transverse fluctuations,

$$\mu(T) = \alpha_0 N \left[1 - (T/T_c^0)^{g_c/(g_c-1)} \right], \quad (13)$$

where $\alpha_0 \simeq 4\pi \tilde{A}(\tilde{C}\tilde{D})^{1/2}/\tilde{B}$, resulting in $\alpha_0 \simeq 12.7$ for $g_c = 1.3$. Remarkably, at $T = 0$, Eq. (13) coincides up to a prefactor of order one with the rigidity $\bar{\mu}$ obtained from standard mean-field relations [20], $\bar{\mu} = \pi^2 n_s R^2 / 2m^* c_s = \bar{\alpha}_0 N$, where n_s is the density of condensed electrons. At $T = 0$, this implies $\bar{\alpha}_0 \approx v_F/c_s$. We conclude that the GL prediction (13) for $\mu(T)$ is robust and useful even outside its validity regime.

QPS's are topological vortex-like excitations of the superconducting phase field $\phi(x, \tau)$. For rope length $L \rightarrow \infty$ and thermal length $L_T = c_s/\pi T \rightarrow \infty$, a QPS with core at (x_i, τ_i) and winding number $\nu_i = \pm 1$ (higher winding numbers are irrelevant) is $\phi(x, \tau) = \nu_i \tan^{-1}[(x - x_i)/c_s(\tau - \tau_i)]$ [23], where the finite L, L_T solution follows by conformal transformation. This form solves the equation of motion for Eq. (12) with a singularity at the core, where superconducting order is locally destroyed. The local loss of condensation energy density E_c (this may also contain other energy costs [11]) leads to the core action $S_c = \kappa^2 E_c / c_s$, with core radius κ as variational parameter. The optimal value of the core radius is $\kappa = (c_s \mu / 2E_c)^{1/2}$, where $S_c \simeq \mu/2$, and κ now serves as UV cutoff length of the field theory. To leading order in $\kappa/L, \kappa/L_T$, the hydrodynamic action (12) of a vortex is $S_{el} = \mu \ln[\min(L, L_T)/2\kappa] + S'(L/L_T)$, where L/L_T measures the anisotropy of this finite-size 2D Kosterlitz-Thouless problem. In particular, we find $S'(L_T \approx L) \simeq 0.11\mu$, while in the opposite limits, $S' \simeq 2\mu/\pi$. Below S' is taken into account as renormalization of S_c .

The next step is to analyze a QPS gas, where textbook analysis [23] leads to the picture of an interacting Coulomb gas of charges $\nu_i = \pm 1$, fugacity $y = e^{-S_c}$, and total charge zero. For $\mu > \mu^* \approx 2$, QPS's are confined into neutral pairs, quasi-long range superconductivity is present, but QPS's cause a finite resistance below T_c [11]. For $\mu = \mu^*$, QPS proliferation leads to a Kosterlitz-Thouless transition to the normal metallic state. (Of course, here “normal” does not imply Fermi-liquid behavior.) The transition temperature T_c is therefore not T_c^0 but follows from the condition $\mu(T_c) = \mu^*$. Equation (13) then yields

$$T_c/T_c^0 = [1 - \mu^*/\alpha_0 N]^{g_c/(g_c-1)}. \quad (14)$$

This T_c depression is normally rather weak, e.g. for $N = 31$, we obtain $T_c/T_c^0 = 0.97$, but for small N , the effect can be large. Furthermore, other mechanisms not included in our model could act to effectively reduce α_0 and hence T_c , e.g. disorder and heating effects [11], or the electromagnetic environment [14].

The temperature dependence of the linear resistance $R(T) = V/I$ for $T < T_c$ can be obtained by computing the voltage drop V for applied current I . Expanding the vortex partition function up to order y^2 and extracting the imaginary part of the free energy $F(I)$ using the Langer approach [24], $\Gamma(\pm I) = -2\text{Im}F(\pm I)$ can be interpreted as the rate for a phase slip by $\pm 2\pi$ [11]. The average change in phase is then $\langle \dot{\phi} \rangle = 2\pi[\Gamma(I) - \Gamma(-I)]$, which from the Josephson relation implies a voltage drop $V = \pi[\Gamma(I) - \Gamma(-I)]/e$. Using $\epsilon = \pi\hbar I/e$, the rate $\Gamma(\epsilon)$ follows for $L, L_T \gg \kappa$ but arbitrary L/L_T in the form

$$\Gamma(\epsilon) = \frac{c_s^2 L y^2}{\kappa^4} \int_{-L/2}^{L/2} dx \int_{-\infty}^{\infty} dt e^{i\epsilon t - \mu[G(t+x/c_s) + G(t-x/c_s)]},$$

where $G(t) = \ln[(L_T/\kappa) \sinh(\pi T|t|)] + i(\pi/2)\text{sgn}(t)$. To evaluate the rate $\Gamma(\epsilon)$ for arbitrary L/L_T , we replace the boundaries for the x -integral by a soft exponential cutoff, switch to integration variables $t' = t - x/c_s$ and $t'' = t + x/c_s$, and use the auxiliary relation

$$e^{-c_s|t''-t'|/L} = \frac{c_s}{\pi L} \int_{-\infty}^{\infty} ds \frac{e^{-is(t''-t')}}{s^2 + (c_s/L)^2}.$$

It is now straightforward to carry out the t', t'' time integrations, and some algebra yields the linear resistance

$$\begin{aligned} \frac{R}{R_q} &= \left(\frac{\pi y \Gamma(\mu/2)}{\Gamma(\mu/2 + 1/2)} \right)^2 \frac{\pi L}{\kappa} \left(\frac{L_T}{\kappa} \right)^{3-2\mu} \\ &\times \int_0^{\infty} du \frac{2/\pi}{1+u^2} \left| \frac{\Gamma(\mu/2 + iuL_T/2L)}{\Gamma(\mu/2)} \right|^4 \end{aligned} \quad (15)$$

in units of the resistance quantum $R_q = \pi\hbar/2e^2$. Equation (15) leads to good agreement with experimental data [1, 3]; a detailed comparison will be given in Ref. [22]. For $L/L_T \gg 1$, the u -integral approaches unity, and hence $R \propto T^{2\mu-3}$, while for $L/L_T \ll 1$, dimensional scaling arguments give $R \propto T^{2\mu-2}$. The exponents are determined by the temperature-dependent stiffness (13). While both power-law behaviors have been reported in Ref. [11], Eq. (15) describes the full crossover for arbitrary L/L_T . In Refs. [1, 3], typical lengths were $L \approx 1\mu\text{m}$, which indeed puts one into the crossover regime $L_T \approx L$.

To conclude, we have studied superconductivity in carbon nanotube ropes, starting from a model of ballistic SWNTs with attractive intra-tube interactions and inter-tube Josephson coupling. We have constructed the Ginzburg-Landau theory including quantum fluctuations. This allows for detailed predictions about the critical temperature T_c and the QPS-induced resistance below T_c . If repulsive Coulomb interactions can be screened off efficiently, our theory suggests that superconductivity may survive down to only a few transverse channels in clean nanotube ropes. — We acknowledge useful discussions with A. Altland, H. Bouchiat, F. Essler, and A. Tsvelik. This work has been supported by the EU network DIENOW and by the SFB-TR 12 of the DFG.

-
- [1] M. Kociak, A. Y. Kasumov, S. Gueron, B. Reulet, I. I. Khodos, Y. B. Gorbatov, V. T. Volkov, L. Vaccarini, and H. Bouchiat, *Phys. Rev. Lett.* **86**, 2416 (2001).
 - [2] Z. K. Tang, L. Zhang, N. Wang, X. X. Zhang, G. H. Wen, G. D. Li, J. N. Wang, C. T. Chan, and P. Sheng, *Science* **292**, 2462 (2001).
 - [3] A. Kasumov, M. Kociak, M. Ferrier, R. Deblock, S. Gueron, B. Reulet, I. Khodos, O. Stephan, and H. Bouchiat (2003), *cond-mat/0307260*.
 - [4] A. Y. Kasumov, R. Deblock, M. Kociak, B. Reulet, H. Bouchiat, I. I. Khodos, Y. B. Gorbatov, V. T. Volkov, C. Journet, and M. Burghard, *Science* **284**, 1508 (1999).
 - [5] A. F. Morpurgo, J. Kong, C. M. Marcus, and H. Dai, *Science* **286**, 263 (1999).
 - [6] J. González, *Phys. Rev. Lett.* **88**, 076403 (2002).
 - [7] J. González, *Phys. Rev. B* **67**, 014528 (2003).
 - [8] A. De Martino and R. Egger, *Phys. Rev. B* **67**, 235418 (2003).
 - [9] H. J. Schulz and C. Bourbonnais, *Phys. Rev. B* **27**, 5856 (1983).
 - [10] C. N. Lau, N. Markovic, M. Bockrath, A. Bezryadin, and M. Tinkham, *Phys. Rev. Lett.* **87**, 217003 (2001).
 - [11] A. D. Zaikin, D. S. Golubev, A. van Otterlo, and G. T. Zimanyi, *Phys. Rev. Lett.* **78**, 1552 (1997).
 - [12] D. S. Golubev and A. D. Zaikin, *Phys. Rev. B* **64**, 014504 (2001).
 - [13] M. Tinkham, *Introduction to Superconductivity, 2nd Edition* (McGraw-Hill, Inc., 1996).
 - [14] H. P. Büchler, V. B. Geshkenbein, and G. Blatter (2003), *cond-mat/0306617*.
 - [15] R. Egger and A. O. Gogolin, *Phys. Rev. Lett.* **79**, 5082 (1997).
 - [16] C. Kane, L. Balents, and M. P. A. Fisher, *Phys. Rev. Lett.* **79**, 5086 (1997).
 - [17] A. A. Maarouf, C. L. Kane, and E. J. Mele, *Phys. Rev. B* **61**, 11156 (2000).

- [18] S. T. Carr and A. M. Tselik, Phys. Rev. B **65**, 195121 (2002).
- [19] S. Lukyanov and A. B. Zamolodchikov, Nucl. Phys. B **493**, 571 (1997).
- [20] N. Nagaosa, *Quantum Field Theory in Condensed Matter Physics* (Springer Verlag, 1999).
- [21] J. E. Mooij and G. Schön, Phys. Rev. Lett. **55**, 114 (1985).
- [22] A. De Martino and R. Egger (2003), in preparation.
- [23] P. M. Chaikin and T. Lubensky, *Principles of Condensed Matter Physics* (Cambridge University Press, 2000).
- [24] J. S. Langer, Ann. Phys. (N.Y.) **41**, 108 (1967).
- [25] Since about 2/3 of all SWNTs are semiconducting, the rope contains $\approx 3N$ SWNTs. In our estimates, to take this into account, below we consider a reduced Josephson coupling.