Entropy Crisis, Ideal Glass Transition and Polymer Melting: Exact Solution on a Husimi Cactus

Andrea Corsi and P.D.Gujrati Department of Polymer Science and Department of Physics The University of Akron, Akron, OH, 44325

April 14, 2024

A bstract

W e introduce an extension of the lattice m odel of m elting of sem i exible polym ers originally proposed by Flory. A long with a bending penalty ", present in the original model and involving three sites of the lattice, we introduce an interaction energy "p, corresponding to the presence of a pair of parallel bonds and an interaction energy "h, associated with a hairpin turn. Both these new terms represent four-site interactions. The m odel is solved exactly on a Husim i cactus, which approxim ates a square lattice. W e study the phase diagram of the system as a function of the energies. For a proper choice of the interaction energies, the model exhibits a rst-order melting transition between a liquid and a crystalline phase at a tem perature $T_{\mbox{\scriptsize M}}$. The continuation of the liquid phase below T_M gives rise to a supercooled liquid, which turns continuously into a new low-tem perature phase, called m etastable liquid, at $T_{M,C}$ < T_{M} . This liquid-liquid transition seems to have some features that are characteristic of the critical transition predicted by the mode-coupling theory. The exact calculation provides a therm odynam ic justi cation for the entropy crisis (entropy becom ing negative), generally known as the K auzm ann paradox, caused by the rapid drop of the entropy near the Kauzm ann tem perature. It occurs not in the supercooled liquid, but in the m etastable liquid phase since its Helm holtz free energy equals the absolute zero equilibrium free energy at a positive tem perature. A continuous ideal glass transition occurs to avoid the crisis when the metastable liquid entropy, and not the excess entropy, goes to zero. The melting transition in the original F lory m odel, corresponding to the vanishing of the four-site interactions, appears as a tricritical point of the new model.

1 IN TRODUCTION

F lory'sm odel of crystallization of sem i exible linear polymers [1,2] is well known and describes a completely inactive crystal (CR) at low tem peratures [3] within

the approximations developed independently by Flory [2], and by Huggins [4]. There is a rst-order melting to a disordered equilibrium liquid (EL) phase, which has made it an attractive model to justify the K augm ann paradox [5] and the ideal glass transition [6] in supercooled liquids (SCL) [5-31]. The ideal glass transition in fragile supercooled liquids [7,9,17] is believed to be a manifestation of a rapid drop in the (con gurational) entropy [32] near the Kauzmann tem perature T $_{\rm K}$, and has been a topic of m any recent investigations [24-31]. The entropy in this work will always refer to the \cos gurational entropy [32]. There are competing theories, both for and against an ideal glass transition, and the situation is far from clear [7]. Even the nature of the melting transition in the Flory model is in dispute [10-13,27], mainly because the Gujrati-Goldstein excitations [3,10,11] destroy the complete inactive nature of the crystal phase. The present work is motivated by this confused state of the eld, and provides a convincing argument in favor of an ideal glass transition at a nite non-zero tem perature. In order to substantiate our claim s, we need to consider an extension of the original F bry m odel of melting. We also clarify the nature of the melting transition in the F bry model [10,11,13,27]. Our conclusions are based on exact calculations. Some of the prelim inary results have appeared earlier [28]. The present work provides the m issing details in Ref. 28.

A coording to the paradox, originally introduced by K auzm ann [5], the extrapolated entropy S_{CCL} (T) of the supercooled liquid becomes less than the entropy S_{CR} (T) of the corresponding CR at temperatures below the glass transition temperature T_G. It is a common belief [5–7,14,15] that the entropy of SCL cannot be less than the entropy of CR. However, it is worth noting [7,28,31] that there is no therm odynam ic requirement for or against this. It also does not violate the third law of therm odynam ics. How ever, treating this possibility as a paradox, now conventionally known as the K auzm ann paradox or catastrophe, K auzm ann suggested that the system would either crystallize spontaneously [5] or undergo an ideal glass transition [5–10,17] to avoid the paradox.

The existence of a glass transition caused by the above paradox has been originally justimed [B] only in the F lory model of melting applied to linear polymers that are long. The approximate calculation [B] shows that the CR phase is completely inactive (zero specific heat, and zero entropy). The supercooled liquid avoids the K augment catastrophe by undergoing a continuous transition called the ideal glass transition. This pivotal work enshrined the K augment catastrophe as probably the most important mechanism behind the glass transition.

It should be stressed that the glass transition is ubiquitous and is also seen in sm all molecules. However, no model calculation exists that demonstrates the paradox for sm all molecules. Unfortunately, the approximations used by G ibbs and D M arzio [8] have subsequently been rigorously proven to be incorrect, and unreliable [10-13], casting doubts on their primary conclusion of the existence of the K auzm ann paradox. Thus, there is currently no justication for the paradox as the root cause for the ideal glass transition, at least in long polymers.

The current work is motivated by a desire to see if we can, nevertheless, justify a therm odynam ic basis of the ideal glass transition in very long linear

polymers. To this end, we perform an exact calculation. We should point out that recently we have discovered the existence of an ideal glass transition in a model of simple uids [31 (a)] and of dimers [31 (b)]. However, this work deals only with long polymers. As discussed elsewhere [28, 31], the ideal glass transition in our view comes about not due to the originally proposed K augmann paradox caused by S_{SCL} (T) $< S_{CR}$ (T), but because of the entropy crisis when the entropy of the state becomes negative. A negative entropy in plies that there cannot be any realizable con guration of the system, which is impossible as there must be at least one con guration for the system to exist in N ature. Thus, in the following, we interpret the K augmann paradox not in the original sense, but in the sense of the above entropy crisis.

In the F bry model, a polymer chain is assumed to consist of n equal seqments, each with the same size as the solvent molecule. Each site of the lattice is occupied by either a polym er segment or a solvent molecule, and the excluded volume e ects are taken into account by requiring a site to be occupied only once, either by a solvent molecule or a polymer segment. We can also think of the solvent as representing voids in the system. The polymer chain occupies a contiguous sequence of all the lattice sites connected by polym er bonds. For concreteness and ease of discussion, we take the lattice to be a square lattice, which approximates a tetrahedral lattice on which the model is supposed to be de ned. Both lattices have the sam e coordination num ber q= 4. At every site, the polymer chain can assume either a trans conformation (the conformation is related to the state of two consecutive bonds), when the consecutive bonds are collinear, or one of the two possible gauche conform ations, when the polymer chain bends. For a sem i exible polymer chain, every gauche conformation has an energy penalty "compared to a trans conform ation. We set the energy for a trans conform ation to be zero. The total energy of the system in a con guration on a lattice of N sites is

$$E = N_{g}"; \qquad (1)$$

where N_g is the number of gauche conform ations present in the conguration of the system. This interaction involves three consecutive molecules of the chain and is the only one considered in the F lory model.

No interaction between non-consecutive portions of the same polymer chain or between di erent polymer chains is taken into account in the Flory model since, according to Flory [2], the crystallization of polymers is not due to interm olecular interactions but due to internal ordering/disordering and excluded volume interactions. Both the Flory [2] and the Huggins [4] approximations predict that the (con gurational) entropy S (g) of the polymer chain for a given fraction g N_g=N of gauche bonds goes to zero at a critical value g_0 (where g_0 is 0.45 in the Flory approximation [2,10(a)] and 0.227 in the Huggins approximation [4,10(b)]). Correspondingly, the predicted entropy of the system is zero for any g g_0 and gives rise to the inactive phase for g g_0 . The result of the calculation is shown schematically in Fig. 1. The system is in a disordered liquid phase EL at temperatures higher than the melting temperature T_M (curve BM).At T_M, the system undergoes a rst order transition to a

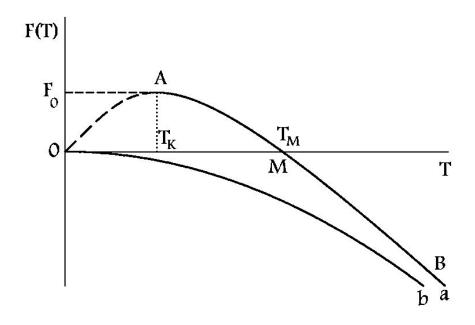


Figure 1: Free energy vs. tem perature for a sem i exible polymer: (a) Flory's calculation; (b) Gujrati-Goldstein upper bound.

com pletely inactive ordered CR, characterized by a zero free energy and a zero density g (portion MO). There is a discontinuity in g at T_M. The results due to F bry and H uggins are qualitatively sim ilar; the main di erence is that F bry's estimate of T_M is about four times higher than that due to H uggins [10(b)]. However, the simulations [12,27] strongly support the presence of the G ujrati-G oldstein excitations that destroy the inactive crystal at low tem peratures, but the nature of the melting transition remains uncertain, which makes the mathematical extrapolation MA representing the supercooled liquid [8] questionable. In particular, it is not clear if the extrapolation of the exact result would give a non-zero tem perature where S (T) would go to zero but where g > 0.

R igorous low er bounds on S (g) per particle (and hence upper bounds for the free energy) as a function of g have been obtained [10,11]. G u jratiand G oldstein were able to prove that the entropy per segm ent of the chain in the case of a single polym er chain that occupies all the sites of the lattice (the H am ilton walk

lim it) satis es

S (g)
$$\frac{g}{8} \ln(\frac{4}{g} 3)$$
: (2)

Hence, S is positive for any value of g > 0, as it surely must be, in contrast with the results obtained by F lory. Bounds are also available for the case of nite-length polymers [11]. The above bound (2) implies that the equilibrium free energy of the system is never zero for T > 0, see curve (b) in Fig. 1, and that the system is never completely ordered at any nite temperature.

W hile the results due to Gujrati and Goldstein clearly show that the approxim ations of F lory and H uggins do not give a satisfactory description of the system, they just provide an upper bound for the equilibrium free energy of the system; nothing is known about the correct equilibrium entropy. Therefore, it is still unknown what the actual behavior of the free energy is, which is needed to obtain the continuation of the SCL liquid phase. The bounds do not say anything about the extrapolated (i.e. continued) SCL free energy or entropy. The knowledge of the reliable free energy form is fundamental in order to understand if there is a phase transition of any kind in the system at any nite tem perature. In particular, it is not clear if the model has a rst-order melting transition. It should be recalled that one can usually continue the free energy only past a rst-order transition, and not a second order transition due to the singularity in the latter case. If there is no melting transition with a latent heat, then there may be no SCL liquid below the melting transition. In this case, there would be no validity to the G ibbs-D M arzio conjecture of a glass transition in the SCL liquid. Thus, an exact calculation is highly desirable.

In recent years, the study of the glass transition has been stimulated by the developm ent of the mode-coupling theory (MCT) [20-22]. This theory was developed in the rst place for simple liquids but has been applied to polymers also [20]. The MCT studies the evolution of the density autocorrelation function that can be measured in scattering experiments or calculated in computer simulations and is, therefore, of practical interest. The main result of this theory is the prediction of a critical temperature $T_{\rm MC}$, above the glass transition temperature, corresponding to a crossover in the dynamics of the system . At $T_{\rm MC}$, the correlation time of the system (the segmental relaxation time in the case of a polymeric glass) diverges with a power law just as one observes near a critical point:

$$/ (T T_{MC})$$
 : (3)

M any neutron and light scattering experiments [20] have shown that the M C T is able to predict at least qualitatively the spectra of low m olecular weight m aterials. M ost of the system s for which M C T gives a good description of the dynam ics (at least qualitatively) belong to the class of fragile glass form ers. The theory has not been tested extensively with polymers that have large m olecular weight but at the same time have been shown to be the most fragile system s yet identi ed [21-23].

Recent activities [24-26] have tried to export the progresses made in the eld of spin glasses [33] to the eld of real glasses. Even though the replica trick is clearly unphysical [34,35], this approach has been extended to the case of real glasses. The replica approach has been applied to m any Lennard-Jones glasses and the results have been interesting [24-26]. They provide som e justi cation for the ideal glass transition. This may also be the case for polymers, which is the focus of this study.

Despite the wide interest in the subject, there is still no comprehensive understanding of the nature of the vitrifying SCL and its relationship with CR, the mechanism responsible for the rapid entropy loss near T_G, and the nature of the ideal glass transition. It would also be interesting to see if there is a possible therm odynam ic basis for the critical (and apparently a mode-coupling) transition in SCL's.

In order to obtain a therm odynam ic justi cation for all these phenom ena, we consider in detail in this work a very sim ple limiting case. The solvent density will be taken to be identically zero. Thus, we consider an incom pressible pure system. The e ect of free volum e is treated in separate publications [29-31]. We also consider the limiting case of a single chain covering the entire lattice. Such a limit is conventionally known as the H amilton walk limit [10,11]. The case of many chains of nite lengths is considered elsewhere [29-31]. To obtain a rst orderm elting, we have to extend the F bry m odelofm elting, as described below. We have substituted the original square lattice with a H usim i cactus (Fig. 2) on which the original problem is solved exactly. This is the only approximation we make. The results of this calculation for the case of a special interaction have been reported earlier [28] but details were not given. The present work also provides the m issing details.

It has been previously shown [36] that the exact calculations on recursive structures like the Husim i cactus are more reliable than conventional meaneld calculations. In this approach, the problem is solved exactly, taking into account all correlations present on the recursive lattice. In most cases, the real lattice is approximated by a tree structure. Because of the tree nature, the correlations are weak. We have chosen the Husim i cactus, obtained by joining two squares (Fig. 2) at each vertex, so that the coordination number q = 4.0 n a square lattice, there are also squares that share a bond. Such squares are not present in the cactus. Thus, the cactus should be thought of representing the checkerboard version of the square lattice, with the further provision that no closed loops of size larger than the elementary square are present. The square is chosen to allow for the Gujrati-Goldstein excitations [10,11] that are important in disordering the ideal crystal at absolute zero. The results from the cactus calculation can be thought of as representing an approximate theory of the model on a square lattice.

The layout of the paper is as follows. In the next section, we introduce the lattice m odel in terms of independent extensive quantities of interest. It is the m ost general m odel provided we restrict these quantities to represent pairs, triplets, and quadruplets of sites within each square. We also discuss the general physics of the m odel. As said above, we use a square lattice for

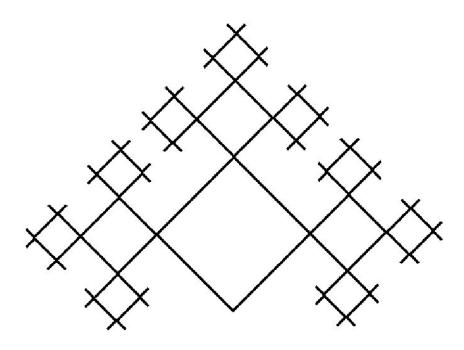


Figure 2: Upper half of a Husim i cactus of generation m = 3. The dangling bonds outside it show its connection through surface sites (not shown in the gure) with the larger in nite cactus, as explained in the text.

simplicity to introduce the model, even though we eventually consider a Husim i cactus, on which the calculations are exactly. In Sect. III, we explain the recursive solution method on a Husim i cactus. We introduce 1-cycle and 2-cycle solutions, representing the disordered and the ordered phase, respectively. The results are presented in Sect. IV along with the discussion, and the nal section contains our conclusions.

2 THE MODEL AND ITS PHYSICS

2.1 Independent extensive quantities

We consider a square lattice of N sites to focus our attention. We will neglect surface e ects. There are N_B = 2N lattice bonds, or distinct pairs of sites. Let us describe the state of a square by the number of polymer bonds j in it. The bonds in the following refer to the polymer bonds. Let N_{S0}, and N_{S1} denote the number of squares (S) with j = 0, and 1, respectively; see Fig. 3.

For j = 2, we distinguish between the case of parallel bonds (p), with the

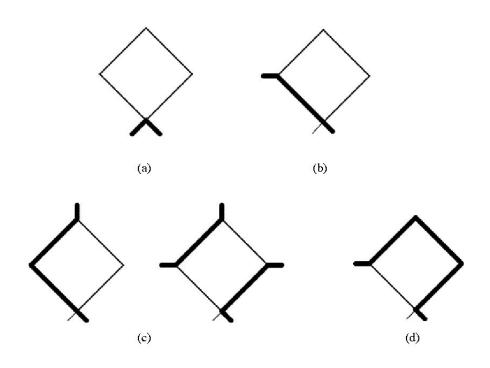


Figure 3: The possible states of a square in the lattice: (a) no bonds, (b) one bond, (c) two bonds and (d) three bonds.

num ber of such squares N $_{\rm Sp}$, and gauche (g) bonds, with the num ber of such squares N $_{\rm Sg}$. The hairpin (h) turn corresponds to j = 3, with the num ber of such squares N $_{\rm Sh}$. No square is allowed to have four bonds in it. Let N $_{\rm t}$ and N $_{\rm g}$ denote the num ber of trans and gauche bonds, respectively, and N $_{\rm p}$ and N $_{\rm h}$ the num ber of pairs of parallel bonds and hairpin turns, respectively, in a given con guration. We will also use them to represent their average values, as there will be no confusion. It is easily seen that the num ber of squares on a square lattice is N $_{\rm S}$ = N . Let B denote the num ber of polym er bonds, and N $_{\rm m\,m}$ the num ber of unbonded m onom er-m onom er contacts. The following topological identities are easily seen to hold:

$$N_{S} = N_{S0} + N_{S1} + N_{Sp} + N_{Sq} + N_{Sh};$$
(4)

$$2N_{mm} = 4N_{S0} + 3N_{S1} + 2N_{Sp} + 2N_{Sg} + N_{Sh};$$
(5)

$$2B = N_{S1} + 2N_{Sp} + 2N_{Sq} + 3N_{Sh};$$
(6)

$$N = N_t + N_q; 2N = B + N_{mm};$$
 (7)

$$N_{p} = N_{Sp} + N_{Sh}; N_{q} = N_{Sq} + 2N_{Sh};$$
 (8)

As said earlier, the cactus represents the checkerboard version of the square lattice, so that the number of squares N_S on both lattices with the same number of sites N are not the same; see Sect. III also. For a square lattice, N_S = N; for the cactus, N_S = N =2. However, the number of lattice bonds N_B on both lattices are the same. Because of this, Eq. (6) must be modiled for the cactus. Since each bond belongs to only one square in the cactus, we have:

$$B = N_{S1} + 2N_{Sp} + 2N_{Sq} + 3N_{Sh}:$$
(6a)

All other identities remain valid on the cactus.

2.2 GeneralM odel

Am ong the eleven extensive quantities, N, B, N_g, N_t, N_{mm}, N_{s0}, N_{s1}, N_{sp}, N_{sg}, N_{st} and N_{sh}, there are six independent geom etrical relations; the second one in (7) is not independent. In addition, for the Ham ilton walk problem, we have B = N. Thus, there are only four independent extensive quantities, which we take to be N, N_g, N_p and N_h. One of these, the lattice size N, will be used to de ne the partition function. The remaining three independent quantities N_p, N_g and N_h will be then used to de ne the con guration uniquely. Corresponding to each of the quantities N_g, N_p and N_h, there is an independent activity w, w_p and w_h, respectively, that will determ ine the partition function for the Ham ilton walk problem as

$$Z_{N} = {}^{X} w^{N_{g}} w^{N_{p}}_{p} w^{N_{h}}_{h}; \qquad (9a)$$

where the sum is over distinct con gurations obtained by all possible values of N_g, N_p and N_h consistent with a xed lattice size N. The activities w, w_p and w_h are determined by the three-site bending penalty " introduced by F lory in his model, an energy of interaction "_p associated with each parallel pair of neighboring bonds, and an energy "_h for each hairpin turn within each square as follow s:

$$w = \exp(("); w_p = \exp(("_p); w_h = \exp(("_h));$$

Here, is the inverse temperature T in the units of the Boltzm ann constant. The original F bry model is obtained when the last two interactions are absent. It should be stressed that "_h is the excess energy associated to the con guration, once the energy of the two bends and the pair of parallel bonds have been subtracted out. Both "_p and "_h are associated with four-site interactions, since it is necessary to determ ine the state of four adjacent sites to determ ine if a pair of parallel bonds or a hairpin turn is present.

The model is easily generalized to include free volume by introducing voids, each of which occupies a site of the lattice. The number of voids N₀ is controlled by the void activity . The number P of polymers is controlled by another activity given by H²: The interaction between nearest neighbor pairs N_c of voids and the monomers of the polymers determines the Boltzmann weight w_c. The partition function of the extended model is given by

$$Z_{N} = {}^{N_{0}} H^{2p} w_{c}^{N_{c}} w_{p}^{N_{g}} w_{p}^{N_{p}} w_{h}^{N_{h}}; \qquad (9b)$$

where the sum is over distinct con gurations consistent with the xed lattice of N sites. Because the activity H only determ ines the average number of linear polymers, but not their individual sizes, the model in Eq. (9b) describes polydisperse polymers [37], each of which must contain at least one bond.

We now turn to our simplied model of the Hamilton walk (P = 1, and N $_0$ = 0). In this model, the energy of interaction in a given con guration is given by

$$E = "N_{g} + "_{p}N_{p} + "_{h}N_{h} = "(N_{g} + aN_{p} + bN_{h});$$
(10)

where a "p=",b "h=". The parameters can in principle assume positive and negative values. However, we will restrict ourselves to "> 0 in this work. The lim it "= "p = "h = 0 corresponds to a completely exible polymer problem, which is of no interest to us here, as it corresponds to the in nite temperature lim it of ourm odel. The lim it, how ever, is of considerable interest in the study of protein folding and has been investigated by several workers [38]. In addition, we will focus mainly on the case 0 < a < 1. A positive a guarantees that parallel bonds are present and a < 1 makes the penalty for a pair of parallel bonds less than that for a gauche conform ation. This guarantees the presence of a crystalline phase at low temperatures, as shown below.

2.3 G round State at T = 0

The physics of the model at absolute zero can be easily understood on general grounds. We are interested in the therm odynamic limit N ! 1. We rst consider b = 0. For a < 1, the ground state at T = 0 has $N_g = 0$, $N_p = N$, $N_h = 0$, as shown in Fig. 4(a). (The labels R and L are related to the state of the sites as introduced in the next section.) Thus, $E = "_pN$. This is what we will call the perfect crystal at absolute zero. For b \in 0, the state in Fig.

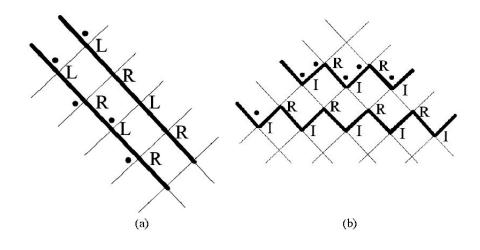


Figure 4: Possible con gurations of the polymer chain at T = 0: (a) crystalline phase with N_g = 0 and N_p = N; (b) step-like con guration with N_p = 0 and N_g = N. See text for the explanation of the symbols.

4 (a) rem ains the ground state as long as 2 + b > 0. This condition ensures that haippin turns are not present. For a > 1, and b = 0, the ground state at T = 0 has $N_g = N$, $N_p = 0$, as shown in Fig. 4 (b). Thus, E = "N. This remains the ground state provided a + b > 0, which ensures that the haippin turns are not present. Since our interest is to have a crystal state as the equilibrium state at low tem peratures, we would only consider the earlier case a < 1, with 2 + b > 0.

It should be recognized that the model considered here is de ned on a lattice. Thus, the ground state also possesses the symmetry of the lattice. This symmetry is imposed by the lattice symmetry and is independent of the model. Thus, this induced symmetry should not be confused with the point group symmetry of a real crystal, which is brought about by the interactions in the system. The symmetry in our model is due to the orientational order between pairs of parallel bonds. It is because of the orientational order de ning the crystal in our model that we can obtain a continuous transition between the crystal and the equilibrium liquid.

The lack of a point group symmetry of a real crystal in our model should not

be a taken as a serious limitation of the model, since our main goal is to study the possibility of a glass transition in a supercooled liquid. The determ ination of the supercooled liquid branch requires the continuation past a rst-order melting transition. Thus, the exact nature of the symmetry of the CR phase is not as important as the existence of a discontinuous melting.

3 RECURSIVE SOLUTION

The Husin i cactus approximates the square lattice, as said above. Both have the coordination number q = 4, and the elemental squares as the smallest loop. However, the most important reason for choosing the square cactus is that it allows for hairpin turns that give rise to the Gujrati-Goldstein excitation in the Flory model of melting. A Bethe lattice would be inappropriate for this reason. As said above, the number of squares on the cactus is half of that on a square lattice with the same number of sites N. This can also be easily seen as follows by assuming hom ogeneity of the lattice. First, consider the square lattice. Four squares meet at each site; however, each square will be counted four times, due to its four comers, assuming hom ogeneity. Thus, N_S = N. On a cactus, only two squares meet, but each one is counted four times as before. Hence, N_S = N = 2. Despite this, N_B = 2N on both lattices, only half of which are going to be taken up by the Ham ilton walk on both lattices.

A site is shared by four bonds and two squares , and 0 that are across from each other on the cactus. On the other hand, there are two di erent pairs of such squares on a square lattice. In a form al sense, we can in agine that each end of a bond contributes $\frac{1}{4}$ of a site, and each corner of a square contributes $\frac{1}{2}$ of a site (on a square lattice each corner contributes $\frac{1}{4}$ of a site.). This form al picture will be useful in determ ining the nature of a hom ogeneous cactus. To m ake the cactus hom ogeneous, we must consider it to be part of a larger cactus. This is shown in Fig. 2, where we show a cactus of generation m = 3 with dangling bonds (each one ending with a surface site, not shown in the qure) outside it to show its connection with the larger in nite cactus. The latter has no boundary. A similar homogeneity hypothesis associated with a Bethe lattice has been discussed in Ref. 37 (b) to which we refer the reader for further details. On a Bethe lattice, each dangling bond was treated as a half-bond to ensure that N_B = qN =2, where q is the coordination num ber of the Bethe lattice. For the case of the cactus, we treat each pair of dangling bonds in Fig. 2 as a half-square, and each surface site as a half-site to calculate the number of sites $N_{\,m}$, and the number of squares $S_{m}\,$ for a cactus of m generations. A trivial calculation shows that

$$N_m = 4 \quad 3^m \quad 2; \quad S_m = 2 \quad 3^m \quad 1;$$
 (11)

so that $S_m = N_m = 2$, as m ! 1. Since each square contributes 4 bonds, it is also evident that $N_B = 2N$ in the limit of an in nite cactus. A detailed calculation of the quantities introduced above is given in the Appendix.

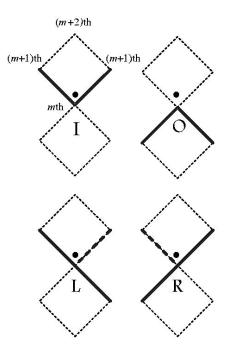


Figure 5: The four possible states of the polymer chain at any site at the m th level of the lattice.

Because of the above-m entioned hom ogeneity, a site is arbitrarily designated as the origin of the cactus. Each square has one site, called the base site, closer to the origin. The base site is given an index m 0, the two sites next to the base site within the square, called the interm ediate sites, the index (m + 1), and the remaining fourth site, called the peak site, the index (m + 2). We will call this square an m th level square; it has its base at the m th level and its peak at the (m + 2)th level; see Fig. 5. The two lower bonds in the m th square connected to the m th site are called the lower bonds and the two upper bonds connected to the peak site are called the upper bonds. The origin of the lattice is labeled as the m = 0 level and the level index m increases as we move outwards from the origin. We can imagine cutting the Husim i tree at an m th site into two parts, one of which does not contain the origin if m > 0. We call this the m th branch of the lattice and denote it by C_m . At the origin, we get two identical branches each containing the origin. We will call each of those the (m = 0)th branch.

W e only consider parallel bonds and hairp in turns that are inside the squares,

since the cactus represents the checkerboard version of the square lattice. Thus, each square can contribute only once to either N_p, or N_h: This means that N_p = N_s = N=2 in the perfect crystal at absolute zero. Similarly, it can be easily seen that the maximum possible value of N_h is $2N_s=3 = N=3$.

3.1 Recursion Relations

We consider a linear polymer that covers all the sites of the Husimi cactus or the square. Its con guration determines the state of the bonds in each square. Consider a pair of two squares , and ⁰ that are across from each other. We distinguish by putting a lled dot () just above the common site. We now face towards ⁰ from within through this common site. The common site has been taken as the base site in Fig. 5, but the following description is valid at any site. The common site can assume 4 possible di erent states depending on the state of the four bonds connected to it. Two of the bonds are in ; and the remaining two are in ⁰:

- 1. In the Istate, both -bonds are occupied by the polymer chain. Since the polymer is linear, the two ⁰-bonds must be unoccupied by the polymer.
- 2. In the 0 state, both -bonds are unoccupied but both ⁰-bonds are occupied by the polymer chain.
- 3. In the L state, only one of the -bonds is occupied and the polymer occupies the left bond in ⁰ (we always think about left and right as we face towards ').
- 4. In the R state, only one of the -bonds is occupied and the polymer occupies the right bond in ⁰.

For the common site at m = 0, the square ⁰ in the above classi cation is the square on the other side of the origin.

It is now easy to understand the labeling of the two con gurations shown in Fig. 4.

W e are interested in the contribution of the portion of the m th branch C_m of the lattice to the total partition function of the system. This contribution is called the partial partition function (PPF) of the branch. It is easy to see that the PPF depends on the state of the m th level site. W e denote this PPF by Z_m (). We now wish to express Z_m () recursively in term s of the PPF's of the two interm ediate sites and the peak site of the m th square. Following Gujrati [36], the recursion relations can always be written in the form :

$$Z_{m}() = Tr[W(;fg)Z_{m+1}(_{1})Z_{m+1}(_{2})Z_{m+2}(_{3})]; \qquad (12)$$

where f g is the set of states $_{i}$; the latter states represent the possible states of the other three sites of the square, and W (; f g) is the localBoltzm ann weight of the square due to conform ation of the polymer chain inside the square.

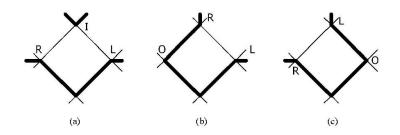


Figure 6: Possible con gurations of the polymer chain when the m th level site is in the I state.

Let us consider in detail the case in which the base site at the m th level is in the I state. The three possible con gurations that the polymer can assume in the m th level square are shown in Fig. 6. In this gure, L, R, I and O represent the possible state of the (m + 1)th and (m + 2)th level sites and w represents the weight of a bend. In order to carefully account for statistical weights, a Boltzm ann weight equal to w is considered only if the bend happens:

- 1. At the m th level and at least one polym er bond at the level is inside the square.
- 2. At the (m + 1)th or (m + 2)th level, and both polym er bonds at the level are inside the polym er.

A weight $w_p = w^a$ is considered for any conguration in which two bonds are parallel to each other within the same square. We can, furthermore, distinguish congurations in which two bonds are parallel to each other from congurations, like those shown in Figs. 6 (b)-(c), where three consecutive bonds form a hairpin conguration. Whenever this conguration is present, an additional weight $w_h = w^b$ is introduced.

It is not important to know along which of the two lower bonds in the (m + 1)th or (m + 2)th square does the polymer chain enter into the m th square. In fact, even if the polymer undergoes a bend while moving from the higher level square to the m th level square, the corresponding weight is already taken into account into the partial partition function of the higher level site.

It is important to consider always the state of a site moving through the lattice towards the origin. In the con guration in Fig. 6(a), the interm ediate

site on the left is in the R state since the polym er undergoes a right turn after entering the square. The interm ediate site on the right is in the L state since the polym er undergoes a left turn after entering the square. Finally, the peak site is in the I state because the polym er is coming from the (m + 1)th level square but not entering the m th level square. The polym er undergoes one bend (at the base site) so that there is a weight w to be taken into account. Thus the contribution to the partition function coming from this con guration is:

$$w Z_{m+1} (R) Z_{m+1} (L) Z_{m+2} (I)$$
: (13)

In the con guration in Fig. 6(b), the intermediate site on the left is in the O state since both the lower bonds in the corresponding (m + 1)th square are unoccupied. The intermediate site on the right is in the L state since the polymer undergoes a left turn after entering the square. Finally, the peak site is in the R state since the polymer undergoes a right turn after entering the square. The polymer undergoes two bends (one at the base site and the other one at the left intermediate site) so that there is a weight w² to be taken into account. There is a pair of parallel bonds in the square and a hairpin turn occurs so that a weight w_hw_p has also to be taken into account. Thus, the contribution to the partition function coming from this con guration is:

$$w^2 w_h w_p Z_{m+1} (O) Z_{m+1} (L) Z_{m+2} (R)$$
: (14)

In the con guration in Fig. 6(c), the interm ediate site on the right is in the O state since both the lower bonds in this particular (m + 1)th square are unoccupied. The interm ediate site on the left is in the R state since the polymer undergoes a right turn after entering the square. Finally, the peak site is in the L state since the polymer undergoes a left turn after entering the square. The polymer undergoes two bends (one at the base site and the other one at the right interm ediate site) so that there is a weight w² to be taken into account. W e also have a pair of parallel bonds and a hairpin turn to take into account in this case. Thus, the contribution to the partition function coming from this con guration is:

$$w^2 w_h w_p Z_{m+1} (O) Z_{m+1} (R) Z_{m+2} (L)$$
: (15)

The recursion relation for Z_m (I), the partition function of the m th branch of the Husim i tree given that the m th level site is in the I state, is therefore given by:

$$Z_{m} (I) = w^{2} w_{h} w_{p} Z_{m+1} (O) [Z_{m+1} (L) Z_{m+2} (R) + Z_{m+1} (R) Z_{m+2} (L)] + w Z_{m+1} (R) Z_{m+1} (L) Z_{m+2} (I):$$
(16)

C onsidering the case in which the m th level site is in the O state, the partial partition function Z_m (O) for the O state can be written as:

$$Z_{m} (O) = Z_{m+1}^{2} (I) Z_{m+2} (I) + Z_{m+1} (I) [Z_{m+1} (L) Z_{m+2} (R) + Z_{m+1} (R) Z_{m+2} (L)] + w Z_{m+1} (R) Z_{m+1} (L) Z_{m+2} (O):$$
(17)

W hen the ${\tt m}$ th level site is in the L state the partial partition function can be written as:

$$Z_{m} (L) = [Z_{m+1} (R) + w Z_{m+1} (L)] f Z_{m+1} (I) Z_{m+2} (I) + w^{2} w_{p} w_{h} Z_{m+1} (O) Z_{m+2} (O) g$$

+ $w_{p} w Z_{m+1}^{2} (L) Z_{m+2} (R) + Z_{m+1}^{2} (R) Z_{m+2} (L)$
+ $[Z_{m+2} (R) + w Z_{m+2} (L)] w Z_{m+1} (I) Z_{m+1} (O):$ (18)

The relation for the R state is obtained from ${\rm Z}_{\,m}$ (L) by the interchange L $\, : \, R:$

$$Z_{m} (R) = [Z_{m+1}(L) + w Z_{m+1}(R)]fZ_{m+1}(I)Z_{m+2}(I) + w^{2}w_{p}w_{h}Z_{m+1}(0)Z_{m+2}(0)g + w_{p} w Z_{m+1}^{2}(R)Z_{m+2}(L) + Z_{m+1}^{2}(L)Z_{m+2}(R) + [Z_{m+2}(L) + w Z_{m+2}(R)]w Z_{m+1}(I)Z_{m+1}(0):$$
(19)

It is possible to write analogous relations for Z_{m+1} () by properly substituting m ! m + 1; m + 1 ! m + 2 and m + 2 ! m + 3: W e introduce the following ratios between partial partition functions at even and odd levels of the lattice:

$$\begin{array}{l} x_{m} (I) = Z_{m} (I) = (Z_{m} (L) + Z_{m} (R)); \\ x_{m} (O) = Z_{m} (O) = (Z_{m} (L) + Z_{m} (R)); \\ x_{m} (L) = Z_{m} (L) = (Z_{m} (L) + Z_{m} (R)); \\ x_{m} (R) = 1 \quad x_{m} (L): \end{array}$$

$$\begin{array}{l} (20) \end{array}$$

As one moves from a level that is in nitely far away from the origin towards the origin itself, the recursion relations (16)-(19) will approach x-point (FP) solutions, x_m () ! x (), x_{m+1} () ! x (), etc., where = I, O, L or R. These x-point solutions of the recursion relations describe the behavior in the interior of the Husim i tree. Once the xed point is reached, the value of x () and x () becomes independent of m: On a Husim i cactus, a site can be classified as a simultaneous peak and a base site, or a simultaneous peak and a middle site, depending on the pair of squares which share the site. Thus, it is expected that the most general FP solutions will correspond to a 2-cycle solution in which x_m () and x_{m+2} () tend to the same limit. In this case, we obtain a sublattice structure in which sites with even levels are different from sites with odd levels. We can write in this case:

The indices a and b refer to even and odd levels, respectively. Using (21), it is easy to prove that the system of equations (16) to (19) can be written in the

following form :

$$i_a Q_{LR} = w (1 \ l_b) l_b i_a + w^2 w_p w_h o_b [l_b (1 \ l_a) + l_a (1 \ l_b)];$$
 (22)

$$O_{a}Q_{LR} = \dot{I}_{b}^{2}\dot{I}_{a} + \dot{I}_{b}[I_{b}(1 \quad I_{a}) + I_{a}(1 \quad I_{b})] + w(1 \quad I_{b})I_{b}O_{a};$$
(23)

$$l_a Q_{LR} = (1 \quad l_b + w \, l_b) [\dot{l}_b \, \dot{l}_a + w^2 w_p w_h o_b o_a]$$

$$+ w o_{\rm b} i_{\rm b} (1 \, l_{\rm a} + w \, l_{\rm a}) + w_{\rm p} (1 \, l_{\rm b})^2 \, l_{\rm a} + w \, w_{\rm p} \, l_{\rm b}^2 (1 \, l_{\rm a}); \quad (24)$$

$$i_{b}Q_{LR} = w (1 \quad l_{a}) l_{a}i_{b} + w^{2}w_{p}w_{h}o_{a} [l_{a} (1 \quad l_{b}) + l_{b} (1 \quad l_{a})];$$
(25)

$$o_{\rm b}Q_{\rm LR}^{'} = \dot{l}_{\rm a}^{2}\dot{l}_{\rm b} + \dot{l}_{\rm a}\left[l_{\rm a}\left(1 \quad l_{\rm b}\right) + l_{\rm b}\left(1 \quad l_{\rm a}\right)\right] + w\left(1 \quad l_{\rm a}\right)l_{\rm a}o_{\rm b};$$
(26)

$$\mathbf{l}_{b}\mathbf{Q}_{LR} = (\mathbf{1} \quad \mathbf{l}_{a} + \mathbf{w} \, \mathbf{l}_{a}) \left[\mathbf{i}_{a} \, \mathbf{i}_{b} + \mathbf{w}^{2} \mathbf{w}_{p} \mathbf{w}_{h} \mathbf{o}_{a} \mathbf{o}_{b} \right]$$

+
$$w o_a i_a (1 l_b + w l_b) + w_p (1 l_a)^2 l_b + w w_p l_a^2 (1 l_b);$$
 (27)

where Q_{LR}° is obtained from Q_{LR} by exchanging a and b subscripts and Q_{LR} can be written as:

$$Q_{LR} = (1 + w) f \dot{i}_{b} \dot{i}_{a} + w^{2} w_{p} w_{h} o_{b} o_{a} + w \dot{i}_{b} o_{b} + w_{p} [l_{b} (1 - l_{a})^{2} + l_{a} (1 - l_{b})^{2}]g;$$
(28)

3.2 2-cycle Free Energy

In order to determ ine which phase is the stable one at some temperature, we have to nd the free energy of all the possible phases of the system as a function of w. We follow the treatment by Gujrati [36], and provide its trivial extension to the 2-cycle FP solution shown above. The free energy per site at the origin of the lattice can be easily calculated from the expressions for the total partition function Z at the (m = 0)th, (m = 1)th and (m = 2)th levels.

The total partition function of the system Z_0 can be written by considering the two (m = 0)th branches C_0 meeting at the origin at the (m = 0)th level. For this, we need to consider all the possible con gurations in the two branches. This is done by considering all the con gurations that the polymer chain can assume in the two squares that meet at the origin of the tree. All the possible con gurations of the (m = 0)th level site (in this case we are not interested in the state of the (m = 1)th level sites) are shown in Fig. 7. Each of the rst two con gurations contributes

$$Z_0$$
 (I) Z_0 (O)

to the total partition function. The third and fourth con gurations both contribute

(1=w)Z_{0;q}(L)Z_{0;q}(R);

where the factor (1=w) is needed in order not to take into account the Boltzm ann weight at the origin twice and the subscripts "g" and "t" refer to the gauche and transpart of the partition function for L and R states. In fact, it is possible to separate these two contributions to the partition function at any level. The

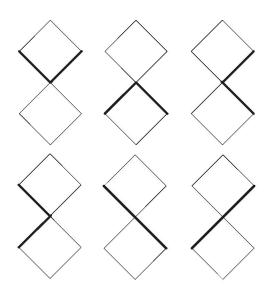


Figure 7: Possible con gurations of the polymer chain at the origin of the tree.

"gauche" portion is the one corresponding to con gurations such that there is a bending at them th level site, while the "trans" portion is the one corresponding to con gurations in which the two bonds com ing out of the m th level site that we are considering are straight. It is easily seen that:

$$Z_{m,t}(\mathbf{L}) = Z_{m+1}(\mathbf{R}) f Z_{m+1}(\mathbf{I}) Z_{m+2}(\mathbf{I}) + w^2 w_p w_h Z_{m+1}(\mathbf{0}) Z_{m+2}(\mathbf{0}) + w_p Z_{m+1}(\mathbf{R}) Z_{m+2}(\mathbf{L}) q + w Z_{m+2}(\mathbf{R}) Z_{m+1}(\mathbf{I}) Z_{m+1}(\mathbf{0});$$
(29)

and

$$Z_{m,g}(\mathbf{L}) = w Z_{m+1}(\mathbf{L}) f Z_{m+1}(\mathbf{L}) Z_{m+2}(\mathbf{L}) + w^2 w_p w_h Z_{m+1}(\mathbf{O}) Z_{m+2}(\mathbf{O}) + w_p Z_{m+1}(\mathbf{L}) Z_{m+2}(\mathbf{R}) + w^2 Z_{m+2}(\mathbf{L}) Z_{m+1}(\mathbf{I}) Z_{m+1}(\mathbf{O}):$$
(30)

F inally, the fth and sixth con gurations contribute $Z_{0,t}^2(L)$ and $Z_{0,t}^2(R)$, respectively. It is then possible to write:

$$Z_{0} = 2Z_{0} (I) Z_{0} (O) + (2=w) Z_{0;g} (I) Z_{0;g} (R) + Z_{0;t}^{2} (I) + Z_{0;t}^{2} (R) : (31)$$

It is clear that Z_0 is the total partition function of the system obtained by joining two branches C_0 together at the origin. Now, let us in agine taking away

from the lattice the two squares that meet at the origin. This leaves behind four di erent branches C_1 and two branches C_2 . We connect the two C_2 branches to form a smaller cactus whose partition function is denoted by Z_2 . Sim ilarly, we join two of the C_1 branches to form an interm ediate cactus whose partition function is denoted by Z_1 . We can form two such interm ediate cactiout of the four C_1 branches. Each partition function Z_1 or Z_2 can be written in a form that is identical to that of Equation (31):

$$Z_{i} = 2Z_{i}(I)Z_{i}(O) + (2=w)Z_{i;g}(L)Z_{i;g}(R) + Z_{i;t}^{2}(L) + Z_{i;t}^{2}(R);$$
(32)

where i = 1;2:

The di erence between the free energy of the complete cactus and that of the three reduced cacti is just the free energy corresponding to a pair of squares so that, following Gujrati [36], we can write the adimensional free energy per square (without the conventionalminus sign) as:

$$! \quad !_{sq} = \frac{1}{2} \ln [\mathbb{Z}_0 = f\mathbb{Z}_1^2 \mathbb{Z}_2 g]:$$
(33)

It is possible to write:

$$Z_{0} = B_{0}^{2}Q_{2} (i_{a}; o_{a}; l_{a}; i_{b}; o_{b}; l_{b});$$
(34)

$$Z_{1} = B_{1}^{2}Q_{2}^{"}(i_{a};o_{a};l_{a};i_{b};o_{b};l_{b});$$
(35)

$$Z_{2} = B_{2}^{2}Q_{2} (i_{a}; o_{a}; l_{a}; i_{b}; o_{b}; l_{b});$$
(36)

where we have introduced

$$B_{m} = Z_{m} (L) + Z_{m} (R);$$
 (37)

and where Q $_2$ is the following polynomial of i_a ; o_a ; l_a ; i_b ; o_b and l_b :

$$Q_{2} = 2i_{a}o_{a} + (2=w)l_{a,g}(1 \quad l_{a})_{g} + l_{a,t}^{2} + (1 \quad l_{a})_{t}^{2};$$
(38)

 $l_{a,t}$ and $l_{a,g}$ correspond to the trans and gauche portions of l_a , respectively, and Q_2^0 is obtained from Q_2 by interchanging a and b subscripts.

It is also easily seen that:

$$B_{0} = B_{1}^{2}B_{2}Q_{LR} (i_{a}; o_{a}; l_{a}; i_{b}; o_{b}; l_{b}):$$
(39)

so that the free energy per square can be written as:

! !
$$g_{q} = \ln \frac{Q_{LR}}{Q_{2}^{0}}$$
 : (40a)

The free energy per site ! site is proportional to ! $_{\rm sq}$:

since there are two sites per square.

The usual Helm holtz free energy per square can be obtained from ! through:

$$\mathbf{F} = \mathbf{T} \mathbf{!} \mathbf{:} \tag{41}$$

If it happens that the even and odd sites are not dierent, we obtain a 1-cycle FP-solution. Below, we will consider the two solutions separately.

3.3 1-cycle solution

In the 1-cycle scheme, we have x_m () = x_{m+1} () as they converge to the same x point. Thus, we have: $i_a = i_b = i$, $o_a = o_b = o$ and $l_a = l_b = 1$: In this case the system of equations reduces to:

$$iQ_{LR} = w (1 \ l) li + 2w^2 w_p w_h ol(1 \ l);$$
 (42)

$$OQ_{LR} = i^3 + 2il(1 l) + w(1 l)lo;$$
 (43)

$$lQ_{LR} = [(1 \ 1) + w \ 1] \ i^{2} + w^{2}w_{p}w_{h}o^{2} + w_{p}l(1 \ 1) + w \ io ; \qquad (44)$$

with:

$$Q_{LR} = (1 + w) i^{2} + w^{2} w_{p} w_{h} o^{2} + w_{p} l(1 + w) i c$$
 (45)

From (44), it is easy to show that we must have $l = \frac{1}{2}$ for every solution obtained in this scheme.

O ne solution that exists for every value of $w\;\;(\text{and, hence, of }T\;)$ is the following:

$$l = \frac{1}{2}; o = 0; i = 0:$$
 (46)

This represents a liquid-like phase without any I, or 0 states. We label this phase m etastable liquid (ML) because, as we will show below, it never represents the equilibrium phase of the system even though it exists at all temperatures. For large enough w, there is another solution of the system of equations with nonzero values for o and i, and it has to be found numerically. We label this second liquid-like phase equilibrium liquid (EL) since, as our free energy calculations will show, it represents the equilibrium phase of the system at high temperature. The temperature at which EL appears is a function of w_p and w_h. We will call the temperature T_{MC}, at which the equilibrium liquid appears, the mode coupling temperature for reasons that will become clear below.

Table 1 shows how the value of T_{MC} changes as a function of a (both positive and negative values of a are considered, see below) as we keep b equal to zero.

а	T _{M C}
-1	2.9586
-0.8	2.6183
-0.5	2.1876
-0.2	1.7359
0	1.4427
0.2	1.1600
0.5	0.7653
8. 0	0.4156
1	0

Table 1: Values of T_{MC} as a function of a (with b = 0).

For the ML, we have $o = i = 0; l = \frac{1}{2}$ so that:

$$Q_2 = \frac{1}{2(1 + w)};$$
 (47)

and

$$Q_{\rm LR} = \frac{w_{\rm p} (1 + w)}{4};$$
 (48)

so that the M L free energy per square assumes the simple form :

$$h_{ML} = \ln w_{p} (1 + w)^{2} = 2 = \ln (1 + w)^{2} = 2 + \ln (w_{p});$$
(49a)

while, for the EL, we have to substitute the num erical solutions i(w); o(w), and $l = \frac{1}{2}$ obtained from Eqs. (42)-(45) in the expression for the free energy. The M L entropy per square is given by

$$s_{M L} = \ln (1 + w)^{2} = 2 + 2w = [\Gamma (1 + w):$$
(49b)

The corresponding energy is given by

$$E_{ML} = 2w = (1 + w) + a$$
: (49c)

It is easily seen that the M L speci c heat is always non-negative. It is very in portant to observe that the free energy of the M L phase does not depend on the value of the parameter a (except for the additive factor $\ln (w_p)$) while the free energy of EL strongly does. At absolute zero, the M L entropy and energy go to $\ln (1=2)$, and a, respectively. We not the modi ed free energy

$$\mathbf{F} = \mathbf{F} \quad \mathbf{"}_{\mathbf{p}} \tag{50}$$

m ore convenient to use than F itself since, at T = 0, the ground state is the one in which all the bonds are parallel to each other and the free energy of the

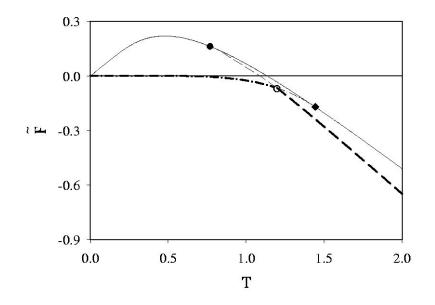


Figure 8: a = 0.5; b = 0. Free energy in the 2-cycle FP scheme for the ML (continuous line), EL/SCL (dashed line) and CR (dash-dot line). We also show T_{CRE} (), T_{M} () and T_{MC} (): Here, as well as in Figures 10 to 12, the stable phases are represented by thick lines while the metastable phases are represented by thin lines.

system is equal to " $_{\rm p}$ so that the crystalline ground state has always F = 0; regardless of the value of " $_{\rm p}$. The free energy curves for the EL and ML phases are shown in Fig. 8. We immediately observe that ML at very low temperatures T . 0:48 (dash-double dot line in Fig. 8 originating at the origin) has negative entropy, since its free energy F is increasing with the temperature. A negative entropy is not possible for states that can exist in Nature.

3.4 2-cycle solution

The phase diagram obtained in the 1-cycle solution scheme cannot be complete because, at low tem peratures, M L cannot be the stable phase. At T = 0; C R contains an alternating ordered sequence of L and R states in addition to having $1 = \frac{1}{2}$ and no 0 and I states; see Fig. 4. This is a 2-cycle pattern in L and R that is completely m issed by the 1-cycle calculation perform ed above. For M L, $1 = \frac{1}{2}$ also, but L and R are statistically distributed. One of these distributions must be the crystal state at T = 0; indeed, $F_{ML}(T = 0) = F_{CR}(T = 0)$:

D espite this, M L immediately above T = 0 can not represent CR, as it has negative entropy. To obtain the alternating sequence in CR at T > 0, the above 1-cycle FP scheme is not su cient to completely describe the physics of the system . We also observe that for T > 0, there must be local Gujati-Goldstein excitations [10,11] creating imperfections by local L ! R interchanges in the ordered [.LRLRLR..] sequence. The excitations change a local string LRL into LLL, or RLR into RRR within a square and require 4 bends only. Other excitations, which require (L or R) ! (I or O) on the cactus, can not be done locally and require in nite am ount of energy, and need not be considered. This m eans that the local density 1 or r will no longer be $\frac{1}{2}$. How ever, if $1 > \frac{1}{2}$ at som e site, then r > $\frac{1}{2}$ at the next site, followed by $1 > \frac{1}{2}$ on the next site and so on.

There are three solutions for the complete system of Eqs. (22)–(27) for any given value of the weights w , $w_{\rm p}$ and $w_{\rm h}$:

i. A metastable liquid M L (already found in the 1-cycle FP scheme) with: $l_a = l_b = r_a = r_b = \frac{1}{2}$ and $i_a = i_b = o_a = o_b = 0$.

As seen above, this phase represents a liquid phase in which no O and I states are present. The R and L states are random ly distributed in the lattice with the only constraint of having the same number of L and R states at both odd and even layers. This solution exists for any tem perature and its free energy has a maximum at $T = T_K$ ' 0:48.

ii. An equilibrium liquid EL characterized by the presence of all possible states $\rm I,O$, $\rm L$ and R at both odd and even levels, so that

 $l_a = l_b = r_a = r_b = \frac{1}{2}$ and $i_a, i_b, o_a, o_b \in 0$.

In the 2-cycle solution, i and o on the two sublattices are di erent, which m akes this solution di erent from the 1-cycle EL solution, in which there is no sublattice structure. D expite this, EL phases in both schem eshave identical free energy and various densities. Thus, we no longer m ake any distinction between the two solutions and identify both of them as the same EL phase. As seen in the previous subsection, the free energy of this phase depends on the value of the parameters a and b. This solution exists only for tem peratures larger than $T = T_{M C}$ (a;b).

iii. A crystal phase CR with double degeneracy that is the ground state and that exists for temperatures lower than $T = T_{CRE} = 1 = \ln(2)$. The state is perfectly ordered at zero temperature and disorders as the temperature is raised. Fig. 9 shows how the values of l_a and l_b change with temperature for the CR phase: the two degenerate solutions correspond to a di erent labeling of the lattice sites where the odd and even levels are just exchanged with each other.

The solutions of the system of Eqs. (22)-(27) corresponding to CR and to M L do not depend on the strength of the three- and four-site interaction and, therefore, the free energy curves corresponding to these two phases do not change when the parameters a and b change. In contrast, the free energy of the EL phase depends on the value of a and b.

For a < 1, we have the ground state at T = 0 in which all the bonds are paralleland there are no bends in the system s. If a > 1, the four-site interaction

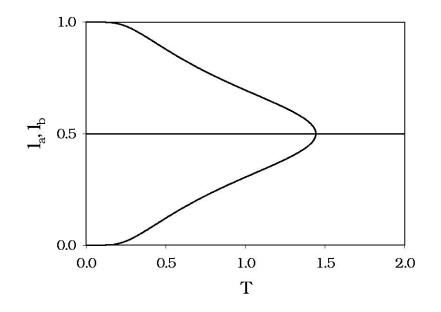


Figure 9: Dependence of l_a and l_b on the tem perature for the two phases obtained at low tem perature in the 2-cycle xed point scheme.

becomes more in portant than the three-site interaction and the ground state at T = 0 is a step like walk in which there are no parallel bonds and all the sites of the lattice are in a gauche conformation (so that $N_g = N_s$, as said earlier). The two possible ground states are shown in Fig. 4.

4 RESULTS AND DISCUSSION

4.1 Therm odynam ic Functions

$4.1.1 \quad b= 0$

The complete free energy diagram for a = 0.5 is given in Fig. 8. The equilibrium phases are represented by the disordered EL at high temperatures and the ordered CR at low temperatures, with a rst order transition at a temperature T_M between the two phases, with a discontinuity in the rst derivative of the free energy with temperature. This remains true as long as a > 0. The situation with a = 0 is different and is discussed later.

The existence of a discontinuous melting temperature for a >~0 makes it possible to have a supercooled liquid phase through continuation. For T $>~T_{\rm M}$, the EL phase is the stable one. If the liquid phase is cooled in such a way that

it is not allowed to undergo the melting transition at $T_{\rm M}$, then it is possible to have (for $T < T_{\rm M}$) a supercooled liquid (SCL). The free energy of SCL is obtained by continuing the free energy of the EL phase. This free energy meets critically (i. e. with continuous slopes) with the ML free energy at a temperature that, as before, we call $T_{\rm M\,C}$. For a=0.5 we nd that $T_{\rm M\,C} > T_{\rm K}$, where $T_{\rm K}$ is the temperature where the ML free energy has its maximum. The critical transition between ML and SCL is a liquid-liquid transition between two liquid phases. As a increases, $T_{\rm M\,C}$ moves towards $T_{\rm K}$. We have observed that for a & 0.8; $T_{\rm M\,C} < T_{\rm K}$ (results not shown). In particular, the EL free energy curve itself has a maximum in this case before it merges with the ML curve and, consequently, has an unphysical portion corresponding to the entropy crisis below its maximum .

Figs. 10 and 11 show the entropy and the speci c heat vs. tem perature, respectively, corresponding to the free energy results shown in Fig. 8. As explained before in the case of the free energy-tem perature graphs, the curves corresponding to CR and to ML do not depend on the choice of a and b. Table 2 shows how the value of T_M changes as a function of a (in the case b = 0).

а	TM
0	1.443
0.2	1.351
0.5	1.198
8 . 0	1.009
1	0.878

Table 2: Values of T_{M} as a function of a (with b = 0).

Only positive values of a are considered since, as it will be shown below, when the parameter a is negative, there is no rst-order melting in the system, provided that b = 0.

W e can calculate the density of gauche bonds g and the density of pairs of parallel bonds p as a function of T and a. W e can write:

$$g = 0!_{site} = 0 (\ln(w))_{y_{n}, w_{h}};$$
(51)

$$p = 0!_{sq} = 0 (\ln (w_p))_{j_{w_h}};$$
(52)

and calculate the two densities from these derivatives. Note that we have de ned the gauche bond density g per site, while the density of parallel bond pairs p is de ned per square, since each square contributes one such pair in the ideal CR at absolute zero. Fig. 12 shows the gauche bond density and the parallel bond density in the case of a = 0.5, b = 0.

4.1.2 b€ 0

The e ect of changing the value of the parameter b is shown in Fig. 13 for a = 0.5. A swe can see, a change in b does not have any e ect on the free energy

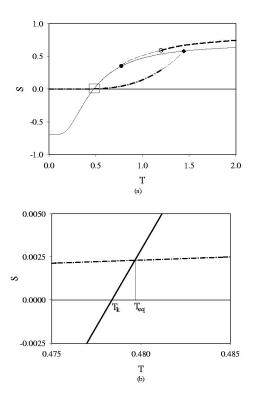


Figure 10: a = 0:5; b = 0. (a) Entropy in the 2-cycle FP scheme for the ML (continuous line), EL/SCL (dashed line) and CR (dash-dot line). We also show T_{CRE} (), T_{M} () and T_{MC} (); (b) m agni cation of the area contained in the box in (a).

of the CR and ML phases but it does a let the EL phase. Apparently, the elect of b is smaller than the elect of a, since the value of the melting temperature does not change signicantly as we change b. It is worth noting that the presence of the hairpin term alone, even in the absence of the interaction between pairs of parallel bonds, is su cient to transform the melting transition from secondorder, as seen in the case a = b = 0 (original F bry model), to rst-order. If b is negative, the melting and mode-coupling temperatures decrease. If b is positive, instead, these temperatures increase and the melting transition turns into a second-order transition. This is true for any positive value of b in the case a = 0, while it is true for large enough negative values of b when a is positive.

It is interesting to observe that the parallel bond density in M L and in C R is always unity while its value for the EL depends on the tem perature.

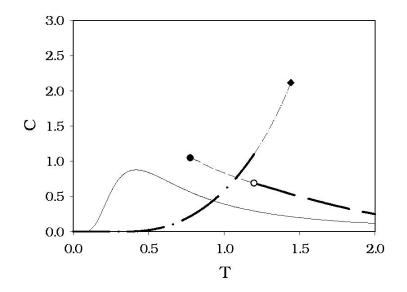


Figure 11: a = 0.5; b = 0. Speci c heat in the 2-cycle FP scheme for the M L (continuous line), EL/SCL (dashed line) and CR (dash-dot line). We also show $T_{\rm CRE}$ (), $T_{\rm M}$ () and $T_{\rm M\,C}$ ().

4.1.3 a>1

We consider now the case a > 1. This case corresponds to a ground state that is not crystalline, as shown in Fig. 4(b). When the four-site interaction is stronger than the three-site interaction, the polymer assumes a conguration that is such that the number of parallel bonds is minimized. In this case there is a very high number of gauche conformations at low temperatures and, even though the polymer assumes an ordered conguration on the lattice, it is not a crystalline conguration according to our de nition. Therefore, we do not consider this case any further.

4.1.4 a < 0

It is also possible to analyze the case in which a < 0. When a is negative (corresponding to a negative four-site interaction energy $"_{\rm p}$) the temperature $T_{M\ C}$ at which the EL appears moves to higher values. Since the temperature $T_{M}\ (\ T_{CRE}\)$ at which CR appears is una ected by the choice of the value of a, a shift of the origin of the EL phase to higher temperatures makes ML the

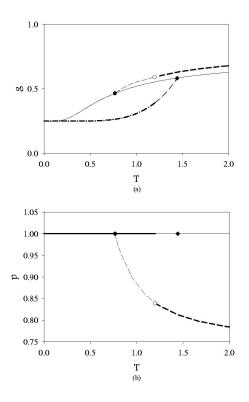


Figure 12: (a) Gauche bond and (b) parallel bond density in the 2-cycle FP scheme for the ML (continuous line), EL/SCL (dashed line) and CR (dash-dot line). We also show T_{CRE} (), T_{M} () and T_{MC} ().

equilibrium phase for tem peratures between T_M and $T_{M\ C}>T_M$; it is no longer a m etastable phase in this range:W e identify the equilibrium portion of the M L phase as a new equilibrium phase, and denote it by $EL_{M\ L}$; the subscript is a rem inder that the phase is associated with the M L phase. The new phase is again a liquid phase. Hence, the transition at $T_{M\ C}$ is a liquid -liquid transition and is continuous. Similarly, the transition at $T_M\ C$ below T_M , we can form ally treat the M L phase below T_M as obtained by continuation of $EL_M\ L$ below T_M , but this continuation should not be taken as a supercooled liquid below T_M , as there will be no energy barrier due to the continuous melting transition. Furtherm ore, since the liquid-liquid transition at $T_M\ C$ occurs at a tem perature higher than the m elting tem perature, this case has no relevance for studying the glass transition. Hence, we do not pursue it further. The same behavior is observed, as explained above, when a=0 and b>0.

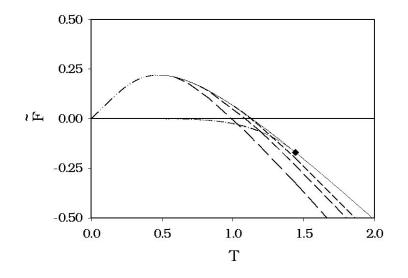


Figure 13: E ect of b on the phase diagram of the system (a = 0.5). The free energy of M L and CR does not depend on b. Three EL/SCL curves are shown corresponding to b = 0.4 (long dash), b = 0 (m edium dash) and b = 0.4 (short dash).

4.1.5 Choice of a

B ecause of the above considerations, we consider a in the range 0 < a < 1. In this range, the four-site interaction is repulsive (the system spends some energy to align two segments parallel to each other) and the ground state is the crystalline one [see Fig. 4(a)]. In this case, the model exhibits a rst order melting transition at a temperature $T_{\rm M} = T_{\rm M}$ (a) between EL, that is stable at temperatures higher than $T_{\rm M}$, and CR, that is stable for temperatures lower than $T_{\rm M}$. It can be observed that the discontinuity in the speci c heat at $T_{\rm M\,C}$ is a function of the parameters a and b. In particular, if we x b, as a increases the discontinuity gets sm aller and sm aller as long as a <0.8, and then starts growing again while the transition temperature keeps moving to lower values; the results are not show n.

The crystalline phase is an ordered one but, unlike the ground state predicted by the original F lory model [1,2] (Fig. 1), it has non zero entropy. It also satis es the G ujrati-G oldstein bounds. The I and O states disappear in the crystalline phase but this phase has non zero entropy because of the m any possible con gurations that the polymer chain can assume corresponding to di erent sequences of L and R states. The entropy of the crystalline phase goes to zero only when the tem perature goes to zero, which is consistent with the third law of therm odynam ics.

If the cooling process is such that the system can avoid crystallization at $T_{\rm M}$, the equilibrium liquid EL can be supercooled to give rise to SCL that transforms s into the m etastable liquid ML through a liquid-liquid second-order transition at $T_{\rm M\ C}$ $T_{\rm M}$ (no latent heat is associated with the transition). The m etastable liquid and the equilibrium liquid phases are somehow sim ilar. The m etastable liquid consists of a random sequence of R and L states, while the equilibrium liquid consists of a random sequence of R, L, I and O states. The presence of O and I states m akes the total energy and the entropy of the equilibrium liquid larger than those of the m etastable liquid, see Figs. 10 and 11.

4.2 Relation with the Mode-coupling Transition

We tentatively identify the critical tem perature $T_{M,C}$ of the liquid-liquid transition as them ode-coupling transition tem perature because the transition exhibits some of the features predicted by the originalm ode coupling theory at the criticalm ode-coupling transition tem perature. It should be remarked that our equilibrium investigation cannot provide any direct information about the dynam ics at $T_{M,C}$ except by inference. Hence, the connection we allude to above should only be taken as tentative, in view of the fact that them ode-coupling transition. We can only add that the mode-coupling theory is not well-understood for long polymers, and it is not clear what its predictions might be for in nite polymers that we are investigating here.

A coording to this theory, the dynamics slows down according to Eq. (3) near $T_{M C}$: The localm olecular structure freezes and only long-time cooperative jumps are allowed below this temperature. Thus, the dynamic transition is between two disordered states, very much like the therm odynamic liquid-liquid transition we observe in our calculation. Let us consider the behavior of the correlation length $_{SCL}$ of the system near the critical temperature $T_{M C}$. As $T_{M C}$ is approached from above (T ! $T_{M C}^{+}$); the correlation length $_{SCL}$ of the system the transition is continuous. It is very easy to observe from the results that there is a discontinuity in the speci c heat of the system at the transition from the supercooled liquid to the metastable liquid. Indeed, the SCL term inates at $T_{M C}$ as T ! $T_{M C}^{+}$: The disappearance of SCL is what gives rise to this divergence, which will contribute to the critical slowing down of the system. Such a critical slowing down is exhibited at the mode-coupling transition [39]; see Eq. (3).

On the other hand, M L exists at all tem peratures. Thus, there would be no divergence at $T_{M\ C}$ in the correlation length $_{M\ L}$ associated with M L . Indeed, its speci c heat remains continuous. This will imply that the dynam ics of the system should not undergo any signi cant change at the critical tem perature $T_{M\ C}$ if we approach it while heating up M L in such a way that M L is not allowed to turn into SCL. In simulation, one can investigate M L by suppressing fast relaxations that are supposed to freeze at the mode-coupling tem perature. Such

an attempt has already been made [25] where one sees no anom alous behavior at the mode-coupling temperature. Parisi and coworkers [25] while analyzing a Lennard-Jones system have observed this kind of dynamics. In their approach, the fast dynamics of the system (the one pertinent to the supercooled liquid in our model) is suppressed and only the slow dynamics of the system is taken into account. The slow dynamics is described as a relaxation process taking place in a connected network of potential energy minima. Indeed, the authors only observes an Arrhenius behavior in the relaxation time, as opposed to the Vogel-Tammann-Fulcherbehavior associated with them ode-coupling transition. E ven though the system studied by Parisi and coworkers is very dierent from the polymer system studied here, it is important to note that all the numerical results obtained in the case of the Lennard-Jones uid are in agreement with the experimental notings in non-network forming glasses and especially in glasses that are fragile according to Angell's de nition [40].

Recent experimental results obtained by Sokolov and cow orkers [41] studying polyisobutylene and polystyrene show the presence of a critical behavior only above T_{MC} along with the failure of the predictions of the mode coupling theory below the critical temperature. These authors show many similarities between the results obtained on these polymeric glasses and the ideas of the liquid-liquid transition in polymeric liquids formulated by Boyer and cow orkers [42,43]. It is worth noting that this liquid-liquid transition would manifest itself through a discontinuity in the rst derivative of the speci c heat (and not the speci c heat itself as in the present case) at the transition temperature. This makes B oyer's result very di erent from our result. The idea introduced by B oyer has been strongly criticized and is still the subject of discussion [44,45].

The second sim ilarity has to do with our choice of the parameter a, so that $T_{M\ C}$ lies above the K augment temperature T_K : This is also what is expected in the mode-coupling theory in which the transition occurs above the conventional glass transition temperature.

The third sim ilarity appears when we allow free volume in our model in Eq. 9(b), as has been done recently [29]. It is found that the free volume in the model for the case of in nite polymers vanishes identically at $T_{M,C}$, and remains zero below it. Consequently, one expects the viscosity to diverge at $T_{M,C}$.

W hile the mode coupling theory describes the transition at $T_{M\ C}$ as dynamic in nature, our results show that the transition at $T_{M\ C}$ is thermodynamic in nature. The sharp transition is due to the polymer being in nitely long, and disappears as soon as polymers become enite in size [29]. However, for polymers of reasonable sizes, there will continue to be a narrow crossover region between two phases (M L and SCL).

4.3 G round State and K auzm ann Tem perature

Below $T_{M\ C}$, the only two phases that are present are the m etastable liquid and the crystal. Above $T_{M\ C}$, the supercooled liquid, which is the continuation of the equilibrium liquid above T_M , is more stable than the m etastable liquid and coexists with the crystal. It is worth noting that the m odi ed free energies F^{e} of

both the m etastable liquid and the supercooled liquid cross over and becomes positive at some nite and non-zero temperature. Let us focus on them etastable liquid as its behavior is easy to describe since its modiled free energy \mathbf{F}^{e} remains independent of a and b. We not observe that the 2-cycle FP solution contains within its possible solutions the 1-cycle solution. We also not that the free energy of all possible 2-cycle solutions (including the 1-cycle solutions) at absolute zero are the same: $\mathbf{F}^{e} = 0$:

Because of the exact nature of our calculation, this equality of the M L and CR free energies at absolute zero is not brought about due to any approximation. Because of this equality at absolute zero, we will now consider the modied free energy F^e in the following. The CR free energy remains negative at all tem peratures and approaches zero at absolute zero. Thus, CR has nonnegative entropy. On the other hand, the ML free energy F, which is negative at higher tem peratures, becom es positive at som e interm ediate and non-zero tem perature $T_{M,0}$ and keeps increasing, as the tem perature is low ered, until the Kauzmann temperature $T_{\rm K}$ (0.48 in our model) is reached. Below $T_{\rm K}$, the ML free energy 🖻 must necessarily decrease since it must vanish at absolute zero. The maximum of \mathbb{P} corresponds to the vanishing of the entropy of the M L phase, below which the entropy must become negative [46]. Thus, the existence of the K auzm ann tem perature is a consequence of the fact that the M L free energy \mathbb{P} , once it crosses the zero at $T_{M\ 0}$, must necessarily decrease at som e lower tem perature so as to return to zero at absolute zero. The existence of the maximum in \mathbb{F}_{ML} as a function of the temperature is the root of the rapid entropy drop noted by K auzm ann [5]. The maximum at a positive T_K is forced by therm odynam ics since the larger speci c heat of M L m akes $\mathbb{F}_{M \ L}$ cross over to positive values at $T_{M\,0}$. If we had carried out our calculation in some approximation, as is the case with the calculation of G ibbs and D M arzio [8], we certainly could not draw this remarkable conclusion.

4.4 $S_{CR} > S_{SCL}$ and Entropy C risis

The crystalline phase has an entropy that is never negative. Hence, its entropy is larger than the entropy of the m etastable liquid in the tem perature interval $T_K < T < T_{eq}$, where T_{eq} is the tem perature at which the entropy of the two phases is the same (see Fig. 10 (b)). This result contrasts the common belief [17] that the entropy of a crystalline phase must always be low er than the entropy of the corresponding liquid phase, even if the latter is an equilibrium phase. Our results clearly show that there is no therm odynam ic requirement for this belief to be true. Indeed, real system s like He conform with this observation.

In order to sustain the common belief that the entropy of the liquid must always be larger than that of the crystal, it was conjectured by Kauzmann that the system must avoid the (Kauzmann) catastrophe caused as soon as the requirement S_{CR} S_{SCL} is violated. The system is supposed to avoid the catastrophe by undergoing either a spontaneous crystallization, as proposed by Kauzmann in his original paper, or an ideal glass transition [5,8,15,47]. The most important result of the present research regarding the K auzmann catastrophe is that since our calculations show that it is possible to observe $S_{C\,R} > S_{SC\,L}$ in an explicit model calculation, the existence of the catastrophe must be reinterpreted in terms of the entropy crisis corresponding to having no realizable state (negative entropy) [46]: the catastrophe happens at a temperature $T_{\rm K}$ where the entropy of the metastable liquid goes to zero and not at the temperature $T_{\rm eq}$ at which the entropy of the liquid becomes equal to the entropy of the crystal. The two temperatures coincide in the original F bry model since the entropy of the crystal is identically equal to zero below $T_{\rm M}$, see Fig. 1, while in our exact calculation, the two temperatures are di erent because the entropy of the crystal is zero only when the temperature goes to zero.

4.5 Ideal G lass Transition

The ML free energy has no physical relevance below $T_K\,$ since it corresponds to negative values of the entropy. D ecreasing the tem perature as T ! T_K^+ the entropy falls very rapidly to zero (as seen, for example, in Fig. 10 (b)). As the tem perature is decreased, the energy of the m etastable liquid cannot increase because this would correspond to a negative speci c heat. At the same time, this energy cannot decrease since there are no states with non-negative entropy (except the crystal phase, but we do not consider this possibility here) available to the system . The only conclusion that can be drawn from these observations is that for $T < T_K$, the m etastable liquid rem ains frozen in the state in which it nots itself at T_K . This describes the ideal glass transition. In our analysis, ML does not undergo any changes in its state at the glass transition, so that this transition cannot be a rst-order transition as recently proposed by Parisi and cow orkers [26 (b)].

It is interesting to notice that the energy of the m etastable liquid increases m onotonically with T and is very similar to the excitation proles for other systems like the mixed Lennard-Jones system [48] and the two states model [49].

It is also interesting to notice that our model predicts, at the K augmentation temperature, an upward discontinuity for the speci c heat. The speci c heat of the m etastable liquid is decreasing with the temperature for $T > T_{\rm K}$. This kind of behavior is in disagreem ent with m any experimental results but has been observed in computer simulations by P arisi and cow orkers [26] and experimentally (at least in some temperature interval immediately above the glass transition) in glasses formed by low molecular weight materials of very dimensionature like 1-butene [45] and the m etallic system Au-Si [40].

4.6 Flory M odel

The value a = 1 corresponds to a borderline case. A swe have shown in Fig. 4, if a is larger than 1 then the ground state is not crystalline anym ore and there are no parallel bonds at T = 0. Correspondingly, we observe from our results that as a ! 1, T_{MC} m oves to low er and low er values and eventually goes to zero

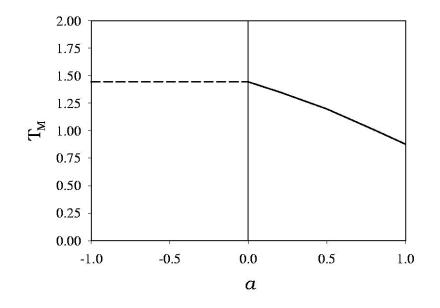


Figure 14: Dependence of the melting temperature on a. The rst-order transition line (continuous line) and the second-order transition line (dashed line) are shown.

when a goes to one. We also nd that, if we keep b xed, then as the value of a increases, the values of T_M and $T_{M,C}$ decrease and, as said above, for a 0.8, the supercooled liquid shows its own K augment the perature corresponding to the maximum in its free energy. If a becomes negative, the critical temperature moves to higher temperatures. Unlike the case of a > 0, there is a temperature interval ($T_M < T < T_{M,C}$) where the metastable liquid becomes the stable phase $E L_{M,L}$. The melting transition that is observed is a continuous transition. This aspect is in disagreement with experimental observations.

If a=b=0, as explained before, the model reduces to the F bry model of polymer melting. In this case $T_{M}=T_{M\,C}=T_{C\,R\,E}$ and the melting transition from the equilibrium liquid to the crystalline phase becomes continuous in contrast with the original calculations of F bry. It is important to notice that in this case there is no possibility to obtain a supercooled liquid since the equilibrium liquid phase disappears continuously into the crystal at T_{M} .

The solution found by F lory for the originalm odel corresponds to a tricritical solution: if we consider the melting transition present in the system, this transition is rst order for a > 0 and continuous for a < 0. In the latter case, we have $T_M = T_{CRE}$, as shown in Fig. 14.

It seems reasonable to assume that in order to be able to describe the physics

of real systems, the value of the parameter a must be chosen in the range between 0 and 0.7 while the value of b should be in the range 0.5 0.5.

4.7 Comparison with A Real System

By a proper choice of various param eters in our model, we can t the predictions of our theory with experiments. We discuss one such example below. Setting a = 0.5 and b = 0, for example, our model predicts $T_M = T_k$ ' 120=0.48. We can consider polyethylene (PE) and try to describe its therm odynamic properties using our model. The experimentally measured melting temperature of PE is T_M (PE) ' 400K. Then the model predicts T_K (PE) ' 160K. This temperature is about 40K below the experimentally determined glass transition. Since we expect the experimental glass transition to occur above the ideal glass transition because of experimental constraints, we can conclude that the prediction of our model is, at least, reasonable.

5 CONCLUSIONS

We have considered an extension of the Flory model of melting by introducing two additional interactions characterized by parameters a and b. One interaction is between a pair of parallel bonds and the second one is due to a hairpin turn. The model is de ned on a checkerboard version of the square lattice, and has been solved exactly on a Husimi cactus, which is a recursive lattice [36]. It should be recalled [36] that calculations done on a recursive lattice have been shown to be m ore reliable than conventionalm ean-eld calculations. The choice of the Husim i cactus is also in portant for the inclusion of the Gujrati-Goldstein excitations that are responsible for destroying the complete order in the crystal phase CR [10-12] in the Flory model. The method of calculation is to look for the x-point (FP) solution of the recursion relations. We need to consider 1cycle and 2-cycle FP solutions to describe the disordered phase and the crystal phase, respectively. This has required us to provide in this work the extension of the Gujrati trick [36] to calculate the free energy of the 1-cycle FP solution to the 2-cycle solution. The exact nature of the solution allows us to draw som e in portant conclusions, which would not have been drawn with the sam e force, had we obtained the solution under am biguous and/or uncontrollable approxim ations.

We have identied an equilibrium liquid phase EL at high temperatures $T_{\rm M}$. There is another liquid phase ML which exists at all temperatures, but which never becomes an equilibrium phase for appropriate choices of the parameters a and b. Below the melting temperature $T_{\rm M}$, the crystal phase CR becomes the equilibrium phase. The melting transition is usually a rst order transition with a latent heat, below which we can continue EL to give rise to the supercooled liquid phase SCL. This phase term inates at a lower temperature $T_{\rm M \ C}$, where it meets ML continuously with no latent heat. The transition at $T_{\rm M \ C}$ is a continuous liquid-liquid transition.

Both SCL and ML represent metastable phases in the system . For a metastable state to exist in Nature, its entropy must be non-negative. A negative entropy (S < 0) in m etastable states (SCL and/or ML) in plies that such states cannot exist. We have argued that the M L free energy must have a maximum at T_{K} as a function of the tem perature T; see Fig. 8. Thus, M L has non-negative entropy above T_K , but gives rise to negative entropy below T_K . We have called the appearance of S < 0 the entropy crisis, which we have used instead of the Kauzmann paradox ($S_{ML} < S_{CR}$) as the driving force behind the ideal glass transition at T_K . The ideal glass transition occurs in the m etastable liquid M L, and not in SCL, which is contrary to the conventional wisdom . The portion of $M \mathrel{\sc L}$ below T_K must be replaced by the ideal glass (see dotted thin horizontal portion below T_K in Fig. 8), which is completely inactive in that its entropy and speci c heat are both zero. The rapid drop in the entropy near the K auzm ann tem perature T_K is a direct consequence of the existence of the maximum in the M L free energy. The liquid-liquid transition at $T_{M C}$ between the twom etastable phases M L and SC L has been shown to share many sim ilarities with the critical m ode-coupling transition, even though the latter is known to be driven by dynam ics in simple uids. It should be remarked that nothing is known about this dynam ic transition in the sem i exible H am ilton walk lim it of in nite polymers.

The F bry model is shown to give rise to a continuous melting. Indeed, the melting point in the F bry model turns out to be a tricritical point in our calculation. It would be interesting to see if this conclusion can be sustained in other computational scheme.

The natural extension of this model in Eq. (9b) involves the analysis of the e ects of compressibility (taking into account voids as another species on the lattice) and of nite chain size, both in the polydisperse and in the monodisperse case. This is reported elsewhere [29,30].

We nally discuss an interesting aspect of the 2-cycle FP solution for EL/SCL observed by Semerianov [50]. The values of i_a , i_b , o_a , and o_b depend on the choice of the initial guesses used in the FP solution of the recursion relations. Thus, there are m any di erent 2-cycle solutions for EL/SCL that differ in the values of i_a , i_b , o_a , and o_b $i\!M$ hat we nd is that the product io remains the same on both sublattices for all initial guesses, and that they all give the same free energy and densities. We hope that the observation will provide some useful inform ation about the free energy landscape picture, but this requires further investigation. We hope to report on this in near future.

ACKNOW LEDGEMENTS

 ${\tt W}$ e would like to thank Sagar R ane and Fedor Sem erianov for fruitful discussions.

APPEND IX

We index the cactus levels in a slightly di erent manner here for sim plicity. If the base site of a square is indexed m, then the interm ediate and the peak sites are all indexed m + 1. The square is still called the m th square. The origin is indexed, as before, m = 0. We evaluate N $_{(m)}$, the number of sites at the m th generation of a tree rooted at the origin (m = 0). The rooted tree is only half of a complete tree. It is evidently given by:

$$N_{(m)} = 3^{m}$$
;

so that the total number of sites belonging to the rst m generations (and excluding the origin) of a rooted tree is:

$$N_{(m)}^{\text{rooted}} = \sum_{k=1}^{X^{m}} N_{(k)} = \frac{3^{m+1}}{2}$$
:

The total number of sites belonging to the rst m generations of the complete tree is then equal to twice the total number of sites belonging to the rst m generations of a rooted tree plus one since we have to consider the origin too:

$$\mathbb{N}_{m} = 2\mathbb{N}_{(m)}^{\text{rooted}} + 1 = 3^{m+1} 23$$

Let us consider now the number S $_{\mbox{(m)}}$ of the m th generation squares (m $\,$ 0) of the rooted tree. C learly we have:

$$S_{(m)} = 3^{m}$$
:

The total number of squares belonging to the rst m generations of a rooted tree (so that the maximum generation of the squares is m = 1) is:

$$S_{(m)}^{\text{rooted}} = \sum_{k=0}^{m X^{-1}} S_{(k)} = \frac{3^{m} - 1}{2}$$
:

The total number of squares belonging to the rstm generations of the complete tree is then just twice the total number of squares belonging to the rstm generations of a rooted tree:

$$\mathfrak{S}_{m} = 2 \operatorname{S}_{(m)}^{\text{rooted}} = 3^{m}$$
 1:

In order to make the cactus hom ogeneous, we must consider it to be part of a larger cactus. Consequently, both S_m and N_m must be modiled in order to take into account the presence of dangling bonds at surface sites: we consider to add half a square to each surface site. Recalling that each square contains four half-sites (a site is shared by two squares), we conclude that each square contributes two sites to the number of sites. Hence, each half-square contributes one site to the site count. Thus, we modify N_m^c by adding 1 site for each surface square. This gives for the total number of sites

$$N_m = N_m^2 + 3^m = 4 3^m 2$$
:

M odifying $\ensuremath{\mathfrak{S}}_{m-1}$ by the half-squares at the surface sites gives for the total number of squares:

$$S_m = S_{m-1} + \frac{1}{2} \quad 2 \quad N_{(m)} = 2 \quad 3^m \quad 1:$$

Now, if we consider the therm odynam ic lim it in which m ! 1 we have:

$$\frac{S_m}{N_m} ! \frac{1}{2}:$$

which is consistent with our earlier hom ogeneous hypothesis N $_{\rm S}$ = N $\,$ relating the total number of squares N $_{\rm S}$ and the total number of sites N .

Let us nally consider the total number \mathbb{B}_m of bonds in the rst m generations (m > 0) of the tree. Each square contains four bonds, and there are \mathbb{S}_m squares in this tree. Thus

$$B_m^2 = 4(3^m 1)$$
:

The modi cation of the lattice introduced above implies that we must now add half-square at each of the surface sites of the m th generations (m > 0) tree. Each half-square contributes 2 bonds. Hence

$$B_m = B_m^2 + 4 \quad 3^m = 8 \quad 3^m \quad 2$$
:

If we consider the therm odynam ic lim it in which m ! 1 we have:

$$\frac{B_{m}}{S_{m}} ! 4;$$

as expected.

References

- [1] P.J.Flory, J.Chem. Phys. 10, 51 (1942).
- [2] P.J.Fbry, Proc.R.Soc.A 234, 60 (1956).
- [3] J.F.Nagle, P.D.Gujzati and M.Goldstein, J. Phys. Chem. 88, 4599 (1984).
- [4] M.L.Huggins, Ann.N.Y.Acad.Sci.41,1 (1942).
- [5] W .Kauzmann, Chem .Rev. 43, 219 (1948).
- [6] J.Jackle, Rep. Prog. Phys. 49, 171 (1986).
- [7] P.G.Debenedetti, Metastable Liquids, Concepts and Principles (Priceton University Press, Princeton, N.J., 1996).
- [8] J.H.Gibbs and E.A.DiMarzio, J.Chem. Phys. 28, 373 (1958); 28, 807 (1958); J.Polymer Sci. 40, 121 (1963); G.Adams and J.H.Gibbs, J. Chem. Phys. 43, 139 (1965).
- [9] The G lass Transition and the Nature of the G lassy State, edited by M. Goldstein and R. Sim ha (Ann. N.Y. A cad. Sci., New York, 1976).
- [10] (a) P.D.Gujzati, J.Phys. A 13, L437 (1980); (b) P.D.Gujzati and M. Goldstein, J.Chem. Phys. 74, 2596 (1981).
- [11] P.D.Gujrati, J.Stat. Phys. 28, 241 (1982).
- [12] (a) R.G.Petschek, Phys.Rev.B 32, 474 (1985); (b) A.Baum gartner, D. Y.Yoon, J.Chem. Phys. 79, 521 (1983).
- [13] J. Suzukiand T. Izuyam a, J. Phys. Soc (Japan) 57, 818 (1988).
- [14] F.H.Stillinger, J.Chem. Phys. 88, 7818 (1988).
- [15] C.A.Angell, J.Non-Cryst. Solids 131-133, 13 (1991).
- [16] D.Kivelson, S.A.Kivelson, X.Zhao, Z.Nussinov, and G.Tarjus, Physica A 219, 27 (1995).
- [17] See articles in J.Res.NIST 102, No.2 (1997).
- [18] G.P.Johari, J.Chem. Phys. 113, 751 (2000).
- [19] F.H.Stillinger, P.G.Debenedetti, and T.M.Truskett, J.Phys.Chem.B 105, 11809 (2001).
- [20] W .G oetze, in Liquids, Freezing and the G lass Transition, edited by J.P. Hansen and D.Levesque (Plenum, New York, 1989).

- [21] U. Bengtzelius, W. Goetze and A. Sjolander, J. Chem. Phys. 77, 5915 (1984); C. A. Angell, L. Monnerie and L. M. Torell, Symp. Mater. Res. Soc. 215, 3 (1991).
- [22] W. Goetze and A. Sjolander, Rep. Prog. Phys. 55, 241 (1992).
- [23] D.J.P lazek and K.L.Ngai, M acrom olecules 24, 1222 (1991).
- [24] S.Franz and G.Parisi, Phys.Rev.Lett. 79, 2486 (1997).
- [25] L.Angelani, G.Parisi, G.Ruocco and G.Viliani, PhysRev.Lett.81, 4648 (1998); Phys.Rev.E 61, 1681 (2000).
- [26] M. Mezard and G. Parisi, Phys. Rev. Lett. 82, 747 (1999); B. Coluzzi, G. Parisi and P. Verrocchio, Phys. Rev. Lett. 84, 306 (2000).
- [27] G.I.M enon and R.Pandit, Phys.Rev.E 59, 787 (1999).
- [28] P.D.Gujrati, and A.Corsi, Phys. Rev. Lett. 87, 025701 (2001).
- [29] P.D.Gujrati, S.S.Rane, and A.Corsi, Phys.Rev.E 67, 052501 (2003).
- [30] S.S.Rane, and P.D.Gujrati, submitted for publication.
- [31] (a) P.D.Gujrati, submitted for publication; (b) P.D.Gujrati and F. Sem erianov, to be published.
- [32] In classical statistical mechanics, which is what is conventionally used to analyze m etastability, the contribution $S_{\rm trans}\left(T\right.$) to the total entropy S (T) from the translational degrees of freedom is the same for various possible phases like SCL or CR that can exist at a given temperature, and is a function only of the temperature T. This is because the kinetic energy is decoupled from the interaction energy in classical mechanics, making the translational degrees of freedom decouple from the rest β 1(a)]. Thus, the translational degrees of freedom do not have to be considered in the investigation. The di erence $S_{conf}(T)$ S(T) S_{trans}(T) can be equally well used to characterize various phases of the system ; it is known as the con gurational entropy of the system and determ ines the con gurational partition function. In lattice m odels like the one considered here, we do not have the translational degrees of freedom, and the translational entropy is zero. Hence, there is no distinction between the total entropy S (T) and the con qurational entropy $S_{conf}(T)$ in lattice models. For this reason, we will not use the subscript "conf" to denote the con gurational entropy in this work.
- [33] M. Mezard, G. Parisi and M. A. Virasoro, Spin Glass Theory and Beyond (World Scientic, Singapore, 1987).
- [34] R.B.Gri ths and P.D.Gujzati, J.Stat. Phys. 30, 563 (1983).
- [35] P.D.Gujzati, Phys. Rev. B 32, 3319 (1985).

- [36] P.D.Gujrati, Phys. Rev. Lett. 74, 809 (1995).
- [37] (a) P.D.Gujzati, Phys. Rev. A 24, 2096 (1981); (b) P.D.Gujzati, J. Chem. Phys. 98, 1613 (1993).
- [38] See for exam ple, H.W. Blote and B.Nienhuis, Phys.Rev.Lett. 72, 1372 (1994); M.T.Batchelor, J.Suzuki, and C.M.Yung, Phys.Rev.Lett. 73, 2646 (1994); J.Kondev and J.L.Jacobsen, Phys.Rev.Lett. 81, 2922 (1998).
- [39] K.Kawasaki, Ann.Phys. 61, 1 (1970).
- [40] C.A. Angell, Science 267, 1924 (1995).
- [41] A.Kisliuk, R.T.M athers and A.P.Sokolov, J.Poly.Sci. Pol. Physics 38, 2785 (2000).
- [42] R.F.Boyer, Pol.Eng.Sci. 19, 732 (1979); R.F.Boyer and R.L.M iller, M acrom olecules 17, 365 (1984).
- [43] S.S.N.Murthy, J.Poly.Sci.: Pol. Physics 31, 475 (1993).
- [44] D.J.Plazek, J.Poly. Sci.: Pol. Physics 20, 1533 (1982).
- [45] O. Yam am uro, S. Takahara, A. Inaba, T. M atsuo and H. Suga, J. Phys. Cond. M att. 6, L169 (1994).
- [46] It should be stressed at this point that the existence of a negative entropy in our exact calculation is caused by the use of the continuation and/or the use of solutions that are not the equilibrium one, i.e. solutions that do not have the lowest possible free energy F: Recall that the exact calculation of the free energy through the use of the partition function only requires that the free energy have the correct convexity property, which in this case corresponds to having a non-negative speci c heat. This rem ains true of all states in our calculation, equilibrium or not. The requirem ent that the entropy be non-negative is an additional postulate, justi ed by the obvious fact that the number of realizable con gurations be at least one. The continuation need not satisfy the entropy requirem ent, the latter being completely independent of the convexity property of the free energy. There will never be a negative entropy equilibrium solution in any exact calculation, as the equilibrium state must correspond to a number of realizable con gurations. This also means that if there is no phase transition in a model, there will be no possibility of any continuation that can then violate the entropy requirem ent. In this case, there cannot exist any K auzm ann tem perature.
- [47] M.Goldstein, J.Chem. Phys. 51, 3728 (1969).
- [48] S.Sastry, P.G.Debenedetti and F.H.Stillinger, Nature 393, 554 (1998).

[49] C.A.Angell, B.E.Richards and V.Velikov, J.Phys.Cond.M att.11, A 75 (1999).

[50] F. Sem erianov, private com munication.