M agnetic O rder and D ynam ics in Stripe-O rdered La $_2$ x Sr_xN iO $_4$

A.T.Boothroyd^{a;}, P.G.Freem an^a, D.Prabhakaran^a, M.Enderle^b, J.Kulda^b

^aD epartm ent of Physics, O xford University, O xford, O X 1 3PU, United K ingdom ^bInstitut Laue{Langevin, BP 156, 38042 G renoble C edex 9, France

A bstract

W e have studied magnetic correlations in several compositions of stripe-ordered $La_2 \times Sr_x N$ iO₄. In this paper we show how polarized-neutron scattering has helped uncover important features of the magnetic ordering and spin dynam ics. In particular, polarization analysis has enabled us (1) to characterize a spin reorientation transition, (2) to identify anisotropy gaps in the spin excitation spectrum, and (3) to investigate an anom alous dip in the spin-wave intensity suggestive of coupling between collective spin and charge excitations.

K ey words: Charge stripe order, spin waves, spin reorientation, $La_2 \times Sr_x N$ iO 4, polarized-neutron scattering PACS: 75.30 D s, 71.45 Lr, 75.30 E t, 75.30 F v

1. Introduction

The layered nickelate fam ily La_{2 x} Sr_xN iO 4 has been the focus of m any recent investigations on account of its stripe-ordered phase. This phase is characterized by the segregation of charge carriers into an ordered array of parallel lines separating antiferrom agnetic dom ains of N f^{+} (S = 1) spins [1]. Stripes represent a novel type of com plex order, and their properties have been energetically researched since the discovery of stripe order in m em bers of the copper-oxide high-T_c superconductors [2]. Experim ents to establish the basic physics of the stripe phase in m odel non-superconducting system s can help determ ine whether or not stripes play an in portant role in the m echanism of superconductivity in the cuprates.

The nature of the spin and charge order in the stripe phase in La_{2 x} $Sr_x N$ iO 4 has been characterized in detail over the doping range 0.15 x 0.5 by electron, x-ray and neutron di raction [1], and it is now of interest to explore the collective spin and charge dynam ics over the same range of com – position. From such studies one can learn about

the nature of the excited states, and hence gain insight into the m icroscopic interactions that stabilize stripe order.

In this paper we describe neutron scattering studies of the magnetic order and dynamics in a number of $La_2 \times Sr_x NiD_4$ compounds. Some of the data for the x = 0:33 and x = 0.5 systems have been reported previously [3,4]. Here we focus on results obtained with polarized neutrons, and emphasize how certain characteristic features of the data vary with composition.

2. Experim entaldetails

A lithe data presented here were collected on the IN 20 triple-axis spectrom eter at the Institut Laue-Langevin.Since its upgrade in 2001, the ux of polarized neutrons on IN 20 has increased by an order of magnitude [5]. This gain has allowed experim entalists to be more ambitious, especially with regard to inelastic scattering measurements.

IN 20 is equipped with focussing arrays of heusler crystals for both monochrom ator and analyser. Typical experiments require measurement of the spin- ip (SF) and non-spin- ip (NSF) scattering, with the neutron polarization P in the horizontal

Corresponding author. Tel.: + 44 1865 272376; fax: + 44 1865 272400.; e-m ail: a boothroyd@ physics.ox ac.uk

scattering plane either parallel or perpendicular to the scattering vector Q , or with P vertical. For the present m easurem ents the analyser was set to re ect neutrons of xed nalenergy $14.7 \,\mathrm{m\,eV}$.

Single crystals of $La_2 \times Sr_x N iO_4$ were prepared in Oxford by the oating-zone method [6]. The crystals were all rod-like with masses of 10{15 g.

3. Results

The rst studies we describe concern the di rection of the ordered magnetic moment of the Ni²⁺ spins in La_{2 x} Sr_x N iO₄. The magnetic ordering tem perature T_{SO} of the N $\dot{\text{f}}^+$ spins in the stripe phase depends on x. For the com positions reported 200K for $x = 0.275\{0.37, and T_{SO}\}$ here, T_{SO} 80K for x = 0.5. The diagonal stripe pattern is tw inned, with stripes either parallel to the [1; 1;0] or [1;1;0] directions of the tetragonal lattice (cell param eter a = 3:8 A). These are described by twodim ensionalm agnetic ordering wave vectors $Q_m =$ (;) and $(\frac{1}{2};\frac{1}{2})$ $(\frac{1}{2};\frac{1}{2})$ (;), respectively, x=2 in reciprocal lattice units. In our where samples we observed an equal population of the twin domains.

U sing polarized-neutron di raction, Lee et al [7 deduced that the ordered m om ents at low tem perature are constrained to lie in the N iO layers at an angle of 27 (x = 0.275) and 53 (x = 0.33) to the stripe direction. In the case of x = 0.33, they also found that a transition takes place on w arming through $T_{\rm SR}$ 50 K such that the spins rotate in the plane towards the stripe direction through an angle of 13.

W e have perform ed sim ilarm easurem entsto Lee et al, but on crystals with x = 0.37 and x = 0.5. The results are presented in Fig. 1, which shows the angle of the spins from the stripe direction as a function of tem perature. Like Lee et al, we are assum ing in this analysis a collinearm agnetic structure with a single canting angle, as opposed to a distribution of dom ains with di erent spin directions, the relative population of which could vary. This assumption needs to be checked out experim entally.

From Fig. 1, both x = 0.37 and x = 0.5 compounds are seen to undergo a spin reorientation transition within the N io planes, with T_{SR} 10K (x = 0.37) and 57K (x = 0.5). The transition is ratherbroad for x = 0.37. The angle through which the spins rotate is 13 (x = 0.37) and 26 (x = 0.5)

Next we discuss two characteristic features




Fig. 1. Tem perature dependence of the in-plane ordered m om ent direction in La_{2 x} Sr_xN iO 4, x = 0:37 and 0.5. The canting angle is de ned with respect to the stripe direction. Lines are visual guides.

observed in the stripe-phase spin dynamics of $La_{2 x} Sr_x NiD_4$. We refer to the energy scans shown in Fig. 2. These scans were obtained with Q xed at the two-dimensional magnetic ordering wavevector Q_m for each composition. As expected, cooperative spin excitations emerge from the Q_m wavevectors. These excitations are found to be strongly dispersive, so much so that magnetic scattering is observed at Q_m over the whole energy range shown in Fig. 2. Inter-plane correlations were observed at low energies, but were found to be negligible for E & 5m eV.

O ne feature common to all the scans shown in Fig.2 is a reduction in intensity below an energy of

7 m eV for x = 0.275 0.37, or 4 m eV for x = 0.5. This reduction is not present in energy scans made at equivalent Q_m wavevectors with a large component along the c axis (not shown). G iven that neutrons scatter from spin uctuations perpendicular to Q, these observations indicate that the intensity reduction below $4\{7 \text{ m eV} \text{ is due to the freezing out of the c-axis component of the spin } \}$

uctuations. This points to the existence of a 4{ 7m eV energy gap due to single-ion out-of-plane anisotropy.

Polarized neutrons provide a direct m ethod to check for an isotropy gaps. Below an an isotropy gap one component of the spin uctuations is frozen out, and the component involved can be identi-

ed by polarization analysis.W e m easured the SF scattering from the x = 0.33 crystal at energies of 3, 10, 15 and 26m eV, with the three-dim ensional wavevector xed at $Q_m = (1:33;1:33;1), 1=0$ or 1. For these m easurem ents the crystal was m ounted with the [1;1;0] and [0;0;1] directions in the horizontal scattering plane, and we switched the neutron polarization between three orthogonal directions: (i) P k Q_m, (ii) P ? Q_m in the scattering

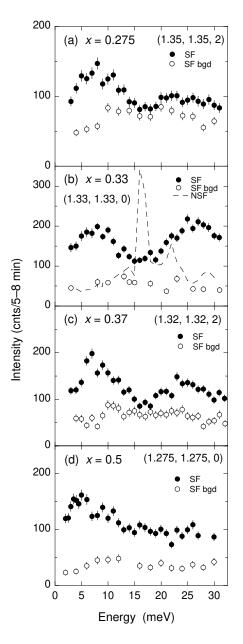


Fig. 2. Polarized-neutron scattering from stripe-ordered La_{2 x} Sr_xNiO₄. The plots show energy scans performed at the magnetic ordering wavevector appropriate to each composition. The spin- ip (SF) scattering was measured with P k Q, and the SF background was estimated from scans centred away from the magnetic excitation peak. The measurements were made at temperatures of 2K (x = 0:275;0:37), 10K (x = 0:5) and 13.5K (x = 0:33).

plane, and (iii) P vertical (i.e. parallel to the stripe direction [1; 1;0]).W e label the corresponding SF intensities I_1 , I_2 and I_3 respectively. For the case l = 0, which was used with energies of 10, 15 and 26 m eV, it can be shown that

$$\frac{I_1}{I_1} = \frac{I_2}{S_k} = \frac{S_c}{S_k};$$
(1)




Fig. 3. Ratio of the magnetic response along the crystal c axis (S_c) to that parallel to the stripe direction (S_k). The measurements were made by neutron polarization analysis at the two-dimensional magnetic zone centre $Q_m = (1:33;1:33)$. The broken line is the calculated ratio for isotropic spin wave oscillations about an ordered moment direction 53 away from the stripe direction. The reduction in $S_c=S_k$ at low energies is due to the suppression of out-of-plane spin uctuations below the 7m eV gap visible in Fig. 2 (b). The solid line is a guide to the eye.

where S_c and S_k are the components of the dynam ic magnetic response function describing spin correlations along the crystal c axis (S_c), and parallel to the stripe direction (S_k). At 3 m eV the intensity at (1:33;1:33;1) shows a slight modulation with 1 due to weak inter-layer correlations. This modulation peaks at odd 1 integers, and we made the 3 m eV m easurem ent at the 1= 1 intensity m axim um .A s far as the crystal orientation is concerned the di erence in angle between (1:33;1:33;0) and (1:33;1:33;1) is only 9, and Eq. (1) is still a very good approximation.

The results of these m easurements are shown in Fig. 3. The ratio $S_c=S_k$ is seen to be constant within experimental error for energies from 10 m eV to 26 m eV. The average value of $S_c=S_k$ in this energy range is close to that calculated on the assumption of isotropic spin uctuations about the ordered moment direction 53 away from the stripe direction [7]. The point at 3 m eV, how ever, ism uch low erthan the others, indicating a strong reduction in out-of-plane spin uctuations at this energy.

These results show that the spin uctuations are predom inantly in-plane at energies of 3 m eV, and isotropic about the direction of the ordered moment at 10 m eV and above. This con mms that the 7 m eV feature in F ig.2 (b) for the x = 0:33 crystal is the out-ofplane anisotropy gap. Sim ilar measurements on the x = 0:5 crystal show ed likew ise for the 4 m eV gap in F ig.2 (d). We searched for the inplane anisotropy gap in energy scans at wavevectors nearly perpendicular to the N iO layers, but could only put an upper lim it on the gap energy of 1 m eV.

Interestingly, the out-of-plane energy gap in undoped La₂N iO ₄ is 16m eV [8]. Together with the data reported here this indicates that the out-ofplane anisotropy decreases with doping. In a spinwave model, the gap energy varies as K_cJ_{tot} , where K_c is the anisotropy energy and J_{tot} is the total exchange energy per spin. Measurements of the overall spin-wave dispersion have established that the intra and inter-stripe N i{N i exchange interactions di er by only a factor 2 [3], so that J_{tot} decreases relatively slow ly with doping. This im – plies a very considerable decrease in K_c with doping, which has been con med by spin-wave analyses for x = 0 and 0.33, for which K_c = 0.52m eV and 0.07m eV respectively [8,3].

The other notable feature is the dip centred on 16m eV and subsequent peak near 26m eVin Figs. 2(a){ (c). This dip{peak structure occurs in an energy range where there is strong scattering from phonons, as evident in the NSF channel shown in Fig. 2(b), and so neutron polarization analysis is an important tool to isolate the m agnetic scattering.

Constant-energy scans performed at energies close to 26m eV showed that the magnetic response is signi cantly broader in Q for x = 0.275than for x = 0.33. Since the scans shown in Fig. 2 m easure the amplitude of the magnetic response it is possible that this broadening has washed-out the 26m eV peak for x = 0.275.

There is no sign of the dip {peak structure in the data for x = 0.5, and although the equivalent energy scans for x = 0 do present a super cial resemblance to those in Fig.2 the analysis in R ef. [8] showed that for the case of x = 0 the signal in this energy range is fully accounted for by a spin wave model with two anisotropy gaps. The anom alous dip {peak structure in Figs.2 (a) { (c) cannot be explained by two anisotropy gaps because, as shown above, the anisotropy gaps for $x = 0.275 \{0.37 \text{ are below 10 m eV}.$

4. D iscussion and conclusions

It is not clear at present what mechanism drives the spin reorientation in La_{2 x} Sr_xN iO₄, but our results show, (i) that the reorientation occurs for several doping levels, including compositions in which the stripes are commensurate (x = 0.33) and incommensurate (x = 0.37 and 0.5) with the host lattice, and (ii) that the angle of the ordered moment relative to the stripe direction tends to increase with doping. The reorientation transition is most prominent for x = 0.5, which has the highest charge ordering temperature (480K) and a slightly-incommensurate checkerboard charge ordering pattern below 180K [4,9].

We also cannot o er an explanation for the pronounced decrease in single-ion anisotropy with doping. W e can, how ever, com m ent on a possible origin of the dip { peak feature in the spin excitation spectrum. An explanation involving purely magnetic interactions seems unlikely since the feature is most prominent for x = 0.33, whose spins order into a two-sublattice antiferrom agnetic structure [3]. The zero- eld spin wave spectrum of such an ordering contains no gaps other than those due to an isotropy, and we have show n above that for x = 0.33 the anisotropy gaps are 7 m eVand 1 m eV. M oreover, the polarization of the spin uctuations is constant over the dip {peak region, as illustrated in Fig. 3. Hybridization with phonon excitations of the host lattice is a possibility, but seems unlikely given that the anom alous dip is absent for x = 0 and x = 0.5. Therefore, the evidence so far points to a hybridization with an excitation associated with the stripes, possibly a cooperative m otion of the charge dom ain walls.

Finally, we mention that the experiments reported here illustrate well the power of neutron polarization analysis to determ ine static and uctuating spin components, and to separate magnetic and non-magnetic scattering unambiguously.

W e thank F R.W ondre for crystal characterization data, and the EPSRC for nancial support.

References

- C.H.Chen, S-W. Cheong, and A.S.Cooper, Phys. Rev. Lett. 71, 2461 (1993); J.M. Tranquada et al, Phys. Rev. Lett. 73, 1003 (1994); H.Yoshizawa et al, Phys. Rev. B 61, R 854 (2000).
- [2] J.M. Tranquada et al, Nature 375 (1995) 561.
- [3] A. T. Boothroyd et al, Phys. Rev. B 67 (2003) 100407 (R).
- [4] P.G.Freem an et al, Phys.Rev.B 66 (2002) 212405.
- [5] J.Kulda et al, Appl. Phys. A 74 [Suppl] (2002) S246.
- [6] D. Prabhakaran et al, J. Cryst. G row th 237 (2002) 815.
- [7] S.H.Lee et al, Phys. Rev. B 63 (2001) 060405 (R).
- [8] K.Nakajim a et al, J.Phys.Soc.Jpn.62 (1993) 4438.
- [9] R.Kajim oto et al, Phys. Rev. B 67 (2003) 14511.