

Ferroquadrupole ordering and Γ_5 rattling motion in clathrate compound $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$

Yuichi Nemoto, Takashi Yamaguchi, Takenobu Horino,
Mitsuhiro Akatsu, Tatsuya Yanagisawa, and Terutaka Goto
Graduate School of Science and Technology, Niigata University, Niigata 950-2181, Japan

Osamu Suzuki
National Institute for Materials Science, 3-13 Sakura, Tsukuba 305-0003, Japan

Andreas Dönni
Department of Physics, Niigata University, Niigata 950-2181, Japan

Takemi Komatsubara
Center for Low Temperature Science, Tohoku University, Sendai 980-8578, Japan
(Dated: March 22, 2022)

Lattice effects in a cerium based clathrate compound $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ with a cubic Cr_{23}C_6 -type structure have been investigated by ultrasonic and thermal expansion measurements. Elastic softenings of $(C_{11} - C_{12})/2$ and C_{44} proportional to the reciprocal temperature $1/T$ above $T_{Q1} = 1.25$ K are well described in terms of the quadrupole susceptibility for the ground state Γ_8 quartet. A huge softening of 50 % in $(C_{11} - C_{12})/2$ and a spontaneous expansion $\Delta L/L = 1.9 \times 10^{-4}$ along the [001] direction in particular indicate the ferroquadrupole ordering of O_2^0 below T_{Q1} . The elastic anomalies associated with the antiferromagnetic ordering at $T_{N2} = 0.75$ K and the incommensurate antiferromagnetic ordering are also found. Notable frequency dependence of C_{44} around 10 K is accounted for by the Debye-type dispersion indicating a Γ_5 rattling motion of an off-center Ce ion along the [111] direction with eight fractionally occupied positions around the 4a site in a cage. The thermally activated Γ_5 rattling motion obeying a relaxation time $\tau = \tau_0 \exp(E/k_B T)$ with an attempt time $\tau_0 = 3.1 \times 10^{-11}$ sec and an activation energy $E = 70$ K dies out with decreasing temperature, and then the off-center tunneling state of Ce ion in the 4a-site cage will appear at low temperatures.

PACS numbers: 71.27.+a, 62.20.Dc, 65.40.De

I. INTRODUCTION

The 4f-electronic systems with spin and orbital degrees of freedom in rare earth compounds frequently reveal electric quadrupole orderings in addition to magnetic dipole orderings at low temperatures. The cubic compounds based on Ce^{3+} ion with a Γ_8 quartet ground state in particular have received much attention because the competitive phenomena associated with magnetic dipole, electric quadrupole and magnetic octupole degrees of freedom are expected. The direct product of $\Gamma_8 \otimes \Gamma_8$ is reduced to a direct sum $\Gamma_1 \oplus \Gamma_2 \oplus \Gamma_3 \oplus 2\Gamma_4 \oplus 2\Gamma_5$. The magnetic dipole J_x, J_y, J_z belonging to Γ_4 symmetry are order parameters for magnetic orderings. The quadrupole orderings of O_2^0, O_2^2 with Γ_3 or O_{yz}, O_{zx}, O_{xy} with Γ_5 are interesting phenomena in the Γ_8 system. We refer to CeAg exhibiting the ferroquadrupole (FQ) ordering of O_2^0 at $T_Q = 15$ K.^{1,2} CeB₆ is known as the antiferroquadrupole (AFQ) ordering of O_{xy} -type with the propagation vector of $\mathbf{k}=[111]$ at $T_Q = 3.2$ K.^{3,4} The octupole moments T_{xyz} with Γ_2 symmetry, $T_x^\alpha, T_y^\alpha, T_z^\alpha$ with Γ_4 and $T_x^\beta, T_y^\beta, T_z^\beta$ with Γ_5 may play a role in the Γ_8 system.⁵

A cerium-based ternary compound $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ with the Γ_8 ground state has received much attention because

the competition between quadrupole and magnetic orderings is expected at low temperatures.⁶ $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ crystallizes in a cubic Cr_{23}C_6 -type structure with a space group $Fm\bar{3}m$ consisting of four molecular units with 116 atoms in a unit cell.⁷ The twelve Ce sites located in cages are divided into two nonequivalent sites in crystallography. As shown in Fig. 1 the Ce ion at 4a site in a cage consisting of twelve Pd-atoms and six Ge atoms possesses point group symmetry O_h , while the Ce ion at 8c site in a cage of sixteen Pd atoms has T_d . The 4a sites form a face-centered cubic lattice, while the 8c sites make a simple cubic lattice. Inelastic neutron scattering on $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ revealed overlapping two peaks for the crystalline electric field (CEF) potentials, which correspond to magnetic dipole transitions from the Γ_8 ground quartet to the Γ_7 excited doublet at 60 K of the 4a site and from the Γ_8 ground quartet to the Γ_7 at 46 K of 8c site.⁸ The entropy obtained by low-temperature specific heat measurement on $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ also indicates the ground state Γ_8 quartet at both 4a and 8c sites.⁹

The low-temperature specific heat of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ shows a rounded small peak at $T_{Q1} = 1.25$ K and a sharp λ -peak at $T_{N2} = 0.75$ K.⁹ Magnetic susceptibility shows a clear cusp at T_{N2} , but exhibits no sign of anomaly at T_{Q1} .⁶ In addition to these experimental results, an elas-

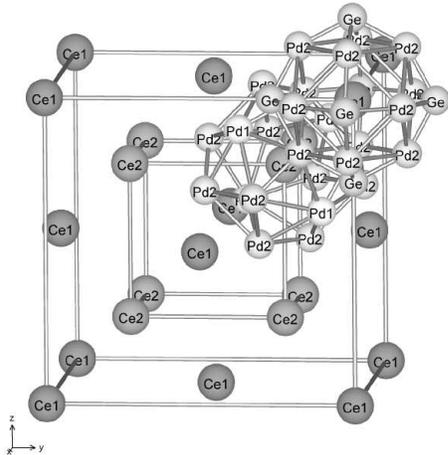


FIG. 1: Cage of 4a site with O_h symmetry consisting of Ge and Pd2 atoms and cage of 8c site with T_d of Pd1 and Pd2 atoms in clathrate compound $Ce_3Pd_{20}Ge_6$. The 4a site Ce2 forms a simple cubic lattice, while 8c site Ce1 makes a face centered cubic one. The ferroquadrupole ordering below T_{Q1} is relevant for the 8c sites and the antiferromagnetic ordering below T_{N2} occurs at 4a sites. The Γ_5 rattling motion originates from the off-center Ce1 atom in 4a-site cage.

tic softening of $(C_{11} - C_{12})/2$ in our preliminary paper suggests that the paramagnetic phase I transforms to the FQ phase II at T_{Q1} and successively changes to the antiferromagnetic (AFM) phase III at T_{N2} .¹⁰ The neutron scattering on $Ce_3Pd_{20}Ge_6$ reveals a paramagnetic state of Ce ions at both 4a and 8c sites even in phase II between T_{Q1} and T_{N2} . The AFM ordering in phase III with a propagation vector $\mathbf{k}_1 = [001]$ for cerium ions at 4a site is observed below T_{N2} .¹¹ Even in phase III below T_{N2} , the 8c site still remains to be the paramagnetic state. The AFM ordering with incommensurate structure at 8c site appears only below $T_N^* = 0.45$ K.

The clathrate compounds exhibiting the rattling motion or off-center motion in a cage have received attention because their remarkable reduction of thermal conductivity is favorable for application to thermoelectric device with a high figure of merit.¹² The ultrasonic waves are scattered by the rattling motion in an over-sized cage of a semiconductor $Sr_8Ga_{16}Ge_{30}$ and a filled skutterudite compound $PrOs_4Sb_{12}$.^{13,14} The off-center tunneling motion of OH ion doped in NaCl gives rise to elastic softening at low temperatures.¹⁵ The rattling motion in the present compound $Ce_3Pd_{20}Ge_6$ with clathrate structure has not been reported so far.

In the present paper we show ultrasonic measurements on $Ce_3Pd_{20}Ge_6$ in order to examine lattice effects associated with the quadrupole ordering and rattling motion in the system. The thermal expansion measurement is also employed to detect the spontaneous distortion be-

low T_{Q1} . In Sec. II, the experimental procedure and apparatus are described. The results of the elastic constant, magnetic phase diagram, thermal expansion are presented in Sec. III. The ultrasonic dispersion due to rattling motion is also argued in Sec. III. In Sec. IV, we present concluding remarks.

II. EXPERIMENT

Single crystals of $Ce_3Pd_{20}Ge_6$ used in the present measurements were grown by a Czochralski pulling method. We have made the ultrasonic velocity measurements using an apparatus consisting of a phase difference detector. Piezoelectric plates of $LiNbO_3$ for the ultrasonic wave generation and detection are bonded on plane parallel surfaces of sample. The x -cut plate of $LiNbO_3$ is available for transverse ultrasonic waves and the $36^\circ y$ -cut plate is for longitudinal waves. The ultrasonic velocity v was measured by fundamental frequencies of 10 MHz and overtone excitations of 30, 50 and 70 MHz. In the estimation of the elastic constant $C = \rho v^2$, we use the mass density $\rho = 10.254$ g/cm³ for $Ce_3Pd_{20}Ge_6$ with a lattice parameter $a = 12.457$ Å.⁶

A homemade ³He-refrigerator equipped with a superconducting magnet was used for low-temperature measurements down to 450 mK in magnetic fields up to 12 T. A ³He-⁴He dilution refrigerator with a top-loading probe was used for the ultrasonic measurements in low-temperature region down to 20 mK in fields up to 16 T. Low input-power condition provides the low-temperature ultrasonic measurements free from a self-heating effect in the ultrasonic transducers. The sample length as a function of temperature or applied magnetic field was measured precisely by a capacitance dilatometer in the ³He-refrigerator.

III. RESULTS AND DISCUSSIONS

A. Temperature dependence of the elastic constants

The elastic constants of C_{11} and $C_L = (C_{11} + C_{12} + 2C_{44})/2$ of $Ce_3Pd_{20}Ge_6$ in Fig. 2 were measured by the longitudinal ultrasonic waves with frequencies 10 MHz propagating along the $[100]$ and $[110]$ directions, respectively. The elastic constant $(C_{11} - C_{12})/2$ of $Ce_3Pd_{20}Ge_6$ in Fig. 3 was measured by the transverse ultrasonic wave of 10 MHz propagating along the $[110]$ direction polarized to the $[1\bar{1}0]$ one. The elastic constant C_{44} of $Ce_3Pd_{20}Ge_6$ in Fig. 3 was determined by the transverse wave of 30 MHz propagating along $[100]$ polarized to $[010]$. The bulk modulus $C_B = (C_{11} + 2C_{12})/3$ in Fig. 2 was calculated by C_{11} in Fig. 2 and $(C_{11} - C_{12})/2$ in Fig. 3.

It is remarkable that $(C_{11} - C_{12})/2$ exhibits a huge softening of 50% with decreasing temperature down to $T_{Q1} = 1.25$ K. In phase II below T_{Q1} the ultrasonic echo

signal of the $(C_{11} - C_{12})/2$ mode completely disappears due to a marked ultrasonic attenuation. The softening of the longitudinal C_{11} and C_L modes in Fig. 2 originates from the softening of $(C_{11} - C_{12})/2$, because C_{11} and C_L involve $(C_{11} - C_{12})/2$ in part. The softening of $(C_{11} - C_{12})/2$ above T_{Q1} and the spontaneous tetragonal distortion below T_{Q1} , that will be shown in Sec. III D, provide evidence for the FQ ordering in phase II. The C_{44} in Fig. 3 also exhibits a softening of 2.5% down to T_{Q1} . The low-temperature behavior of C_{11} and C_{44} shown in insets of Figs. 2 and 3 indicates the transition to the FQ phase II at T_{Q1} and successive transition to the AFM phase III at $T_{N2} = 0.75$ K. On the other hand, C_B shows monotonic increase with decreasing temperature.

Neutron scattering on $Ce_3Pd_{20}Ge_6$ revealed the paramagnetic state for Ce ions at both 4a and 8c sites in phase II, which is consistent with the present scenario of the FQ ordering at 8c site in phase II below T_{Q1} .¹¹ The AFM ordering in phase III at 4a site below T_{N2} has been detected by the neutron scattering. It has been proposed that the inter-site quadrupole interaction among 8c sites brings about the FQ ordering at 8c sites in phase II and Ce ions at 4a sites still remain to be the para-state even in phase II. The inter-site magnetic interaction among 4a sites gives rise to the AFM ordering in phase III below T_{N2} . The magnetic ordering at 8c sites appears only below 0.4 K. We discuss about this transition in the following Sec. III C.

B. Quadrupole susceptibility

In order to analyze the elastic softening of $(C_{11} - C_{12})/2$ and C_{44} in $Ce_3Pd_{20}Ge_6$ of Fig. 3, we introduce the coupling of the quadrupole $O_{\Gamma\gamma}$ of Ce ions to the elastic strain $\varepsilon_{\Gamma\gamma}$ as¹⁶

$$H_{QS} = - \sum_i g_{\Gamma} O_{\Gamma\gamma}(i) \varepsilon_{\Gamma\gamma}, \quad (1)$$

where the summation \sum_i takes over Ce ions in unit volume and g_{Γ} is a coupling constant. The inter-site quadrupole interaction mediated by phonons and conduction electrons is written in a mean field approximation as

$$H_{QQ} = - \sum_j g'_{\Gamma} \langle O_{\Gamma\gamma} \rangle O_{\Gamma\gamma}(j), \quad (2)$$

where $\langle O_{\Gamma\gamma} \rangle$ denotes a mean field of the quadrupole and g'_{Γ} means a coupling constant for the inter-site quadrupole interaction. By differentiating the total free energy consisting of 4f-electron and lattice parts with respect to the elastic strain $\varepsilon_{\Gamma\gamma}$, we obtain the temperature dependence of the elastic constant $C_{\Gamma}(T)$ as¹⁶

$$C_{\Gamma}(T) = C_{\Gamma}^0 - \frac{N g_{\Gamma}^2 \chi_{\Gamma}(T)}{1 - g'_{\Gamma} \chi_{\Gamma}(T)}. \quad (3)$$

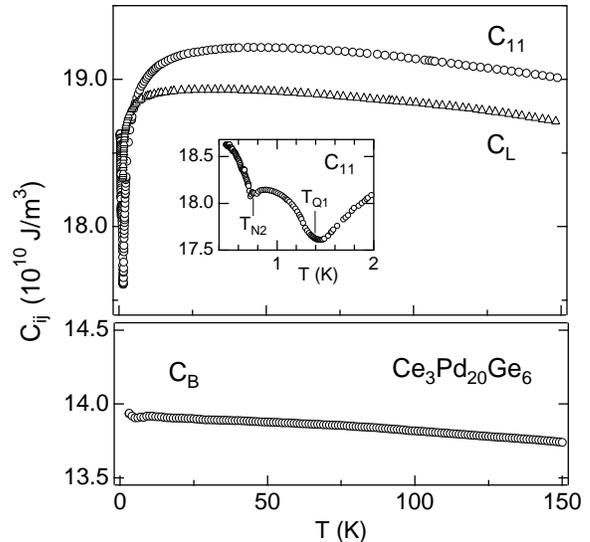


FIG. 2: Temperature dependence of the elastic constants C_{11} , C_L and the bulk modulus C_B of $Ce_3Pd_{20}Ge_6$. Inset shows the anomalies of C_{11} around the ferroquadrupole transition $T_{Q1} = 1.25$ K and the antiferromagnetic transition $T_{N2} = 0.75$ K.

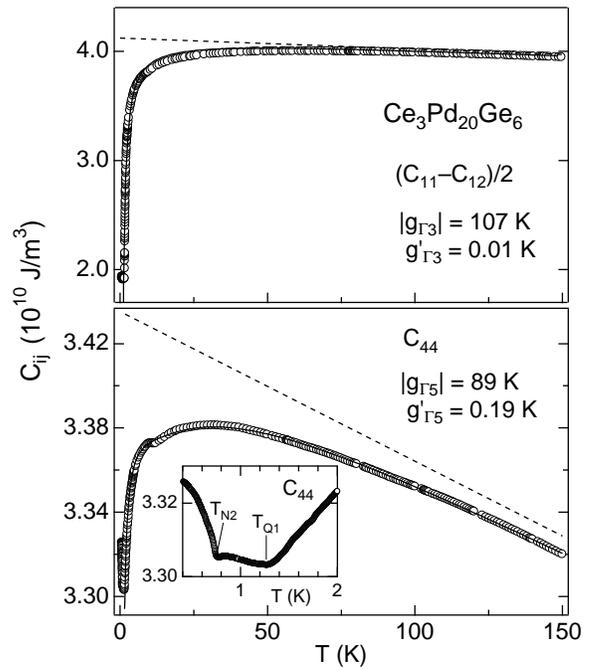


FIG. 3: Temperature dependence of the elastic constants $(C_{11} - C_{12})/2$ and C_{44} corresponding to shear waves in $Ce_3Pd_{20}Ge_6$. Inset shows the anomalies of C_{44} around the ferroquadrupole transition $T_{Q1} = 1.25$ K and the antiferromagnetic transition $T_{N2} = 0.75$ K. Solid lines are the calculation by the quadrupole susceptibility for the Γ_8 ground state and Γ_7 state at 46 K of Ce ions. The broken lines were back ground C_{Γ}^0 as shown in the text. A shoulder in C_{44} around 30 K means the ultrasonic dispersion due to the Γ_5 rattling motion.

Here $C_{\Gamma}^0(T)$ denotes a background elastic constant without the quadrupole-strain interaction and N is the number of Ce ions in unit volume. The quadrupole susceptibility of $\chi_{\Gamma}(T)$ in Eq. (3) is written as

$$-g_{\Gamma}^2 \chi_{\Gamma}(T) = \langle \frac{\partial^2 E_i}{\partial \varepsilon_{\Gamma\gamma}^2} \rangle - \frac{1}{k_B T} \{ \langle (\frac{\partial E_i}{\partial \varepsilon_{\Gamma\gamma}})^2 \rangle - \langle \frac{\partial E_i}{\partial \varepsilon_{\Gamma\gamma}} \rangle^2 \} (4)$$

where E_i is a second-order perturbation energy with respect to $\varepsilon_{\Gamma\gamma}$ for CEF state.¹⁶ The first part in right hand of Eq. (4) corresponds to the Van Vleck-term and the second part to the Curie term. The Ce ions at both 4a and 8c sites in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ have the Γ_8 ground state, while the Γ_7 state has excited energies of 46 K at 8c site and 60 K at the 4a site. As was already mentioned, the neutron scattering revealed that the FQ ordering of 8c sites occurs at $T_{Q1} = 1.25$ K and the AFM ordering of 4a sites appears at $T_{N2} = 0.75$ K. These facts indicate that the inter-site quadrupole interaction of Eq. (2) among the Ce ions at 8c sites dominates the softening of $(C_{11}-C_{12})/2$ as a precursor of the FQ ordering at T_{Q1} . In the following analysis we simply assume the quadrupole-strain interaction of Eq. (1) and quadrupole interaction of Eq. (2) for the 8c site with the CEF splitting of Γ_8 (0 K) and Γ_7 (46 K).

The solid lines for $(C_{11} - C_{12})/2$ and C_{44} with Eq. (3) in Fig. 3 reproduce well the softening in paramagnetic phase I above T_{Q1} . It should be noted that the softening above T_{Q1} proportional to the reciprocal temperature $1/T$ originates from the Curie term of Eq. (4). The coupling constants were determined to be $|g_{\Gamma 3}| = 107$ K, $g'_{\Gamma 3} = 0.01$ K for $(C_{11} - C_{12})/2$ and $|g_{\Gamma 5}| = 89$ K, $g'_{\Gamma 5} = 0.19$ K for C_{44} . The background $(C_{11}^0 - C_{12}^0)/2 = (4.12 - 0.001T) \times 10^{10}$ J/m³ and $C_{44}^0 = (3.44 - 0.0007T) \times 10^{10}$ J/m³ indicated by broken lines in Fig. 3 was used. The positive value of $g'_{\Gamma 3} > 0$ are consistent with the FQ ordering in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$. A shoulder like anomaly in C_{44} around 10 K results from ultrasonic dispersion that is caused by a rattling motion of the rare-earth ion at 4a site in an oversized cage of Fig. 1. We discuss about this remarkable behavior in Sec. III E.

C. Magnetic phase diagram

In order to examine the magnetic phase diagrams of the FQ and AFM orderings in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$, we have made the low-temperature ultrasonic measurements of C_{11} , C_{44} and $(C_{11} - C_{12})/2$ under magnetic fields. The softening of C_{11} of Fig. 4 reduces with increasing fields applied along the [001] direction parallel to the propagation direction of longitudinal wave. The FQ transition points T_{Q1} indicated by downward arrows in Fig. 4 shift to higher temperatures and become indistinct in high fields up to 6 T. In Fig. 5, the FQ transition points T_{Q1} also shift to higher temperatures accompanied by reduction of the softening in C_{44} with increasing applied fields along the [001] direction.

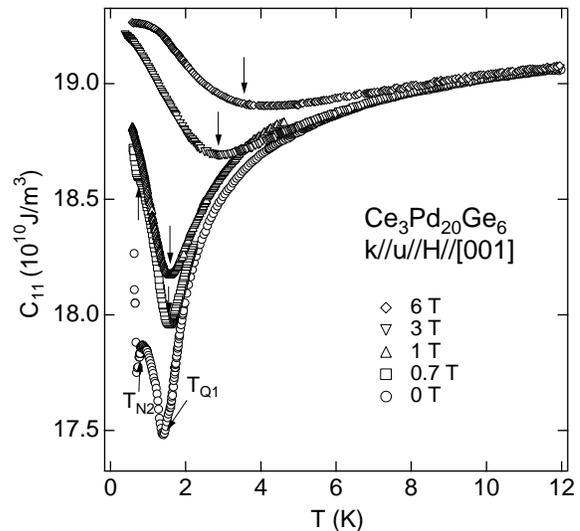


FIG. 4: Low-temperature behavior of C_{11} of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ under magnetic fields along the [001] direction. Downward arrows indicate the ferroquadrupole ordering temperature T_{Q1} and upward arrow means the antiferromagnetic ordering temperature T_{N2} .

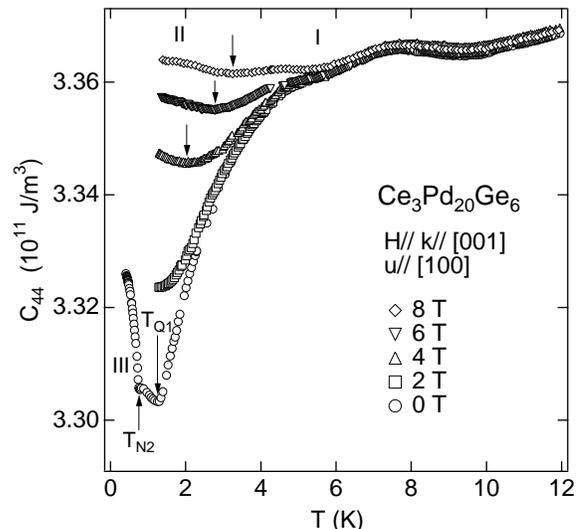


FIG. 5: Low-temperature behavior of C_{44} of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ under magnetic fields along [001]. Downward arrows indicate the ferroquadrupole ordering temperature T_{Q1} and upward arrow means the antiferromagnetic ordering temperature T_{N2} .

In Figs. 6 and 7, we show the field dependence of $(C_{11} - C_{12})/2$ applying fields along the [001] and [110] directions, respectively. In zero magnetic field, the $(C_{11} - C_{12})/2$ mode exhibits the considerable softening of 50% and the strong ultrasonic attenuation losing the echo signal in the vicinity of the FQ transition $T_{Q1} = 1.25$ K. The magnitude of the softening decreases abruptly with increasing fields along both [001] and [110] directions.

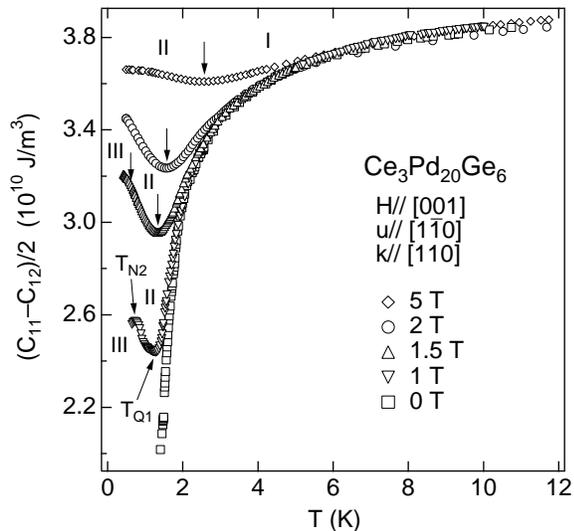


FIG. 6: Low temperature behavior of $(C_{11} - C_{12})/2$ of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ under magnetic fields along the $[001]$ direction. The successive phase transitions I-II-III are indicated by arrows.

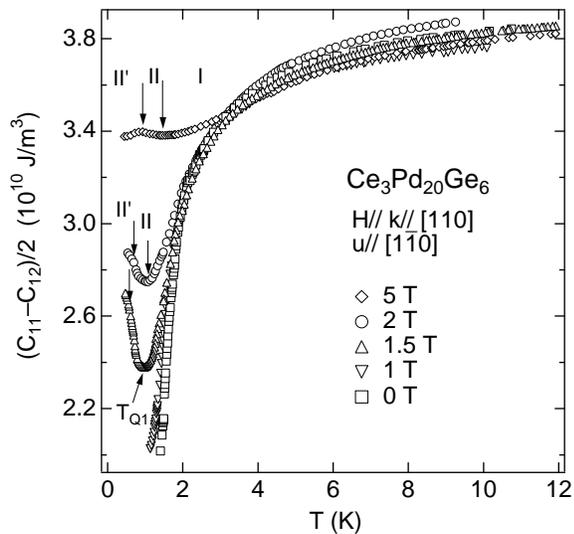


FIG. 7: Low temperature behavior of $(C_{11} - C_{12})/2$ of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ under magnetic fields along the $[110]$ direction. The successive phase transitions I-II-II' are indicated by arrows.

In magnetic fields, clear minima of $(C_{11} - C_{12})/2$ corresponding to the transitions T_{Q1} from the paramagnetic phase I to the FQ phase II shift to higher temperatures. Only broad round anomalies around T_{Q1} have been observed in high fields of 5 T. This behavior of T_{Q1} is similar to the results of the FQ ordering accompanied by the soft C_{44} mode in HoB_6 .¹⁷ The Neel temperature T_{N2} in Fig. 6 shifts slightly to lower temperatures with increasing magnetic fields. In Fig. 7 the anomalies associated with the

transition between phase II and II' below T_{Q1} have been found.

For the investigation of low-temperature and high-field behavior in FQ II and AFM III phases, we have measured field dependence of the C_{44} and $C_L = (C_{11} + C_{12} + 2C_{44})/2$ employing the dilution refrigerator. In Fig. 8 we show C_{44} versus H at 30 mK in fields up to 12 T applied along $[001]$. Inset of Fig. 8 is expanded view below 2.5 T. An anomaly of the phase II-III boundary at 2.1 T indicated by a vertical line has been observed. Furthermore, several anomalies at 0.5, 1.2 and 1.6 T associated with sub-phases of the phase III have been found. It should be emphasized that appreciable hysteresis phenomena between increasing and decreasing field sequences have been found only in phase III.

In Fig. 9 we show the low-temperature field dependence of the C_L in fields up to 16 T applied along $[110]$. Low-field behavior below 2.5 T is shown in inset of Fig. 9. We have observed a new phase boundary around 8.2 T in phase II, which is probably a sub-phase of the FQ phase II. However, this phase boundary is absent in fields along $[001]$ as shown in Fig. 8. At low field in phase III, we have found several anomalies in C_L of Fig. 9 showing a hysteresis behavior. As can be seen in inset of Fig. 9, this hysteresis becomes pronounced with decreasing temperature. These sub-phases with hysteresis behavior in phase III in magnetic fields along both $[001]$ and $[110]$ are well consistent with the results of neutron scattering experiments that detect weak incommensurate magnetic Bragg peaks with a propagation vector $\mathbf{k}=[0\ 0\ 1-\tau]$, ($\tau \sim 0.06$) at 8c site.¹¹

The magnetic phase diagrams of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ in Figs. 10 and 11 are obtained in fields along the $[001]$ and $[110]$ directions, respectively. We present the results of the ultrasonic measurements together with the results of thermal expansions in Sec. III D. It is of importance that the FQ phase II is stabilized in fields for the $[001]$ direction in Fig. 10 and the $[110]$ direction in Fig. 11. The FQ sub-phase II' was added to the phase diagram and the upper limit at 8.2 T of the phase II' newly determined in fields along $[110]$ of Fig. 11. However, the FQ sub-phase is absent in fields along $[001]$ of Fig. 10. This result indicates strong anisotropy of the quadrupole interaction of O_2^0 in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$.

The series of $\text{R}_3\text{Pd}_{20}\text{X}_6$ compounds usually show two successive AFM orderings of 8c site at T_{N1} with a propagation vector $\mathbf{k}_1 = [111]$ and of 4a site at $T_{N2} (< T_{N1})$ with $\mathbf{k}_2 = [001]$, $\text{Nd}_3\text{Pd}_{20}\text{Ge}_6$ ($T_{N1} = 1.75 \text{ K}$, $T_{N2} = 0.58 \text{ K}$)¹⁸, $\text{Nd}_3\text{Pd}_{20}\text{Si}_6$ ($T_{N1} = 2.4 \text{ K}$, $T_{N2} = 0.7 \text{ K}$)¹⁹, $\text{Tb}_3\text{Pd}_{20}\text{Si}_6$ ($T_{N1} = 10.2 \text{ K}$, $T_{N2} = 4.1 \text{ K}$)²⁰, $\text{Dy}_3\text{Pd}_{20}\text{Si}_6$ ($T_{N1} \sim 5.8 \text{ K}$, $T_{N2} \sim 1.8 \text{ K}$)²¹ and so on. One can reasonably expect that the transition temperature T_{N1} at 8c site is always higher than T_{N2} at 4a site since the distance $\sim 6.2 \text{ \AA}$ between rare-earth ion of 8c site is much shorter than the one $\sim 8.8 \text{ \AA}$ of 4a site. In the present $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$, at first the FQ ordering at 8c site with a structural change from cubic lattice to tetragonal one occurs at $T_{Q1} = 1.25 \text{ K}$. Therefore, the AFM

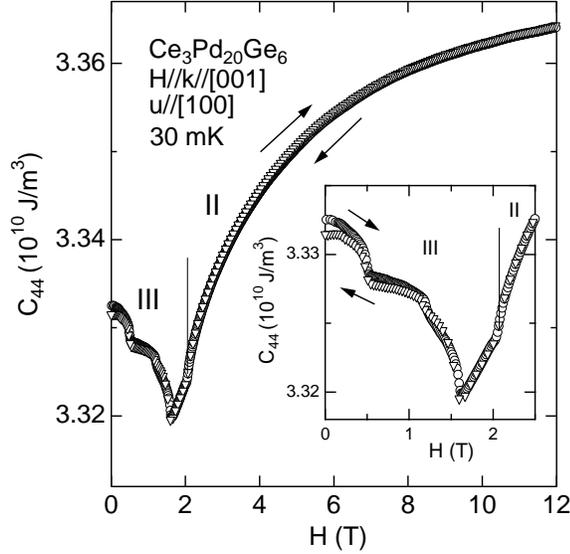


FIG. 8: Field dependence of the C_{44} at 30 mK in fields along $[001]$ up to 12 T. Inset is expanded view below 2.5 T indicating the magnetic transitions.

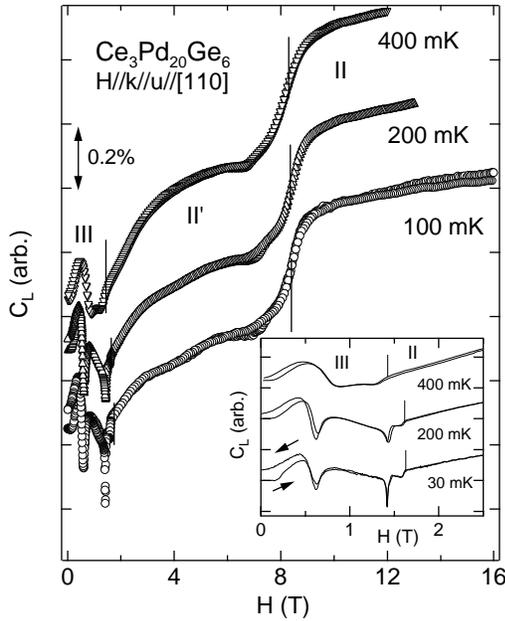


FIG. 9: Field dependence of the $C_L = (C_{11} + C_{12} + 2C_{44})/2$ at various temperatures in fields along $[110]$ up to 16 T. Inset is expanded view below 2.5 T indicating the magnetic transitions

ordering at 8c site is hard to take place because the favorable propagation vector $\mathbf{k}_1 = [111]$ of 8c site does not match to the tetragonal lattice in phase II. In other words, the AFM ordering at 8c site is replaced by the FQ ordering in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$. While, the AFM ordering of 4a site with a propagation vector $\mathbf{k}_2 = [001]$ is easy to

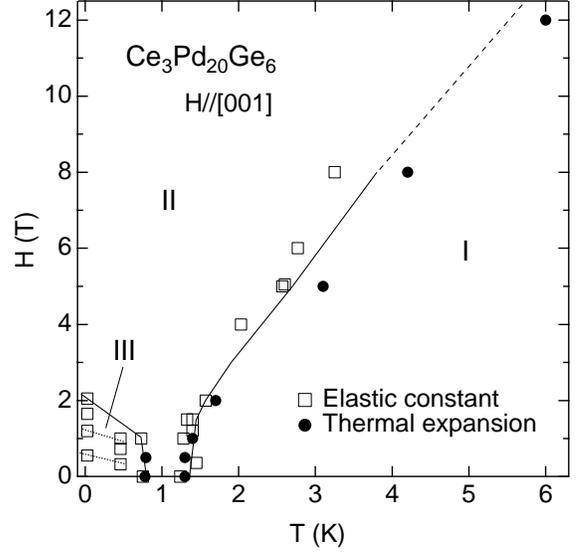


FIG. 10: Magnetic phase diagram of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ under fields along the $[001]$ direction. The boundary from paramagnetic phase I to the ferroquadrupole phase II shifts to higher temperatures with increasing fields, while the boundary from phase II to the antiferromagnetic phase III shifts to lower temperatures in fields.

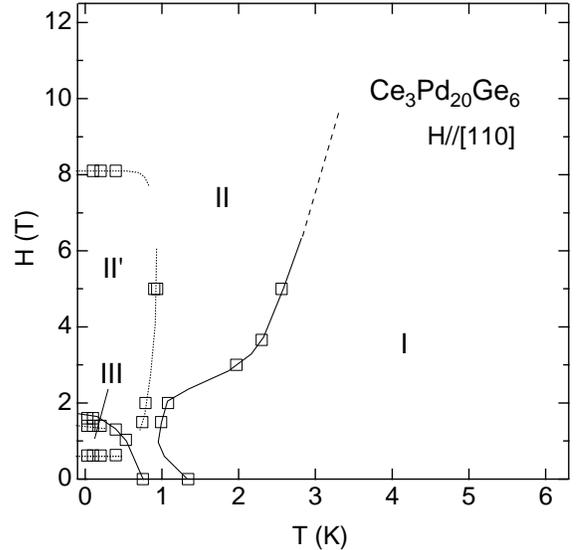


FIG. 11: Magnetic phase diagram of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ under fields along the $[110]$ direction. The sub-phase II' exists in the AFQ phase II.

occur even in tetragonal structure below T_{N2} . Neutron experiments detected large enough value of saturation cerium moments $\mu(4a) = (1.1 \pm 0.1)\mu_B/\text{Ce}$ that is expected from the ground state quartet Γ_8 perpendicular to the $\mathbf{k}_1 = [001]$ in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ far below T_{N2} at 50 mK.¹¹

D. Thermal expansion

In order to examine the structural change due to the FQ ordering at $T_{Q1} = 1.25$ K, we have measured the thermal expansion along the [001] direction in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$. The sample lengths along the [001] and [111] directions are written by the symmetry strains as $(\Delta L/L)_{[001]} = \varepsilon_{zz} = \varepsilon_B/3 + \varepsilon_u/\sqrt{3}$ and $(\Delta L/L)_{[111]} = \varepsilon_B/3 + 2(\varepsilon_{yz} + \varepsilon_{zx} + \varepsilon_{xy})/3$. Here, $\varepsilon_B = \varepsilon_{xx} + \varepsilon_{yy} + \varepsilon_{zz}$ is a volume strain with Γ_1 symmetry, $\varepsilon_u = (2\varepsilon_{zz} - \varepsilon_{xx} - \varepsilon_{yy})/\sqrt{3}$ is a tetragonal strain with Γ_3 and ε_{xy} is a shear strain with Γ_5 . The length along [001] in Fig. 12 shows a monotonous decrease with decreasing temperature in paramagnetic phase I above T_{Q1} and abruptly expands about $\Delta L/L = 1.9 \times 10^{-4}$ below T_{Q1} . The thermal expansion along [001] in phase II and the huge softening of 50% in $(C_{11} - C_{12})/2$ of Fig. 3 indicate the O_2^0 -type FQ ordering accompanied by the structural transition from cubic lattice to tetragonal one with the spontaneous strain $\langle \varepsilon_u \rangle$ in phase II. This spontaneous strain is proportional to the order parameter as $\langle \varepsilon_u \rangle = Ng_{\Gamma_3} \langle O_2^0 \rangle / (2(C_{11}^0 - C_{12}^0))$ in mean-field approximation. Below $T_{N2} = 0.75$ K, the $\Delta L/L$ along [001] slightly shrinks. Inset of Fig. 12 is expanded view of $\Delta L/L$ and the coefficient of the thermal expansion α at low temperatures. A sharp anomaly in the coefficient α has been found at the FQ transition T_{Q1} .

Measurements of $\Delta L/L$ versus T in various magnetic fields parallel to [001] are shown in Fig. 13. The magnitude of the expansion $\Delta L/L$ in fields exhibits noticeable increase up to $\Delta L/L = 2.5 \times 10^{-4}$ compared with that in zero magnetic field. The sharp increase of $\Delta L/L$ at the

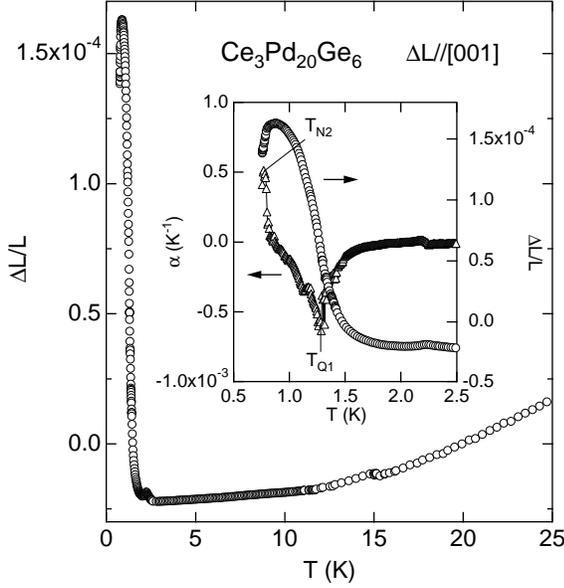


FIG. 12: Thermal expansion $\Delta L/L$ in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$. Inset shows the thermal expansion coefficient α and thermal expansion $\Delta L/L$ at low temperatures.

transition point to the FQ phase II has been observed in low magnetic fields below 1 T. On the other hand, the gradual increase in the thermal expansion $\Delta L/L$ above 5 T up to 12 T indicates an obscure character of the I-II phase boundary in high fields. This is consistent with the fact that the elastic constants in fields of Figs. 4, 5, 6 and 7 show obscure transitions in fields. This behavior is similar to the liquid-gas transition near the critical end point under hydrostatic pressures.

The thermal expansion along the [001] direction in fields parallel to [001] and the considerable softening of $(C_{11} - C_{12})/2$ of 50% in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ strongly suggests that the order parameter of the FQ ordering in phase II is O_2^0 with Γ_3 symmetry. The relatively small softening of 2.5% in C_{44} in Fig. 3 means that the quadrupole of O_{xy} -type with Γ_5 is irrelevant for the transition at T_{Q1} . The thermal expansion of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ along [111] is required to examine an interplay of the spontaneous strain ε_{xy} for the phase II. We refer to our recent study of the FQ transition in HoB_6 and the phase IV in $\text{Ce}_x\text{La}_{1-x}\text{B}_6$ ($x=0.75, 0.70$),^{17,22} where the trigonal strain $\varepsilon_{yz} = \varepsilon_{zx} = \varepsilon_{xy}$ plays a significant role and the tetragonal strain ε_u is irrelevant. These facts are well consistent with the pronounced elastic softening in C_{44} of 70% in HoB_6 and of 31% in $\text{Ce}_x\text{La}_{1-x}\text{B}_6$ ($x=0.75, 0.70$).

E. Ultrasonic dispersion of C_{44}

The C_{44} mode associated with the elastic strain $\varepsilon_{yz}, \varepsilon_{zx}, \varepsilon_{xy}$ of Γ_5 symmetry of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ in Figs. 3 and 5 exhibits a shoulder like anomaly around 10 K in addition to the characteristic softening due to the quadrupole

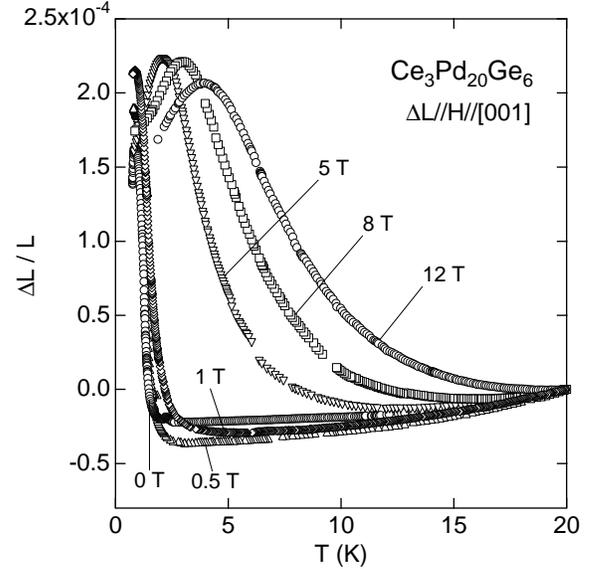


FIG. 13: Thermal expansion $\Delta L/L$ along [001] in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ under fields up to 12 T along the [001] direction.

lar coupling above $T_{Q1} = 1.25$ K. It should be noted that this anomaly is absent for the $(C_{11} - C_{12})/2$ mode associated with Γ_3 elastic strain ε_v and the bulk modulus C_B with Γ_1 volume strain ε_B . In order to examine the origin of this anomaly, we have measured the frequency dependence of C_{44} from 10 MHz up to 250 MHz. The elastic constant C_{44} of Fig. 14(a) exhibits shoulders showing remarkable frequency dependence. An increase in ultrasonic attenuation around shoulder has also been found, but not discussed here. We describe this frequency dependence of the elastic constant $C_{44}^D(\omega)$ in terms of Debye-type dispersion as

$$C_{44}^D(\omega) = C_{44}^D(\infty) - \frac{C_{44}^D(\infty) - C_{44}^D(0)}{1 + \omega^2\tau^2}, \quad (5)$$

where $C_{44}^D(\infty)$ and $C_{44}^D(0)$ are the elastic constants of high frequency limit and low frequency one, respectively. Here ω is an angular frequency of the ultrasonic wave and τ means the relaxation time of the system. In fittings of Fig. 14(b), we take into account the superposition of two susceptibilities by the quadrupole one of Eq.(3) and the Debye-type dispersion of Eq.(5) as $C_{44} = C_{44}^Q + C_{44}^D(\omega)$. The inflection points around 10 K in C_{44} indicated by arrows in Fig. 14(a) mean the temperatures where the τ coincides with the ω as $\omega\tau = 1$. The ultrasonic attenuation is expected to be maximum at the temperatures for $\omega\tau = 1$. The solid lines of Fig. 14(b) being the calculations with Eq. (5) well reproduce the experimental results of Fig. 14(a). The relaxation time obeying the Arrhenius-type temperature dependence $\tau = \tau_0 \exp(E/k_B T)$ with the attempt time $\tau_0 = 3.1 \times 10^{-11}$ sec and the activation energy $E = 70$ K has been determined. The parameter of $\Delta C = C_{44}^D(\infty) - C_{44}^D(0) = 0.004 \times 10^{10}$ J/m³ is used.

The ultrasonic dispersion due to electron thermal hopping has already found in the inhomogeneous valence fluctuation compounds of Sm_3X_4 ($\text{X}=\text{Se}, \text{Te}$), $\text{Yb}_4(\text{As}_{0.71}\text{Sb}_{0.29})_3$ ²³ and $\text{Sr}_{12}\text{Ca}_2\text{Cu}_{24}\text{O}_{41}$ ²⁴. It is remarkable that the very slow relaxation time τ and extremely low activation energy E for $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ are exceptional as compared to those of charge fluctuation compounds Sm_3Se_4 ²⁵ and Sm_3Te_4 ²⁶, $\tau_0 \sim 2.5 \times 10^{-13}$ sec and $E \sim 1600$ K, and $\text{Sr}_{12}\text{Ca}_2\text{Cu}_{24}\text{O}_{41}$, $\tau_0 = 1.01 \times 10^{-13}$ sec and $E = 1900$ K.²⁴ This discrepancy of the order of τ_0 and E between the present $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ and the charge fluctuation compounds indicates that thermally activated rattling motion of heavy mass particle, which is probably rare-earth ion in a cage, gives rise to the ultrasonic dispersion in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$.

Glass materials and charge fluctuation compounds exhibit frequently the ultrasonic dispersion, which results from a thermally activated motion in a double- or multi-well potential. The compounds such as Sm_3X_4 ($\text{X}=\text{S}, \text{Se}, \text{Te}$) with different valence of Sm^{2+} and Sm^{3+} ions and $\text{Sr}_{12}\text{Ca}_2\text{Cu}_{24}\text{O}_{41}$ with Cu^{2+} and Cu^{3+} ions cause the ultrasonic dispersions due to thermally assisted charge fluctuation in the temperature region between 100-200 K. The two-level system (TLS) due to an atomic tunneling²⁷ or electron tunneling²⁶ manifests itself in glass materials

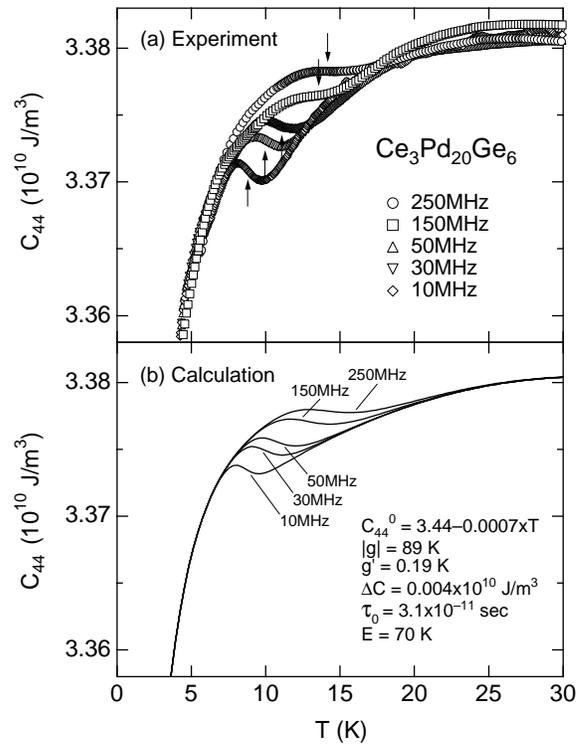


FIG. 14: Frequency dependence of the elastic constant of the transverse C_{44} mode in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$. (a) represents the experimental results with the frequencies from 10 MHz up to 250 MHz. (b) is the calculation in terms of the Debye-type dispersion of Eq. (5) in text.

at low temperatures, where the thermally activated motion dies out. The TLS yields the decrease in the elastic constant proportional to $\ln T$,²⁸ the specific heat to T and thermal conductivity to T^2 .²⁹ Besides in the case of Sm_3Te_4 , remarkable logarithmic decrease in the elastic constant appears below about 15 K down to the spin glass transition at $T_g = 1.5$ K, which suggests the existence of the 4f-electron tunneling motion between Sm^{2+} and Sm^{3+} ions situated charge glass state.²⁶

The present clathrate compound $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ is a crystal possessing an ideal periodic arrangement of cages in space. The stable trivalent Ce ions in cages of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ are free from the valence fluctuation phenomena. As shown in Fig. 1, the clathrate compound $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ is made up of the cage at 4a site consisting of Pd and Ge with distances $d_{\text{Ce1-Pd}}=3.332$ Å, $d_{\text{Ce1-Pd2}}=3.067$ Å, and the cage at 8c site of Pd with $d_{\text{Ce2-Pd1}}=2.868$ Å, $d_{\text{Ce2-Pd2}}=3.373$ Å. The trivalent Ce ion with radii $a = 1.7 \sim 1.8$ Å inside the 4a-site cage in particular is expected to show the rattling motion over the off-center positions being away from the center of the cage. Actually the neutron scattering on $\text{Pr}_3\text{Pd}_{20}\text{Ge}_6$ and $\text{Nd}_3\text{Pd}_{20}\text{Ge}_6$ revealed the sharp transition peaks indicating the stable CEF splitting at 8c site and no indication for CEF state at 4a site.⁸ These results may imply

TABLE I: Rattling modes with eight off-center positions along the three-fold [111] direction in the 4a-site cage with O_h point group symmetry. Corresponding elastic strains are also listed. There is a Γ_5 rattling mode coupled to the ε_{xy} -type strain of the C_{44} mode. This is contrary to the absence of the Γ_3 rattling mode to the $\varepsilon_u, \varepsilon_v$ of the $(C_{11} - C_{12})/2$ mode. The present ultrasonic dispersion in C_{44} of $Ce_3Pd_{20}Ge_6$ originates from the Γ_5 -type rattling at 4a site.

Symmetry	Rattling mode	Strain
Γ_1	$\rho_{\Gamma_1} = \rho_1 + \rho_2 + \rho_3 + \rho_4 + \rho_5 + \rho_6 + \rho_7 + \rho_8$	$\varepsilon_B = \varepsilon_{xx} + \varepsilon_{yy} + \varepsilon_{zz}$
Γ_2	$\rho_{\Gamma_2} = \rho_1 + \rho_2 + \rho_3 + \rho_4 - \rho_5 - \rho_6 - \rho_7 - \rho_8$	
Γ_3		$\varepsilon_u = (2\varepsilon_{zz} - \varepsilon_{xx} - \varepsilon_{yy})/\sqrt{3}$ $\varepsilon_v = \varepsilon_{xx} - \varepsilon_{yy}$
Γ_4	$\rho_{\Gamma_4,x} = \rho_1 - \rho_2 - \rho_3 + \rho_4 + \rho_5 - \rho_6 + \rho_7 - \rho_8$ $\rho_{\Gamma_4,y} = \rho_1 - \rho_2 + \rho_3 - \rho_4 + \rho_5 - \rho_6 - \rho_7 + \rho_8$ $\rho_{\Gamma_4,z} = \rho_1 + \rho_2 - \rho_3 - \rho_4 - \rho_5 - \rho_6 + \rho_7 + \rho_8$	
Γ_5	$\rho_{\Gamma_5,yz} = \rho_1 - \rho_2 - \rho_3 + \rho_4 - \rho_5 + \rho_6 - \rho_7 + \rho_8$ $\rho_{\Gamma_5,zx} = \rho_1 - \rho_2 + \rho_3 - \rho_4 - \rho_5 + \rho_6 + \rho_7 - \rho_8$ $\rho_{\Gamma_5,xy} = \rho_1 + \rho_2 - \rho_3 - \rho_4 + \rho_5 + \rho_6 - \rho_7 - \rho_8$	ε_{yz} ε_{zx} ε_{xy}

the obscure CEF state due to the off-center Ce ion at 4a site contrary to the well-defined CEF splitting at 8c site being stable Ce ion position.

F. Γ_5 rattling motion

Notable finding of Fig. 14 is that the ultrasonic dispersion in the C_{44} mode associated with ε_{xy} -type strain indicates the rattling motion with specific Γ_5 symmetry in $Ce_3Pd_{20}Ge_6$. It is expected that the Ce ion in 4a cage with cubic symmetry O_h favors off-center positions along one of the three principle directions of [100], [110] and [111]. As one can see the cage at 4a site in Fig. 1, it is of particular interest that no atom exists along the three-fold [111] directions, while the Ge atom occupies along the four-fold [100] and the Pd atom along the two-fold [110] ones. This crystallographic character may promise a flat potential along the three-fold [111] directions and profound potentials along the four-fold [100] and two-fold [110] directions. Presumably the Ce ion at 4a site prefers the off-center eight positions along the [111] directions, which are defined as $r_1 = (a, a, a)$, $r_2 = (-a, -a, a)$, $r_3 = (-a, a, -a)$, $r_4 = (a, -a, -a)$, $r_5 = (a, a, -a)$, $r_6 = (-a, -a, -a)$, $r_7 = (a, -a, a)$, $r_8 = (-a, a, a)$. The atomic densities $\rho_i = \rho_i(r_i)$ ($i = 1 \sim 8$) at the eight off-center positions are also defined. When 48 symmetry operators of O_h point group are acted on the atomic densities ρ_i , one can derive the transfer representation matrices with 8×8 elements. Consequently, one obtains the characters $\chi_{rat}^{[111]}$ for the rattling motion by tracing the diagonal elements of the representation matrices. Using the characters $\chi_{rat}^{[111]}$ and the character table for the irreducible representations of O_h ,³⁰ the rattling motion over the eight off-center positions along the [111] direction is reduced to the direct sum of $\Gamma_1(1D) \oplus \Gamma_2(1D) \oplus \Gamma_4(3D) \oplus \Gamma_5(3D)$.

Employing projection operators on appropriate atomic density ρ_i , we obtain the rattling modes for the irreducible representations as listed in Table 1 together

with the elastic strains $\varepsilon_{\Gamma\gamma}$. One can see the presence of Γ_5 rattling mode $\rho_{\Gamma_5,yz}, \rho_{\Gamma_5,zx}, \rho_{\Gamma_5,xy}$ coupled to the strain $\varepsilon_{yz}, \varepsilon_{zx}, \varepsilon_{xy}$ contrary to the absence of Γ_3 rattling mode coupled to the strain $\varepsilon_u, \varepsilon_v$. This is consistent with the fact that the ultrasonic dispersion reveals in C_{44} and is absent in $(C_{11} - C_{12})/2$. The Ce atom in the cage of $Ce_3Pd_{20}Ge_6$ obeys a harmonic oscillation of $\zeta(z) = (1/\pi z_0)1/2\exp(-z^2/2z_0^2)$ with a mean square displacement $z_0 = (1/2\pi)(h\tau_0/M)^{1/2}$. The attempt time $\tau_0 = 3.1 \times 10^{-11}$ sec and the mass $M = 140m_p$ where m_p is a proton mass, leads to the mean square displacement z_0 being approximately twice of off-center distances a as $z_0 = 2a = 0.48 \text{ \AA}$.³¹

The full symmetry Γ_1 rattling mode $\rho_{\Gamma_1} = \rho_1 + \rho_2 + \rho_3 + \rho_4 + \rho_5 + \rho_6 + \rho_7 + \rho_8$ means the uniform atomic distribution with fraction 1/8 at each eight off-center positions. While the Γ_5 rattling mode, for instance $\rho_{\Gamma_5,xy} = \rho_1 + \rho_2 - \rho_3 - \rho_4 + \rho_5 + \rho_6 - \rho_7 - \rho_8$, represents anisotropic atomic distribution being quadrupole O_{xy} at the lowest order such as fraction 1/4 at r_1, r_2, r_5, r_6 and zero at r_3, r_4, r_7, r_8 as shown in Fig. 15. The present group theoretical analysis for the rattling mode is essentially the same treatment previously argued for the charge fluctuation mode.^{24,26,32} In the present system $Ce_3Pd_{20}Ge_6$, the thermally activated Γ_5 rattling mode may be a ground state and the $\Gamma_1, \Gamma_2, \Gamma_4$ be excited states.

Our group has recently found similar ultrasonic dispersion around 30 K in a heavy fermion superconductor $PrOs_4Sb_{12}$ with a filled skutterudite structure. It should be noted that ultrasonic dispersion in the $(C_{11} - C_{12})/2$ mode of $PrOs_4Sb_{12}$ indicates the Γ_3 rattling motion of Pr atom over six fractionally occupied positions along [100]. The dispersion of $(C_{11} - C_{12})/2$ in $PrOs_4Sb_{12}$ is contrary to the one of C_{44} in the present compound of $Ce_3Pd_{20}Ge_6$.¹⁴ The attempted time $\tau_0 = 8.8 \times 10^{-11}$ sec, activation energy $E = 168$ K and mean square displacement $z_0 = 0.80 \text{ \AA}$ in $PrOs_4Sb_{12}$ are comparable to the present results of $Ce_3Pd_{20}Ge_6$.

The thermally activated Γ_5 rattling motion with fractional atomic state in $Ce_3Pd_{20}Ge_6$ dies out with decreas-

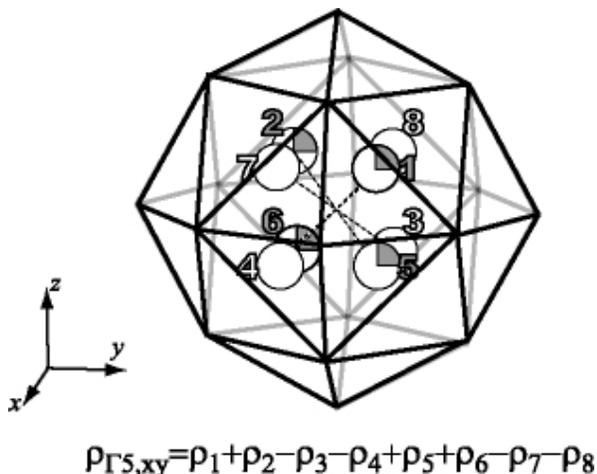


FIG. 15: Schematic view for the Γ_5 rattling mode $\rho_{\Gamma_5,xy}$ due to the off-center Ce-ion along the three-fold [111] direction in the 4a-site cage. The $\rho_{\Gamma_5,xy}$ represents that fractional atomic density 1/4 is located at r_1, r_2, r_5, r_6 and null at r_3, r_4, r_7, r_8 . The freezing of the thermally activated motion of the Γ_5 rattling mode brings about the atomic tunneling state at low temperatures.

ing temperature. At further low temperatures, the off-center tunneling state of Ce ions in the 4a-site cages will appear, which means a quantum state being occupied four positions, for instance at r_1, r_2, r_5, r_6 for the case of $\rho_{\Gamma_5,xy}$, at the same time. The charge glass state in the inhomogeneous mixed valence compound Sm_3Te_4 revealed the low-temperature softening in elastic constants proportional to $\ln T$ being resemble the structural glass.²⁶ The present scenario of the atomic tunneling of Ce ions in 4a-site cages in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ is also expected to show the elastic softening at low temperatures. However, the low-temperature quadrupole and magnetic orderings in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ may mask the character of the tunneling state in the present case. In order to clarify the tunneling and rattling in the present clathrate compounds, the low-temperature thermodynamic and ultrasonic measurements on $\text{La}_3\text{Pd}_{20}\text{Ge}_6$ without 4f-electron in particular is required.

IV. CONCLUDING REMARKS

In the present paper we have measured the elastic constants and thermal expansion of $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$. The characteristic elastic softening in $(C_{11} - C_{12})/2$ and C_{44} is well described in terms of the quadrupole susceptibility for the Γ_8 ground state. The important finding is that the $(C_{11} - C_{12})/2$ shows the huge softening of 50% towards $T_{Q1} = 1.25$ K and the C_{44} exhibits the softening of 2.5% only. This result strongly indicates the FQ ordering

with the order parameter of the Γ_3 symmetry in phase II below T_{Q1} . Actually we have successfully observed the sharp increase of $\Delta L/L = 1.9 \times 10^{-4}$ in length along the [001] direction below T_{Q1} . This is the evidence for the O_2^0 -type FQ ordering accompanied by the structural change from cubic lattice to tetragonal one at T_{Q1} in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$.

For the investigation of the magnetic phase diagram concerning the FQ phase II and AFM phase III in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$, the elastic constants and thermal expansion in fields have been measured. We have found that the boundary from the paramagnetic phase I to the FQ phase II of O_2^0 shifts to higher temperatures with increasing magnetic fields. The result that the I-II phase transition becomes obscure in fields is similar to the liquid-gas transition approaching to the critical end point under pressure. This result consistent with the fact that the FQ order parameter O_2^0 in $\text{Ce}_3\text{Pd}_{20}\text{Ge}_6$ has the total symmetry under fields along the [001] direction.⁵ The boundary from the phase II to the AFM ordering shifts to lower temperatures as similar as the conventional AFM ordering.

We have found the ultrasonic dispersion in the C_{44} mode indicating the rattling motion with Γ_5 symmetry. Taking into account the absence of the atom along the [111] direction in 4a-site cage, we have successfully picked up the specific Γ_5 rattling mode $\rho_{\Gamma_5,yz}, \rho_{\Gamma_5,zx}, \rho_{\Gamma_5,xy}$ with the fractional atomic density over the eight minimum positions of potential along the four-fold [111], $[\bar{1}\bar{1}\bar{1}]$, $[\bar{1}\bar{1}1]$ and $[11\bar{1}]$ directions. The dispersion of the C_{44} mode obeying the Debye-formula revealed the thermally activated-type relaxation time $\tau = \tau_0 \exp(E/k_B T)$ for the Γ_5 rattling mode with an attempt time $\tau_0 = 3.1 \times 10^{-11}$ sec and an activation energy $E = 70$ K. The estimated mean square displacement $z_0 = 0.48$ Å for the harmonic oscillation of Ce atom leads to the distance of the potential minima along the [111] direction as $a = z_0/2 = 0.24$ Å. In order to confirm the anisotropic atomic distribution in the 4a-site cage, the neutron or x-ray scattering is required. The freezing of the thermally activated motion due to the Γ_5 rattling mode with lowering temperature brings about the atomic tunneling state. By analogy of the charge glass compound Sm_3Te_4 , the Ce-ion tunneling is expected at low temperatures. The ultrasonic investigation on $\text{La}_3\text{Pd}_{20}\text{Ge}_6$ free from the long-range ordering due to 4f-electrons is now in progress to shed light on the tunneling and rattling in cages.

Acknowledgments

This work was supported by a Grant-In-Aid for Scientific Research from the Ministry of Education, Culture, Sports, Science and Technology of Japan.

-
- ¹ D. Schmitt, P. Morin, and J. Pierre, *J. Magn. Magn. Mater.* **8**, 249 (1978).
 - ² R. Takke, N. Dolezal, W. Assmus, and B. Lüthi, *J. Magn. Magn. Mater.* **23**, 247 (1981).
 - ³ H. Nakao, K. Magishi, Y. Wakabayashi, Y. Murakami, K. Koyama, K. Hirota, Y. Endoh, and S. Kunii, *J. Phys. Soc. Jpn.* **70**, 1857 (2001).
 - ⁴ S. Nakamura, T. Goto, S. Kunii, K. Iwashita, and A. Tamaki, *J. Phys. Soc. Jpn.* **63**, 623 (1994).
 - ⁵ R. Shiina, H. Shiba, and P. Thalmeier, *J. Phys. Soc. Jpn.* **66**, 1741 (1997); R. Shiina, O. Sakai, H. Shiba, and P. Thalmeier, *J. Phys. Soc. Jpn.* **67**, 941 (1998).
 - ⁶ J. Kitagawa, N. Takeda, and M. Ishikawa, *Phys. Rev. B* **53**, 5101 (1996).
 - ⁷ A. V. Grivanov, Yu. D. Seropegin, and O. I. Bodak, *J. Alloys. Comp.* **204**, L9 (1994).
 - ⁸ L. Keller, A. Dönni, M. Zolliker, and T. Komatsubara, *Physica B* **259-261**, 336 (1999).
 - ⁹ J. Kitagawa, N. Takeda, M. Ishikawa, T. Yoshida, A. Ishiguro, N. Kimura, and T. Komatsubara, *Phys. Rev. B* **57**, 7450 (1998).
 - ¹⁰ O. Suzuki, T. Horino, Y. Nemoto, T. Goto, A. Dönni, T. Komatsubara, and M. Ishikawa, *Physica B* **259-261**, 334 (1999); T. Goto, T. Horino, Y. Nemoto, T. Yamaguchi, A. Dönni, O. Suzuki, and T. Komatsubara, *Physica B* **312-313**, 492 (2002).
 - ¹¹ A. Dönni, T. Herrmannsdörfer, P. Fischer, L. Keller, F. Fauth, K. A. McEwen, T. Goto, and T. Komatsubara, *J. Phys.: Condens. Matter* **12**, 9441 (2000).
 - ¹² L. Mihaly, *Nature* **395**, 839 (1998); V. Keppens, D. Mandrus, B.C. Sales, B.C. Chakoumakos, P. Dai, R. Coldea, M.B. Maple, D.A. Gajewski, E.J. Freeman, and S. Bennington, *Nature* **395**, 876 (1998).
 - ¹³ V. Keppens, B.C. Sales, D. Mandrus, B.C. Chakoumakos, and C. Laermans, *Phil. Mag. Lett.*, **80**, 807 (2000).
 - ¹⁴ T. Goto, Y. Nemoto, K. Sakai, T. Yamaguchi, M. Akatsu, T. Yanagisawa, H. Hazama, K. Onuki, H. Sugawara, and H. Sato, to be submitted *Phys. Rev. Lett.*
 - ¹⁵ E. Kanda, T. Goto, H. Yamada, S. Suto, S. Tanaka, T. Fujita, and T. Fujimura, *J. Phys. Soc. Jpn.* **54**, 175 (1985), H. Yamada, S. Tanaka, Y. Kayanuma, T. Kojima, *J. Phys. Soc. Jpn.* **54**, 1180 (1985).
 - ¹⁶ P. Thalmeier and B. Lüthi, *Handbook on the Physics and Chemistry of Rare Earths*, ed. K. A. Gschneider Jr. and L. Eyring (North-Holland, 1991) Vol. 14. Chap. 96.
 - ¹⁷ T. Goto, Y. Nemoto, Y. Nakano, S. Nakamura, T. Kajitani, and S. Kunii, *Physica B* **281-282**, 586 (2000); T. Yamaguchi, M. Akatsu, Y. Nakano, T. Washizawa, Y. Nemoto, T. Goto, A. Dönni, S. Nakamura, and S. Kunii, *Physica B*, **329-333**, 622 (2003).
 - ¹⁸ A. Dönni, L. Keller, P. Fischer, Y. Aoki, H. Sato, F. Fauth, M. Zolliker, T. Komatsubara, and Y. Endoh, *J. Phys.: Condens. Matter* **10**, 7219 (1998); N. Kimura, N. Tateiwa, M. Nakayama, H. Aoki, T. Komatsubara, T. Sakon, M. Motokawa, Y. Koike, and N. Metoki, *Physica B* **259-261**, 338 (1999).
 - ¹⁹ T. Herrmannsdörfer, A. Dönni, P. Fischer, L. Keller, E. Clementyev, A. Furrer, S. Mango, B. van den Brandt, and H. Kitazawa, *J. Alloys. Comp.* **323-324**, 509 (2001).
 - ²⁰ T. Herrmannsdörfer, A. Dönni, P. Fischer, L. Keller, G. Böttger, M. Gutmann, H. Kitazawa, and J. Tang, *J. Phys.: Condens. Matter* **11**, 2929 (1999).
 - ²¹ T. Herrmannsdörfer, A. Dönni, P. Fischer, L. Keller, and H. Kitazawa, *Physica B* **281-282**, 167 (2000).
 - ²² O. Suzuki, T. Goto, S. Nakamura, T. Matsumura, and S. Kunii, *J. Phys. Soc. Jpn.* **67**, 4243 (1998); M. Akatsu, T. Goto, Y. Nemoto, O. Suzuki, S. Nakamura, and S. Kunii, *J. Phys. Soc. Jpn.* **72**, 205 (2003).
 - ²³ Y. Nemoto, H. Aoki, T. Goto, A. Ochiai, and T. Suzuki, *Physica B* **259-261**, 275 (1999).
 - ²⁴ T. Goto and B. Lüthi, *Advances in Phys.* **52**, 67 (2003).
 - ²⁵ A. Tamaki, T. Goto, S. Kunii, T. Suzuki, T. Fujimura, and T. Kasuya, *J. Phys. C: Solid State Phys.* **18**, 5849 (1985).
 - ²⁶ Y. Nemoto, T. Goto, A. Ochiai, and T. Suzuki, *Phys. Rev. B* **61**, 12050 (2000).
 - ²⁷ P. W. Anderson, B. I. Halperin, and C. M. Varma, *Philos. Mag.* **25**, 1 (1972).
 - ²⁸ See for example; S. Hunklinger and W. Arnold, *Physical Acoustics* (Academic, New York, 1976), Vol. XII, p. 155.
 - ²⁹ See for example; *Amorphous Solids: Low-Temperature Properties*, edited by W. A. Phillips (Springer, Berlin, 1981).
 - ³⁰ T. Inui, Y. Tanabe, and Y. Onodera, *Group Theory and Its Applications in Physics* (Springer, Berlin, 1990).
 - ³¹ D.L. Cox and A. Zawadowski, *Advances in Phys.*, **47**, 599 (1998).
 - ³² T. Goto, Y. Nemoto, A. Ochiai, and T. Suzuki, *Phys. Rev. B* **59**, 269 (1999).