

# First-principles extrapolation method for accurate CO adsorption energies on metal surfaces

Sara E. Mason, Ilya Grinberg and Andrew M. Rappe  
The Makineni Theoretical Laboratories, Department of Chemistry  
University of Pennsylvania, Philadelphia, PA 19104-6323  
(Dated: March 22, 2024)

We show that a simple first-principles correction based on the difference between the singlet-triplet CO excitation energy values obtained by DFT and high-level quantum chemistry methods yields accurate CO adsorption properties on a variety of metal surfaces. We demonstrate a linear relationship between the CO adsorption energy and the CO singlet-triplet splitting, similar to the linear dependence of CO adsorption energy on the energy of the CO  $2^*$  orbital found recently [Kresse et al., *Physical Review B* 68, 073401 (2003)]. Converged DFT calculations underestimate the CO singlet-triplet excitation energy  $E_{ST}$ , whereas coupled-cluster and CI calculations reproduce the experimental  $E_{ST}$ . The dependence of  $E_{chem}$  on  $E_{ST}$  is used to extrapolate  $E_{chem}$  for the top, bridge and hollow sites for the (100) and (111) surfaces of Pt, Rh, Pd and Cu to the values that correspond to the coupled-cluster and CI  $E_{ST}$  value. The correction reproduces experimental adsorption site preference for all cases and obtains  $E_{chem}$  in excellent agreement with experimental results.

## I. INTRODUCTION

The chemisorption of carbon monoxide on transition metal surfaces is regarded as a prototypical system for the study of molecule-surface interactions and has been intensely studied theoretically and experimentally [1]. For first-principles theoretical studies, density functional theory (DFT) with the generalized gradient approximation (GGA) to the exchange-correlation functional has emerged as the method of choice, and DFT-GGA studies have significantly advanced understanding of surface phenomena [2, 3].

Despite these successes, two of the most basic properties of CO-metal surface interactions { the chemisorption energy and the preferred adsorption site, cannot be reliably predicted by DFT calculations. Theoretical CO chemisorption energies obtained by the widely used PW91 [4] and PBE [5] functionals are significantly higher than experimental values, sometimes by as much as 0.4 eV [6] (30%). The RPBE functional [6] does improve the adsorption energetics, but at the expense of lower accuracy in metal lattice constants and a severe underestimation of surface energies. Even more importantly, neither PBE nor RPBE calculations can correctly predict the relative energetics of the high symmetry sites, favoring the more coordinated bridge and hollow sites over the top site, and resulting in a wrong site preference in a number of systems. This was first discussed by Feibelman et al. [7] where a variety of DFT-GGA methodologies and codes predicted adsorption at the fcc or hcp hollow site to be preferred over the experimentally preferred top site adsorption on the Pt(111) surface at low coverage. Since then this "puzzle" has been addressed [8, 9, 10, 11] and the DFT-GGA inaccuracy traced to the incorrect description of CO electronic structure and bond-breaking.

Grinberg et al. showed that the inaccuracy in site preference was due to the poor treatment of CO bond breaking by GGA functionals. Analyzing the CO electronic

structure, Gillet al. found that PBE and B3LYP [12, 13] functionals place the unfilled CO  $2^*$  orbital too low in energy. This makes it too close in energy to the metal d-band, which results in an unrealistic strengthening of the  $2^*$ -d-band bonding interaction. More recently, Kresse and co-workers [11] used DFT calculations of varying accuracy and showed that a linear relationship exists between the difference of top and hollow site chemisorption energies for CO on Pt(111) and the gas-phase energy of the CO  $2^*$  orbital.

By using a GGA + U type functional, Kresse et al. [11] were able to adjust the energetic position of the gas-phase CO  $2^*$  orbital, restoring the correct prediction that top site adsorption is preferred on Pt(111). However, the "correct" value of U is not known a priori. Furthermore, they studied adsorption on Pt(111) and did not address CO on other metal surfaces. In this paper, we demonstrate that a linear relationship exists between the CO chemisorption energy and the CO singlet-triplet excitation energy for the top, bridge and hollow sites on a variety of metal surfaces. Unlike the energetic position of the  $2^*$  orbital, the CO singlet-triplet excitation energy is rigorously well-defined and is accurately computed by coupled-cluster [14] and configuration interaction (CI) quantum chemical calculations [15]. Extrapolation of  $E_{chem}$  values to the correct CO singlet-triplet excitation energy relies only on first-principles calculations, and yields chemisorption and site-preference energies in excellent agreement with experiment for all systems studied.

## II. METHODOLOGY

Calculations are carried out using the PBE GGA exchange-correlation functional [5] and norm-conserving optimized pseudopotentials [16] with the designed non-local method [17] for metals. All pseudopotentials were

constructed using the OPIUM pseudopotential package [18]. CO chemisorption is modeled at 1/4 monolayer coverage on  $\sqrt{3}\times\sqrt{3}$  layer slabs, separated by vacuum, with allowed relaxation in the top two layers. All calculations are done, and tested to be converged, using a  $4\times4\times1$  grid of Monkhorst-Pack k-points [19]. The Kohn-Sham orbitals are expanded in a plane-wave basis set truncated at either 81 or 50 Ry, the higher cutoff being required in calculations using C and O pseudopotentials with small real-space cutoffs. We calculate the chemisorption energy for CO adsorbed on the (111) and (100) surfaces of Pt, Rh, Pd, and Cu, in three high symmetry sites: top, bridge, and hollow. On the (111) surfaces, adsorption at the fcc hollow site is not reported, since it is well known that differences between calculated fcc and hcp hollow site adsorption are negligible [20, 21].

We repeat these calculations using different sets of C and O pseudopotentials described in Table I. We use three sets of C and O pseudopotentials to calculate  $E_{\text{chem}}$  at each site on each surface. To evaluate whether three data points are adequate to describe trends in the chemisorption energies, we expand the number of C and O pseudopotential sets to five, and repeat the calculations for the hollow site on Pt(111). The slope for  $E_{\text{chem}}^{\text{GGA}}$  versus  $E_{\text{ST}}$  is unchanged on going from three points to five, as is the goodness of fit. Based on this, the remainder of our results use the first three pseudopotential sets.

### III. RESULTS

For CO on Pt(111), our calculations show a linear relationship between  $E_{\text{chem}}^{\text{hcp}}$  and CO  $E_{\text{ST}}$  excitation energy (Figure 1), similar to the linear relationship between CO/Pt(111)  $E_{\text{top fcc}}$  site preference energy and the energy of the CO  $2\pi^*$  for the Pt(111) adsorption observed by Kresse and coworkers [11]. A linear fit also describes well the behavior of chemisorption energies on the seven other substrates included in the present work. Since the CO triplet state is produced by an excitation of an electron from the  $5\sigma$  orbital to the  $2\pi^*$  orbital, the singlet-triplet excitation energy is closely related to the  $5\sigma-2\pi^*$  gap and to the position of the  $2\pi^*$  orbital. This gives rise to a similar linear dependence of  $E_{\text{chem}}$  on the energy of CO  $2\pi^*$  orbital and on  $E_{\text{ST}}$ .

Coupled-cluster [14] and CI [15] quantum chemical calculations accurately reproduce the experimental  $E_{\text{ST}}$  of 6.095 eV [22]. On the other hand, regardless of the pseudopotential set, our DFT-GGA calculations always predict a  $E_{\text{ST}}$  that is too small. The correct chemisorption energy  $E_{\text{chem}}^{\text{corr}}$  can be obtained by using the relationship between  $E_{\text{chem}}$  and  $E_{\text{ST}}$  and extrapolating to the CI  $E_{\text{ST}}$  value:

$$E_{\text{chem}}^{\text{corr}} = E_{\text{chem}}^{\text{GGA}} + (E_{\text{ST}}^{\text{CI}} - E_{\text{ST}}^{\text{GGA}}) \frac{E_{\text{chem}}^{\text{GGA}}}{E_{\text{ST}}^{\text{GGA}}}; \quad (1)$$

where  $E_{\text{ST}}^{\text{CI}}$  and  $E_{\text{ST}}^{\text{GGA}}$  are respectively the CI and

GGA CO singlet-triplet excitation energies, and  $E_{\text{chem}}^{\text{GGA}} / E_{\text{ST}}^{\text{GGA}}$  is the slope of the fit of  $E_{\text{chem}}$  versus  $E_{\text{ST}}$ .

A universal feature of the corrected chemisorption energies in Table II is that they all indicate weaker chemisorption than the corresponding uncorrected values, with the  $E_{\text{chem}}^{\text{corr}}$  values for the preferred site demonstrating much better agreement with experimentally determined adsorption energies. For example, the  $E_{\text{chem}}^{\text{GGA}}$  for the experimentally seen CO/Pd(111) hollow site is 1.96 eV, as compared to 1.47-1.53 eV obtained by temperature programmed desorption (TPD) measurements [23]. This rather large 0.46 eV error is eliminated by the use of the extrapolation, with  $E_{\text{chem}}^{\text{corr}}$  of 1.60 eV, in very close agreement with experimental results. For the experimentally observed top site on Cu(111) the results are less dramatic but still noticeable, with  $E_{\text{chem}}^{\text{GGA}}$  of 0.746 eV changed to  $E_{\text{chem}}^{\text{corr}}$  of 0.621 eV in better agreement with the experimental value of 0.49 eV [24]. Overall, comparison of PBE and corrected results shows an improvement from 0.38 eV (30%) average overestimation for the PBE functional to 0.16 eV (13%) average error for our corrected results.

Examination of the data in Table II shows that there is a strong correlation between the magnitude of the correction and the chemisorption site. This is due to the different strengths of the metal-CO interactions in different local geometries. While the chemisorption bond is formed through both  $\sigma$  donation and  $\pi^*$  back-donation, the contribution of  $\pi^*$  back-donation to the adsorption bonding in the systems considered here is dominant because the fillings of the late transition metals studied here are greater than half [25]. The back-donation mechanism is strongly enhanced by going from top site to polycordinated adsorption sites [11, 20, 26, 27]. Accordingly, the incorrect DFT-GGA  $E_{\text{ST}}$  (or the incorrect placement of the  $2\pi^*$  orbital) will require the smallest correction for  $E_{\text{chem}}$  of the top site, followed by the bridge site, the three-fold hcp hollow site on the (111) surfaces and the four-fold hollow on the (100) surfaces. This ranking is evident in the tabulated results. In the chemical language, the CO bond weakening is smallest for the top site and largest for the four-fold hollow site.

The DFT-GGA errors in the prediction of the preferred site are a direct outcome of the unequal treatment of the CO bond weakening at the top and hollow sites due to the unrealistically small  $E_{\text{ST}}$  and low  $2\pi^*$  energy. Using our first-principles extrapolation to eliminate the CO bond weakening errors, our corrected DFT results give the highest value of  $E_{\text{chem}}^{\text{corr}}$  for the experimentally observed sites in all cases. For Pt(111), our raw DFT data show an incorrect site preference with an energy of 0.076 eV. The corrected energies agree with experimental site preference [28, 29, 30] with an energy difference of 0.163 eV. Likewise, our raw DFT data for Rh(111) is disparate with experimental site preference [31, 32] while our corrected energies are in agreement. For Cu(111) the use of the correction gives the experimental site preference [24, 33], though the corrected DFT results predict small (0.1 eV) differences between the top, bridge and

hollow sites. Both the raw DFT and the corrected results for Pd(111) agree with the site preference observed by experiment [23, 34, 35]. Our corrected results for the (100) surfaces agree with experimentally observed preferred adsorption sites for Pt [36, 37, 38], Rh [39, 40], Pd [38, 41], and Cu [42, 43].

A less exact but simpler correction can be extracted from our data and applied to any CO/metal surface system. The data in Table II show that for any given site the  $E_{\text{chem}}^{\text{GGA}} / E_{\text{S-T}}^{\text{GGA}}$  values and the consequent correction energy are fairly constant with scatter of about 0.1 eV across a range of systems.

As discussed above, the similarities for the same site and the differences among the sites are consequences of the different degrees of CO bond weakening. The degree of CO bond weakening can be estimated from the frequency shift of adsorbed CO relative to the gas-phase CO molecule, which can be easily calculated for any system. Then the frequency can be compared to those of top (typically 2000-2100  $\text{cm}^{-1}$ ), bridge (1850-1950  $\text{cm}^{-1}$ ), hcp (1750-1800  $\text{cm}^{-1}$ ) or four-fold hollow (1600-1700  $\text{cm}^{-1}$ ) sites and a corresponding correction applied.

For example, for CO adsorption on Ni(111), DFT-GGA calculations with PBE or PW91 functionals find the preferred site to be hcp or fcc [44], in agreement with experimental results [45]. However, the  $E_{\text{chem}}$  are in 1.9-2.0 eV range, in contrast to experimental  $E_{\text{chem}}$  of 1.12-1.55 eV. Since the hollow site CO/Ni(111) stretch frequency of 1800  $\text{cm}^{-1}$  [44] is similar to the 1830  $\text{cm}^{-1}$  frequency for CO on Pd(111) hollow site [21], we expect the  $E_{\text{chem}}$  error to be similar, and the corrected value of  $E_{\text{chem}}$  is about 1.55 eV, in much better agreement with experimental results. A graphical representation of the suggested correction to  $E_{\text{chem}}$  as a function of CO stretch frequency is given in Figure 2.

#### IV. CONCLUSION

We have shown that the chemisorption energies of CO adsorbed on metal surfaces depend linearly on gas-phase CO singlet-triplet splitting. The difference between the high level quantum chemistry coupled-cluster/CI and DFT-GGA singlet-triplet excitation energies can then be used to extrapolate to chemisorption energies with the CO error removed. The corrected values are in good agreement with experimental results. The correction also eliminates the GGA errors in site preference. We find a strong correlation between the amount of CO bond breaking and the correction magnitude. This suggests that an estimate of the GGA error due to the incorrect description of CO electronic structure can be readily obtained through the frequency shift of adsorbed CO at any site on a metal surface. The demonstrated method should be applicable to various adsorption systems where the charge transfer responsible for chemisorption is sensitive to the adsorbate electronic structure.

TABLE I: Pseudopotential details. Core radii are in  $a_0$ , plane wave cutoff  $\epsilon_q$  in Ry. All PSPs were created from the  $s^2p^2$  reference configuration for carbon and the  $s^2p^4$  reference configuration for oxygen. For each pseudopotential set, results from gas-phase molecule calculations for the  $2^1\Sigma^+$  energy, as well as the  $5^1\Sigma^+$  gap and the singlet-triplet energy are given, all in eV.

	$r_c^O$	$r_c^C$	$q_c^O$	$q_c^C$	$E_2$	5	2	$E_{\text{S-T}}$
PSP 1	0.94	1.09	81,81	-2.10	6.91			5.35
PSP 2	1.60	1.49	47,50	-1.90	7.01			5.53
PSP 3	1.70	1.49	30,50	-1.61	7.35			5.84
PSP 4	1.65	1.49	42,50	-1.94	7.04			5.56
PSP 5	1.70	1.49	39,50	-1.87	7.09			5.61

#### V. ACKNOWLEDGMENTS

This work was supported by the Air Force Office of Scientific Research, Air Force Materiel Command, USAF, under grant number F49620-00-1-0170, and the NSF MRSEC Program, under Grant DMR-00-79909. AMR acknowledges the support of the Camille and Henry Dreyfus Foundation. Computational support was provided by the Defense University Research Instrumentation Program, the National Center for Supercomputing Applications and the High-Performance Computing Modernization Office of the Department of Defense.

TABLE II: Results of linear regression of chemisorption energy versus singlet-triplet splitting energy. The correlation coefficient for each fit is in parenthesis next to each slope. The DFT/GGA values for the chemisorption energies are given, along with the corrected energies obtained by extrapolation. For convenience, the value of the difference between top and hollow site adsorption energies,  $E_{th}$ , and how it evolves with the magnitude of correction,  $\Delta$ , are also listed. Positive value of  $E_{th}$  indicates that top site is preferred. For each substrate, the site found to be preferred by experiment is marked with an asterisk (\*). Experimental values for  $E_{chem}$  are given in parentheses next to  $E_{GGA}^{corr}$  for Pt(111) [28, 29, 30], Rh(111) [31, 32], Pd(111) [23, 35], Cu(111) [24, 33], Pt(100) [36, 37, 38], Rh(100) [39, 40], Pd(100) [38, 41], and Cu(100) [42, 43]

	Site	Slope	$E_{chem}^{GGA}$	$E_{chem}^{corr}$	$\Delta$
Pt(111)	top*	-0.211 (0.989)	1.717	1.560 (1.43-1.71)	-0.157
	bridge	-0.435 (0.999)	1.758	1.433	-0.325
	hcp	-0.532 (0.999)	1.793	1.397	-0.396
	$E_{th}$	0.321	-0.076	0.164	0.240
Rh(111)	top*	-0.259 (0.975)	1.866	1.673 (1.43-1.65)	-0.193
	bridge	-0.456 (0.997)	1.920	1.581	-0.339
	hcp	-0.559 (0.996)	2.059	1.644	-0.415
	$E_{th}$	0.300	-0.193	0.030	0.223
Pd(111)	top	-0.185 (0.977)	1.385	1.247	-0.138
	bridge	-0.399 (0.977)	1.784	1.487	-0.297
	hcp*	-0.535 (0.995)	1.962	1.602 (1.47-1.54)	-0.360
	$E_{th}$	0.350	-0.577	-0.355	0.222
Cu(111)	top*	-0.169 (0.981)	0.746	0.621 (0.46-0.52)	-0.125
	bridge	-0.329 (0.951)	0.822	0.576	-0.246
	hcp	-0.375 (0.993)	0.889	0.610	-0.279
	$E_{th}$	0.206	-0.143	0.011	0.154
Pt(100)	top*	-0.212 (0.975)	1.954	1.796 (1.62-2.18)	-0.158
	bridge*	-0.422 (0.996)	2.139	1.824 (1.62-2.18)	-0.315
	hollow	-0.607 (0.999)	1.698	1.246	-0.452
	$E_{th}$	0.395	0.256	0.551	0.295
Rh(100)	top*	-0.246 (0.989)	1.905	1.723 (1.24-1.65)	-0.182
	bridge*	-0.427 (0.999)	2.092	1.774	-0.318
	hollow	-0.651 (0.999)	2.087	1.603	-0.484
	$E_{th}$	0.405	-0.182	0.120	0.302
Pd(100)	top	-0.196 (0.980)	1.494	1.348	-0.146
	bridge*	-0.384 (0.995)	1.927	1.641 (1.3-1.71)	-0.286
	hollow	-0.583 (0.999)	1.937	1.503	-0.434
	$E_{th}$	0.387	-0.443	-0.155	0.288
Cu(100)	top*	-0.170 (0.996)	0.830	0.703 (0.55-0.57)	-0.147
	bridge	-0.286 (0.991)	0.834	0.620	-0.214
	hollow	-0.523 (0.999)	0.831	0.441	-0.477
	$E_{th}$	0.353	-0.001	0.262	0.263

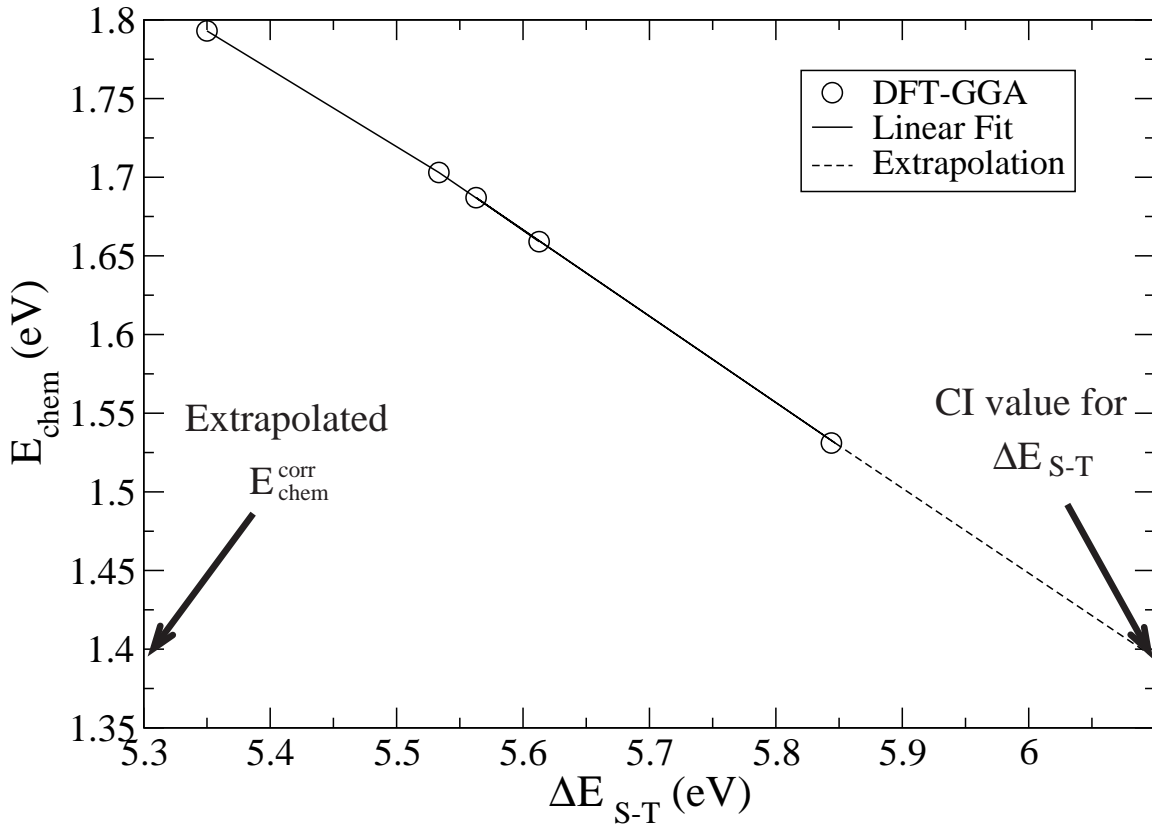


FIG. 1:  $E_{\text{chem}}^{\text{hcp}}$  for CO on Pt(111) versus  $E_{\text{S-T}}$  of CO for various pseudopotential sets (circles) and as determined by CI calculations (square). Similar clear linear relationships are also obtained for other sites and metal surfaces. For both the most accurate pseudopotential set as well as for the CI data point, dashed lines guide the eye to the corresponding values of  $E_{\text{chem}}^{\text{hcp}}$ . First-principles extrapolation procedure:  $E_{\text{chem}}^{\text{GGA}}$  and  $E_{\text{S-T}}^{\text{GGA}}$  values are plotted and fit to a line (solid). This line is extended to the abscissa representing  $E_{\text{S-T}}^{\text{CI}}$ . The corresponding ordinate value is  $E_{\text{chem}}^{\text{corr}}$ . Chemisorption on the hcp site of Pt(111) is used in this example.

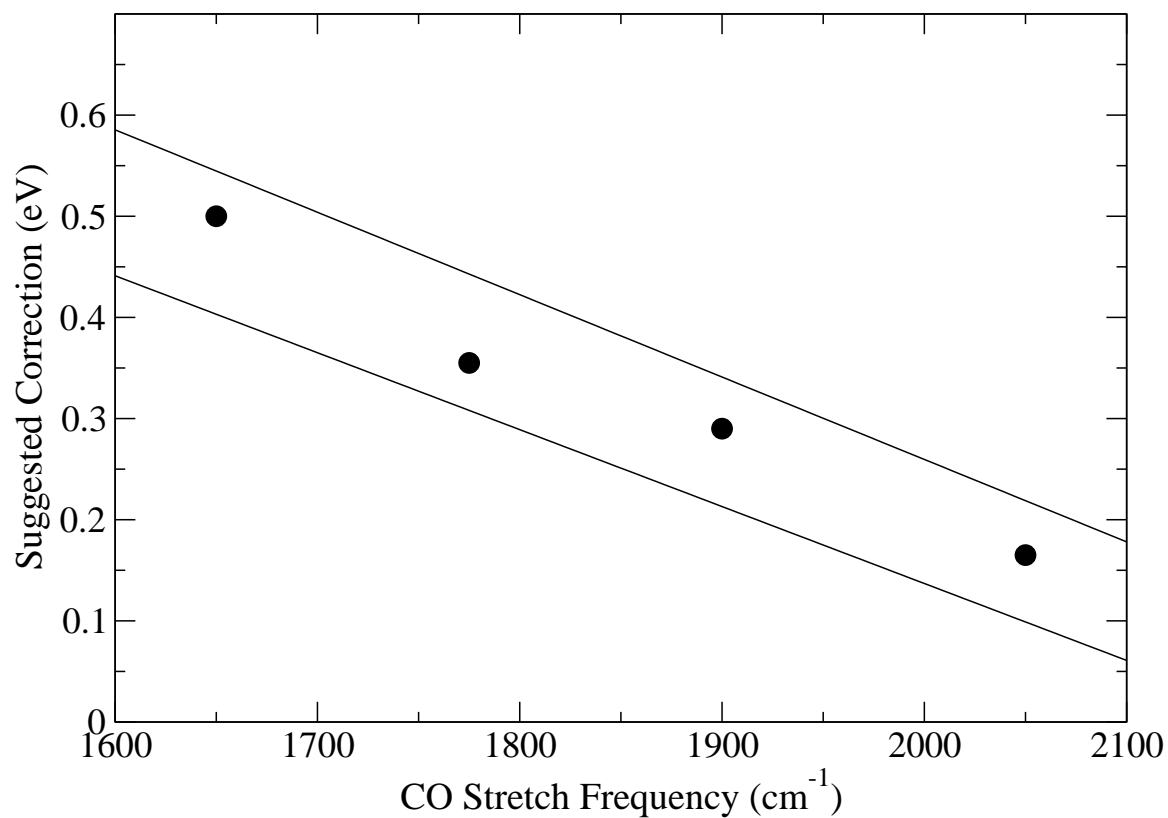


FIG. 2: Graphical guide for estimating  $E_{\text{chem}}^{\text{GGA}}$  from CO stretch frequency. Correction energy as a function of the adsorbed CO stretch frequency provides a simpler, more user-friendly method of applying the correction. Lines represent boundaries for suggested correction values, average correction values for high-symmetry sites for our highest quality DFT-GGA results in this study are shown as circles.

- 
- [1] Q. Ge, R. Kose, and D. A. King, *Adv. Cat.* 45, 1 (2000).
- [2] A. Gross, *Theoretical Surface Science* (Springer-Verlag, Berlin Heidelberg, Princeton, NJ, 2003).
- [3] J. Greeley, J. K. Nørskov, and M. Mavrikakis, *Annu. Rev. Phys. Chem.* 53, 319 (2002).
- [4] J. P. Perdew, J. A. Chevary, S. H. Vosko, K. A. Jackson, M. R. Pederson, and C. Fiolhais, *Phys. Rev. B* 46, 6671 (1992).
- [5] J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* 77, 1227 (1996).
- [6] B. Hammer, L. B. Hansen, and J. K. Nørskov, *Phys. Rev. B* 59, 7413 (1999).
- [7] P. J. Feibelman, B. Hammer, J. K. Nørskov, F. Wagner, M. Scheer, R. Stumpf, R. Watwe, and J. Dumescic, *J. Phys. Chem.* 105, 4018 (2001).
- [8] I. Grinberg, Y. Yourisdshahyan, and A. M. Rappe, *J. Chem. Phys.* 117, 2264 (2002).
- [9] R. A. Olsen, P. H. T. Philipsen, and E. J. Baerends, *J. Chem. Phys.* 119, 4522 (2003).
- [10] A. Gil, A. Cblot, J. M. Ricart, G. Kresse, M. Garcia-Hernandez, N. Rosch, and P. Sautet, *Surf. Sci.* 530, 71 (2003).
- [11] G. Kresse, A. Gil, and P. Sautet, *Phys. Rev. B* 68, 073401 (2003).
- [12] A. D. Becke, *J. Chem. Phys.* 98, 5648 (1993).
- [13] C. Lee, W. Yang, and R. G. Parr, *Phys. Rev. B* 38, 3098 (1988).
- [14] W. B. Zeinen, G. C. Groenenboom, and A. van der Avoird, *J. Phys. Chem.* 119, 103 (2003).
- [15] D. Talbi and G. S. Chandler, *J. Phys. Chem.* 104, 5872 (2000).
- [16] A. M. Rappe, K. M. Rabe, E. Kaxiras, and J. D. Joannopoulos, *Phys. Rev. B Rapid Comm.* 41, 1227 (1990).
- [17] N. J. Ramer and A. M. Rappe, *Phys. Rev. B* 59, 12471 (1999).
- [18] <http://opus4.kit.edu/opus4/handle/10018/10018>.
- [19] H. J. Monkhorst and J. P. Pack, *Phys. Rev. B* 13, 5188 (1976).
- [20] M. T. M. Koper, R. A. van Santen, S. A. W. Asileski, and M. J. Weaver, *J. Chem. Phys.* 113, 4392 (2000).
- [21] D. Loreda, D. Simon, and P. Sautet, *Surf. Sci.* 425, 68 (1999).
- [22] G. Herzberg, *Electronic Spectra of Polyatomic Molecules* (Van Nostrand, Princeton, NJ, 1966).
- [23] H. Conrad, G. Ertl, J. Koch, and E. E. Latta, *Surf. Sci.* 43, 462 (1974).
- [24] W. KIRSTEIN, B. KUGER, and F. THIEME, *Surf. Sci.* 176, 505 (1986).
- [25] B. Hammer, Y. Morikawa, and J. K. Nørskov, *Phys. Rev. Lett.* 76, 2141 (1996).
- [26] F. Illas, S. Zúñiga, and J. Rubio, *Phys. Rev. B* 52, 12372 (1995).
- [27] G. Blyholder, *J. Phys. Chem.* 68, 578 (1964).
- [28] G. Ertl, M. Neumann, and K. M. Streit, *Surf. Sci.* 64, 393 (1977).
- [29] H. Steininger, S. Lehwald, and H. Ibach, *Surf. Sci.* 123, 264 (1982).
- [30] Y. Y. Yeo, L. Vattuone, and D. A. King, *J. Chem. Phys.* 106, 392 (1996).
- [31] K. A. Peterlinz, T. J. Curtiss, and S. J. Sibener, *J. Chem. Phys.* 95, 6972 (1991).
- [32] M. J. P. Hopstaken and J. W. Niemantsverdriet, *J. Chem. Phys.* 113, 5457 (2000).
- [33] P. Hollins and J. Pritchard, *Surf. Sci.* 89, 486 (1979).
- [34] M. K. Rose, T. M. Itsu, J. Dunphy, A. Borg, D. F. Ogletree, M. Salmeron, and P. Sautet, *Surf. Sci.* 512, 48 (2002).
- [35] X. Guo and J. T. Y. Jr., *J. Chem. Phys.* 90, 6761 (1989).
- [36] D. Curulla, A. Cblot, and J. M. Ricart, *Surf. Sci.* 460, 101 (2000).
- [37] P. A. Thiel, R. J. Behn, P. R. Norton, and G. Ertl, *J. Chem. Phys.* 78, 7448 (1983).
- [38] Y. Y. Yeo, L. Vattuone, and D. A. King, *J. Chem. Phys.* 106, 1990 (1997).
- [39] R. Kose, W. A. Brown, and D. A. King, *J. Phys. Chem. B* 103, 8722 (1999).
- [40] V. K. Medvedev, V. S. Kulik, V. I. Chernyi, and Y. Su-chorski, *Vacuum* 48, 341 (1997).
- [41] J. C. Tracy and P. W. Palmberg, *J. Chem. Phys.* 51, 4852 (1969).
- [42] J. C. Tracy, *J. Chem. Phys.* 56, 2748 (1972).
- [43] C. M. Thnuong, J. A. Rodriguez, and D. W. Goodman, *Surf. Sci.* 271, L385 (1992).
- [44] A. Eichler, *Surf. Sci.* 526, 332 (2003).
- [45] R. Davis, P. Hoffmann, O. Scha, V. Fernandez, K. M. Schindler, V. Fritzsche, and A. M. Bradshaw, *J. Phys.: Condens. Matter* 8, 1367 (1996).