

Current-driven domain wall motion in thin ferromagnetic wires

S. E. Barnes and S. Maekawa

Institute for Materials Research, Tohoku University, Sendai 980-8577, Japan

(dated: December 28, 2021)

The coupling between a current and a Bloch wall is examined in the half-metal limit of the double exchange model. The conduction electrons transfer angular momentum to the Bloch wall with 100% efficiency in the absence of pinning. The wall is displaced without distortion with velocity proportional to the current. In the presence of a pinning potential either the angular momentum is destroyed by the perpendicular component of the anisotropy field or is converted to coherent magnons. A moving wall has its velocity reduced by pinning. The expression for the velocity agrees surprisingly well with experiment.

PACS numbers: 75.60.-d, 73.40.Cg, 73.50.Bk, 75.70.i

Spintronic devices have great technological promise but represent a challenging problem at both an applied and fundamental level. It has been shown theoretically [1, 2] that the direction of a magnetic domain might be switched using currents alone. Devices designed to use this principle often consist of multilayers of magnetic and non-magnetic materials. The advantages of similar devices based upon the current induced displacement of Bloch wall are simplicity and the fact that the switching current is smaller [3-5]. Experimentally the current induced displacement of a Bloch wall has been clearly demonstrated and in a recent experiment the velocity of the displaced wall was measured [5].

In this Letter is developed a first principles theory for the coupling between a current and a Bloch wall based upon a standard model for ferromagnets, i.e., within the double exchange model. Great care is taken in order to ensure that angular momentum is conserved. Using the s-d-exchange model, Berger [2] shows the polarization of the s-electrons rotates as it passes through a wall. The reaction force might then be assumed to cause wall movement. However, as will be shown, the situation is complicated. Angular momentum given to the wall can be taken up either by (i) the displacement of the wall, (ii) the production of coherent spin waves or (iii) a rotation of the wall so that the angular momentum is absorbed by the anisotropy energy. These issues are most easily addressed in the half-metal limit. This is technologically pertinent since it corresponds to the most efficient devices. Most work has been performed on Permalloy ($\text{Ni}_{81}\text{Fe}_{19}$). For this material, the current \vec{j} has a polarization $p \approx 0.7$ [5] and so the present description based upon $p = 1$ is not hopelessly unrealistic. When making comparison with experiment, the difference will be accounted for by adding factors of p as appropriate.

The standard double exchange model is

$$H = \sum_{\langle ij \rangle} t_{ij}^X \sum_{\sigma} c_{i\sigma}^\dagger c_{j\sigma} + H_{\text{ex}} + U \sum_i n_{i\uparrow} n_{i\downarrow} + \sum_i (J_H S_i - J_A S_{iz}^2 - K_2 S_{iy}^2) + \sum_i J_0 S_i \cdot S_j \quad (1)$$

where S_i is the localized spin operator and c_i^\dagger creates an electron with spin \uparrow at site i . The wire is assumed to extend along the z -direction. That this is an easy axis implies $A > 0$.

Corresponding to highly correlated electrons, the limit $U \rightarrow \infty$ is taken. This permits a spinless majority electron operator $c_i^\dagger \rightarrow \tilde{c}_i^\dagger$ to be defined, and in terms of this the minority $c_{i\downarrow}^\dagger = s_i \tilde{c}_i^\dagger$ where s_i is the conduction electron spin operator. A large Hund's rule coupling $j_H \rightarrow \infty$ is also assumed. With this only the largest total angular momentum manifold is relevant. At a site occupied by a conduction electron only states with $J = S + 1 = 2$ need to be accounted for and it follows that $s_i \rightarrow S_i = (2S)$. This is not an assumption about local equilibrium of the conduction electron but rather is an immediate and rigorous consequence of the Wigner-Eckart theorem.

The Holstein-Primakoff transformation [6] $S_{iz} = S - b_i^\dagger b_i$, $S_i^+ = (2S - b_i^\dagger b_i)^{1/2} b_i$, $(2S)^{1/2} b_i$ is used to quantize the spin degrees of freedom. In principle, the axes of quantization are arbitrary, however, as the standard theory of ferromagnetic magnons illustrates, in fact the local axis of quantization must be taken along the classical equilibrium direction, i.e., the spin direction in the limit $S \rightarrow \infty$. When this is the case the approach generates and expansion in $1/S$. This local equilibrium direction is specified by the Euler angles θ_i and ϕ_i . In this Letter the solution will most often be time dependent. Rather than setting up the complicated equations of motion, here extensive use will be made of rotating frames. The aim is to reduce the problem to that of static equilibrium but within the time dependent frame. The time dependent solution is then obtained upon reverting to the laboratory frame.

In the absence of a wall, for large U , the kinetic energy term is $\hat{T} = \sum_{ij} t_{ij} (c_i^\dagger c_j + s_i c_i^\dagger c_j s_j^\dagger) + H_{\text{ex}}$. The Bloch wall is generated through via the static rotations by θ_i and ϕ_i . For this large U regime, the usual $SU(2)$ rotation of the conduction electron operators simplifies to $c_i^\dagger \rightarrow \sum_{\sigma} U_{\sigma}^\dagger c_{i\sigma}^\dagger$ and the rotated $\hat{T} = \sum_{ij} t_{ij} \cos[(\theta_i - \theta_j)/2] (c_i^\dagger c_j + s_i c_i^\dagger c_j s_j^\dagger)$

it $\sum_{ij} \sin[(\theta_i - \theta_j)/2] (s_i c_j^y c_j^z - c_i^y c_j^z s_j^x) + H_{\text{sc}}$: Charge motion arises principally via $H_t = \sum_{ij} t_{ij} c_i^y c_j^z + H_{\text{sc}}$ where $t_{ij} = t \cos[(\theta_i - \theta_j)/2]$. The reduction of t_{ij} in the Bloch wall implies a barrier, however this has a height

SA which is taken to be negligible compared to E_F . The solutions of H_t are, to a good approximation, plain k -states independent of the wall position or its motion.

Using the Wigner-Eckart theorem, the part of \hat{T} linear in s_i reduces to:

$$H_{\text{tj}} = \frac{t}{2(2S)^{1/2}} \frac{\partial}{\partial z} a \sum_i c_{i+1}^y (b_i^y - b_{i+1}^y) + H_{\text{sc}}; \quad (2)$$

which is the key spin-charge current interaction. The, bilinear in s_i , part of \hat{T} is also of importance. When acting on eigenstates of H_t these lead to a renormalization, $J = J_0 + (\chi^0/2S^2)$, of the total exchange coupling J . The effective concentration $x^0 = (1/N) \sum_k (\cos k_z a) n_k$, assuming isotopic hopping.

A small wall translation by z amounts to a small rotation generated by $R(z) = \sum_i \exp(i(\theta_{i+1} - \theta_i) S_{iy}) \approx (1 + (1/2) \sum_i (\partial \theta_i / \partial z) z (2S)^{1/2} (b_i^y - b_{i+1}^y)) \approx 1 + S^{1/2} (2A/J)^{1/4} (z/a) (b_w^y - b_0^y)$ which defines $b_w^y = (J/8A)^{1/4} \sum_i (\partial \theta_i / \partial z) a b_i^y$. That the translation $R(z)$ leaves the energy unchanged implies that b_w^y creates a zero energy excitation localized in the wall. This special b_w^y mode is key to a understanding of not only the dynamics but also pinned static solutions of a Bloch wall. It is of the nature of a discrete Goldstone boson associated with the translational invariance of the wall.

The effective, $H = E_f; i; g + H_t + H_s + H_{\text{tj}}$, where $E_f; i; g$ is the classical energy functional, H_t is given above and H_s is the magnon Hamiltonian. The Bloch wall structure can be determined by minimizing $E_f; i; g$. The standard result is $\theta(z) = 2 \cot^{-1} e^{(z-w)/a}$ with $\theta_i = 0$ for $K_F > 0$. The wall width $w = a \frac{J}{2A}^{1/2}$. The local axes change from $\theta = 0$ to $\theta = \pi$ with increasing z and the wall lies in the $x-z$ plane.

The conservation of the spin angular momentum J_z is a central issue. If the coupling to the contacts is ignored and $K_F = 0$, it follows that $[J_z; H] = 0$. A wall with speed v implies $J_z = \sim S v = a_R$ and, in fact this must be equal to the surface integral $\oint \mathbf{s} \cdot \mathbf{A}$ where \mathbf{s} is the spin current. The conduction electrons have their spin reversed in the wall implying a contribution $\oint \mathbf{s} \cdot \mathbf{A} / I$, the charge current. Such a finite surface term gives rise to a local term $\mathbf{r} \cdot \mathbf{s} / j$, the charge current density, in the equation for dS_1/dt and will lead to wall motion even when $K_F = 0$.

Whatever the value of K_F , the translational invariance of the Hamiltonian implies that the wall will move with a constant velocity in the presence of a charge current. In order to prove this, use is made of a rotating frame. Consider again the current carrying states which are eigenstates of $\hat{n}_k = c_k^y c_k^z$. The spin-charge coupling

reduces to

$$H_{\text{tj}} = \sum_i \frac{\sim j a^2}{2eS} \frac{\partial}{\partial z} a (2S)^{1/2} (b_i^y - b_{i+1}^y); \quad (3)$$

Here $(2S)^{1/2} (1/2i) (b_i^y - b_{i+1}^y) = S_{iy}'$ defined to be strictly perpendicular to the instantaneous axis of quantization. The only derivative which is finite during this short period is the similar instantaneous $S_{ix}' = S \frac{\sim j a^2}{2eS} \frac{\partial}{\partial z} a$. This derivative can also be made to be zero by a suitable rotating frame, i.e., via $r = \exp(i(\theta_i - \theta_t) S_{iy}')$ so that $S_{ix}' \rightarrow r S_{ix}' r^{-1}$ and $S_{iy}' \rightarrow S_{iy}' + i(\theta_i - \theta_t) [S_{iy}', S_{ix}'] = S_{iy}' - i(\theta_i - \theta_t) S$. The wall is therefore stationary, when the local axes of quantization rotate according to

$$\frac{\partial \theta_i}{\partial t} = v_0 \frac{\partial \theta_i}{\partial z}; \quad v_0 = \frac{j a^3}{2eS}; \quad (4)$$

The solution of this is $\theta_i = \theta_i(z - v_0 t)$ where $\theta_i(z) = 2 \cot^{-1} e^{(z-w)/a}$ is the static solution. In the laboratory frame, the wall is translated without distortion. The velocity v_0 [5, 7] is such that the net conduction electron spin current which enters the wall is exactly compensated by the similar current implied by its uniform displacement.

The simplest model for the pinning of the Bloch wall is to reduce by a small amount the anisotropy energy at the origin. The added term $H_p = + A S_0 z^2$ generates a pinning gap E_p . The problem of such a pinned wall is surprisingly complicated. Our results developed below show, for finite K_F , the wall tilts by an angle and the critical charge current j_c is determined by the condition that $E_p = 0$. However, when K_F is negligible, the wall generates magnons which take away the conduction electron angular momentum given to the wall. In this case, j_c is found to reflect the equality of the rate of creation of linear magnon momentum to the maximum force generated by the pinning.

The largest pinning gap E_p arises when the wall is centered at the origin, i.e., with $\theta_0 = \pi/2$. Explicitly then, $S_{0z} \rightarrow S_{0x}$ and the diagonal part of $H_p = 2S A b_0^y b_0^y$. The value of E_p is determined by evaluating the commutator $[H_p; b_w^y]; b_w^y$, which is equivalent to taking the expectation value with respect to the b_w^y magnon wave function, and, with $j = 0$, gives,

$$E_p = S \frac{2A}{J}^{1/2} A; \quad (5)$$

The wall can now tilt so that θ is finite. The anisotropy $K_F \sum_i S_{iy}^2$ contains $3SK_F \sin^2 \theta \sum_i b_i^y b_i^y$ which gives the b_w^y mode an energy shift of $2SK_F \sin^2 \theta$. The maximum allowed value of θ therefore corresponds to $E_p = S (2A/J)^{1/2} A - 2SK_F \sin^2 \theta = 0$. This is related to the current through the terms in $K_F \sum_i S_{iy}^2$ which are linear in b_i and b_i^y . These are imaginary and can be

written as $j_x = (J=2A)^{1/2} K \sin 2\theta$ (where $K = \frac{eS}{\hbar}$). This cancels H_{tw} if $(\sim ja^2 = 2eS) = (S=2)(J=2A)^{1/2} K \sin 2\theta$ whence eliminating θ , assuming this is small, gives a critical current

$$j_{c1} = \frac{2eS^2}{\hbar a^2} \frac{J}{2A} \frac{1}{2} \frac{K}{A} \quad (6)$$

If K is small there is an intrinsic maximum current, $j_x = (eS^2/\hbar a^2)(J=2A)^{1/2} K$; for $\theta = \pi/4$, which will be reached before $E_p = 0$. It follows for large A that $j_x < j_{c1}$ and K is negligible. In order to conserve angular momentum, the wall must now produce magnons, i.e., be time dependent. Sought again are current-carrying eigenstates. To the $j = 0$ wall is added a twist characterized by $k(z) = \theta/z$ and the solution is rendered stationary by a rotation of angular frequency ω about the new axes i and i' . The new axes of quantization then correspond to $i = i' + i$ and i' . The effect of such a rotation is to add an effective magnetic field $\sim \hbar \omega/g_B$ which has an component $\sin i' \sim \hbar \omega/g_B$ perpendicular to the i' axis. The twist of the bond $i' + 1$ by $(\theta/z)a$ is introduced by $R_{i'i'+1} = e^{i(\theta/z)a S_{i'0} S_{i'+10}}$. Equilibrium, in the rotating frame, implies zero coefficients of both $b_{i'}$ and $b_{i'}$. The easiest fashion by which to establish these equilibrium conditions is to observe the local $S_{ix} = (2S)^{1/2} (1=2)(b_i + b_{i'})$ while $S_{iy} = (2S)^{1/2} (1=2i)(b_i - b_{i'})$. Given that, e.g., $R_y = e^{iS_{iy}}$ rotates the i th spin by a small θ it is easy to show by evaluating $[S_{iy}, H]$ that the coefficient of S_{ix} in H must be $(1=2S)(\theta E = \theta i)$ where $E f_{i'}$ is the already defined classical energy. The exchange part of this is $E_J = J \sum_i [\cos i \cos i+1 + \sin i \sin i+1 (\cos i \cos i+1 + \sin i \sin i+1)]$. A small rotation by θ is generated rather by $R_z = e^{iS_{iz}}$ where $S_{iz} = \cos i S_{iz} + \sin i S_{ix}$. However $[S_{iz}, H]$ contains no c -numbers and so this rotation determines the coefficient of S_{iy} , i.e., this is $(1=2S \sin i)(\theta E = \theta i)$. That the coefficient of S_{ix} be zero implies $[AS \sin 2i + JSa^2 (\theta^2/z^2) + (JSa^2)(\theta/z)^2 \sin 2i + \sim \hbar \sin i] = 0$. This can be re-integrated by i to give back the energy to within a constant, i.e., it is implied that:

$$[AS + \frac{JSa^2}{2} k(z)^2 \sin^2 i + (1=2)JSa^2 (\theta/z)^2 \sim \hbar (\cos i - 1)] = 0 \quad (7)$$

Using $\theta E_J = \theta$ for the coefficient of S_{iy} is obtained

$$\frac{\partial}{\partial z} i + \frac{JSa^2}{2} (\sin i) \frac{1}{\partial z} k(z) \sin^2 i = 0:$$

Integrating this with respect to z results in an equation relating currents:

$$(JSa)k(z) \sin^2 i + \frac{\sim ja^2}{eS} \cos i = \frac{\sim ja^2}{eS} \quad (8)$$

and gives

$$k(z) = \frac{1}{2(JSa) \cos^2 \frac{i}{2}} \frac{\sim ja^2}{eS} \quad (9)$$

which, with Eqn. (7), gives an equation for i . However, except to the extreme right of the wall, $i = i'$ and Eqn. (7) gives directly i while Eqn. (9) determines the twist $k(z)$. For the extreme right Eqn. (9) reduces to $(JSa)k_s i^2 = (\sim ja^2 = eS)$ which equates spin currents and ultimately determines amplitude i of the magnons leaving the system to the right, while Eqn. (7) reduces to $\sim \hbar = 2AS + JSa^2 k_s^2$ which, correctly, equates the frequency of the rotating frame to the magnon energy. The whole solution is then parameterized by the value of k_s . This, in turn, is determined by requiring that the absolute value of the ground state energy be a minimum. Given that the system is large compared to the width of the wall, the energy to be minimized is that of the coherent magnons to the right of the wall. The result is $k_s a = (2A=J)^{1/2}$ which corresponds a magnon energy per unit site of $e_r = (2A=J)^{1/2} (\sim ja^2 = e)$.

A relationship between e_r and the force on the wall is obtained by considering a wall displacement z generated by $R(z) = 1 + S^{1/2} (2A=J)^{1/4} (z=a)(b_{i'}^\dagger b_{i'})$. For the displaced wall $H R \dagger i = E_0 + e_r(z=a) R \dagger i$, not accounting for pinning. It follows that $E = [H; R(z)] = e_r(z=a)$ and that there is force $f = -E/z = -e_r/a$. Using $[H; R(z)] = S^{1/2} (2A=J)^{1/4} (z=a)[H; (b_{i'}^\dagger b_{i'})] = e_r(z=a)$ shows H contains $(2S)^{1/2} (2A=J)^{1/4} (\sim ja^2 = e)(b_{i'}^\dagger + b_{i'})$. A similar term arises from the linear part $P = S A \sin i \cos i (2S)^{1/2} (b_0^\dagger + b_0)$ of the pinning term, i.e., $[P; b_{i'}] = S^{3/2} (J=2A)^{1/4} S A \sin i \cos i (\theta/z)a$. Corresponding to $i = 55^\circ$, the maximum pinning force, is $(4=3\sqrt{3})S^{3/2} A (b_{i'}^\dagger + b_{i'})$. Finally, the magnon depinning current is obtained:

$$j_{c2} = \frac{4}{3} \frac{eS^2}{\hbar a^2} A \quad (10)$$

This key result is equivalent to equating the rate of creation of linear magnon momentum to the maximum force produced by the pinning potential.

The voltage across the wall is easily deduced. For large S , a non-polarized contact will inject a majority "electrons on the left and this defines $\mu = \mu_L$ as the chemical potential of the left contact. For an eigenstate, the energy to add the last "electron cannot depend on position and thus μ is the chemical potential for these electrons. One could imagine measuring μ on the right with a spin polarized contact. The destruction of such an electron involves destroying a magnon and hence μ must be exactly $\sim \hbar k$ higher in energy than $\mu = \mu_r$, i.e., the majority and contact chemical potential to the right, i.e., $\mu_r = eV = \sim \hbar k = 4AS$ for small currents. There is evidently a branch in balance.

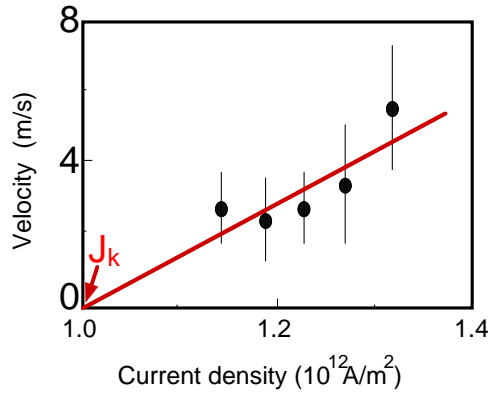


FIG. 1: The experimental points are taken from [3]. The solid line is estimated to correspond to the value of C from Eqn. (11) and to a $j_k = 1.0 \times 10^{12} \text{ A/m}^2$. (This has been corrected for the fact that the experimental material has a polarization $p = 0.7$.) Evidently to within the errors the conduction electron angular momentum, not destroyed by the pinning center is, transmitted to wall motion with efficiency equal to $p = 0.7$.

By design, Perm alloy has a small intrinsic anisotropy and both A and K_2 might be expected $\sim 2 M_0$ typically $\sim 0.1 \text{ T}$. This is several orders of magnitude smaller than J and it must be expected that, e.g., variations in the wire width lead to variations J_k and pinning. The largest effect occurs for the components of \vec{J} with a length scale which are comparable to the wall width. In this case the pinning gap E_p can be as large as $\sim S \cdot A \cdot J$. With this it would be the case that $j_k < j_{c1}$ and the time dependent solution with j_{c2} will apply.

Having considered free motion and pinning it is easy to solve the problem of slow motion with a pinning potential. If a wall is moving slowly and there are many pinning centers, the wall will adiabatically adjust to remain in the ground state. The wall width is $w = (J/2A)^{1/2}a$ and therefore the characteristic time the wall, with velocity v , interacts with the pinning center is $\tau = w/v$ and corresponds to an energy $E_c \sim \tau \sim (2A/J)^{1/2}(v/a)$. Adiabaticity requires that this be less than the energy of the magnons which are involved in the pinning deformations. At the worst these have a $k = 1/w$ and the energy involved is $\sim 2SA$ the gap in spin wave spectrum. Adiabaticity then implies $v < v_c \sim 2S(a/\sim)(A/J)^{1/2}$ which is $\sim (A/J)^{1/2}$ times the maximum spin wave velocity. Given the experimental values [5] correspond to $v \sim 3 \text{ m/s}$ this criterion is surely satisfied.

The principle of the calculation is to divide into two parts the rotating frames used to render the Bloch wall stationary, one of which corresponds to the translational motion and a second which reflects the pinning. The displacement corresponds to the rotation operator $R(\vec{z}) = \exp(i \sum_i (1+2) (\vec{e}_i \cdot \vec{z}) \cdot \vec{S}_i) (2S)^{1/2} (\vec{e}_i^y \cdot \vec{b}_i))$ where $\vec{z} = v\vec{t}$. Given the adiabatic approximation is well satisfied the rotations $R(v\vec{t})$ can be absorbed into slowly time dependent conduction electron operators $R(v\vec{t})c_i^\dagger R^\dagger(v\vec{t})$. In

this moving frame, the effective current density is reduced to $j^0 = j(1 - \frac{v}{v_0})$. Then following the calculation for pinning, the remaining rotations R_i^p are those required for the pinned ground state. The resulting j^0 is given by Eqn. (10) and is determined by the pinning strength. The difference between the actual current and that which can be pinned is $j - j^0$, and this in turn, determines v and its relationship with the current j . The velocity v is given by:

$$v = C(j - j_k); \quad C = \frac{a^3}{2eS} \quad (11)$$

where, as stated, j_k is the j_c given by Eqn. (10) except that average rather than maximum pinning strength is involved. The important result here is that C is independent of j_k , i.e., that part of the angular momentum current which is in excess of that converted to magnons by the pinning potential is 100% converted into motion of the wall. In Fig. (1) this prediction, corrected for $p = 0.7$, is compared with the experiments of Yamaguchi et al. Experimentally it is observed that there is a minimum velocity of $\sim 3 \text{ m/s}$ for which uniform motion is observed. It is reported that no motion of the wall is seen for currents smaller than $1.0 \times 10^{12} \text{ A/m}^2$ and taking this to be j_k implies the solid line shown in the figure with a gradient which would correspond to pC . What is strange is that the same velocity is reported for currents in the range $1.15 \times 10^{12} \text{ A/m}^2$ to $1.25 \times 10^{12} \text{ A/m}^2$. It is unfortunate that it is not possible to follow the system to higher velocities in order to see if the initial points have to do with threshold effects, e.g., reflecting the first order nature of the transition to the magnon producing pinned state. The wall will be displaced during the time that the magnon amplitude is developed and, in a pulse experiment, this might be interpreted as depinning.

This work was supported by a Grant-in-Aid for Scientific Research on Priority Areas from the Ministry of Education, Science, Culture and Technology of Japan, CREST and NAREGI. The SEB is on a temporary leave from the Physics Department, University of Miami, FL, U.S.A. and wishes to thank the members of IMR for their kind hospitality.

-
- [1] J.C. Slonowski, J. Mag. Mater. 159, L1 (1996).
 - [2] L. Berger, Phys. Rev. B 54, 9353 (1996).
 - [3] J. J. Versluijs, M. A. Bari, and J. M. D. Coey Phys. Rev. Lett. 87, 026601 (2001).
 - [4] D. A. Allwood, et al. Science 296, 2003-2006 (2002).
 - [5] A. Yamaguchi et al., Phys. Rev. Lett. 92, 077205 (2004).
 - [6] See e.g., C. Kittel, Quantum theory of solids, Wiley, New York (1963)
 - [7] G. Tataru, and H. Kohno, Phys. Rev. Lett. 92, 086601 (2004).