

1. 24 March 1997 (final accepted version)
2. Effect of the orthorhombic distortion on the magneto-optical properties of SrRuO_3
3. I. V. Solovyev
4. Joint Research Center for Atom Technology, Angstrom Technology Partnership, 1-1-4 Higashi, Tsukuba, Ibaraki 305, Japan
5. Abstract

It is argued that the non-collinear orbital magnetism accompanying the orthorhombic distortion is an important ingredient which should be taken into consideration for making promising materials with the best magneto-optical characteristics on the basis of SrRuO_3 .
6. keywords: Magneto-optical properties, Canted ferromagnetism, Band calculations, Perovskite structure
7. Corresponding author.

I. V. Solovyev
 JRCAT-ATP, c/o NAIR
 1-1-4 Higashi
 Tsukuba, Ibaraki 305
 JAPAN
 Fax: +81-298-54-2788
 E-mail: igor@jrcat.or.jp

Besides other interesting properties, SrRuO_3 is considered as one of rare examples of 4d itinerant magnets and a good candidate for applications in magneto-optical devices because of the large spin-orbit interaction (SOI) at the Ru sites [1]. The perspectives seem to be even more favorable after recent band structure calculations predicting nearly half-metallic behavior for SrRuO_3 in the actual orthorhombic D_{2h}^{16} structure [2]. Unfortunately, the magnetic ordering compatible with the space group D_{2h}^{16} implies a non-collinearity [3], which can be especially large for the orbital counterpart [4]. It means, although the spin magnetic moments (M_S) are ordered ferromagnetically, the orbital magnetic moments (M_L) can be canted on the spin directions and show an appreciable antiferromagnetic component. The latter is definitely a destructive factor for the magneto-optical characteristics of SrRuO_3 . The situation is just opposite to that considered in Ref.[4], where essentially non-collinear orbital magnetic ordering was the source of a pronounced optical nonreciprocity in the series of LaMnO_3 perovskites displaying only weak spin ferromagnetism.

In the present work we investigate the orbital non-collinearity and its consequences on the magneto-optical properties of SrRuO_3 using the band structure calculations in the local-spin-density approximation. Structural parameters were taken from Ref. [5]. In our numerical procedure we align the spin magnetic moments sequentially along the principal a , b and c directions of the orthorhombic cell and evaluate the responding band structure after including SOI as a pseudopoturbation in the ASA-LMTO method [6]. Then, the interband optical conductivity can be calculated using Eq.(5.1) of the work [7]. Details can be found elsewhere [4].

In the cubic perovskite structure, M_S at the Ru site is $1.220 \mu_B$, whereas M_L is almost negligible ($0.005 \mu_B$) due to the large cancelation of contributions with different spin quantum numbers. The effect of the orthorhombic distortion, which is accompanied by substantial rotations of RuO_6 octahedra relative to each other, is twofold. As the $\text{Ru}-\text{O}-\text{Ru}$ bond angles are reduced [5], the 4d-band is narrowed [2] and the spin polarization is increased ($M_S = 1.469 \mu_B$). These factors enhance the local orbital moments (Table 1). On the other hand, the orientational modulation of the RuO_6 octahedra causes analogous changes in the directions of the orbital moments [4]. Indeed, while initial arrangement of the spin magnetic moments was

ferromagnetic and totally collinear, the obtained distribution of the orbital magnetic moments largely deviates from the ferromagnetic one (Table 1) and, depending on the direction of the spin magnetization, belongs to one of the four types compatible with the space group D_{2h}^{16} [3].

Similar behavior is expected for the magneto-optical properties. For any direction of the ferromagnetic moment, the antisymmetric part of the conductivity tensor $\sigma^A(\omega) = (1/2) \sum_{\alpha\beta} \sigma_{\alpha\beta}^A(\omega) \hat{e}_\alpha \hat{e}_\beta$ is strongly suppressed in the region corresponding to the charge transfer excitations (around 4.5 eV in Fig.1) when the orthorhombic distortion is taken into account, whereas the diagonal part $\sigma_0(\omega) = (1/3) \sum_{\alpha} \sigma_{\alpha\alpha}(\omega)$ undergoes only small changes. Thus, the nonreciprocal optical rotation being proportional to $\sigma^A(\omega)$ can be renormalized dramatically in the orthorhombic SrRuO_3 . An example of the polar Kerr rotation, estimated as

$$\theta_K(\omega) = \text{Re} \left[\frac{\sigma^A(\omega)}{\sigma_0(\omega) \left(1 + \frac{\sigma^A(\omega)}{\sigma_0(\omega)} \right)^2} \right];$$

is shown in Fig.2 (we found that even in the orthorhombically distorted SrRuO_3 , the anisotropy of the diagonal conductivity is small and in fact $\sigma_0(\omega) \approx \sigma_{\alpha\alpha}(\omega)$). The renormalization will presumably be even more pronounced due to essential non-collinearity of the spin arrangement in this compound expected from the analysis of interatomic magnetic interactions [8], which implies a self-consistent treatment for the directions of the spin magnetic moments beyond the scopes of the present calculations.

The author is grateful to K. Terakura, Y. Suzuki and Y. Yokoyama for valuable discussions. The work is partly supported by New Energy and Industrial Technology Development Organization (NEDO).

References

- [1] L. Klein et al, Appl. Phys. Lett. 66, 2427 (1995).
- [2] D. J. Singh, J. Appl. Phys. 79, 4818 (1996).
- [3] D. Treves, Phys. Rev. 125, 1843 (1962).
- [4] I. V. Solovyev, Phys. Rev. B 55, 8060 (1997).
- [5] M. Shikano et al, Solid State Commun. 90, 115 (1994).
- [6] O. K. Andersen, Phys. Rev. B 12, 3060 (1975).
- [7] C. S. Wang and J. Callaway, Phys. Rev. B 9, 4897 (1974).
- [8] I. V. Solovyev, N. Hamada and K. Terakura, to be published in Physica B.

Table 1: Three possible directions of the ferromagnetic spin axis in the orthorhombic cell (S), orbital magnetic ordering induced by SOI (L), local orbital moment at Ru site (M_L) and deviation of the orbital moment from the ferromagnetic axis (θ). The non-collinear orbital ordering is classified by the type (antiferro-A, C, G and ferro-F) for each a, b and c projection of the magnetic moment.

S	L			M_L (μ_B)	θ (°)
eka	F _a	C _b	G _c	0.061	34.5
ekb	C _a	F _b	A _c	0.054	37.9
ekc	G _a	A _b	C _c	0.069	40.9

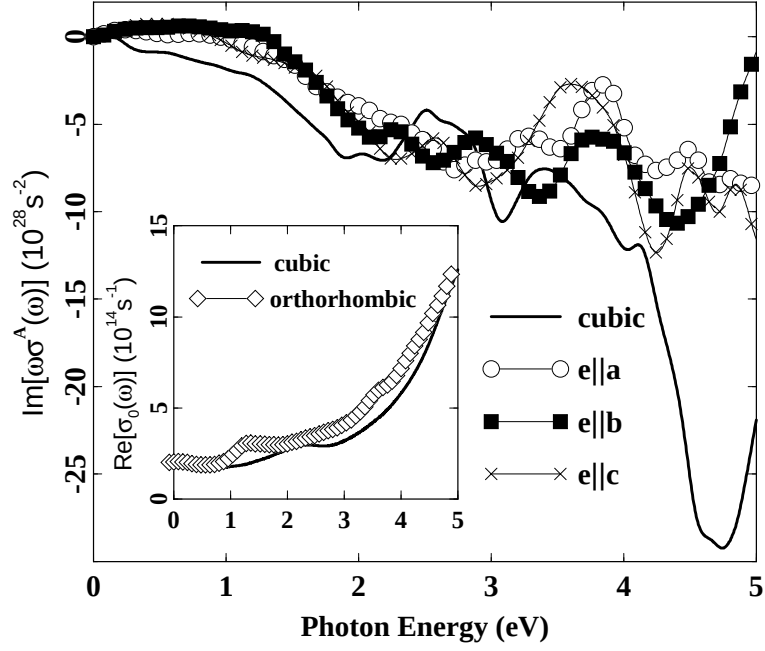


Figure 1: Antisymmetric (A) and diagonal ($_0$) parts of the interband optical conductivity calculated in the cubic perovskite and the actual orthorhombic structure of SrRuO_3 for three possible directions of the ferromagnetic spin moments in the orthorhombic cell. The phenomenological relaxation time of 10 m Ry was used for the broadening.

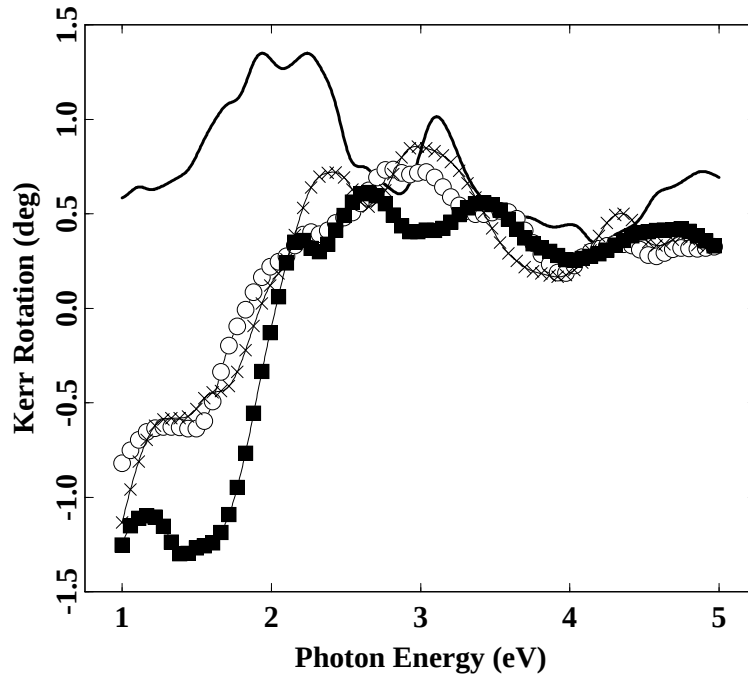


Figure 2: Polar Kerr rotation corresponding to the optical conductivities shown in Fig.1. No intraband Drude contributions have been added. Therefore, the infrared region of the spectra is not shown.