

Penetration depth anisotropy in two-band superconductors

V. G. Kogan, N. V. Zhelezina

Ames Laboratory – DOE and Department of Physics, Iowa State University, Ames, IA 50011

(Dated: July, 2003; March 22, 2024)

The anisotropy of the London penetration depth is evaluated for two-band superconductors with arbitrary inter- and intra-band scattering times. If one of the bands is clean and the other is dirty in the absence of inter-band scattering, the anisotropy is dominated by the Fermi surface of the clean band and is weakly temperature dependent. The inter-band scattering also suppresses the temperature dependence of the anisotropy.

PACS numbers: 74.70.Ad, 74.25.Nf, 74.60.-w

The two-gap superconductivity of MgB_2 is established experimentally^{1,2,3,4,5} and by solving the Eliashberg equations for the gap distribution on the Fermi surface.^{6,7} According to the latter, the gap on the four Fermi surface sheets of this material has two sharp maxima: $\Delta_1 \approx 1.7 \text{ meV}$ at the two γ -bands and $\Delta_2 \approx 7 \text{ meV}$ at the two π -bands. Within each of these groups, the spread of the gap values is small.

A number of physical properties of MgB_2 were reasonably well described within a model with two constant gaps on two separate Fermi sheets. Still, the data on anisotropy of the magnetic field penetration depth are controversial. The anisotropy parameter $\lambda = \lambda_c = \lambda_a$ has been calculated within the weak-coupling clean-limit model and shown to increase from about 1.1 at $T = 0$ to ≈ 2.6 at T_c .⁸ Similar prediction has been made within Eliashberg formalism.⁹ Qualitatively, the predictions were confirmed in STM,^{10,11} small angle neutron scattering,¹² and magnetization experiments.¹³ However, other groups recorded different behavior.^{14,15,16} Given variety of samples used, it seems imperative to consider effects of scattering upon λ , a non-trivial problem given different roles of the intra- and inter-band scattering in two-band materials.

In the following, we reiterate that in the presence of inter-band scattering, the energy gap in the quasiparticle excitation spectrum as revealed by the density of states (DOS) differs from both Δ_1 and Δ_2 ,^{17,18} the situation reminiscent of the Abrikosov-Gor'kov pair breaking.¹⁹ For this reason, we use the term "order parameter" for Δ 's. We stress that all thermodynamic properties depend on the actual DOS and are affected by the inter-band scattering. Then, we show that $\lambda = \lambda_c = \lambda_a$ depends on both inter- and intra-band scattering.

Our approach is based on the quasiclassical version of the BCS theory for a general anisotropic Fermi surface and for an arbitrary anisotropic order parameter $\Delta(\mathbf{k})$.²⁰ In the absence of currents and fields we have for the Eliashberg Green's functions $f(\mathbf{k}; i\omega)$ and $g(\mathbf{k}; i\omega)$:

$$0 = 2\Delta(\mathbf{k})g(\mathbf{k}; i\omega) + I; \quad 1 = g^2(\mathbf{k}; i\omega) + f^2(\mathbf{k}; i\omega) \quad (1)$$

Here the scattering term I is given by the integral over

the full Fermi surface:

$$I(\mathbf{k}) = \int_{\text{FS}} d^2q(\mathbf{q}) W(\mathbf{k}; \mathbf{q}) [g(\mathbf{k})f(\mathbf{q}) - f(\mathbf{k})g(\mathbf{q})] \quad (2)$$

with $W(\mathbf{k}; \mathbf{q})$ being the scattering probability from $\mathbf{q}$ to $\mathbf{k}$ at the Fermi surface. The Matsubara frequencies are $i\omega = T(2n+1)$ with an integer n ($\hbar = 1$). The local DOS $\rho(\mathbf{q})$ is normalized: $\int_{\text{FS}} d^2q \rho(\mathbf{q}) = 1$.

This system (1)–(2) should be complemented with an equation for $\Delta(\mathbf{k})$. We will not use it here, rather taking $\Delta(\mathbf{k})$ as a given. This simplifies the problem greatly because solving for $\Delta(\mathbf{k})$ usually involves a number of assumptions which are difficult to control.

We use the approximation of the scattering time:

$$\int_{\text{FS}} d^2q \rho(\mathbf{q}) W(\mathbf{k}; \mathbf{q}) f(\mathbf{q}) = \langle f \rangle; \quad (3)$$

where $\langle f \rangle$ stands for the average over the Fermi surface. Clearly, the approximation amounts to the scattering probability $W = 1$ being constant for any $\mathbf{k}$ and $\mathbf{q}$.

For two well-separated Fermi surface sheets, the probabilities of intra-band scatterings may differ from each other and from processes involving $\mathbf{k}$ and $\mathbf{q}$ from different bands. The effects of the inter- and intra-band scattering upon various properties of the system are different, e.g., the intra-band scattering does not affect T_c , whereas the inter-band does. Therefore, Eq. (3) is replaced by

$$\int_{\text{FS}} d^2q \rho(\mathbf{q}) W(\mathbf{k}; \mathbf{q}) f(\mathbf{q}) = \langle f \rangle_{\mathbf{k}} \quad (4)$$

Here $\langle f \rangle_{\mathbf{k}} = 1/2$ are band indices and $\langle f \rangle_{\mathbf{k}}$ denotes averaging only over the $\mathbf{k}$ -band.

We now assume the order parameters $\Delta(\mathbf{k})$ taking constant values Δ_1 and Δ_2 at each of the two bands. Writing Eq. (1) for $\mathbf{k}$ in the first band, we have:

$$0 = 2\Delta_1 g_1(\mathbf{k}; i\omega) + I_1; \quad 1 = g_1^2(\mathbf{k}; i\omega) + f_1^2(\mathbf{k}; i\omega) + \frac{1}{11} [g_1 \langle f \rangle_{i_1} - f_1 \langle g \rangle_{i_1}] + \frac{1}{12} [g_1 \langle f \rangle_{i_2} - f_1 \langle g \rangle_{i_2}]; \quad (5)$$

For a uniform sample in zero field and with $\mathbf{k}$ independent Δ 's in each band, the functions $f; g$ are $\mathbf{k}$ independent: $\langle f \rangle_{i_1} = f$ and $\langle g \rangle_{i_1} = g$. Then, we have:

$$0 = \Delta_1 g_1(\mathbf{k}; i\omega) + I_1; \quad 1 = g_1^2(\mathbf{k}; i\omega) + f_1^2(\mathbf{k}; i\omega) + 2\Delta_2 g_2(\mathbf{k}; i\omega) + I_2 \quad (6)$$

The equation for the second band differs from this by replacement $1 \leftrightarrow 2$. The fact that ϵ_{11} and ϵ_{22} do not enter the system (6) is similar to the case of one-band isotropic material for which non-magnetic scattering has no effect upon T_c (the Anderson theorem). It is the inter-band scattering that makes the difference in the two-gap case, the fact stressed already in early work.^{17,18}

Two equations (6) are complemented with normalizations $g^2 + f^2 = 1$ to form a sufficient set. Following Ref. 19, we introduce variables $u = g = f$ and obtain after simple algebra:^{17,18,21}

$$\frac{1}{u_1} = u_1 + \frac{1}{2} \frac{u_1 u_2}{u_2^2 + 1}; \quad \frac{1}{u_2} = \frac{1}{2} \frac{1}{u_1};$$

$$\frac{1}{u_2} = u_2 + \frac{1}{2} \frac{u_2 u_1}{u_1^2 + 1}; \quad \frac{1}{u_1} = \frac{1}{2} \frac{1}{u_2}; \quad (7)$$

The Eilenberger functions in terms of variables u read:

$$f = \frac{1}{1 + u^2}; \quad g = \frac{1}{1 + u^2}; \quad (8)$$

In general, the system (7) can be solved only numerically. However, near T_c , $u = g = f = 1$ and one obtains:

$$u_1 = \frac{1}{1} \frac{1 + \frac{1}{2} \frac{1 + \frac{1}{2} \frac{1}{2}}{1 + (\frac{1}{2} + \frac{1}{2}) \frac{1}{2}}}{1}; \quad (9)$$

u_2 is obtained by $1 \leftrightarrow 2$. Clearly, $u = 1$ in the absence of inter-band scattering. For 1 , we have:

$$u_1 = \frac{1}{1} \frac{1}{1 + \frac{1}{2} \frac{1}{2}}; \quad \frac{1}{u_2} = \frac{(1 + \frac{1}{2}) \frac{1}{2}}{1 + \frac{1}{2} \frac{1}{2}}; \quad (10)$$

Moreover, if the inter-band scattering is strong, Eq. (10) holds at any T . To see this, look for solutions of Eqs. (7) in the form

$$u = \frac{1}{1} + v; \quad \frac{1}{u} = 1; \quad (11)$$

where v are small corrections. Substitute these in Eqs. (7) and keep only linear terms in v to obtain

$$v_1 = \frac{g(1)}{1[1 + g(1 + \frac{1}{2})]} + \frac{(1 + \frac{1}{2} \frac{1}{2}) \frac{1}{2} (1 + \frac{1}{2})}{1 \frac{1}{2} [1 + g(1 + \frac{1}{2})]}; \quad (12)$$

where $g = \frac{1}{1 + \frac{1}{2} \frac{1}{2}}$. For 1 , v_1 remains small only if 1 is given by expression (10).

The DOS for two-band materials is $N(\epsilon) = N(0) \text{Re}(\frac{1}{2} g_1 + \frac{1}{2} g_2)$; g_i are fractions of the total DOS $N(0)$ at the two pieces of the Fermi surface. For strong inter-band scattering, this gives in the lowest approximation

$$N(\epsilon) = N(0) \frac{1}{2}; \quad (13)$$

i.e., 1 is the common for both bands energy gap.

It does not seem possible to provide a general expression for 1 in terms of 1 and an arbitrary inter-band scattering strength. Still, in principle, we can evaluate any thermodynamic property of a two-band material knowing the solutions u of the system (7) and the gap 1 .

If the ground state functions (which we call now $f^{(0)}$, $g^{(0)}$) are known, one can study perturbations of the uniform state such as penetration of a weak magnetic field, i.e., the problem of the London penetration depth. The perturbations, $f^{(1)}$; $g^{(1)}$, should be found from the full Eilenberger equations;²⁰ we have for the first band:

$$v \cdot f_1 = \frac{1}{2} g_1 - \frac{1}{2} f_1 + \frac{1}{11} [g_1 h f_{i1} - f_1 h g_{i1}] + \frac{1}{12} [g_1 h f_{i2} - f_1 h g_{i2}]; \quad (14)$$

Here, v is the Fermi velocity, $1 = r + 2 i A = 0$. The second equation is obtained by $1 \leftrightarrow 2$. Two equations for the "anomalous" functions f^+ are obtained from these by complex conjugation and by $v \rightarrow -v$.²⁰ The normalizations $g^2 + f^2 = 1$ complete the system.

We look for solutions in the form

$$f = (f^{(0)} + f^{(1)}) e^{i(x)}; \quad f^+ = (f^{(0)} + f^{(1)+}) e^{-i(x)};$$

$$g = g^{(0)} + g^{(1)}; \quad \frac{1}{g} = 1; \quad (15)$$

where $f^{(0)}$ and $g^{(0)}$ can be expressed in terms of u 's obtained solving the system (7). The form (15) takes into account that in the London approximation only the over-all phase depends on coordinates. We obtain for the corrections after some algebra:

$$g_1^{(1)} \frac{1}{1} - f_1^{(1)} \frac{1}{1} = i f_1^{(0)} v P = 2;$$

$$g_1^{(1)} \frac{1}{1} - f_1^{(1)+} \frac{1}{1} = i f_1^{(0)} v P = 2; \quad (16)$$

$$2 g_1^{(0)} g_1^{(1)} + f_1^{(0)} (f_1^{(1)} + f_1^{(1)+}) = 0;$$

where $P = r + 2 i A = 0$ and

$$\frac{1}{1} = \frac{1}{2} + f_1^{(0)} = \frac{1}{2} + f_2^{(0)} = \frac{1}{2}; \quad (17)$$

$$\frac{1}{1} = \frac{1}{2} + g_1^{(0)} = \frac{1}{2} + g_2^{(0)} = \frac{1}{2}; \quad (18)$$

The equations for the second band (decoupled from the first) are obtained by $1 \leftrightarrow 2$.

To evaluate the penetration depth we turn to the Eilenberger expression for the current density,²⁰

$$j = \frac{4}{3} \frac{1}{N(0) T} \text{Im} \sum_{k>0} h v g_i; \quad (19)$$

and compare it with the London relation

$$\frac{4}{c} j_i = (\epsilon^{-2})_{ik}^{-1} \frac{1}{2} r + A_k; \quad (20)$$

Here, $(\epsilon^{-2})_{ik}^{-1}$ is the tensor of the inverse squared penetration depth (proportional to the superfluid density tensor); summation over k is implied. We now find $g_i^{(1)}$ from

the system (16):

$$g_1^{(1)} = \frac{if_1^{(0)2} v_P}{2(f_1^{(0)} + f_1^{(0)})} = i \frac{f_1^{(0)2} g_1^{(0)}}{2f_1^{(0)}} v_P; \quad (21)$$

$g_2^{(1)}$ is obtained by replacement 1 $\leftrightarrow$ 2. Substituting $g^{(1)}$ in Eq. (19) and comparing with Eq. (20) we obtain:

$$(\lambda^2)_{ik}^{-1} = \frac{16 e^2 N(0) T^X}{c^2} \frac{h v_{ik} i}{f_1^{(0)}} \frac{f^2 g}{f_1^{(0)}}; \quad (22)$$

Only the unperturbed functions $f; g$ enter the penetration depth; for brevity we dropped the superscript (0). Equation (22) is our main result. Thus, to evaluate the penetration depth for given order parameters in the presence of scattering, one has to solve the system (7) for $u(i)$, then to substitute the equilibrium functions $f; g$ (given in (8)) in Eq. (22) to sum up over i .

The band calculations²² yield for MgB_2 the following averages: $h v_a^2 i_1 = 33.2$, $h v_c^2 i_1 = 42.2$, $h v_a^2 i_2 = 23$, and $h v_c^2 i_2 = 0.5 \cdot 10^4 \text{ cm}^2/\text{s}^2$. Tensors $h v_{ik} i_1$ and $h v_{ik} i_2$ have opposite anisotropies:

$$\frac{h v_a^2 i_1}{h v_c^2 i_1} = 0.79; \quad \frac{h v_a^2 i_2}{h v_c^2 i_2} = 46.; \quad (23)$$

whereas averaging over the whole Fermi surface yields a nearly isotropic result: $h v_a^2 i = h v_c^2 i = 1.2$.

In the clean limit (all $i \rightarrow 1$) $f^{(0)} = 1$ and $g^{(0)} = 0$. Besides, $u = 1$ and $f^2 g = 0 = 2/(1 + 2)^{3/2}$. Expression (22) reduces to the result given in Ref. 8. For MgB_2 , it gives nearly isotropic penetration depth at low temperatures: at $T = 0$ the sums over i in Eq. (22) are the same; this gives $(\lambda^2)_{ik} = \lambda_{cc}^2 = \lambda_{aa}^2 = \frac{h v_a^2 i = h v_c^2 i}{h v_a^2 i = h v_c^2 i} = 1.1$. Near T_c , the sums are $\propto 1/T^2$, and the contribution of the strongly anisotropic b -band with the large gap dominates; this gives $(\lambda^2)_{ik} \rightarrow 2.6$. The curve 1 in Fig. 1 shows $(\lambda^2)_{ik}$ for this case.

Zero inter-band scattering ($i_2 = i_1 = 1$). If only the intra-band scattering is present, the functions $f; g$ are the same as in the clean limit. We readily obtain:

$$\frac{f^2 g}{f_1^{(0)}} = \frac{2}{2(1 + 1/2)}; \quad (24)$$

with $2 = 1^2 + 2^2$. This expression appears in the standard penetration depth calculations, see e.g. Ref. 23. For known $(\lambda^2)_{ik}(T)$, the sums in Eq. (22) can be evaluated numerically; however, for $T \rightarrow 0; T_c$, and in the dirty limit they can be done analytically.

At $T = 0$, the sums are replaced with integrals according to $2 T \sum_i = \int_0^1 d! \cdot$. Denoting $I(T) = 2 T \int_0^1 d! = 2(1 + 1/2)$ we obtain $I(0) = 1$ for $i \rightarrow 1$ and $I(0) = 2$ for $i \rightarrow 2$.

Near T_c , $g \rightarrow 1$ and we have for clean bands $f^2 = 1 = 7/8 = 3 T_c^3$, whereas for dirty bands it is $f^2 = 4 T_c^2$.

Different impurities introduced to MgB_2 may affect differently the scattering within the bands.^{24,25} It is of interest to see how the anisotropy of λ is affected by differences in scattering times τ_1 and τ_2 . We first look at two limiting situations when one of the bands is clean while the other is dirty. If the first (i_1) band is clean and the second (i_2) is a dirty extreme ($i_2 \rightarrow 0$), one can disregard the contribution of the dirty band to obtain for both $T = 0$ and $T = T_c$:

$$(\lambda^2)_{ik} = (\lambda^2)_{ik}(T_c) \frac{\sum_i \frac{h v_a^2 i_1}{h v_c^2 i_1}}{\sum_i \frac{h v_a^2 i_1}{h v_c^2 i_1}} = 0.89; \quad (25)$$

If the (i_1) band is dirty and the (i_2) is clean, we have

$$(\lambda^2)_{ik} = (\lambda^2)_{ik}(T_c) \frac{\sum_i \frac{h v_a^2 i_2}{h v_c^2 i_2}}{\sum_i \frac{h v_a^2 i_2}{h v_c^2 i_2}} = 6.8; \quad (26)$$

These two numbers constitute the minimum and maximum possible values for anisotropy of MgB_2 . Thus, when one of the bands is clean and the other is dirty we expect a weakly T dependent λ , the value of which is determined by the clean band.

If the intra-band scattering is strong in both bands ($i_1 \rightarrow 0, i_2 \rightarrow 0, i_1 = i_2 = 1$), the bands contribute to the superfluid density tensor $(\lambda^2)_{ik}^{-1}$ as two independent dirty superconductors. To see this, we note that $f_1^{(0)} g_1 = 2 \tau_1$ and the sums over i in Eq. (22) can be evaluated exactly:

$$\sum_i \frac{f_1^2 g_1}{f_1^{(0)}} = \sum_i \frac{2 \tau_1 \frac{1}{2}}{1^2 + \frac{1}{2}} = \frac{11}{2T} \tanh \frac{1}{2T}; \quad (27)$$

Then, we arrive at the result obtained by Gurevich with the help of the dirty limit Usadel equations:²⁶

$$(\lambda^2)_{ik}^{-1} = \frac{4}{c^2} \sum_i \frac{(\lambda^2)_{ik}}{\tau_{ik}} \tanh \frac{1}{2T} \quad (28)$$

where the anisotropic conductivities of the two bands $(\lambda^2)_{ik} = 2e^2 h v_{ik} i N(0)$ are introduced (we write here $\sim$ explicitly to avoid confusion in dimensions). This yields:

$$(\lambda^2)_{ik} = \frac{\frac{(1)_{aa}}{cc} \frac{1}{1} + \frac{(2)_{aa}}{cc} \frac{2}{2}}{\frac{(1)_{aa}}{cc} \frac{1}{1} + \frac{(2)_{aa}}{cc} \frac{2}{2}}; \quad (29)$$

$$(\lambda^2)_{ik}(T_c) = \frac{\frac{(1)_{aa}}{cc} \frac{2}{1} + \frac{(2)_{aa}}{cc} \frac{2}{2}}{\frac{(1)_{aa}}{cc} \frac{2}{1} + \frac{(2)_{aa}}{cc} \frac{2}{2}}; \quad (30)$$

Finally, we discuss the possibility of a strong inter-band scattering. As was shown above, in this case $u = 1 = 1 +$

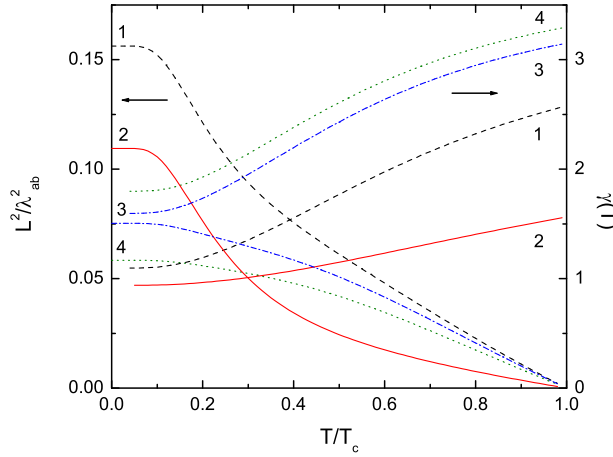


FIG. 1: The anisotropy $\gamma = \frac{\lambda_c^2}{\lambda_{ab}^2}$ and the inverse square of the penetration depth $L^2 = \frac{\lambda_c^2}{\lambda_{ab}^2}$ versus T/T_c ; $L^2 = 16 \frac{e^2 N(0) \hbar v_a^2}{c^2}$. The curves labelled 1 is the clean limit, all Γ 's are zero. The curves labelled 2 and 3 are calculated for a weak inter-band scattering: $\Gamma_{12} = \Gamma_{21}(0) = 500$, $\Gamma_{11} = \Gamma_{22}(0) = 2000$ (~ 1); the curve 2 is for a clean band, $\Gamma_{11} = \Gamma_{22}(0) = 10$, and a dirty band, $\Gamma_{22} = \Gamma_{22}(0) = 0.1$; the curve 3 is for a dirty and clean band: $\Gamma_{11} = \Gamma_{11}(0) = 0.1$, $\Gamma_{22} = \Gamma_{22}(0) = 10$. Curves 4 are for the intermediate inter-band scattering strength $\Gamma_{12} = \Gamma_{21}(0) = 5$, $\Gamma_{11} = \Gamma_{11}(0) = 20$, and $\Gamma_{22} = \Gamma_{22}(0) = 0.05$, $\Gamma_{21} = \Gamma_{21}(0) = 2$.

0 ($\Gamma = 0$) in both bands, see Eqs. (11) and (12). Then, the Eilenberger functions are also the same in the two bands: $f = \frac{\Gamma_{12}}{\Gamma_{11} + \Gamma_{12}}$, $g = \frac{\Gamma_{21}}{\Gamma_{22} + \Gamma_{21}}$. Evaluation of the sums over $\mathbf{k}$ in Eq. (22) is now simple:

$$(\gamma^2)_{ik}^1 = \frac{8 \frac{e^2 N(0)}{c^2} \tanh \frac{\hbar v_k}{2T}}{\hbar v_k} \quad (31)$$

where $\gamma(T)$ is given in Eq. (10) and

$$\gamma_1 = \frac{\Gamma_{12}}{\Gamma_{11} + \Gamma_{12}}; \quad \gamma_2 = \frac{\Gamma_{21}}{\Gamma_{22} + \Gamma_{21}} \quad (32)$$

Thus, all components of $(\gamma^2)_{ik}$ have the same T dependence and the anisotropy parameter is T independent:

$$\gamma^2 = \frac{\gamma_1 \hbar v_a^2 \gamma_1 + \gamma_2 \hbar v_a^2 \gamma_2}{\gamma_1 \hbar v_c^2 \gamma_1 + \gamma_2 \hbar v_c^2 \gamma_2} \quad (33)$$

If all Γ 's are the same, we have:

$$\gamma^2 = \hbar v_a^2 \gamma \hbar v_c^2 \gamma \quad (34)$$

For $T \rightarrow T_c$, this result was obtained in Ref. 8; we now see that it holds at any temperature.

To recover the behavior of $\gamma(T)$ between 0 and T_c one needs explicit dependencies $\gamma(T)$. Qualitatively, this behavior can be studied assuming $\gamma(T) \approx \gamma(0) (1 - T/T_c)$ with, e.g., $\gamma_2(0) = 4 \gamma_1(0) = 2T_c$. Figure 1 shows results of numerical evaluation of $\gamma(T)$ for scattering parameters given in the caption (which are not that extreme as in the above discussion). The curves $\gamma(T)$ are obtained by solving Eqs. (7) for u 's in two bands and then by evaluation of the sums in Eq. (22). It is worth noting that although the T dependences shown in the figure are obtained using approximate $\gamma(T)$, the end points of these curves at $T = 0$ and $T = T_c$ are exact.

We conclude that both the inter- and intra-band scattering affect strongly the superconducting anisotropy of two-band superconductors in general and of MgB_2 , in particular. If one of the MgB_2 bands is dirty, the anisotropy is dominated by a cleaner band: $\gamma(T)$ is close to unity (and might be even less than 1) if the band is in the clean limit, whereas in the opposite situation of a clean band, $\gamma(T)$ is large being in both cases weakly T dependent. The inter-band scattering suppresses the T dependence of γ as compared to the clean limit discussed earlier.⁸

We thank J. Clem and S. Bud'ko for useful discussions. Ames Laboratory is operated for the U. S. Department of Energy by Iowa State University under Contract No. W-7405-Eng-82.

- ¹ F. Bouquet et al. N.E. Phillips, Europhys. Lett. 56, 856 (2001).
- ² P. Szabo et al. Miraglia, C. Phys. Rev. Lett. 87, 137005 (2001).
- ³ F. Gubileo et al. Phys. Rev. Lett. 87, 177008 (2001).
- ⁴ Y. Wang, T. Plackovski, A. Junod, Physica C, 355, 179 (2001).
- ⁵ H. Schmidt et al. Phys. Rev. Lett., 88, 127002 (2002).
- ⁶ H. J. Choi et al. cond-mat/0111183.
- ⁷ A. Y. Liu, I. I. Mazin, and J. Kortus, Phys. Rev. Lett. 87, 0877005 (2001).
- ⁸ V. G. Kogan, Phys. Rev. B 66, 020509 (2002).
- ⁹ A. A. Golubov et al. Phys. Rev. B 66, 054524 (2002).
- ¹⁰ M. R. Eskildsen et al. Physica C, 143-144, 388 (2003).
- ¹¹ M. R. Eskildsen et al. Phys. Rev. B 68, 100508 (2003).

- ¹² R. Cubitt et al. Phys. Rev. Lett. 91, 047002 (2003).
- ¹³ L. Lyard et al. cond-mat/0307388.
- ¹⁴ K. Takahashi et al. Phys. Rev. B 66, 012501 (2002).
- ¹⁵ M. Angst et al. Phys. Rev. Lett. 88, 167004 (2002).
- ¹⁶ G. K. Perkins et al. Superc. Sci. Technol. 15, 1156 (2002).
- ¹⁷ V. A. Moskalenko, A. M. Ursu, and N. I. Botoshan, Phys. Lett. 44A, 183 (1973).
- ¹⁸ N. Schopohl and K. Schamberg, Sol. State Comm., 22, 371 (1977).
- ¹⁹ A. A. Abrikosov and L. P. Gor'kov, Sov. Phys. JETP, 12, 1243 (1961).
- ²⁰ G. Eilenberger, Z. Phys. 214, 195 (1968).
- ²¹ C. C. Sung and V. K. Wong, Journ. Phys. Chem. Solids, 28, 1933 (1967).
- ²² K. D. Belashchenko, M. van Schilfhaarde, and V. P.

- Antropov, Phys. Rev. B 64, 092503 (2001).
- ²³ A. A. Abrikosov, L. P. Gor'kov, and I. E. Dzyaloshinsky, Methods of the Quantum Field Theory in Statistical Physics, 1962.
- ²⁴ I. Mazin et al. Phys. Rev. Lett. 89, 107002 (2002).
- ²⁵ M. Putti et al. Superc. Sci. Technol. 16, 188 (2003).
- ²⁶ A. Gurevich, Phys. Rev. B 67, 184515 (2003).