

Large anisotropy in the paramagnetic susceptibility of  $\text{SrRuO}_3$  films

Yevgeny Kats, Isaschar Genish, and Lior Klein

Department of Physics, Bar-Ilan University, Ramat-Gan 52900, Israel

James W. Reiner and M. R. Beasley

T. H. Geballe Laboratory for Advanced Materials, Stanford University, Stanford, California 94305

By using the extraordinary Hall effect in  $\text{SrRuO}_3$  films we performed sensitive measurements of the paramagnetic susceptibility in this itinerant ferromagnet, from  $T_c$  ( $\sim 150$  K) to 300 K. These measurements, combined with measurements of magnetoresistance, reveal that the susceptibility, which is almost isotropic at 300 K, becomes highly anisotropic as the temperature is lowered, diverging along a single crystallographic direction in the vicinity of  $T_c$ . The results provide a striking manifestation of the effect of exceptionally large magnetocrystalline anisotropy in the paramagnetic state of a 4d itinerant ferromagnet.

PACS numbers: 75.30.Gw, 75.40.Cx, 75.50.Cc, 72.25.Ba

The coupling of spin to electronic orbitals yields the ubiquitous phenomenon of magnetocrystalline anisotropy (MCA) in ferromagnets [1]. While the manifestation of MCA below  $T_c$  in the form of hard and easy axes of magnetization is well studied, the fact that the strength of the MCA decreases with temperature as a high power of the spontaneous magnetization [2] could give the impression that MCA effects above  $T_c$  are at most a weak perturbation. Here we show that the MCA has a significant effect in the paramagnetic state of the 4d itinerant ferromagnet  $\text{SrRuO}_3$  over a wide range of temperatures (not only is the susceptibility diverging along a single axis at  $T_c$ , but the difference between the susceptibilities along the different crystallographic axes is noticeable (more than 30%) already at  $T - T_c = T_c = 0.5$ ).

A paramagnetic susceptibility diverging along only one crystallographic direction has been reported previously for bulk specimens of  $\text{Cu}(\text{NH}_4)\text{Br}_4 \cdot 2\text{H}_2\text{O}$  [3], but the anisotropy there was found to be only 2% of the exchange integral  $J$  (compared to 20% which we find in  $\text{SrRuO}_3$ ). Another report refers to two-dimensional cobalt films, where an anisotropy of 5% was measured [4]. In both cases, the temperature range for which the susceptibility was measured is by an order of magnitude smaller (in units of  $T_c$ ) than in our measurements of the three-dimensional  $\text{SrRuO}_3$  films.

Measuring the paramagnetic susceptibility in films poses a considerable technical challenge due to the combination of small magnetic moment of the film with large background signal from the substrate. We avoided these difficulties by using the extraordinary Hall effect (EHE) whose signal depends on the film internal magnetization and not on the total magnetic moment of the sample. Therefore, the signal does not diminish with decreasing thickness, neither is it affected by the substrate magnetization.

We study high-quality epitaxial films of the itinerant ferromagnet  $\text{SrRuO}_3$  ( $T_c \sim 150$  K) with thicknesses in the range of 6–150 nm patterned by photolithography for

measurements of resistivity and Hall effect. The unit cell is orthorhombic ( $a = 5.53$  Å,  $b = 5.57$  Å,  $c = 7.85$  Å), and the single easy axis of magnetization is roughly in the  $b$  direction [5, 6]. The films are grown by reactive electron beam coevaporation [7] on miscut ( $\sim 2^\circ$ )  $\text{SrTiO}_3$  substrates. This technique produces single-phase films with the [110] direction perpendicular to the surface (as was shown by transmission electron microscopy study of films grown in the same apparatus [5]), so that the  $b$  direction is at  $45^\circ$  out of the plane of the film.

The transverse electric field  $E_H$  in magnetic conductors originates from both the ordinary (or regular) Hall effect (OHE), which depends on the magnetic induction  $B$ , and the extraordinary (or anomalous) Hall effect (EHE), which depends on the magnetization  $M$ :

$$E_H = R_0 J \times B + R_s J \times \nabla M,$$

where  $J$  is the current density,  $R_0$  is the ordinary Hall coefficient related to the carrier density  $n$ , and  $R_s$  is the extraordinary Hall coefficient whose temperature dependence in the ferromagnetic phase of  $\text{SrRuO}_3$  has been reported in Refs. [8, 9].

In measurements above  $T_c$  we found that a significant Hall effect develops even when the magnetic field is applied parallel to the current which flows along the [110] direction. The temperature dependence of this Hall effect resembles the behavior of the induced magnetization (see Fig. 1). These results indicate that the in-plane field generates a significant out-of-plane component of  $M$ , resulting in a measurable EHE. This implies that the paramagnetic susceptibility of  $\text{SrRuO}_3$  films is described by an anisotropic tensor.

For quantitative characterization of the susceptibility anisotropy, we measured the Hall effect as a function of field direction at various temperatures. For each temperature above  $T_c$ , a small field limit exists, where the magnetization depends linearly on the field and can be fully described in terms of constant susceptibilities  $\chi_a$ ,

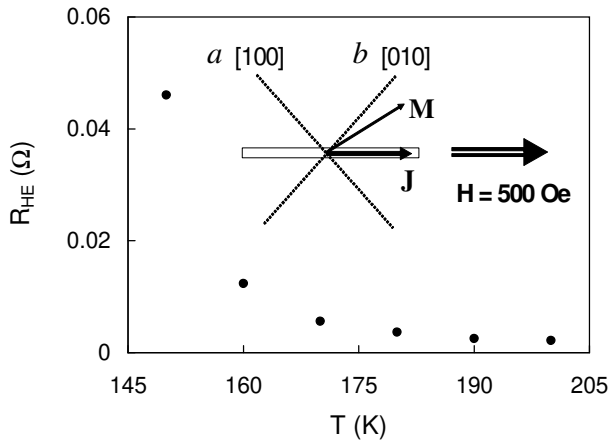


FIG. 1: Hall effect with  $H = 500$  Oe applied parallel to the current (along the  $[110]$  direction) as a function of temperature above  $T_c$  ( $\approx 147$  K).

$b$ , and  $c$  along the  $a$ ,  $b$ , and  $c$  crystallographic directions, respectively ( $\chi_0 M_a = \chi_a H_a$ , etc). An example of measurements in this limit is shown in Fig. 2, where the EHE resistance ( $R_{EHE} = \chi_0 R_s M_z / t$ , where  $t$  is the thickness of the sample) is shown for two different fields at  $T = 153$  K as a function of the angle (see inset). The solid curve is a fit obtained by assuming certain values of  $\chi_a$  and  $\chi_b$ , based on the equation:

$$R_{EHE}(H; \theta) = \frac{R_s H}{2t} (\chi_b \cos \theta + \chi_a \sin \theta).$$

Figure 2 also demonstrates the relatively small magnitude and different angular dependence of the OHE, which was subtracted from the measured signal [10].

The main result of this Letter is presented in Fig. 3, which shows the temperature dependence of the susceptibilities  $\chi_a$  and  $\chi_b$  (multiplied by  $R_s$ ). We see that the susceptibility is very anisotropic throughout most of the investigated temperature range. Particularly,  $\chi_b$  exhibits striking divergence at  $T_c$ , while  $\chi_a$  changes moderately. The actual divergence of  $\chi_b$  is even stronger than shown in Fig. 3 since  $\chi_b$  was not corrected for the demagnetizing field (because of uncertainty in the value of  $R_s$ ); consequently, the apparent susceptibility in our measurement configuration is only  $\chi_b = (1 + N_b) \chi_b$ .

Since the  $c$  direction is in the plane of the film, the EHE measurement could not be used to determine  $\chi_c$  (the insensitivity of EHE to a field component in the  $c$  direction was experimentally confirmed). Therefore, measurements of magnetoresistance (MR)  $R(H) = R(0) + \Delta R$  were employed [11]. Based on previous [12] and current results (see inset to Fig. 4),  $\Delta R / M^2$  (for a constant direction of magnetization). Thus we can infer the susceptibility behavior along  $a$ ,  $b$ , and  $c$  directions by comparing the MR obtained with fields applied along these directions. The results, shown in Fig. 4, clearly indicate that the induced magnetization along the  $b$  direc-

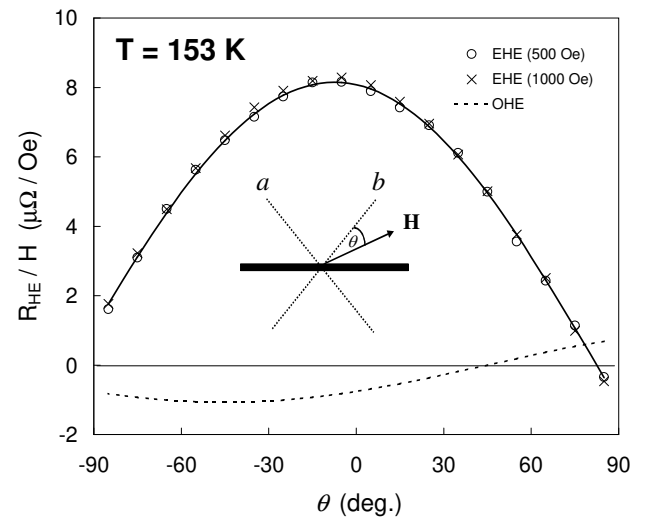


FIG. 2: EHE at  $T = 153$  K divided by the applied field  $H$  (circles: 500 Oe, crosses: 1000 Oe) as a function of the angle between  $H$  and the  $b$  direction (see illustration). The dashed curve is the OHE. The solid curve is a fit obtained by assuming certain constant values for the susceptibility along the  $a$  and  $b$  directions:  $R_s \chi_a = 0.48 \times 10^{-9}$  m/T,  $R_s \chi_b = 3.60 \times 10^{-9}$  m/T.

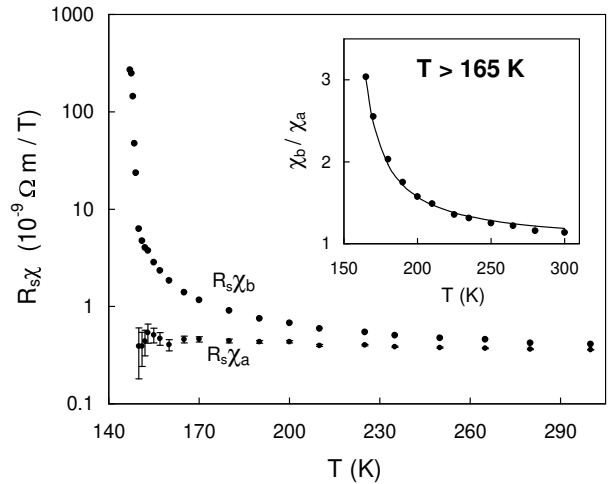


FIG. 3: Susceptibility along the crystallographic directions  $[100]$  ( $\chi_a$ ) and  $[010]$  ( $\chi_b$ ) as a function of temperature, on a semi-log plot. The values are multiplied by  $R_s$ , whose temperature dependence is expected to be smooth. The error bars for  $R_s \chi_a$  reflect an uncertainty of up to 2 in  $\chi$ . The inset shows the ratio  $\chi_b / \chi_a$  for  $165 \text{ K} < T < 300 \text{ K}$ . The solid curve is a fit to  $T / T_{c/a}^{M/F} = T / T_{c/b}^{M/F}$  with  $T_{c/a}^{M/F} = 123 \text{ K}$ ,  $T_{c/b}^{M/F} = 151 \text{ K}$ .

tion grows as  $T_c$  is approached much more rapidly than along the  $a$  or  $c$  directions. The divergence here is less pronounced than in Fig. 3 since for fields applied here the magnetization along  $b$  is sub-linear (but using lower fields would not allow obtaining accurate MR data for the  $a$  and  $c$  directions). The temperature dependence of the MR with  $H \parallel c$  is very similar to the MR with

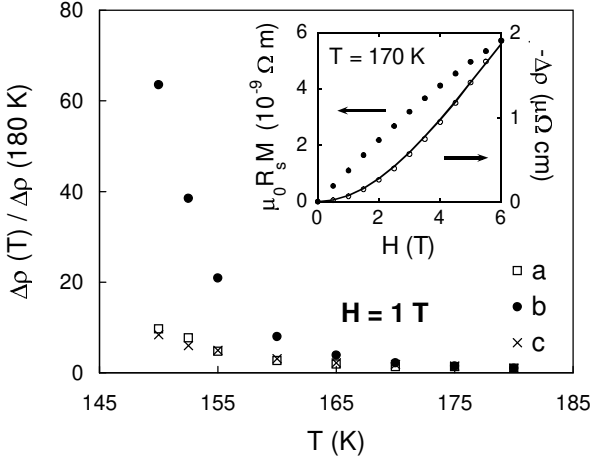


FIG. 4: Magnetoresistance as a function of temperature with a field of 1 T applied along the different crystallographic directions (the values are normalized to the values at 180 K). The inset shows the magnetization ( $\mu_0 R_s M$ ) and magnetoresistance ( $\Delta\rho$ ) as a function of a field (applied along the b direction, at  $T = 170$  K). The solid curve is a fit to  $\Delta\rho/M^2$ .

Hooka, suggesting that the behavior of  $\rho_c$  is similar to the behavior of  $\rho_a$ .

The data in Figs. 3 and 4 imply that only the susceptibility along the b direction (which is also the easy axis of the spontaneous magnetization [5, 6]) diverges at the phase transition; moreover, the large anisotropy of the susceptibility is noticeable ( $> 30\%$ ) already at  $T - T_c = T_c = 0.5$ .

We note that this result is consistent with a previous report on Ising-like critical behavior in  $\text{SrRuO}_3$  [12] and with the possibility to fit specific heat data of  $\text{SrRuO}_3$  crystals with Ising exponent [13]; an alternative analysis of the critical behavior given in Ref. [13] does not seem to be consistent with the results reported here.

Anisotropy in the behavior of the susceptibility arising from MCA may be described microscopically by Heisenberg model with anisotropic exchange:

$$H = \sum_{\langle ij \rangle} J_{ij} S_i \cdot S_j \quad (1)$$

or with single-site anisotropy:

$$H = \sum_{\langle ij \rangle} J_{ij} S_i \cdot S_j + \sum_i D_i S_i^2, \quad (2)$$

where  $a, b, c$  denotes spin components along the crystalline directions, and  $i, j$  denote lattice sites. Band calculations [14] and spin polarization measurements [15] show that  $\text{SrRuO}_3$  is an itinerant ferromagnet. However, various theoretical models (e.g., the local band theory [16]) indicate that magnetic moments in itinerant ferromagnets can behave as if localized even above  $T_c$ , thus vindicating the description of their magnetic interactions by Heisenberg Hamiltonian. The experimental

observation that the exchange splitting in  $\text{SrRuO}_3$  does not change much as  $T_c$  is approached [17] supports the relevance of such a treatment to  $\text{SrRuO}_3$ .

Since  $T_c/J$ , anisotropic exchange results in a different effective  $T_c$  for each spin component. Consequently, only the susceptibility along the direction with the largest  $J$  diverges at the actual  $T_c$  [18]. Single-site anisotropy yields the same critical behavior [18], with an effective  $J = D/z$ , where  $z$  is the number of nearest neighbors.

The anisotropy  $J$  (or  $D$ ) can be estimated from the susceptibilities in the mean-field region, which are expected to follow the Curie-Weiss  $1/T - T_c^{MF}$  law (with different mean-field transition temperature  $T_c^{MF}$  for each direction), if Pauli paramagnetism and diamagnetism can be neglected [19]. We cannot treat  $R_{sa}$  or  $R_{sb}$  as a function of temperature because the temperature dependence of  $R_s$  is unknown. However, the ratio  $\rho_b/\rho_a$  does not depend on  $R_s$ , and fitting the data to the expression  $T - T_{cja}^{MF} = T - T_{cjb}^{MF}$  converges to the values  $T_{cja}^{MF} = 123 \pm 2$  K,  $T_{cjb}^{MF} = 151 \pm 1$  K for  $165 \text{ K} < T < 300$  K (see inset in Fig. 3). From these values we find an anisotropy of  $J_b/J_a \approx 0.2 J_{\text{avg}}$  or  $D_b/D_a \approx 0.2 J_z$ . This result is almost thickness-independent from 6 to 150 nm (the data presented above are from a 30-nm film).

To examine whether the paramagnetic anisotropy is consistent with the ferromagnetic anisotropy we performed magnetization measurements below  $T_c$ . However, noting that the easy axis of the magnetization, which is along the b direction close to  $T_c$ , changes its orientation as the temperature is lowered (by a maximum of  $15^\circ$  at zero temperature) [21] and considering that additional factors become significant when the magnetization is large, the most we can expect is an order-of-magnitude agreement between the paramagnetic and the ferromagnetic anisotropy.

Using a SQUID magnetometer which measures the whole magnetization vector we estimated the ferromagnetic anisotropy by measuring the rotation of  $\mathbf{M}$  resulting from applying a magnetic field in the  $[1\bar{1}0]$  direction. We find, between 10 and 90 K, a smooth rotation of  $\mathbf{M}$  in the (001) plane by up to  $20^\circ$  at  $H = 5$  T (see Fig. 5) almost without change of magnitude [22]. This behavior can be described by an anisotropy energy,  $E_{\text{anis}} = K \sin^2 \theta$ , with a weakly-temperature-dependent anisotropy constant  $K$  whose low-temperature value is  $(1.2 \pm 0.1) \times 10^7$  erg/cm<sup>3</sup>.

The large anisotropy constant (compared to  $5 \times 10^5$  erg/cm<sup>3</sup> in Fe [23],  $8 \times 10^5$  erg/cm<sup>3</sup> in Ni [24], and  $4 \times 10^6$  erg/cm<sup>3</sup> in hcp Co [25]) is probably a result of the reduced symmetry (orthorhombic) [26] and the large spin-orbit coupling [27] through which the spin direction is affected by the crystal structure.

To relate the ferromagnetic anisotropy with Eqs. (1) and (2), we note that at low temperature the exchange aligns the spins along a single direction, thus the en-

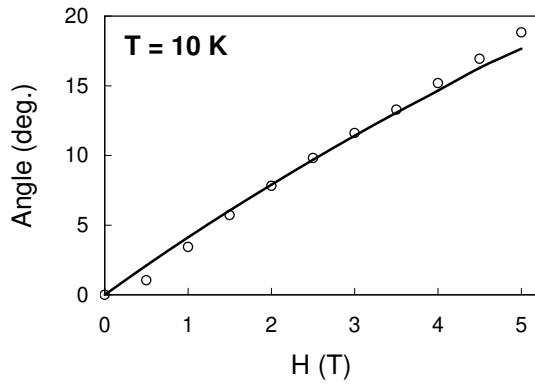


FIG. 5: Deviation of the magnetization from the easy axis as a function of the field which is applied at 60° relative to the easy axis. The solid curve presents the expected behavior with an anisotropy constant of  $1.2 \cdot 10^7$  erg/cm<sup>3</sup>.

ergy cost of magnetization rotation from the *b* direction toward the *a* direction by an angle  $\theta$  in the case of anisotropic exchange is  $E = zN S^2 (J_b - J_a) \sin^2 \theta$ , where  $N$  is the number of spins per unit volume. A similar result is obtained in the case of single-site anisotropy. Considering that the zero-temperature magnetization is  $1.4 \mu_B$  per Ru ion, and calculating  $J$  according to the relation  $J = 3k_B T_C^M / F = 2zS(S+1)$  we obtain  $J_b - J_a = 0.1 J_{\text{avg}}$ . This result is in reasonable agreement with  $J_b - J_a = 0.2 J_{\text{avg}}$  extracted from the anisotropic susceptibility.

Finally we would like to note that while it is common to use the EHE as an indicator of magnetization, it is seldom used for a quantitative analysis of magnetic behavior. In this work we presented a striking example of the latter, by performing sensitive measurements of the zero-field-limit magnetic susceptibility in thin films of SrRuO<sub>3</sub>, which allowed us to gain microscopic insight into the effect of MCA in the paramagnetic state of a 4d itinerant ferromagnet.

We would like to thank V. Kosoy for an illuminating discussion, and A. Aharony, J. S. Dodge, and M. Gitterman for useful comments on the manuscript. We acknowledge support by the Israel Science Foundation funded by the Israel Academy of Sciences and Humanities.

Present address: Department of Applied Physics, Yale University, New Haven, Connecticut 06520-8284

- [1] C. Kittel, Introduction to Solid State Physics (Wiley, 1986), p. 450.  
 [2] H. B. Callen and E. Callen, J. Phys. Chem. Solids 27, 1271 (1966).

- [3] H. Suzuki and T. Watanabe, J. Phys. Soc. Jpn. 30, 367 (1971).  
 [4] P. J. Jensen et al., Phys. Rev. B 67, 184417 (2003).  
 [5] A. F. Marshall et al., J. Appl. Phys. 85, 4131 (1999).  
 [6] L. Klein et al., J. Phys.: Condens. Matter 8, 10111 (1996).  
 [7] S. J. Benero et al., J. Vac. Sci. Technol. B 12, 1217 (1994).  
 [8] M. Izumi et al., J. Phys. Soc. Jpn. 66, 3893 (1997).  
 [9] L. Klein et al., Phys. Rev. B 61, R7842 (2000).  
 [10] OHE was subtracted based on the value of  $R_0$  determined for each sample by measuring the Hall effect at a temperature where  $R_s$  vanishes, close to 130 K (we could determine that temperature up to the desired accuracy by the methodology of Ref. [9]). While small changes in  $R_0$  as a function of temperature cannot be excluded, our main results would be affected very little by such changes.  
 [11] The MR in SrRuO<sub>3</sub> is negative and related to suppression of spin-dependent scattering. Only at very low temperatures positive Lorentz magnetoresistance appears.  
 [12] Y. Kats et al., Phys. Rev. B 63, 054435 (2001).  
 [13] D. Kim et al., Phys. Rev. B 67, 100406 (2003).  
 [14] G. Santi and T. Jarlborg, J. Phys.: Condens. Matter 9, 9563 (1997).  
 [15] D. C. Worledge and T. H. Geballe, Phys. Rev. Lett. 85, 5182 (2000); B. N. Adgomy et al., Appl. Phys. Lett. 82, 427 (2003); P. Raychaudhuri et al., Phys. Rev. B 67, 020411(R) (2003).  
 [16] V. Korenman, J. L. Murray, and R. E. Prange, Phys. Rev. B 16, 4032 (1977).  
 [17] J. S. Dodge et al., Phys. Rev. B 60, R6987 (1999).  
 [18] P. Pfeuty and G. Toulouse, Introduction to the Renormalization Group and to Critical Phenomena (Wiley, 1977), Chapter 8.  
 [19] The Pauli paramagnetism and diamagnetism in SrRuO<sub>3</sub> are approximately 10% of the susceptibility at 300 K [20]. It is not clear whether their contribution to the EHE should go with the same  $R_s$ . If same  $R_s$  is assumed, taking them into account does not have a significant effect on the result or the quality of the fit.  
 [20] G. Cao et al., Phys. Rev. B 56, 321 (1997).  
 [21] This feature has been reported previously [6], and it does not depend on film thickness. It is not due to the shape anisotropy, which is small ( $M_s^2 \approx 5 \cdot 10^6$  erg/cm<sup>3</sup> K).  
 [22] The contribution of the substrate was subtracted based on measurements of a bare substrate. Its signal is mainly diamagnetic, being for  $H = 5$  T about 20% of the ferromagnetic signal of the 150-nm film which was measured.  
 [23] C. D. Graham, Jr., Phys. Rev. 112, 1117 (1958).  
 [24] R. M. Bozorth, Ferromagnetism (Van Nostrand, New York, 1951), p. 569.  
 [25] D. Weller et al., Phys. Rev. Lett. 72, 2097 (1994).  
 [26] A remarkable example of the dependence of MCA on the crystal symmetry is the order-of-magnitude difference in the anisotropy constants between hcp and fcc Co [25].  
 [27] The SOC constant in Ru ion ( $\approx 900$  cm<sup>-1</sup>) is significantly larger than, for example, in Fe ( $\approx 400$  cm<sup>-1</sup>), Ni ( $\approx 600$  cm<sup>-1</sup>), and Co ( $\approx 500$  cm<sup>-1</sup>). See: J. S. Griffith, The Theory of Transition-Metal Ions (Cambridge University Press, Cambridge, 1971), p. 437-439.