

Muon Spin Relaxation Measurements in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$

A. Kanigel, A. Keren, L. Patlagan, K. B. Chashka, B. Fisher

Department of Physics, Technion-Israel Institute of Technology, Haifa 32000, Israel.

P. King

Rutherford Appleton Laboratory, Chilton Didcot, Oxfordshire OX11 0QX, U.K.

A. Amato

Paul Scherrer Institute, CH-5232 Villigen PSI, Switzerland

(March 22, 2024)

Using the transverse field muon spin relaxation technique we measure the temperature dependence of the magnetic field penetration depth, in the $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ system. We find that λ , which is determined by superfluid density n_s and the effective mass m^* , is very small and on the edge of the TF-SR sensitivity. Nevertheless, the results indicate that the order parameter in this system has nodes and that it obeys the Uemura relation. By comparing λ with the normal state electron density we conclude that m^* of the superconductivity carrier is 70 times larger than the mass of bare electrons.

The discovery of the new superconductor $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ caused excitement in the unconventional superconductivity community. Of main interest are three questions: (I) what is the symmetry of order parameter and does it have nodes? (II) what is the gender of this material; is it a relative of the cuprates, the heavy fermions, metallic superconductors, or a class in its own? and (III) does this superconductor satisfy the Uemura relation? Regarding the first question, several works have given contradictory answers. For example ^{59}Co NMR/NQR measurements by Kobayashi et. al. [1] and Wakabayashi et. al. [2] suggest the existence of a coherence peak indicating a complete gap over the Fermi surface. In contrast, Fujimoto et. al. [3] and Ishida et. al. [4] found no coherence peak, questioning the previous result. Therefore, an additional and different experimental approach is required. A possible approach is to measure the temperature dependence of the magnetic field penetration depth. At low temperatures, λ is sensitive to low-lying excitations, and, in the case of a complete gap $\lambda(T=0)$ should vary exponentially as a function of T . On the other hand, nodes in the gap lead to a power-law dependence of this penetration depth difference. A study of λ can help addressing the other two questions as well. For the third question, one of the most universal correlations among the unconventional superconductors is the relation between the transition temperature T_c and the width of the transverse field muon spin rotation (TF-SR) line at low temperatures, $\lambda(0)/T_c^2$. Uemura et. al. [5] were able to show that the same relation holds for the underdoped cuprates, the bismuthates, Chevrel-phase and the organic superconductors. This relation has no explanation in the framework of the BCS theory, and it is usually explained in terms of phase coherence establishment in a theory of local fluctuations of the order parameter [6]. It

is interesting to know if $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ also obeys this relation. The second question would be addressed by the absolute value of $\lambda(0)$.

The aim of this work is to measure the temperature dependence of λ with TF-SR in $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. TF-SR is a very useful way to study superconductors in the mixed state. In this method 100% spin polarized muons are implanted in the sample, which is cooled in a field perpendicular to initial muon spin. Above T_c , where the external field penetrates the sample uniformly, the second moment of the field distribution at the muon stopping site B^2 is relatively small and determined only by fields produced by nuclear moments. Consequently the muon spins rotate in a coherent way and weak depolarization of the muon ensemble is observed. When the sample is cooled below T_c a flux lattice (FLL) is formed in the sample resulting in an inhomogeneous field and a therefore a larger second moment at the muon site. This increase in B^2 leads, in turn, to a high muon spin depolarization rate in the sample. The penetration depth is related to the field distribution width by

$$B^2 = \frac{0.00371 F^2}{\lambda^2} \quad (1)$$

where λ is the in-plane penetration depth, ϕ_0 is the flux quantum, and $F = 0.44$ for anisotropic compounds [7].

Polycrystalline samples of $\text{Na}_{0.5}\text{CoO}_2$ were prepared by solid state reaction [8] from mixtures of Co and Na_2CO_3 . These samples were intercalated as in Ref. [9] using a solution of Br_2 in CH_3CN , with Br_2 to Na molar ratio of 3. Then the material was washed in water and dried. The resulting compound was identified as $\text{Na}_{0.5}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ [10]. The transition temperature was measured using a home-built DC magnetometer. In Fig. 1 we show the field cooled magnetization measured

in a field of 50 Gauss. The T_c of the sample is about 3.5K. In the inset we show the magnetization vs. the applied field in zero field cooling conditions, measured at 1.8K. As can be seen in the figure the lower critical field H_{c1} is about 35 G.

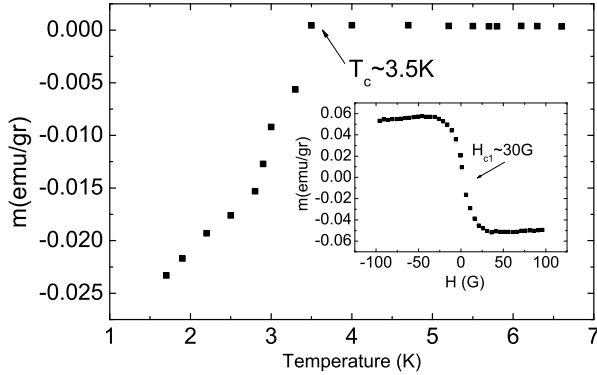


FIG. 1. Magnetization measurements of the $\text{Na}_{0.3}\text{CoO}_2 \cdot y\text{H}_2\text{O}$ vs temperature. The transition temperature is 3.5K. Inset: M vs. H for the same sample. $H_{c1} \sim 30$ G.

The SR experiments were done on the μSR spectrometer at the ISIS spallation source at the Rutherford-Appelton Lab in the UK, and in the GPS instrument on the M3 beam line at PSI Switzerland. At ISIS we used the ^3He sorb cryostat which allows a base temperature of about 350 mK. The sample was cooled in a field of 400 G, which is above H_{c1} . At PSI the base temperature available was 1.6 K and we measured in field cooled conditions in fields of 400 G and 3 kG. It has been reported that $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ is a very unstable system. It decays into another hydrated phase which is non-superconducting. The system is sensitive to temperature and humidity. For that reason we used a cell which allowed the sample to be cooled without losing the water content. The cell and the window were made of Titanium, a material in which the muon polarization relaxes very slowly. Although this material is superconducting below 400 mK its H_c is lower than our working field of 400 G. We tried to minimize as much as possible the exposure of the sample to dry and warm atmospheres. The sample was exposed to lab atmosphere for no more than a few minutes before it was sealed in the cell. The magnetization of the samples was measured to be the same before and after the ISIS experiment.

The nuclear moment of the Co and the protons lead to relatively large B^2 and causes the muon polarization to relax quite fast in $\text{Na}_{0.3}\text{CoO}_2 \cdot y\text{H}_2\text{O}$ even in the normal state. Combined with fact that this compound might be an extreme type II SC with a very large penetration depth, we expect only a small contribution to the relaxation from the formation of the vortex lattice. Usually, 10^4 Å is considered as the limit of the TF-SR

technique. Here we expect values of that order, so very high statistics runs are needed. In addition, the use of the ISIS facility which is optimized for weak relaxation is an advantage. The μSR spectrometer in ISIS consists of 32 counters arranged on two circles. For demonstration purpose we combine all 32 counters using a RRF transformation and binning, and depict in Fig 2 (a) and (b) the imaginary and real rotation signals respectively, at both the highest and lowest temperatures. A small but clear difference is seen in the relaxation rate between these two temperatures especially after 4 sec.

However, for analysis purposes, in order not to degrade the data by the RRF transformation, we fitted the 32 raw histograms separately. The same holds for the GPS spectrometer which contains only 3 counters in TF mode. We did not group the counter histograms nor bin them in the fits. The fit function is Gaussian since in a powder samples it describes the data sufficiently well. Also this Gaussian is not sensitive to core radius and to the symmetry of the vortex lattice. To account for muons that missed the sample we used two Gaussian relaxation functions one with very slow relaxation representing muons hitting the Ti cell. The overall function is given by: $A(t) = A_0 \exp\left(-\frac{(t)^2}{2}\right) \cos(Bt) +$

$$A_{\text{cell}} \exp\left(-\frac{(t_{\text{cell}})^2}{2}\right) \cos(B_{\text{cell}}t).$$

where A_0 and A_{cell} are the initial asymmetries, and t and t_{cell} are the relaxation rates, and B and B_{cell} are the averaged fields in the sample and cell respectively. The results of the fit for the PSI data indicates that around 7% of the muons missed the sample. In ISIS the background signal is negligible due to the larger sample used. In the inset of Fig. 3 we show χ^2 vs. temperature for the data taken in PSI in 400 G and in 3 kG, and in ISIS at 400 G.

As can be seen the change in relaxation in passing through T_c is quite small; between 4 K and 2 K it is only about 5% of the normal state relaxation χ_n . As mentioned before, χ_n stems from nuclear moments and seems to be field independent. Below T_c the relaxation is from a combination of nuclear moments and the vortex lattice formed in the sample. When the origin of the relaxation is a convolution of two distributions, it results in a multiplication of two relaxation functions in the time domain. Since both the nuclear moments and the vortex lattice in a powder sample generate Gaussian field distributions we can obtain the FLL part by: $\chi_{\text{FLL}} = \frac{\chi_n^2}{2} \frac{1}{\chi_n}$. In Fig. 3 we show χ_{FLL} as function of temperature below T_c . This figure includes all the data from PSI and ISIS, and the point at $T = 0.37$ K. Unfortunately, due to experimental problems we do not have at present data between 0.37 K and 1.6 K. As one can see there is no field dependence, as expected for a compound with $H_{c2} \sim 61$ T [12]. The penetration depth at base temperature is calculated from Eq. 1 and $\chi_{\text{FLL}} = \frac{\mu_0^2}{h} B^2 i$ where $i = 85.16 \text{ MHz} = k\text{G}$ is the gyromagnetic constant of the muon. This calculation gives $\lambda = 9100(500) \text{ Å}$ at

$T = 0.37$ K, which is very large, and on the order of what is considered as the limit of TF-SR. Indeed, the error bars on $\sigma_{\text{FLL}}(T)$ are quite big and there is scatter in the data. Nevertheless it is clear from Fig. 3 that the temperature dependence of σ_{FLL} is inconsistent with the phenomenological two-fluid model prediction: $\sigma_{\text{FLL}}(T) \propto 1 - (T/T_c)^4$ [14]. The fact that σ_{FLL} does not saturate even at low temperatures indicates that there are nodes in the gap. Higemoto et. al. [11] reached a similar conclusion based on muon Knight shift results which indicated a non-complete gap.

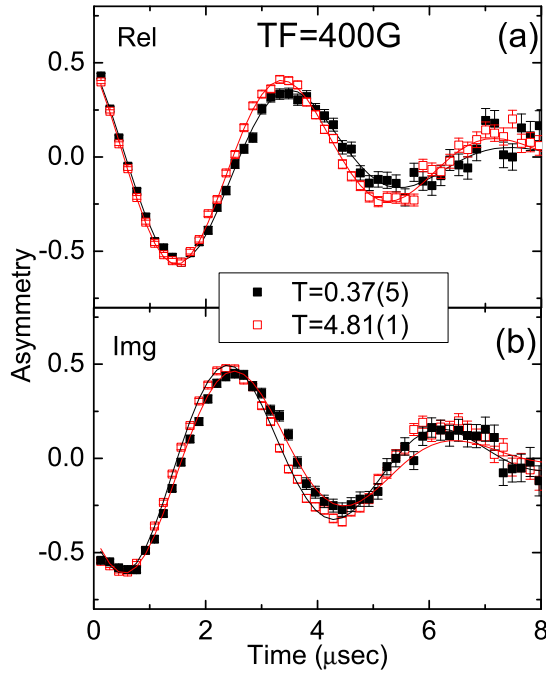


FIG. 2. Transverse field SR data at two different temperatures taken at ISIS in 400 G. Both real and imaginary data are shown in a reference frame rotating at 380G.

Next, we would like to compare the superfluid density of the $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ system with that of other unconventional SC and see if it agrees with the Uemura relation. In Fig. 4 we depict the original Uemura line using data only from the high temperature superconductors $\text{YBa}_2\text{Cu}_3\text{O}_y$ (YBCO) [5], $\text{La}_{1-x}\text{Sr}_x\text{CuO}_4$ (LSCO) [5], and $(\text{Ca}_x\text{La}_{1-x})(\text{Ba}_{1.75-x}\text{La}_{0.25+x})\text{Cu}_3\text{O}_y$ [CLBLCO (x)] [15]. Underdoped and overdoped samples are presented with solid and open symbols. The $\sigma_{\text{FLL}} = 0.125(10)$ at $T = 0.37$ K and $T_c = 3.5$ K fall exactly on this line. For comparison we added the data for Nb, which is a BCS type II SC with $T_c = 9.26$ K.

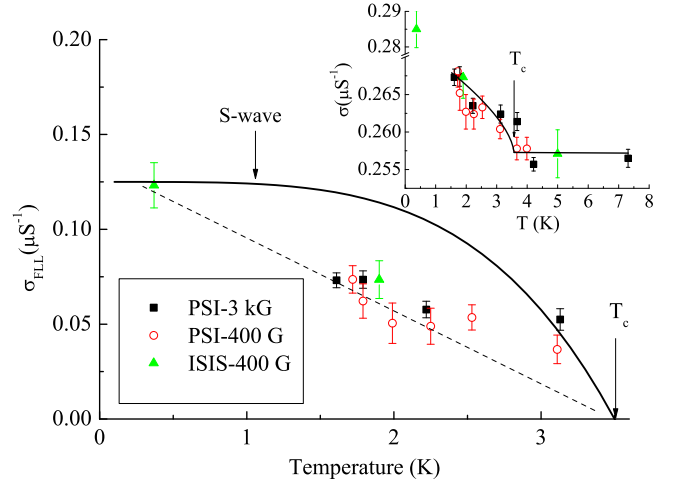


FIG. 3. The part of the muon relaxation associated with the flux lattice formation σ_{FLL} as function of temperature. The solid line is the temperature dependence predicted by the two-fluid model and an S-wave gap. The dashed line is a guide to the eye. Inset: The total muon relaxation rate, as taken in ISIS and PSI in a field of 400 G and 3 kG.

Finally we discuss the carrier density of $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$. Assuming 0.3 free electrons per Co [16], we get for our system a free electron density of about $3.8 \times 10^{21} \text{ cm}^{-3}$, which is comparable with the value for optimally doped YBCO. The free electron density of Nb, for example, is $5.56 \times 10^{22} \text{ cm}^{-3}$, about an order of magnitude higher than in $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$. Using the London equation

$$\lambda_L^{-2} = 4 n_s e^2 / m c^2 \quad (2)$$

where n_s is the superconducting carriers density and m is the effective mass of this carriers we can calculate the superfluid density. The separation of n_s and m is impossible using SR alone and it is very hard in general. But we can get useful insight from the comparison with Nb. Assuming that roughly all the normal state carriers contribute to the superconductivity, so that at $T \rightarrow 0$ the superfluid density equals the free electron density, we can extract the effective mass of the carrier from (2). In the case of Nb we get an effective mass $m \approx 3m_e$, on the other hand for $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ we get $m \approx 75m_e$. Despite this crude estimation, the mass is huge and comparable to the effective masses of the heavy fermion superconductors. It is much larger than the mass that the same calculation would yield for YBCO ($m \approx 2m_e$), for example. In fact, thermopower [10] and specific heat measurements [17,18] point to the narrow band character of the $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ system which results in an enhancement of the electron mass.

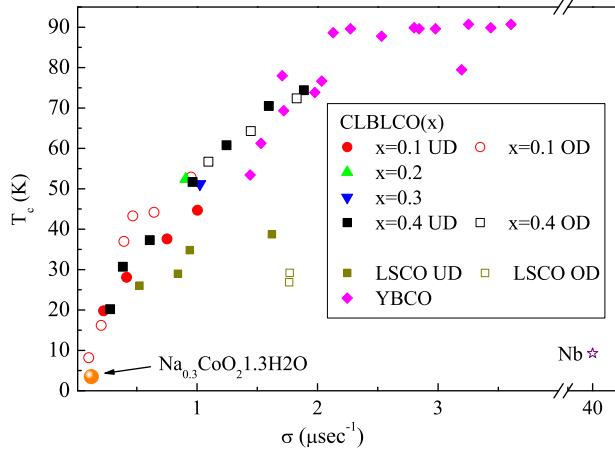


FIG. 4. The Uemura plot showing T_c vs. the muon relaxation rate at the lowest temperature for LSCO, YBCO, and CLBLCO (x) cuprates, and for Nb. The results from $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ fall on the line defined by the cuprates.

In summary, we performed TF-SR experiments on a sample of $\text{Na}_{0.3}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$. The temperature dependence of the penetration depth indicates that superconductivity in this system is unconventional and that the order parameter has nodes. The value of the relaxation rate at low temperature agrees with the well known prediction of the Uemura line. Comparing the normal state carrier density with the superfluid density reveals an unusually heavy superconductive carrier.

We would like to thank ISIS and PSI facilities for their kind hospitality. We are grateful to A. Auerback for very helpful discussions. This work was funded by the Israeli Science Foundation.

-
- [1] Kobayashi Y., Yokoi M. and Sato M., cond-m at/0306264.
 - [2] Waki T. et. al., cond-m at/0306036 Fujimoto T. et. al., cond-m at/0307127.
 - [3] Fujimoto
 - [4] Ishida K. et. al., cond-m at/0308506.
 - [5] Y. J. Uemura et. al. Phys. Rev. Lett. 66, 2665 (1991).
 - [6] Emery V. J. and Kivelson S. A., Nature 374, 434 (1995).
 - [7] E. H. Brandt, Phys. Rev. B 37, 2349 (1988).
 - [8] Kawata T., Iguchi Y., Takahata K., and Terasaki I. Phys. Rev. B 60, 10584 (1999).
 - [9] Takada K. et. al. Nature 422, 53 (2003).
 - [10] B. Fisher et. al., J. Phys. Condens. Matter 15, L571 (2003).
 - [11] Higemoto Wataru et. al., cond-m at/0310324.
 - [12] H. Sakurai et. al., cond-m at/0304503.
 - [13] M. L. Foo et. al., Solid State Comm. 127, 33 (2003).
 - [14] M. Tinkham, Introduction to superconductivity, McGraw-Hill, 1996, Sec. Ed. New York.

- [15] A. Keren, A. Kanigel, J. S. Lord, and A. Amato, Solid State Comm. 126, 39 (2003).
- [16] Schaak R. E. et. al., Nature 424, 527 (2003).
- [17] Yang H. D. et. al., cond-m at/0308031.
- [18] Ueland B. G. et. al., cond-m at/0307106.