

## High-bias stability of monatomic chains

R. H. M. Smit,<sup>1</sup> C. Untiedt,<sup>1,2</sup> and J. M. van Ruitenbeek<sup>1</sup><sup>1</sup>Kamerlingh Onnes Laboratorium, Universiteit Leiden,  
Postbus 9504, 2300 RA Leiden, The Netherlands<sup>2</sup>present address: Departamento de Física Aplicada, Universidad de Alicante,  
Campus de San Vicente del Raspeig, E-03690 Alicante, Spain

(Dated: April 14, 2024)

For the metals Au, Pt and Ir it is possible to form freely suspended monatomic chains between bulk electrodes. The atomic chains sustain very large current densities, but finally fail at high bias. We investigate the breaking mechanism, that involves current-induced heating of the atomic wires and electromigration forces. We find good agreement of the observations for Au based on models due to Todorov and coworkers. The high-bias breaking of atomic chains for Pt can also be described by the models, although here the parameters have not been obtained independently. In the limit of long chains the breaking voltage decreases inversely proportional to the length.

PACS numbers: 65.80+n, 68.65.-k, 73.63.Rt

## I. INTRODUCTION

As the down-scaling of electronic components is advancing at an impressive rate, the general interest in dissipation and thermal transport at comparable scales is increasing. Technical applications using these small scale devices will have higher and higher densities of components making heat generation one of the biggest problems to overcome. We, therefore, need to develop a better fundamental understanding of the properties of matter at small size scales. A recent review<sup>1</sup> on thermal transport at the nanoscale shows how fast this field has been growing during the last few years. It also shows that at scales of the order of several nanometers the quantum behavior of matter starts to have a major impact on the thermal behavior of the sample. As an example, Yao et al.<sup>2</sup> have shown that the current through a single-wall carbon nanotube is saturating as the voltage reaches values of several volts, a behavior which is not expected from a simple down-scaling of classical effects.

Here we study the thermal behavior of metals at the smallest length-scales, below 1 nm. A review of results in this field has recently appeared<sup>3</sup>. In recent experiments it was shown that some metals have the property of spontaneously forming monatomic chains just before rupture<sup>4,5</sup>. Although atomic chains are intrinsically metastable, experiments at high bias voltages showed they have a surprising current-carrying capacity<sup>4</sup>, and current densities up to  $10^9$  A/mm<sup>2</sup> could be reached. Currently the lengths of these chains is limited to about seven atoms. A better understanding of dissipation and relaxation phenomena may lead the way to fabricate longer chains. With these monatomic chains being nearly ideal one-dimensional conductors this would provide means to further study the fundamental properties of conductors in one dimension.

In the experiments described below we probe the stability of many individual monatomic chains by looking at their rate of survival at high bias voltages. Although these nanowires due to their small size are ballistic, high

bias results in a small probability for inelastic scattering of the electrons to phonons. Energy dissipation has been demonstrated to come into play when eV for the bias voltages applied is raised above the characteristic zone-boundary phonon energy<sup>6</sup>. Energy dissipation will take place on the scale of the electron-phonon scattering length (typically 100 nm), but the number of scattering events per volume will be largest inside the atomic wire itself due to the large current density. As a consequence the average lattice vibration energy at the narrowest cross-section will be larger than anywhere else in the contact, which can be viewed as an increased local effective temperature,  $T_e$ . This elevated local temperature can lead to the rupture of the contact and is therefore an important parameter.

There have been several experimental attempts in measuring this local effective temperature inside metallic point contacts, but it has been difficult to obtain quantitative results. Van den Brom et al.<sup>7</sup> have exploited the switching rate between two different configurations in atomic sized contacts. When the energy barrier between the two configurations is low enough (which is often found on the verge of an atomic reconstruction) the local temperature can activate the jumps between the two levels, and the switching rate is determined by the ratio of the effective barrier and the thermal energy. To obtain the effective temperature from this switching rate an estimate of this barrier is required, which is difficult in view of the unknown atomic configurations. In order to circumvent this problem the switching rate between the two states was followed while changing the bias voltage and the bath temperature independently<sup>8</sup>. A comparison between the changes in the switching rates in these two cases would provide a calibration of the relation between the bias voltage and the effective temperature. However, the thermal expansion in the electrodes due to the changing temperature changes the atomic configuration considerably, making it difficult to draw definite conclusions.

Here we discuss measurements of the fracture rate of

atomic chains as a function of the voltage bias. The advantage over previous work on  $T_e$  in atomically-sized conductors is that they are free of lattice imperfections and impurities and the structure is known, except for the configuration at the end points. The energy barrier that has to be considered in the process is therefore less complex. Moreover, it is possible to consider chains of various lengths, which provides us with a control parameter of the point contact geometry.

The paper is organized as follows. After some details on the experimental techniques we show in section III that the breaking of an ensemble of chains cannot be described by a simple activated process. We argue (section IV) that there are a number of parameters involved that lead to a distribution of Boltzmann factors and we show that the observed distribution in breaking voltages can be fairly well described without adjustable parameters. One of the assumptions, here, is that there is a variation in effective barriers to breaking as a result of a distribution of tensile forces in the chains. We verify this assumption in section V by comparison to the measured phonon mode energy in the chains, which reflects the actual tensile force in the monatomic wire. All experiments to this point were done on gold chains and this is compared to results for platinum in section VI, which can only be qualitative for lack of data available in the literature. We conclude (section VII) that we have a fairly good description of Joule heating in these atomically-sized conductors and we obtain a realistic estimate for the lattice temperature at finite bias.

## II. EXPERIMENTAL TECHNIQUES

The experiments have been performed using the Mechanically Controllable Break Junction (MCBJ) technique<sup>9</sup>. By this technique one breaks a wire of the desired metal in a controlled fashion with the use of a piezo-electric element. The wire is only broken once the sample is under vacuum and the temperature in the vacuum chamber is stable at 4.2 K. Thermal contact to the sample is provided by a copper finger in order to avoid using thermal contact gas. The advantages of the MCBJ technique are, firstly, a large mechanical stability due to the small mechanical loop connecting the two wire ends. This can be of crucial importance when one tries to determine the stability of monatomic chains. Secondly, the cryogenic vacuum without use of thermal exchange gases ascertains the absence of gas molecules in the environment that could lead to additional cooling of the contact and contamination of the metal nanowire. Our relying on cryogenic vacuum has the disadvantage that we cannot increase the temperature of the experiment much since this would lead to a deterioration of the vacuum. The gold and platinum wires used here have a purity of at least 99.998%.

Chains of atoms were produced in the following way. During the breaking of the wire by use of the piezo-

element the wire conductance decreases in steps<sup>10</sup>, which have been shown to be due to atomic reconstructions<sup>11</sup>. The last plateau in the conductance, observed just before the conductance suddenly drops to a negligible value and the wire is broken, is generally due to a contact with the cross section of a single atom<sup>12</sup>. When the length of this plateau exceeds the typical length for a single atom it can be considered as a measure for the length of an atomic chain being formed<sup>4,13</sup>. In order to fabricate atomic chains of a given length  $L$  the process is repeated as long as the contact breaks before the plateau (and chain) reaches the desired length: The two electrodes are pushed together again to reestablish a big contact and a new atomic contact is pulled out. When after several attempts the desired chain-length is reached the piezo movement is halted and measurements on the properties of the atomic chain are started. During this procedure the conductance of the atomic contact is measured using a constant bias voltage of the order of 10 mV.

The effective length  $L$  that we will use as a parameter below refers to the length of the last plateau in the conductance, as was done in previous studies<sup>4,13</sup>. The length measures the stretching of the contact from the point where the conductance first drops to the value of a single-atom contact. It is widely accepted that the starting point corresponds to a contact of one atom. Depending on the detailed evolution of the chain a plateau length of  $L = 0.5 \text{ nm}$  for gold would have two or three atoms in a row, and  $L = 1 \text{ nm}$  would have four or five atoms. Some recent model calculations<sup>14,15</sup> suggest that the structure of the contact at the starting point of a plateau can be viewed as two electrodes ending in a single atom and touching vertex-atom to vertex-atom which would make the chains one atom longer, but this remains to be verified experimentally.

## III. RATE OF DECAY OF ATOMIC CHAINS

One would expect the stability of the monatomic chain to be determined by the ratio of the energy barrier against breaking,  $W$ , and the effective temperature,  $T_e$ . A population,  $P$ , of chains would then show an exponential decay as a function of time,  $t$ ,

$$P(t) = P(0) \exp(-t/\tau); \quad \tau = \frac{1}{f} \exp(W/k_B T_e); \quad (1)$$

where  $f$  is the frequency by which the system attempts to overcome the barrier. In estimates and simulations given below we will take  $f = 3.5 \cdot 10^{12} \text{ Hz}$ , a typical phonon frequency for monatomic gold chains<sup>6,16</sup>.

In order to investigate this stability by a simple experiment the decay of a population of monatomic gold chains was followed as a function of time. The moment a chain of the desired length is created is taken as  $t = 0$  and the time until the chain spontaneously breaks was stored for a set of consecutively formed chains. The evolution of the number of surviving chains as a function of time, out

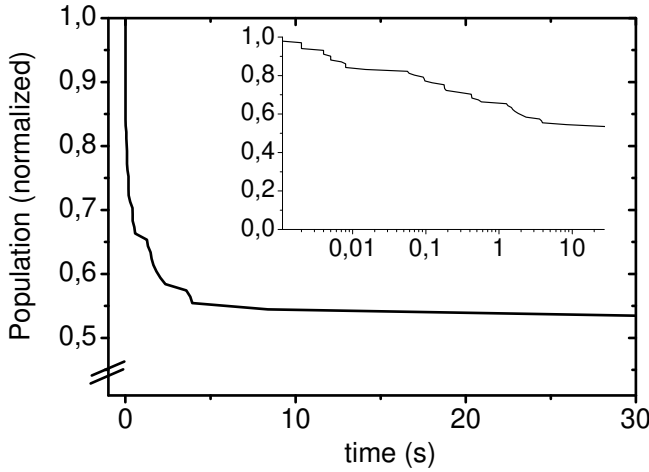


FIG. 1: The number of monatomic chains remaining intact as a function of time out of an initial population of 100. The inset shows the same data on a logarithmic time-axis. The results were obtained for monatomic gold chains with an effective length of 0.4 nm, at a temperature of 4.2 K and at a constantly applied bias voltage of 200 mV.

of an initial population of 100, is presented in figure 1. Clearly, the observed dependence is not described by the expected exponential decay. The inset in figure 1 shows that it actually more closely follows a logarithm. A logarithm can be obtained if we consider for the chains in the population a distribution of barriers, a distribution of effective temperatures, or both. Note that the characteristic time for breaking is influenced by the applied bias voltage, which is 200 mV in the example of figure 1. Near zero bias the lifetime of atomic chains at 4.2 K is mainly limited by the patience of the experimentalist.

#### IV. A DISTRIBUTION OF BOLTZMANN FACTORS

The distribution of lifetimes for given effective length  $L$  observed in figure 1 may result from a variation in the energy barrier  $W$  of the chain, which is likely due to variation in the tensile force. From the fact that a chain will always break when the tensile force exerted is large enough, one can conclude that the effective barrier height must decrease with force. As shown by the force measurements on monatomic chains performed by Rubio et al.<sup>11</sup> the force varies strongly while pulling to form a chain, and will sensitively depend on the atomic configurations at the connection points to the banks. Assuming a dominant lowest order (linear) term the barrier energy can be written as

$$W = W_0 - \gamma_j - \beta_j \quad (2)$$

where  $W_0$  is the equilibrium barrier energy. We have also included a linear decrease of the barrier due to electromigration upon application of a bias voltage  $V$ . This

term is motivated by model calculations by Todorov et al.<sup>17,18</sup> Using a single-orbital tight-binding model they have shown that the barrier against breaking reduces linearly with voltages up to 1 V. More recent calculations based on density functional theory by Brandbyge et al.<sup>19</sup> have shown that the electromigration force can be highly non-linear. However, for many configurations it will be a reasonable approximation.

Apart from a variation in the energy barrier we should also consider the local effective temperature at the point contact. For vanishing bias voltages the effective temperature approaches the bath temperature,  $T_0$ . Beyond a certain threshold voltage it should rise due to a voltage-driven term,  $T_V$ . Following reference 17 we describe the local effective temperature of the atomic contact as:

$$T_e = (T_0^4 + T_V^4)^{1/4} \quad (3)$$

An estimate for the dependence of  $T_V$  on voltage can be obtained from an earlier paper by Todorov<sup>20</sup>. Three terms are included in the estimate: (1) Heating by the electrons due to creation of phonons in the atomic wire, (2) the cooling by the electrons due to absorption of phonons, and (3) cooling by the thermal transport of energy away from the point contact into the metal banks. If only the first two terms are included the temperature is simply proportional to the voltage,  $k_B T_e \propto eV$ , where it has been assumed that electrons exchange at most a single quantum of vibration energy. Note that recent experimental work by Zhitenov et al.<sup>21</sup> on molecular junctions indicates that several vibrational quanta can be deposited per electron. However, this effect can be attributed to the relatively long residing times of the electrons inside the molecular bridge<sup>22</sup>. Earlier experimental work on phonon spectroscopy in monatomic gold chains<sup>6</sup> shows that multiple phonon scattering is negligibly small for these ballistic wires, in agreement with the assumption by Todorov.

An effective temperature  $k_B T_e \propto eV$  would correspond to thousands of Kelvins at commonly employed bias voltages. However, the third term, the thermal conduction to the banks, limits the heating considerably. It is more difficult to make precise estimates, but when the behavior of the banks is taken to follow the bulk heat conduction and heat capacity we obtain<sup>20</sup>

$$T_V = \frac{\beta}{L \gamma_j} \quad (4)$$

where  $\beta$  is a proportionality constant given as  $\beta = 60 \text{ K V}^{-1/2} \text{ nm}^{-1/2}$  and  $L$  is the length of the chain. This was qualitatively confirmed by an independent approach by Chen et al.<sup>23</sup>.

In order to investigate experimentally the effect of bias voltage heating on the stability of the chains, taking a distribution of wire properties into account, we proceeded as follows. First chains of the desired length are produced following the procedure described above. This is done at a bias voltage of 10 mV, a value which is below the typical electron-phonon excitation energy<sup>6</sup>. This

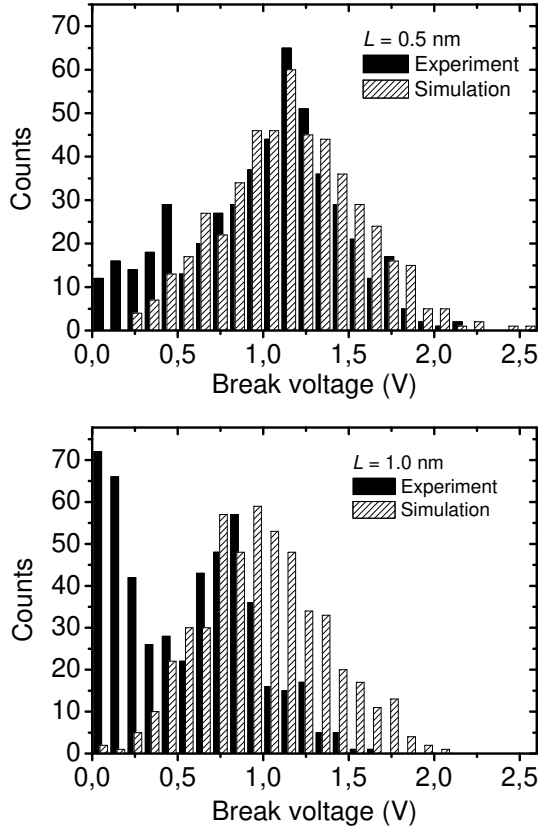


FIG. 2: A distribution of the number of gold atomic chains as a function of bias voltage at which they were observed to break. The upper panel shows the experimental and simulated result for 500 chains with  $L = 0.5$  nm long at a temperature of 4.2 K, while the lower panel shows similar data for chains of  $L = 1.0$  nm long.

ensures that the effective temperature in the point contact will remain close to the bath temperature. Once a chain has been formed we wait for 1 s to see whether the chain is indeed stable. Next, the voltage is ramped with a constant speed of about 1 V/s until the chain breaks. The bias voltage at breaking is stored and it is reset to 10 mV. The electrodes are then pushed together again to repeat the experiment for the next chain. The results for such an experiment are represented in figure 2. The top panel shows a histogram constructed from the measured bias voltages at breaking for a set of 500 gold atomic chains with  $L = 0.5$  nm. The distribution clearly peaks at 1.2 V with a full width at half maximum of 0.6 V. The lower panel shows a similar set of experimental results for chains of  $L = 1.0$  nm in length. In this case we observe two peaks in the distribution, one at low bias representing a large fraction of chains that break early, and a second peak at 0.8 V. A possible dependence on the voltage ramp speeds was not investigated, but earlier work found negligible influence of this parameter in atomic contacts<sup>24</sup>.

We have suggested above that the breaking of the

atomic chains can be described as a thermally activated process. However, for this we need to verify that the energy barrier is not significantly modified by thermal expansion due to the rising of the local effective temperature at high bias voltage. In a test we measured two sets of 500 atomic chains. With the first set the bias voltage was suddenly increased from 15 to 800 mV once the chains had been formed. A large number of chains was seen to break following a similar logarithmic time dependence as displayed in figure 1. With the second set we suddenly dropped the voltage from 300 to 50 mV after which we observed not a single chain breaking. Note that a higher bias should lead to thermal expansion of the electrodes<sup>25</sup> and thus to a smaller tensile stress than at low bias. These two tests show that the influence of the thermal expansion on the energy barrier, if present, is dominated by the thermally activated breaking.

In order to compare the results of figure 2 with the proposed model for the variation of the energy barrier and effective temperature on bias voltage we need realistic estimates for the constants in equation 2. We adopt the values  $W_0 = 0.738$  eV and  $\alpha = 0.14$  eV/V obtained in reference 17 from a non-equilibrium tight-binding calculation for a gold atomic chain. The value for  $\tau$  in equation 2 can be estimated from the results by Rubio et al.<sup>11</sup> They found that gold atomic chains typically break at a tensile force of 1.5 nN. At the point of breaking the lifetime,  $\tau$ , of a chain has been reduced to the experimental time scale, which is 0.1 s in the experiments of reference 11. The local effective temperature at the point of contact will be given by the bath temperature in view of the low bias voltage of 10 mV used in these experiments. For  $\tau = 0.1$  s and  $T_e = T_0 = 4.2$  K we obtain from equation 1 an average barrier of 0.011 eV at breaking. The barrier of 0.738 eV therefore nearly vanishes under the influence of a tensile force of 1.5 nN, resulting in a value of  $\alpha = 0.49$  eV/nN.

We will now see whether the combination of these values give a reasonable description of the experimental results of figure 2. We assume here that the only missing, i.e. not measured, parameter is the tensile force. The average tensile force on an atomic chain can be estimated from figure 1 in reference 11 to be  $0.95 \pm 0.15$  nN. We performed a numerical simulation of these data based on equations 1 to 4 and using a normal distribution of forces with a mean value of 0.95 nN and a standard deviation of 0.15 nN, which produces the distribution presented in figure 2. The peak position and width agree very well with those observed in the experiment. Note that all parameters have been obtained from independent model calculations and experimental data, so that there are no adjustable parameters. For an effective length  $L = 1$  nm (lower panel) the peak in the numerical simulation is slightly higher than observed. A more significant disagreement is in the width of the distribution, which is about twice as large in the numerical result, and also the peak at zero bias remains unexplained. Nevertheless, the qualitative agreement obtained using literature values

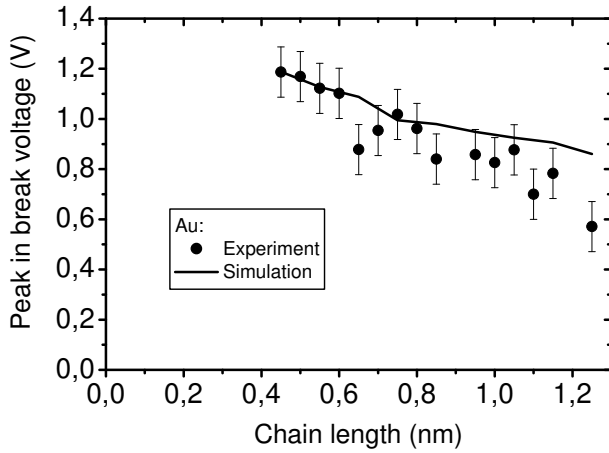


FIG. 3: Position of the maximum in the distribution of breaking voltages (figure 2) for monatomic gold chains as a function of their effective length. The bullets represent the experimental results obtained by fitting a Gaussian curve to each population formed by 500 chains. The curve is a numerical simulation, as described in the text.

for the parameters suggests that we have at least captured some of the physics involved. Thus, this analysis suggests that the broad distribution in breaking voltages is mainly caused by the large distribution of tensile forces in an ensemble of atomic chains. The processes leading to the relatively unstable chains breaking at very low voltages is unclear as of yet. A possible explanation would be a large portion of chains quickly breaking when the bias voltage reaches the threshold value of the lowest phonon mode in the point contact.

In order to follow the length dependence in more detail we have constructed histograms similar to the ones shown in figure 2 for many chain-lengths. From the histograms we extract the position of the maximum of the distribution at finite bias and plot this as a function of length. This dependence is depicted in figure 3 and shows that the average breaking voltage decreases from 1.2 V at  $L = 0.45$  nm to just below 0.6 V at  $L = 1.25$  nm.

With the same values for the model parameters as used above we obtained the curve shown in figure 3. In view of the fact that there are no free parameters the agreement between the model and experiment is surprisingly good, although the values at greater length demonstrate a larger deviation. The reason for the deviation may be in the model or the choice of parameters. However, one aspect that we have ignored and that should become important for longer chains is the contribution of the entropy. The larger number of bonds present in longer chains will reduce the effective barrier<sup>26</sup>.

## V. TEST OF THE VARIATION IN TENSILE FORCES

In order to test whether the width in the experimental distribution at higher bias voltages is the result of a variation in the tensile forces one would like to be able to measure the forces in the point contact. The MCBJ in its original configuration is not suitable to determine these, but it is possible to obtain some information in an indirect way using Point Contact Spectroscopy (PCS)<sup>27</sup>. By this technique one probes the differential conductance  $dI=dV$  as a function of voltage using a small modulation superimposed on the dc bias ramp. As soon as the excess energy,  $eV$ , of the electrons shooting through the point contact becomes larger than the energy of a phonon mode inside the contact a new channel for back-scattering sets in resulting in a sudden reduction of the conductance. This technique was applied to atomic contacts by Untiedt et al.<sup>28</sup> and to monatomic gold chains by Agrait et al.<sup>6</sup>, who showed that the observed phonon energy decreases when the tensile force on the chain is increased. This is as intuitively expected: As the tensile force  $F$  increases the distance between the atoms  $a$  in the chain increases leading to a weaker bond and a lower stiffness  $\kappa = dF/da$ . Since the observed longitudinal phonon mode energy is proportional to  $\sqrt{\kappa}$  the phonon frequency changes accordingly.

We make use of this effect in the following experiment. First we produce a chain of the desired length via the procedure described above. Next, a point contact spectrum is recorded by measuring the differential conductance as a function of bias voltage in the interval between -50 and +50 mV, using a lock-in amplifier. Some chains are lost during this procedure due to an increase of the effective temperature caused by the increased bias voltage. When this happens the data are discarded and a new chain is formed. After having measured the differential conductance the bias voltage is ramped up similar as in the previous experiment, at a rate of 1 V/s. The data are stored and analyzed after collecting a large set of curves. For all point contact spectra that show a clear phonon signal the phonon frequency can be compared to the breaking voltage. The data are then sorted according to the observed phonon frequencies and collected in bins of 1 meV wide. For the data within each bin the average breaking voltage and its standard deviation are evaluated.

Figure 4 shows the average breaking voltage as a function of the observed phonon frequencies, where the error bars on each data point represent the standard deviation. For a small fraction of about 2% of the spectrum more than one phonon frequency could be identified, and these were not taken into account in figure 4. The break voltage in the graph clearly rises as a function of phonon energy, just as is expected. For a higher phonon frequency the force constant is higher and the chain is expected to be less strained, and thus the energy barrier to breaking is higher. The distribution of breaking voltages at each phonon energy is still quite broad. From this ob-



strain) =  $200 \text{ K V}^{-1} = 2 \text{ nm}^{-1}$  and  $\epsilon = 0.39 \text{ eV/V}$ , a set of values which is within reasonable limits, the resulting curve shown in figure 5 describes the experimental data quite well. This set of values is not unique as can be seen from inspection of equation 5: the values of  $\epsilon$ ,  $\alpha$  and  $W_F$  can be scaled by an arbitrary constant. Yet, we can find reasonable values for the constants and obtain a good qualitative description of the data using the same model as for Au above. For  $L \rightarrow 0$  the break voltage assumes a value  $W_F = \epsilon$  while for large  $L$  the break voltage decreases as  $1/L$ , but is expected to saturate when  $\epsilon V$  approaches the characteristic phonon energies of the chain.

## VII. CONCLUSIONS

We have studied monatomic chains for Au and Pt and found a systematic dependence of the characteristic chain-breaking voltage vs the chain length. Atomic chains sustain surprisingly large current densities, but the maximum current (or voltage) decreases as the chain length grows. We have adopted a model proposed by Todorov and coworkers and found a satisfactory agreement with

the observations. Especially for gold the agreement is surprisingly good in view of the fact that we have not used any adjustable parameter. Yet, there are deviations that are not captured by the model and that require further study. For Pt the general behavior of the average breaking voltage as a function of length can also be closely described by the model, although the parameters have not been independently verified. The agreement obtained inspires confidence in equations 3 and 4 and we can now estimate the effective (lattice) temperature inside the atomic wire. It rises proportional to the square root of the bias voltage for sufficiently large bias and for a monatomic gold chain of length  $L = 1 \text{ nm}$  at  $V = 1 \text{ V}$  it reaches a temperature of  $60 \text{ K}$ , which is well above the bath temperature of  $4.2 \text{ K}$ .

We thank M. Pohlkamp and M. Heijdra for valuable assistance with the experiments and gratefully acknowledge discussions with T. N. Todorov, J. Hoekstra and A. P. Sutton. This work is part of the research program of the 'Stichting FOM', C.J. has been supported by the European Union under contract No. HPMF-CT-2000-00724 and by the Spanish 'Ramón y Cajal' program of the M.CyT.

- 
- <sup>1</sup> Cahill D G, Ford W K, Goodson K E, Mahan G D, Majumdar A, Maris H J, Merlin R and Philpot S R 2003 J. Appl. Phys. 93 793
  - <sup>2</sup> Yao Z, Kane C L and Dekker C 2000 Phys. Rev. Lett. 84 2941
  - <sup>3</sup> Agrat N, Levy Yeyati A and van Ruitenbeek J M 2003 Phys. Rep. 377 81
  - <sup>4</sup> Yanson A I, Rubio Bollinger G, van den Brom H E, Agrat N and van Ruitenbeek J M 1998 Nature 395 783
  - <sup>5</sup> Ohnishi H, Kondo Y and Takayanagi K 1998 Nature 395 780
  - <sup>6</sup> Agrat N, Untiedt C, Rubio-Bollinger G and Vieira S 2002 Chem. Phys. 281 231
  - <sup>7</sup> van den Brom H, Yanson A I and van Ruitenbeek J M 1998 Physica B 252 69
  - <sup>8</sup> van den Brom H E, Noat Y and van Ruitenbeek J M 2001 In: Kondo Effect and Dephasing in Low-Dimensional Metallic Systems Chandrasekhar V, van Haesendonck C and Zawadowski A, editors (Kluwer Academic Publishers, Dordrecht) 249
  - <sup>9</sup> van Ruitenbeek J M, Devoret M H, Esteve D and Urbina C 1997 Phys. Rev. B 56 12566
  - <sup>10</sup> Muller C J, van Ruitenbeek J M and de Jongh L J 1992 Phys. Rev. Lett. 69 140
  - <sup>11</sup> Rubio-Bollinger G, Bahn S R, Agrat N, Jacobsen K W and Vieira S 2001 Phys. Rev. Lett. 87 026101
  - <sup>12</sup> Krans J M, Muller C J, Yanson I K, Govaert Th C M, Hesper R and van Ruitenbeek J M 1993 Phys. Rev. B 48 14721
  - <sup>13</sup> Untiedt C, Yanson A I, Grande R, Rubio-Bollinger G, Agrat N, Vieira S and van Ruitenbeek J M 2002 Phys. Rev. B 66 85418
  - <sup>14</sup> Jelinek P, Perez R, Ortega J and Flores F 2003 Phys. Rev. B 68 085403
  - <sup>15</sup> Nakamura A, Brandbyge M, Hansen L B and Jacobsen K W 1999 Phys. Rev. Lett. 82 1538
  - <sup>16</sup> Montgomery M J, Hoekstra J, Todorov T N and Sutton A P 2003 J. Phys.: Condens. Matter 15 731
  - <sup>17</sup> Todorov T N, Hoekstra J and Sutton A P 2001 Phys. Rev. Lett. 86 3606
  - <sup>18</sup> Todorov T N 2002 J. Phys.: Condens. Matter 14 3049
  - <sup>19</sup> Brandbyge M, Stokbro K, Taylor J, Mozos J-L and Ordejon P 2003 Phys. Rev. B 67 193104
  - <sup>20</sup> Todorov T N 1998 Philosophical Magazine B 77 965
  - <sup>21</sup> Zhitenev N B, Meng H and Bao Z 2002 Phys. Rev. Lett. 88 226801
  - <sup>22</sup> Ajl V, Moore J E and Varna C M 2003 Preprint cond-mat/0302222
  - <sup>23</sup> Chen Y-C, Zwolak M and DiVentra M 2003 Preprint cond-mat/0302425
  - <sup>24</sup> Nielsen S K 2002 PhD thesis, University of Aarhus, Denmark
  - <sup>25</sup> Kolesnychenko O Yu, Toonen A J, Shklyarevskii O I and van Kempen H 2001 Appl. Phys. Lett. 79 2707
  - <sup>26</sup> Hageman J C L, de Wijs G A, de Groot R A and Meier R J 2000 Macromolecules 33 9098
  - <sup>27</sup> Yanson I K 1974 Zh. Eksp. Teor. Fiz. 66 1035 [Sov. Phys.-JETP 39 506]
  - <sup>28</sup> Untiedt C, Rubio-Bollinger G, Vieira S and Agrat N 2000 Phys. Rev. B 62 9962
  - <sup>29</sup> Smith R H M, Untiedt C, Yanson A I and van Ruitenbeek J M 2001 Phys. Rev. Lett. 87 266102