Effect of Sr substitution on the stability of CuO_{1-d} chains in oxygen and nitrogen annealed $YBa_{2-x}Sr_xCu_3O_{7-d}$ (x = 0.0, 0.50, 1.0) superconducting system

M.A. Ansari^{*}, V.P.S. Awana, Anurag Gupta, R.B. Saxena, and H. Kishan

National Physical Laboratory, K.S. Krishnan Marg, New Delhi 110012, India.

Samples of YBa_{2-x}Sr_xCu₃O_{7- δ} (x = 0.0, 0.50, 1.0) series were synthesized by solid-state reaction and first annealed in flowing Q gas. All samples crystallized in orthorhombic structure, where orthorhombic distortion was found to decrease with an increase in x. Four probe resistivity measurements showed that superconducting transition temperature (T_c) decreases monotonically with x at a rate of dT_c/dx = 1.3 K/at%. The sample with x=0 had a T_c = 91 K. The samples were further annealed in flowing N₂ gas at 450 ^oC. The T_c of all samples decreased by nitrogen annealing. Interestingly, the decrease in T_c(x) became nearly three times larger at a rate of dT_c/dx = 3.7 K/at%. The sample with x=0 had a T_c = 42 K. We discuss possible reasons and implications of the T_c(x) suppression vis -à-vis stability of CuO_{1- δ} chains. Key words: Y-123, Sr substitution, Superconducting transition

*Presenting /corresponding Author: E-mail <u>ansari@mail.nplindia.ernet.in</u>

1. INTRODUCTION

The RE-123 structure can be viewed as (Ba)O / CuO₂ / RE / CuO₂ / (Ba)O slabs interconnected by a Cu-O sheets containing chains of Cu and O atoms with variable composition CuO_{1- δ} [1]. The oxygen sites in the CuO₂ planes are identified as O(2) and O(3). The oxygen site in the SrO plane is called O(4). The RE plane is devoid of any oxygen. In general oxygen sites O(2), O(3), and O(4) are

always fully occupied and any intake or release of oxygen takes place only from $\text{CuO}_{1-\delta}$ chains. The amount of oxygen released and as a result the decrease in T_c (superconducting transition temperature) depends not only on external reducing parameters but the intrinsic stability of $\text{CuO}_{1-\delta}$ chains.

The substitution of Sr at Ba-site though decreases marginally the superconducting

transition temperature (T_c) of the RE-123 [2], it increases substantially the performance of the compound under magnetic field, or otherwise improves the irreversibility line characteristics [3]. Under normal synthesis conditions Ba can be substituted only upto 50 % by Sr, for full substitution one needs to employ the high pressure high temperature route [4]. In the present study we study the change in the structure and T_c of the YBa_{2-x}Sr_xCu₃O_{7- δ} (x = 0.0, 0.50, 1.0) samples with respect to the removal of oxygen from chains. Our results show that the release of oxygen from YBa₂. $_{x}Sr_{x}Cu_{3}O_{7-\delta}$ compound increases with x, confirming the fact that Sr substitution at Ba-site introduces instability in Cu-O chains of RE-123 structure.

2. EXPERIMENTAL DETAILS

Samples of YBa_{2-x}Sr_xCu₃O_{7- δ} (x = 0.0, 0.50, 1.0) series were synthesized by solid-state reaction using ingredients Y₂O₃, SrCO₃, BaCO₃ and CuO. Calcinations were carried out on mixed powders at 880 °C, 890 °C, 900 °C and 910 °C each for 24 hours with intermediate grindings. Two set of pressed pellets were annealed in a flow of oxygen at 920 °C for 40 hours and subsequently cooled slowly to room temperature with an intervening annealing for 24 hrs. at 600 °C. On one set of pellets called "O₂-annealed" X-ray diffraction (XRD) data were obtained at room temperature (MAC Science: MXP18VAHF²²; CuK_{α} radiation) and four probe

resistance (R) measurements in the temperature (T) range of 12 - 300 K, were performed in a close cycle refrigerator. The other set of pellets was further annealed in flowing N_2 gas at 450 ^{0}C for 24 hrs., and will be called as "N₂-annealed". R(T) measurements were also performed on these samples.

3. RESULTS AND DISCUSSION

X-ray diffraction (XRD) patterns of all the O₂-annealed YBa_{2-x}Sr_xCu₃O_{7- δ} (x = 0.0, 0.50, 1.0 samples are shown in Fig.1. All the samples studied are phase pure in nature, except for x =1.0 sample where small unidentified impurity lies in the compound. Worth mentioning is the fact that through normal synthesis routes (without applying HPHT process) x = 1.0 is the solubility limit of Sr at Ba site in YBa2- $_{x}Sr_{x}Cu_{3}O_{7-\delta}$ compounds. Lattice parameters determined from XRD data revealed that these samples crystallize in an orthorhombic structure. The lattice parameters are: a = 3.824(2) Å, b =3.892(1) Å, and c = 11.672(3) Å, for x = 0.0; a =3.806(4) Å, b = 3.869(3) Å, and c = 11.606(3)Å, for x = 0.50 and a = 3.805(2) Å, b = 3.856(3)Å, and c = 11.572(5) Å, for x = 1.0. Substantial decrease in c-axis lattice parameter indicates successful Sr substitution at Ba-site in YBa₂. $_{x}Sr_{x}Cu_{3}O_{7-\delta}$. Orthorhombic distortion, i.e. *b-a*, decreases with x, indicating a decrease of oxygen content from Cu-O chains in the structure with Sr substitution, which is in agreement with previous reports [2,3].

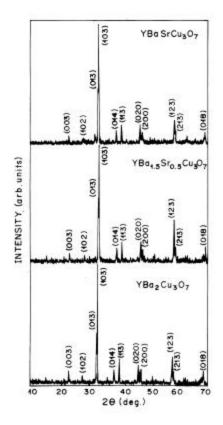


Fig.1 X-ray diffraction patterns for Q-annealed YBa_{2-x}Sr_xCu₃O_{7-δ} samples

Fig. 2 shows the resistance versus temperature plots for both O_2 - and N_2 - annealed YBa_{2-x}Sr_xCu₃O_{7- δ} compounds in temperature range of 12 to 200 K. In Q-annealed YBa₂₋ _xSr_xCu₃O_{7- δ} samples the superconducting transition temperature decreases monotonically with x. Decrease of T_c with x in YBa_{2-x}Sr_xCu₃O_{7- δ} is in agreement with previous report [2,3]. Quantitatively the decrease in T_c (dT_c/dx) is 1.3K/at% of Sr substituted at Ba-site in YBa₂₋ _xSr_xCu₃O_{7- δ}.

It was expected that substitution of bigger Ba cation by smaller cation Sr in RE-123 structure could increase the T_c by providing the internal crystallographic pressure. However this does not happen and ironically the T_c decreases

with x in YBa_{2-x}Sr_xCu₃O_{7- δ} system. However, note that the internal crystallographic pressure probably does get applied with Sr substitution, being evidenced by decrease in c-lattice parameter, but the same is probably not uniform over the unit cell. In particular the distance between the two superconducting CuO₂ planes increases instead of decreasing with x in YBa_{2-x}Sr_xCu₃O_{7- δ} [4,5].

This explains why T_c decreases with x in YBa_{2-x}Sr_xCu₃O_{7-δ} system. Another fact evidenced by decrease in orthorhombic distortion by increase in x is that oxygen content decreases with x in $YBa_{2-x}Sr_{x}Cu_{3}O_{7-\delta}$ system. We believe that the latter fact of decreased oxygen content coupled with the decreasing internal pressure on Cu-O₂ superconducting planes are both responsible for decrease of T_c in YBa_{2-x}Sr_xCu₃O_{7- δ} system.

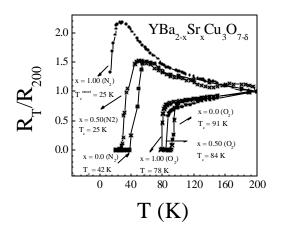


Fig. 2 Resistance versus temperature plots for both O_2 and N_2 annealed $YBa_{2-x}Sr_xCu_3O_{7-\delta}$ samples

Decrease in oxygen content of $YBa_{2-x}Sr_xCu_3O_{7-\delta}$ with x reveals that Sr substitution increases the instability of CuO_{1-\delta} chains of the

normal RE-123 structure and makes them more susceptible to the release of oxygen. The results of resistance versus temperature for N₂-annealed YBa_{2-x}Sr_xCu₃O_{7- δ} compounds are shown in Fig.2. The T_c for x = 0 (pristine) sample decreases from 91 K to 42 K. For x = 0.50 and 1.0 samples the T_c decreases from 84 K and 78 K to 25 K and around 5 K (extrapolated) respectively after N₂-annealing at 450 ^oC. Quantitatively the decrease in T_c (dT_c/dx) is 3.7 K/at% of Ba site Sr substitution in N₂-annealed YBa_{2-x}Sr_xCu₃O_{7- δ}. Interestingly the dT_c/dx for N₂-annealed samples is 3 times (3.7 K/at%)

REFERENCES

- "Crystal chemistry of High Tc superconducting Copper Oxides" by B. Raveau et al (Springer Verlag, 1991).
- T. Wada et al. Phys. Rev. B 41 (1190) 11209.

when compared to oxygen annealed (1.3 K/at%) $YBa_{2-x}Sr_{x}Cu_{3}O_{7-\delta}$. This shows that Sr substitution at Ba-site decreases T_c much faster in oxygen deficient YBa2-xSrxCu3O7-8 system than in oxygenated compounds. Before practical applications of YBa_{2-x}Sr_xCu₃O_{7-δ} compounds, due to their better irreversibility line characteristics [3], one should consider the relative instability of $CuO_{1-\delta}$ chains in them at various Sr content. Conclusively, our results show that stability of the YBa_{2-x}Sr_xCu₃O_{7-δ} compounds towards release of oxygen decreases with x.

- T. Nakane et al. Physica C 338 (2000) 25.
- O.I. Lebedev et al. Phys. Rev. B. 66 (2002) 132510.
- F. Licci et al. Phys. Rev. B 58 (1998) 15208.