

Tunneling spectroscopy of  $\text{Na}_x\text{CoO}_2$  and  $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ L. Shan<sup>1</sup>, H. Gao<sup>1</sup>, Y. G. Shi<sup>1</sup>, H. P. Yang<sup>1</sup>, X. F. Lu<sup>1</sup>, G. H. Cao<sup>2</sup>, Z. A. Xu<sup>2</sup> and H. H. Wen<sup>1</sup><sup>1</sup> National Laboratory for Superconductivity, Institute of Physics, Chinese Academy of Sciences, P. O. Box 603, Beijing 100080, P. R. China and<sup>2</sup> Department of Physics, Zhejiang University, Hangzhou 310027, P. R. China

(Dated: April 14, 2024)

The single electron tunneling spectroscopy on superconductor  $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$  and its starting compound  $\text{Na}_x\text{CoO}_2$  has been studied with point-contact method. The spectra of  $\text{Na}_x\text{CoO}_2$  have two types of distinct shapes at different random locations, this is attributed to the non-uniformly distributed sodium escaped from the inner part of the sample. While all the measured spectra of the superconducting samples  $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$  have a good spatial reproducibility, and show a remarkable zero bias conductance depression appearing below an onset temperature which associates very well with the resistance upturn at around 45 K. The latter behavior resembles in some way the pseudogap feature in high- $T_c$  cuprate superconductors.

PACS numbers: 74.50.+r, 74.62.Bf, 74.70.-b

After many years of intensive research on the physics of high  $T_c$  cuprate superconductors (HTSCs), there are still some crucial points needed to be clarified. A significant one is to determine the form of any other ground state coexisting and competing with superconductivity [1, 2], which is related to the possible existence and origin of the pseudogap [a suppression of the electronic states at the Fermi level in the normal state of HTSCs [3, 4]. Nonetheless, it is now widely accepted that the physics of HTSCs is that of the doped Mott insulator. Note that the recent synthesized superconductor  $\text{Na}_{0.35}\text{CoO}_2 \cdot y\text{H}_2\text{O}$  may also be viewed as a Mott insulator with electron doping of 35% while its  $T_c$  is only about 5 K [5]. Furthermore, the superconductivity phase diagram of  $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$  system is found to be analogy to the HTSCs [6]. Therefore, the investigation on the electronic and magnetic behavior of these materials may highlight the characteristics responsible to the high  $T_c$  superconductivity of the cuprates. Besides the extensive experimental [7, 8, 9, 10, 11, 12, 13] and theoretical [14, 15, 16, 17, 18, 19, 20, 21, 22] studies of this new superconducting system, its starting compound  $\text{Na}_x\text{CoO}_2$  has also attracted much attentions [23, 24, 25, 26, 27] and has been demonstrated to have some unconventional transport behavior and magnetic transition when  $x = 0.75$  [28]. However, to our knowledge no spectroscopic studies of both  $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$  and  $\text{Na}_x\text{CoO}_2$  have been reported so far in literature.

In this paper, we present the results of point-contact spectroscopy measurements on  $\text{Na}_x\text{CoO}_2$  and  $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$  compounds. The spectra of these two kinds of compounds have some essential differences not only on the spectral shape but also on their temperature dependence and spatial uniformity. Some possible mechanisms are suggested to explain all the observed novel spectral characteristics.

TABLE I: Sample information of the superconducting  $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$  (a and c are lattice parameters).

sample	x	a (Å)	c (Å)	y	$T_c$ (K)
SC 026	0.26	2.821	19.807	1.3	3.5
SC 031	0.31	2.820	19.650	1.3	4.1

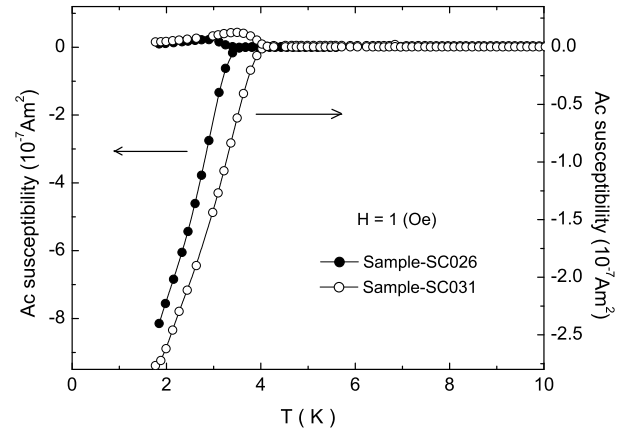


FIG. 1: Superconducting transitions measured by AC susceptibility.

The information of the  $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$  samples used in this work are presented in Table I. Fig. 1 shows the superconducting transition characterized by AC susceptibility measurements. The starting compounds of these two samples is  $\text{Na}_{0.70-0.05}\text{CoO}_2$  (NSC 070). Details of the sample preparation and characterizations have been given in Ref. [29] for  $\text{Na}_{0.26}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$  (SC 026) and in Ref. [10] for  $\text{Na}_{0.31}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$  (SC 031). Powder X-ray diffraction measurements indicate that both samples are hexagonal single phase. The spectroscopy measurements on these samples (SC 026, SC 031 and NSC 070) were proceeded with N/S (N = PtIr alloy; S denote samples) point contacts in the sample chamber of an Oxford cryo-

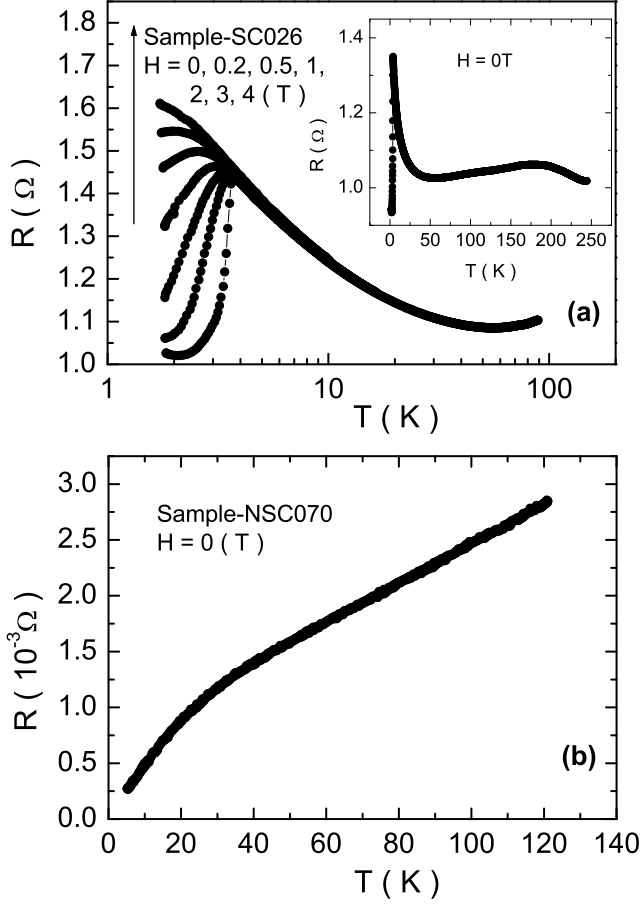


FIG. 2: (a) Temperature dependence of resistance of sample-SC026 at various magnetic fields from 0T to 4T. Inset is the large scale data measured at 0T. It is clear that a low temperature upturn of resistance appears at around 50 K. (b) Temperature dependence of resistance of sample-NSC070 measured at 0T.

genic system MgLaB<sub>6</sub> [12]. As described in our previous works [30], the PtIr tips were prepared by electrochemical etching in  $\text{CaCl}_2$  solution using  $\text{Pt}_{0.9}\text{Ir}_{0.1}$  wire with a diameter of 0.25 mm. The approaching of the tip toward the sample was controlled by a differential screw. Typical four-terminal and lock-in technique were used to measure the differential resistance  $dV=dI$  vs  $V$  of the point contacts. Then the  $dV=dI$  vs  $V$  curves were converted into the dynamical conductance  $dI=dV/dV$  (or  $dV/dI$ ) curves. In our tunneling spectroscopy measurements, we have processed bidirectional bias-voltage scanning in various rates, all the spectra presented in this paper are reproducible and have no hysteresis, so that the heating effect can be ruled out in these data.

Fig. 2 (a) shows the temperature dependence of the resistance of sample-SC026 at various magnetic fields. The superconducting transition becomes broad with increasing field and an increase of normal-state resistance with decreasing temperature occurs at about 50 K. However,

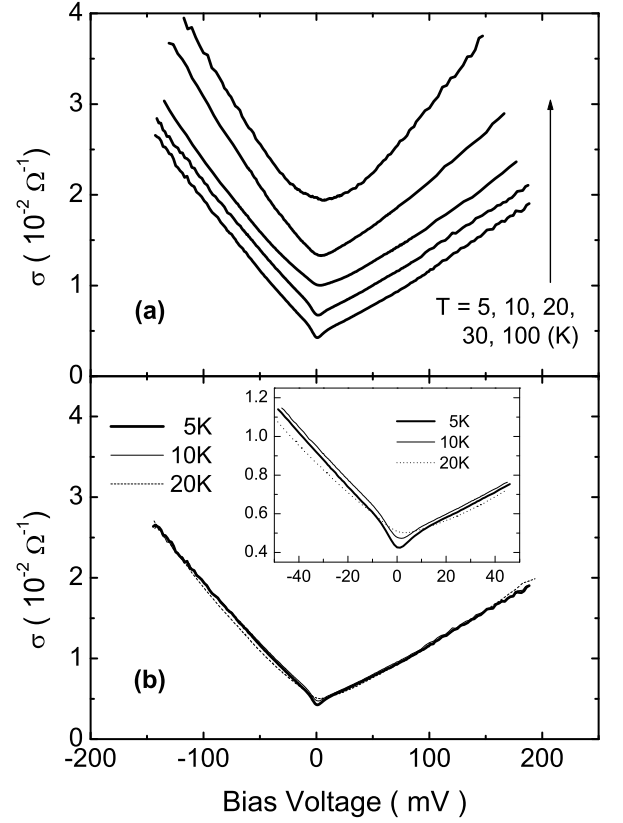


FIG. 3: Typical tunneling spectra of PtIr/NSC070 point contact measured at a fixed point on the sample surface for various temperatures. (a) All curves except the bottom one have been shifted upwards for clarity. (b) Raw data of three consecutive temperatures. Inset shows the enlarged detail around zero bias voltage.

the onset  $T_c$  does not depend significantly on the magnetic field. These characteristics are the same as that of sample-SC031 and the results presented in Ref. [5]. Similar behavior is always observed in high- $T_c$  copper oxides. As a comparison, we present in Fig. 2 (b) the  $R$ - $T$  relation of sample-NSC070. It is noted that the resistance decreases monotonically with decreasing temperature and a weak inflexion occurs at around 30 K. Such remarkable resistive difference between the superconductors and their starting compounds with similar structure should be a reflection of their different electronic states.

Fig. 3 shows the typical tunneling spectra measured on the PtIr/NSC070 point contacts. Examining the gross features of a tunneling conductance curve shown in Fig. 3, one notes the background with a slight positive curvature, which is ordinary for the metal-insulator-metal junctions. A closer scrutiny in the region near zero bias reveals a small conductance dip as shown in the inset of Fig. 3 (b). Such small dips exist between a narrow bias range of  $\sim 10$  mV at low temperatures while disappears for higher temperatures. These features are similar to that of nonequilibrium electron tunneling in metal-insulator-

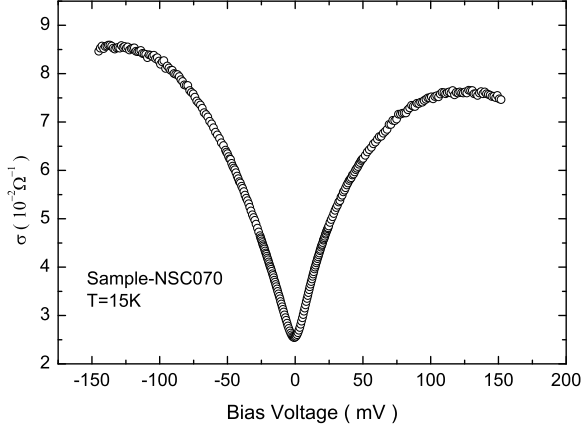


FIG. 4: The other type of spectra of PtIr/NSC 070 point contact observed occasionally, which is associated with Giaever-Zeller two step tunneling as discussed in the text.

metal junctions [31, 32].

As shown in Fig. 4, the other type of spectrum of sample-NSC 070 has also been observed occasionally at some random positions of the sample surface. However, the little probability of observing such spectrum and its bad reproducibility indicate that it comes from some local properties. The zero bias conductance dip shown in Fig. 4 is much more significant than that shown in Fig. 3, that is, a giant resistance peak occurs. According to the model proposed by Zeller and Giaever [33], such giant resistance peak around zero bias can be achieved if tunneling occurs through intermediate states on metal particles embedded in the oxide barrier. This is very close to the surface condition of sample-NSC 070, since the sodium atoms between the  $\text{CoO}_2$  layers in  $\text{Na}_x\text{CoO}_2$  are easy to escape from the bulk. Because the small amount of separated sodium on the surface are easily oxidated, it is possible in some positions of sample surface to form the oxide (or carbonate) barrier with embedded sodium particles, and hence the Giaever-Zeller two step tunneling model is favored. A direct consequence of such spatial un-uniformity is that, when the tip locates closely to the phase boundaries of the normal regions and the Giaever-Zeller regions, even a slight tip relaxation caused by temperature variation can lead to a remarkable change of the measured spectra. This is indeed observed in few cases in our measurements.

The measured tunneling spectra of samples SC 026 and SC 031 are presented in Fig. 5(a) and (b) respectively. No characteristic of superconductivity such as coherence peak can be detected in the measured tunneling spectra. This may be ascribed to the very low  $T_c$ , broad superconducting transition, and extremely low density of charge carriers. However, by comparing these results with that of NSC 070, we can find following remarkable differences between them besides their distinct spectral details. Firstly, the spectra of superconducting samples have a good symmetry for the opposite sides

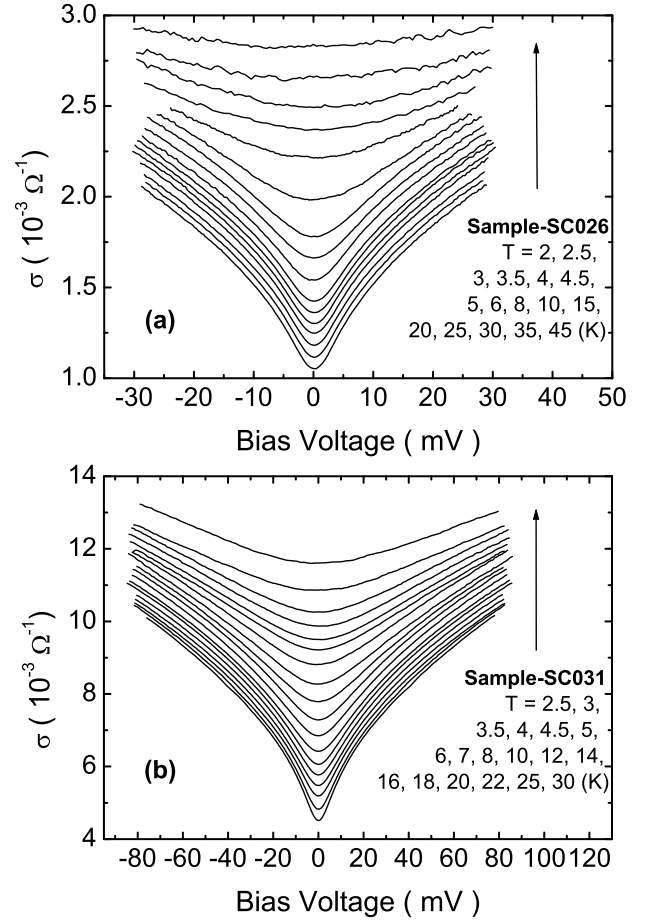


FIG. 5: Temperature dependence of the tunneling spectra of PtIr/SC 026 (a) and PtIr/SC 031 point contacts. All curves except the bottom one has been shifted upwards for clarity. Noting the similar spectral shape and temperature dependence of these two samples.

of zero bias while the non-superconducting sample does not; Secondly, the spectral shape is identical for various positions on the surfaces of the superconducting samples, unlike their starting compounds. The good reproducibility of the temperature dependent spectra for the samples SC 026 and SC 031 in several thermal cycles indicates the phase stability and spatial homogeneity of the electronic states. The spatially consistent conductance depression may rule out the spatial-related mechanisms such as above discussed Giaever-Zeller model and the magnetic impurity effect. A rough estimation of the onset temperature of this characteristic is somewhat above 45K for sample-SC 026, which is close to the onset temperature of the resistance upturn as shown in Fig. 2 (a). Another explanation for this conductance depression is the pseudogap effect as observed in cuprate high  $T_c$  superconductors. In fact, the shape and temperature dependence of this conductance depression are similar to that observed in the electronic doped cuprate superconductor  $\text{Pr}_{2-x}\text{Ce}_x\text{CuO}_{4-y}$  [2, 34]. In this sense,

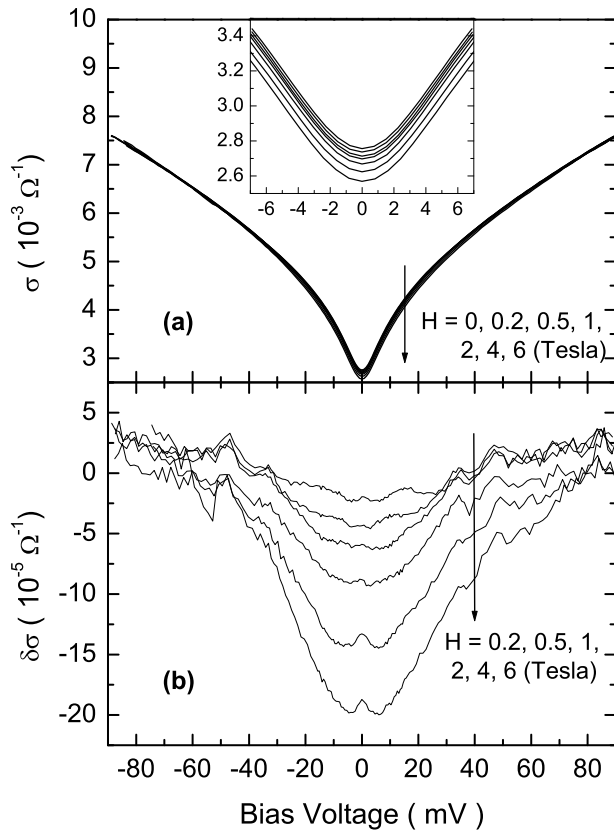


FIG. 6: (a) Magnetic field dependence of the tunneling spectra of PtIr/SC031 point contact. Inset shows the enlarged details around zero bias voltage. (b) Redraw the data as shown in (a) after a subtraction of the data of 0T.

the occurrence of the conductance depression and the resistance enhancement with decreasing temperature correspond to the opening of the pseudogap around the Fermi

level.

In order to get further insight into this anomalous conductance depression, we have studied the magnetic field influence on the tunneling spectroscopy. Fig. 6(a) shows the field dependence of the tunneling spectra and the details around zero bias are enlarged in the inset. It is noted that the spectra measured at various fields overlap each other at high bias while gradually separate from each other with decreasing bias voltage. In order to give a more clear elucidation, we present in Fig. 6(b) the field dependent spectra after a subtraction of the zero field one. It is obvious that the applied magnetic field induces an additional zero bias conductance depression with a magnitude in proportional to the magnetic field.

In summary, we have performed tunneling spectroscopy measurements on the PtIr/ $\text{Na}_x\text{CoO}_2$  and PtIr/ $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$  point contacts. The observed spatially sensitive spectra of  $\text{Na}_x\text{CoO}_2$  are associated with the non-uniformly distributed escaped sodium and its oxide. While the spatially consistent conductance depression in the spectra of  $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$  seems to be related to the resistance upturn at low temperature, which resembles in some way the pseudogap effect observed in the underdoped cuprate superconductors. However, its anomalous magnetic field dependence can not be directly comparable to the cuprate superconductors. Additional experiments are still needed to clarify this issue.

#### Acknowledgments

This work is supported by the National Science Foundation of China (NSFC 19825111, 10074078), the Ministry of Science and Technology of China (project: NKBR SF-G 1999064602), and Chinese Academy of Sciences with the Knowledge Innovation Project.

- 
- [1] H. J. Kang, Pengcheng Dai, J. W. Lynn, M. Matsura, J. R. Thompson, Shou-Cheng Zhang, D. N. Argyriou, Y. Onose, and Y. Tokura, *Nature* 423, 522 (2003).
  - [2] L. Ali, Y. Krockenberger, B. Welter, M. Schonecke, R. Gross, D. Manske, and M. Naito, *Nature* 422, 698 (2003).
  - [3] J. L. Tallon, and J. W. Loram, *Physica C* 349, 53 (1999).
  - [4] T. Timusk, and B. Statt, *Rep. Prog. Phys.* 62, 61 (1999).
  - [5] K. Takada, H. Sakurai, E. Takayama-Muromachi, F. Izumi, R. A. Dilanian, and T. Sasaki, *Nature* 422, 53 (2003).
  - [6] R. E. Schaak, T. Klimczuk, M. L. Foo, and R. J. Cava, *Nature* 424, 527 (2003).
  - [7] M. L. Foo, R. E. Schaak, V. L. Miller, T. Klimczuk, N. S. Rogado, Yayu Wang, G. C. Lau, C. C. Haley, H. W. Zandbergen, N. P. Ong, and R. J. Cava, *Solid State Commun.* 127, 33 (2003).
  - [8] H. Sakurai, K. Takada, S. Yoshii, T. Sasaki, K. Kondo, and E. Takayama-Muromachi, *cond-matt/0304503*.
  - [9] B. Lorenz, J. Chaudhary, R. L. Meng, and C. W. Chu, *cond-matt/0304537*.
  - [10] G. H. Cao, C. Feng, Y. Xu, W. Lu, J. Q. Shen, M. H. Fang, and Z. A. Xu, *cond-matt/0305503*.
  - [11] Y. Kobayashi, M. Yokoi, and M. Sato, *cond-matt/0305649*; *cond-matt/0306264*.
  - [12] B. G. Ueland, P. Schier, R. E. Schaak, M. L. Foo, V. L. Miller, and R. J. Cava, *cond-matt/0307106*.
  - [13] J. W. Lynn, Q. Huang, C. M. Brown, V. L. Miller, M. L. Foo, R. E. Schaak, C. Y. Jones, E. A. Macey, and R. J. Cava, *cond-matt/0307263*.
  - [14] G. Baskaran, *cond-matt/0303649*.
  - [15] B. Kumari, and B. S. Shastry, *cond-matt/0304210*.
  - [16] Q. H. Wang, D. H. Lee, and P. A. Lee, *cond-matt/0304377*.
  - [17] M. Ogata, *cond-matt/0304405*.
  - [18] A. Tanaka, and X. Hu, *cond-matt/0304409*.
  - [19] D. J. Singh, *Phys. Rev. B* 68, 020503 (2003).

- [20] K. Sano, and Y. Ono, cond-m att/0304620.
- [21] T. Li, and Y. J. Jiang, cond-m att/0309275.
- [22] D. Sa, M. Sardar, and G. Baskaran, cond-m att/0309563.
- [23] I. Terasaki, Y. Sasago, and K. Uchinokura, Phys. Rev. B 56, R12685 (1997).
- [24] T. Tanaka, S. Nakamura, and S. Iida, Jpn. J. Appl. Phys. 33, L581 (1994).
- [25] R. Ray, A. Ghoshray, K. Ghoshray, and S. Nakamura, Phys. Rev. B 59, 9454 (1999).
- [26] Y. Ono, R. Ishikawa, Y. Miyazaki, and T. Kajitani, J. Phys. Soc. Jpn. 70, 235 (2001).
- [27] M. Z. Hasan, Y. D. Chuang, A. P. Kuperin, Y. Kong, D. Qian, Y. W. Li, B. L. Mesler, Z. Hussain, A. V. Fedorov, R. Kimmeling, E. Rotenberg, K. Rossnagel, H. Koh, M. Rogado, M. L. Foo, and R. J. Cava, cond-m att/0308438.
- [28] T. Motohashi, R. Ueda, E. Naulis, T. Tojo, I. Terasaki, T. Atake, M. Karppinen, and H. Yamachi, Phys. Rev. B 67, 064406 (2003).
- [29] Y. G. Shi, J. Q. Li, H. C. Yu, Y. Q. Zhou, H. R. Zhang, and C. Dong, cond-m att/0306070.
- [30] L. Shan, H. J. Tao, H. Gao, Z. Z. Li, Z. A. Ren, G. C. Che, and H. H. Wen, Phys. Rev. B 68, 144510 (2003).
- [31] J. G. Aklers, H. J. Kreuzer, and J. Straus, Phys. Rev. B 11, 2812 (1975).
- [32] E. L. Wolf, Principle of Electron Tunneling Spectroscopy (Oxford University Press, New York, 1985).
- [33] H. R. Zeller, and I. Giaever, Phys. Rev. 181, 789 (1969).
- [34] A. Biswas, P. Fournier, V. N. Smolyaninova, R. C. Budhani, J. S. Higgins, and R. L. Greene, Phys. Rev. B 64, 104519 (2001).