

Resonant Raman scattering in mercurate single crystals

Y. Gallais¹, A. Sacuto^{1,2} and D. Colson³

¹ *Laboratoire de Physique du Solide (UPR 5 CNRS) ESPCI,
10 rue Vauquelin 75231 Paris.*

² *Matériaux et Phénomènes Quantiques (FER 2437 CNRS), Université Paris 7
2 place Jussieu 75251 Paris.*

³ *Service de Physique de l'Etat Condensée, CEA-Saclay, 91191
Gif-sur-Yvette, France*

Abstract

We report resonant electronic Raman scattering in optimally doped single layer $\text{HgBa}_2\text{CuO}_{4+\delta}$ (Hg-1201) and trilayer $\text{HgBa}_2\text{Ca}_2\text{Cu}_3\text{O}_{8+\delta}$ (Hg-1223) single crystals. Analysis of the B_{1g} and B_{2g} channels in the superconducting state of Hg-1201 advocates for a gap having d-wave symmetry. In addition a resonant study B_{1g} pair-breaking peak and the A_{1g} peak suggests that the A_{1g} peak is not directly related to the d-wave superconducting gap amplitude. Comparison with trilayer Hg-1223 demonstrates the universal behavior of this two energy scales in optimally doped cuprates.

1. Introduction

In recent years electronic Raman scattering (ERS) has been used extensively to probe both the normal and the superconducting states of the cuprates. While the broad Raman continuum in the normal state is only poorly understood at present, Raman spectra in the superconducting state have been described quite successfully in terms of BCS theory with a d-wave gap in optimally doped cuprates [1,2]. By using different incident and scattered light polarisation ERS probes different directions in reciprocal space allowing an analysis of the gap symmetry. The B_{1g} symmetry is sensitive to the $k_x = 0$ and $k_y = 0$ directions and thus gives a pair-breaking peak at $2\Delta_0$ while the B_{2g} symmetry probes the $k_x = k_y$ directions and is sensitive to the nodes of the d-wave gap. Although spectra taken in these two symmetries cuprates are consistent with a d-wave gap in most optimally doped cuprates, spectra taken in the fully symmetrical A_{1g} channel reveal a peak below $2\Delta_0$ whose intensity and position are difficult to reconcile with a simple d-wave gap picture [3]. In this symmetry, vertex corrections due to Coulomb interaction and charge conservation (or backflow) are expected to strongly suppress the scattering intensity

in the superconducting state [4]. Therefore the intensity in the A_{1g} channel is expected to be much smaller than in the B_{1g} symmetry. This contradicts experimental results in most cuprates which show an A_{1g} peak intensity stronger than the B_{1g} one in most cases [1,2,5]. Many scenarios have been proposed to explain this discrepancy: coupling between adjacent CuO_2 planes [3], resonant effect of the Raman vertex [6] and, for three and four layer cuprates, contribution from the c-axis bilayer plasmon observed in the far-infrared spectra of the c-axis conductivity [7]. Recently we have shown using Ni substitution in optimally doped Y-123 that the energy of the A_{1g} peak follows intriguingly the energy of the neutron resonance detected in the spin excitation spectrum by Inelastic Neutron Scattering (INS) [5]. However the exact microscopic mechanism of the A_{1g} peak remains unclear and more experimental work is clearly needed. In this paper we report Raman scattering in $\text{HgBa}_2\text{CuO}_{4+\delta}$ (Hg-1201) and $\text{HgBa}_2\text{Ca}_2\text{Cu}_3\text{O}_{8+\delta}$ (Hg-1223) where the $2\Delta_0$ pair breaking peak and the A_{1g} peak have been studied as a function of the excitation energy. Both energy scales show very different resonant behaviors in Hg-1201, suggesting different underlying microscopic mechanisms. Comparison with the trilayer Hg-1223 demonstrates

that the nature of the two energy scales is independent of the number of CuO₂ layers and is therefore a universal property of the superconducting CuO₂ plane.

2. Experimental

Raman scattering experiments were performed on two different single crystals: the single layer Hg-1201 ($T_c=95$ K) and the trilayer Hg-1223 ($T_c=125$ K). Both crystals are very close to optimal doping and have tetragonal symmetry. The single crystal of Hg-1201 has been successfully grown by the flux method. The detailed procedure for crystal growth will be described elsewhere [8]. Details on the synthesis of Hg-1223 single crystals can be found in ref. [9]. Plane polarised spectra were taken using different lines from a Ar⁺-Kr⁺ laser and by a JY T64000 spectrometer (except for the Hg-1223 data where a JY U1000 was used). The spectra were corrected from the spectrometer response, the Bose factor and the optical constants thus yielding the imaginary part of the Raman response. Temperature indicated are corrected from the laser heating for Hg-1201 spectra (typically 10 to 15K) and are the nominal temperatures for Hg-1223 spectra.

3. Results and discussion

3.1. Hg-1201

In Figure 1 we show spectra in the B_{1g} , A_{1g} and B_{2g} channels in the normal and superconducting states using the 2.4 eV (514.5 nm) excitation line. In the B_{1g} channel, which probes the antinodal region (($\pi,0$) points), the response in the superconducting state shows the usual $2\Delta_0$ pair breaking peak located around 520 cm^{-1} . This gives a coupling ratio $\frac{2\Delta_0}{k_B T_c}$ of 7.9. The response in the A_{1g} symmetry on the other hand shows a very strong superconductivity induced peak located below the $2\Delta_0$ at an energy of 330 cm^{-1} ($\frac{E_{A_{1g}}}{k_B T_c}=5.1$). The presence of the two different energy scales is consistent with data on other optimally doped cuprates [5]. We note that the presence of a strong A_{1g} peak in a single layer cuprate rules out a scenario in which the peak is due to unscreened charge fluctuation between adjacent CuO₂ layers. In the B_{2g} symmetry, which probes the nodal region, we do not observe any superconductivity induced peak. The presence of a weak peak in the superconducting state of the B_{2g} symmetry appears to be material dependant and could be sensitive to disorder [10].

As was pointed out by Devereaux et al. [1] careful inspection of the power law behaviors in the B_{1g} and B_{2g}

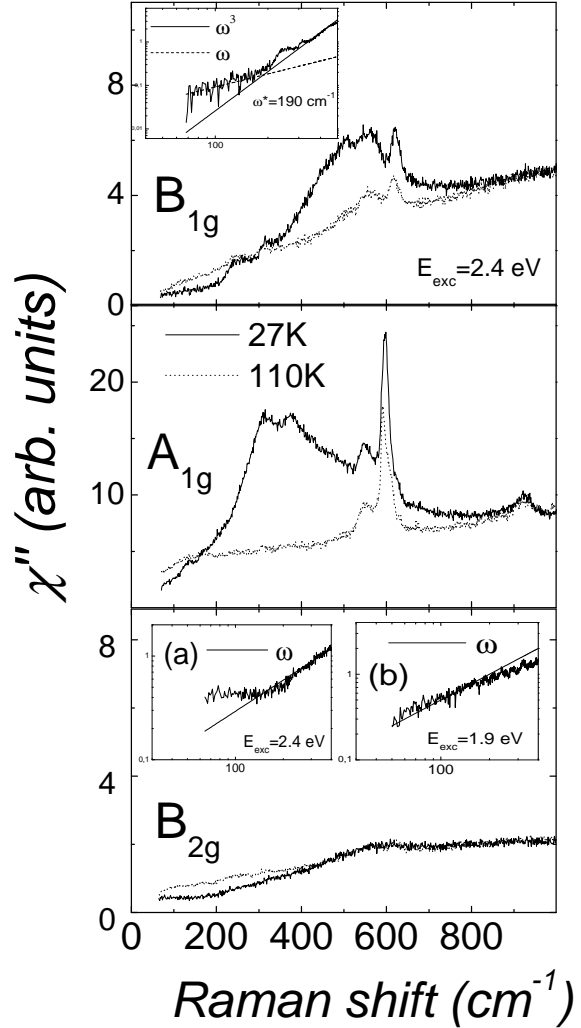


Fig. 1. Raman responses of optimally doped Hg-1201 in B_{1g} , A_{1g} and B_{2g} symmetries in the normal and superconducting states. The A_{1g} symmetry was obtained by subtracting the B_{2g} component to the spectra taken in ($x'x'$) scattering geometry ($A_{1g} + B_{2g}$). Insets show log-log plots of the response in B_{1g} and B_{2g} symmetries with linear and cubic fits. All spectra are taken using the 2.4 eV excitation line except spectrum shown in the inset (b) for the B_{2g} channel which was performed using the 1.9 eV excitation line.

channels can yield information on the gap anisotropy. For a clean d-wave superconductor the low energy Raman response in B_{1g} symmetry is expected to follow a cubic law while the B_{2g} symmetry should be linear. In the B_{1g} channel a crossover between linear and cubic behavior is observed around 190 cm^{-1} (see inset) consistent with theoretical prediction for disordered d-wave superconductors [10]. Similar behavior in this symmetry using the 2.2 eV and the 1.9 eV excitation is observed (see Figures 2 and 3). On the other hand spectrum in the B_{2g} is linear except below 140 cm^{-1} where

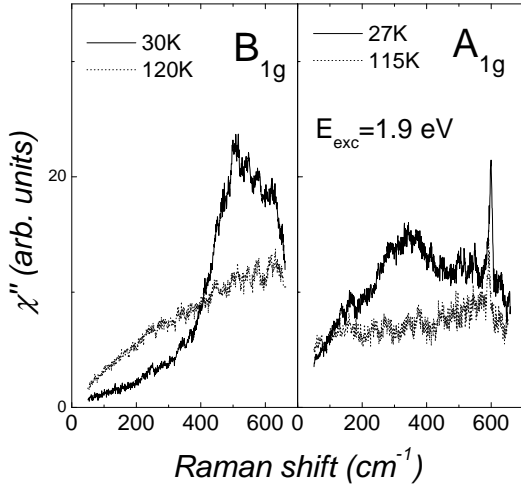


Fig. 2. Raman responses of Hg-1201 in the B_{1g} and A_{1g} symmetries using the 1.9 eV excitation line.

additional scattering is found producing a nearly flat continuum at low energy. The origin of this anomalous additional intensity is unclear but the same spectrum taken using the 1.9 eV excitation energy display a linear behavior at low energy down to the lowest energy measured (50 cm^{-1}) suggesting the presence of nodes in the (π, π) direction in the gap function (see inset (b) of Figure 1). Thus the increase of scattering at low energy using the 2.4 eV excitation is most likely spurious and we conclude that the present data indicate a gap of d-wave symmetry in optimally doped Hg-1201.

In figures 2 and 3 we examine the resonant behavior of the B_{1g} and A_{1g} peaks. In Figure 2 we have plotted spectra in the normal and superconducting states performed using the 1.9 eV excitation. We note that if both peak are located at the same energy as the one taken using the 2.4 eV, their relative intensities have changed drastically. While for the 2.4 eV excitation the A_{1g} peak intensity more than twice the B_{1g} pair breaking peak intensity, the situation is opposite in the case of the 1.9 eV excitation energy where the A_{1g} peak intensity is now a factor 1.5 smaller than the B_{1g} pair breaking peak. In Figure 3 the B_{1g} and A_{1g} channels in the superconducting state are shown as a function of the excitation energy used. Similarly to the case of Y-123 and Bi-2212 the A_{1g} peak position in Hg-1201 is found to be insensitive to the choice of excitation energy and remains centered around 330 cm^{-1} . Its intensity is nearly constant between 2.4 eV and 1.9 eV but is decreased by about a factor 2 when using the 2.2 eV excitation line (see Figure 3). The B_{1g} pair breaking peak on the other hand shows a remarkable resonant behavior toward 1.9 eV (see figure 3): its intensity is nearly the same for 2.4 eV and 2.2 eV but is enhanced for 1.9 eV by more than a factor 4. In a similar way the normal state B_{1g} continuum intensity is also enhanced

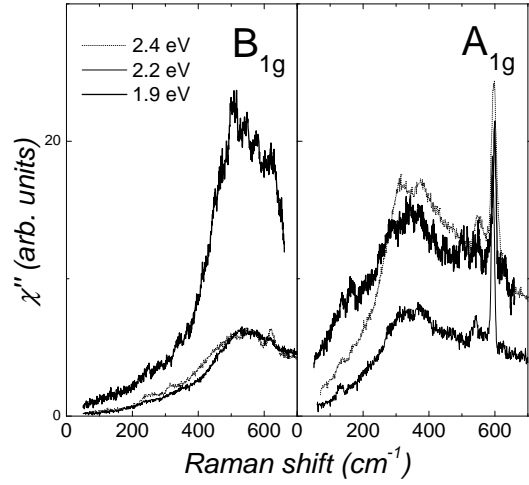


Fig. 3. B_{1g} and A_{1g} symmetries in the superconducting state ($T=27\text{K}-30\text{K}$) taken at three different excitation energies.

towards 1.9 eV (see Figures 1 and 2). Such a simultaneous resonant behavior in both the normal and superconducting states in the B_{1g} channel has also been observed in Tl2201 [11] and strongly advocates for an electronic origin of the normal state B_{1g} Raman continuum below 1000 cm^{-1} .

Previous resonant Raman scattering studies have been mainly focused on the resonant properties of the B_{1g} (or B_{2g}) pair breaking peak. Resonant Raman scattering data in Tl-2201 [11] show a strong increase of the B_{1g} peak intensity toward high excitation energies (3 eV) and more recently resonant behavior of the B_{2g} channel towards low excitation energy (1.9 eV) was found in electron doped NCCO [12]. In a free electron-like picture of Raman scattering, resonant behavior is achieved when the incident (or scattered) photon energy equals an interband distance in k-space. In principle resonance effects can strongly affect the actual k-dependence of the Raman vertices and thus be used to selectively probe different directions in k-space [6]. In our case the resonance enhancement at 1.9 eV in the B_{1g} channel indicates the presence of an interband transition near the $(\pi, 0)$ point of the Brillouin zone in Hg-1201. If we believe band structure calculations, this transition most likely takes place between the non bonding bands and the Fermi level (antibonding band) [13].

We now discuss on the implications of the different resonant behaviors of the B_{1g} pair breaking peak and the A_{1g} peak. As mentioned in the introduction, theoretical Raman responses in a standard BCS d-wave framework systematically fail to reproduce the experimentally observed A_{1g} response. Probing essentially the whole Fermi surface the A_{1g} channel is expected to be greatly influenced by resonances. As a consequence, the A_{1g} peak position, if related to the amplitude of the

superconducting gap, should be very sensitive to the choice of excitation energy, especially near resonances. In the present case, the resonant behavior of the Raman vertex in the $(\pi,0)$ direction should result in a shift of the A_{1g} peak position towards $2\Delta_0$ [6]. In contrast our data show that its position is constant despite the resonance effect in the $(\pi,0)$ direction observed in the B_{1g} channel with the 1.9 eV excitation line. Thus the A_{1g} peak is a true energy scale which is not directly related the amplitude of the d-wave superconducting gap. In fact near the optimally doped regime of many cuprates this energy scale tracks closely that of the neutron resonance observed in the spin excitation spectrum by INS [5].

3.2. Hg-1223

In figure 4 the B_{1g} and A_{1g} spectra in the superconducting state of Hg-1223 are shown for the 1.9 and 2.4 eV excitation lines. As in the case of Hg-1201 the B_{1g} response shows a resonance toward 1.9 eV but this time its intensity increases only by less than a factor 2. The pair breaking peak position shifts slightly towards lower energy: from $2\Delta_0=780\text{ cm}^{-1}=9.0\text{ k}_BT_c$ for 2.4 eV it moves down to $2\Delta_0=720\text{ cm}^{-1}=8.3\text{ k}_BT_c$ for 1.9 eV. These coupling ratios are very similar to the one measured in Hg-1201 ($2\Delta_0=8.1\text{ k}_BT_c$) and suggest that the amplitude of the gap is controlled by T_{cmax} in the Hg-based cuprates family. A similar behavior was found in a ARPES study of the Bi family [14]. In the case of the A_{1g} channel the peak is located at $500\text{ cm}^{-1}=5.7\text{ k}_BT_c$ (5.1 k_BT_c for Hg-1201). We also note that its intensity is the same for both excitation energies (again similar to the case of Hg-1201, see Figure 3). The very similar behavior between $n=1$ and $n=3$ in the A_{1g} channel with respect to both their resonance behavior and their scaling with T_c rules out the possibility that the peak is dominated by a c-axis plasmon component in three and four layers cuprates as has been suggested recently [7]. On the contrary it clearly indicates that the A_{1g} peak has the same origin for both single and trilayer cuprates.

4. Conclusion

We have reported resonant Raman scattering in single layer Hg-1201. Analysis of the low energy part of the spectra in the superconducting indicates a gap of d-wave symmetry. Spectrum in the B_{1g} channel, contrary to the A_{1g} channel, shows a remarkable resonant behavior of the pair breaking towards the 1.9 eV excitation energy. The different resonant behavior between both channels indicates different microscopic ori-

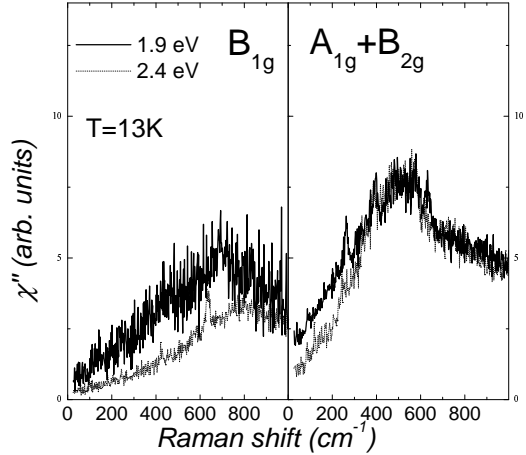


Fig. 4. Raman spectra of Hg-1223 in the superconducting state in B_{1g} and $A_{1g}+B_{2g}$ symmetries at 1.9 and 2.4 eV. The B_{2g} component is much weaker than the A_{1g} so that the $A_{1g}+B_{2g}$ spectrum is essentially dominated by the A_{1g} component.

gins for the B_{1g} pair breaking peak and the A_{1g} peak. The latter appears to be related to the neutron resonance energy scale. In addition, data on trilayer Hg-1223 demonstrate the universal character of the two energy scales, irrespective to the number of CuO_2 layers. The presence in the A_{1g} Raman spectra of an energy scale also seen in the spin excitation spectrum by INS is presently not understood and requires further experimental and theoretical investigations.

References

- [1] T. P. Devereaux et al., Phys. Rev. Lett. **72**, 396 (1994).
- [2] A. Sacuto, J. Cayssol, D. Colson and P. Monod, Phys. Rev. B **61**, 7122 (2000).
- [3] T. Strohm and M. Cardona, Phys. Rev. B **55**, 12725 (1997).
- [4] M. V. Klein and S. B. Dierker, Phys. Rev. B **29**, 4976 (1984).
- [5] Y. Gallais et al., Phys. Rev. Lett. **88** 177401 (2002).
- [6] E. Sherman, C. Ambrosch-Draxl and O. V. Misochko, Phys. Rev. B **65**, 140510 (2002).
- [7] D. Munzar and M. Cardona, Phys. Rev. Lett. **90**, 077001 (2003).
- [8] D. Colson et al. to be published.
- [9] D. Colson, A. Bertinotti, J. Hammann, J. F. Marucco and A. Pinatel, Physica C **233**, 231 (1994).
- [10] T. P. Devereaux, Phys. Rev. Lett. **74**, 4313 (1995).
- [11] M. Kang, G. Blumberg, M. V. Klein and N. N. Kolesnikov, Phys. Rev. Lett. **77**, 4434, (1996).
- [12] G. Blumberg et al., Phys. Rev. Lett. **88**, 107002 (2002).
- [13] C. Osvaldo Rodriguez, Phys. Rev. B **49**, 1200 (1994).

[14] T. Sato et al., Phys. Rev. Lett. **89**, 067005 (2002).