

Substitution Effect by Deuterated Donors on Superconductivity in $-(\text{BEDT-TTF})_2\text{CuN}(\text{CN})_2\text{Br}$

Naoki YONEYAMA¹, Takahiko SAKAI¹ and Norio KOBAYASHI^{1,2}

¹Institute for Materials Research, Tohoku University, Sendai 980-8577, Japan

²Center for Low Temperature Science, Tohoku University, Sendai 980-8577, Japan

We investigate the superconductivity in the deuterated BEDT-TTF molecular substitution system $-(\text{h8-BEDT-TTF})_{1-x}(\text{d8-BEDT-TTF})_x)_2\text{CuN}(\text{CN})_2\text{Br}$, where h8 and d8 denote fully hydrogenated and deuterated molecules, respectively. Systematic and wide range ($x = 0 \{ 1$) substitution can control chemical pressure nearly near the Mott boundary, which results in the modification of the superconductivity. After cooling slowly, the increase of T_c observed up to $x = 0.1$ is evidently caused by the chemical pressure effect. Neither reduction of T_c nor suppression of superconducting volume fraction is found below $x = 0.5$. This demonstrates that the effect of disorder by substitution is negligible in the present system. With further increase of x , both T_c and superconducting volume fraction start to decrease toward the values in $x = 1$.

KEYWORDS: organic superconductor, deuterium substitution, chemical pressure, Mott transition, cooling rate

The $-(\text{BEDT-TTF})_2\text{X}$ type family of organic charge transfer salts, $-(\text{BEDT-TTF})_2\text{X}$, has a two-dimensional crystal structure consisting of alternating layers of conducting donors and insulating anions,¹⁾ where BEDT-TTF (ET) is bis(ethylenedithio)tetrathiafulvalene. The strongly correlated electron interaction plays an important role in the electronic states of this system, which is quite sensitive to hydrostatic pressure, anion, and deuterium substitution. In the salt with $\text{X} = \text{CuN}(\text{CN})_2\text{Cl}$, whose ground state is an antiferromagnetic insulating (AFI) state at ambient pressure, a superconducting (SC) state appears by pressure of a few hundred bar.²⁽⁵⁾ This insulator-to-metal transition has been explained as a Mott transition under the control of the conduction band width.⁶⁾ The Mott transition can also be induced by substituting Br for Cl; the ground state of the salt with $\text{X} = \text{CuN}(\text{CN})_2\text{Br}$ (hereafter abbreviated as the $\text{CuN}(\text{CN})_2\text{Br}$ salt) is a SC one at ambient pressure. This change of the ground state by anion substitution is caused by the larger anion size of Br than that of Cl (chemical pressure). However, for the appearance of the bulk SC state in the $\text{CuN}(\text{CN})_2\text{Br}$ salt, the conventional hydrogenated ET (h8-ET) donor is needed. It is because deuterium substitution in the h8-ET, forming the deuterated ET (d8-ET), results in an AFI ground state coexisting with a minor SC phase.^{7,8)} This metal-to-insulator transition by deuterium substitution is attributed to (negative) chemical pressure, originated from the slight difference between the C-H and C-D bond lengths. In addition, deuterium substitution increases T_c by 0.3 K in the SC salt with $\text{X} = \text{Cu}(\text{NCS})_2$ (the $\text{Cu}(\text{NCS})_2$ salt).⁹⁾ Even in other superconductors, i.e., $-(\text{ET})_2\text{SF}_5\text{CH}_2\text{CF}_2\text{SO}_3$ and $-(\text{ET})_2\text{Ag}(\text{CF}_3)_4$ (1-bromo-1,2-dichloroethane), the similar increase of T_c in the corresponding deuterated salts has been observed.¹⁰⁾ Thus deuterium substitution in the ET-based SC salts will not give the normal BCS isotope

effect in general.¹¹⁾

Taking account of the chemical pressure effect described above and the negative slope of T_c with pressure in the electronic phase diagram of the $-(\text{ET})_2\text{X}$ system,¹²⁽¹⁴⁾ T_c is expected to increase by deuterium substitution in the $\text{CuN}(\text{CN})_2\text{Br}$ salt. However, a decrease of T_c has been found.^{15,16)} This contradiction in the variation of T_c is unclear, while it may be related to the non-bulk SC property in the deuterated salt.

To control chemical pressure, partial deuteration of ET molecules has been studied in the $\text{CuN}(\text{CN})_2\text{Br}$ salt.¹⁷⁽²⁰⁾ This method provides a systematic variation based on the uniform donor molecules, but only three kinds of the partially-deuterated ET have been synthesized between the d8- and h8-ET molecules. Moreover the preparation of such unique donors may not always be convenient for making crystalline samples large enough for physical measurements.

As another method to apply chemical pressure to the $\text{CuN}(\text{CN})_2\text{Br}$ salt, we here investigate the d8-ET molecular substitution for the h8-ET molecule: $-(\text{h8-ET})_{1-x}(\text{d8-ET})_x)_2\text{CuN}(\text{CN})_2\text{Br}$. This simplified method is capable of giving systematic and wide range ($x = 0 \{ 1$) substitution and controlling chemical pressure nearly near the Mott boundary. After cooling slowly, the increase of T_c by about 0.1 K is observed up to $x = 0.1$, which is evidently caused by the chemical pressure effect. Neither reduction of T_c nor suppression of the SC volume fraction is found below $x = 0.5$. This indicates that the effect of disorder by substitution is negligible in the present system.

The single crystals of $-(\text{h8-ET})_{1-x}(\text{d8-ET})_x)_2\text{CuN}(\text{CN})_2\text{Br}$ were grown by a standard electrocrystallization method. The crystals with nominal concentrations of $x = 0, 0.01, 0.05, 0.1, 0.2, 0.25, 0.3, 0.4, 0.5, 0.6, 0.7, 0.75, 0.8, 0.9$, and 1 were prepared. In this paper the concentration x is used as the nominal

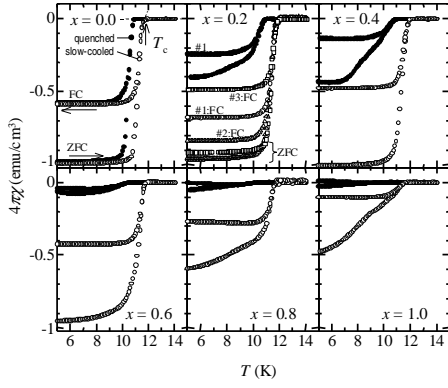


Fig. 1. Temperature dependence of the magnetic susceptibility in $-(\text{h8-ET})_{1-x}(\text{d8-ET})_x\text{Cu}[\text{N}(\text{CN})_2]\text{Br}$, where $x = 0, 0.2, 0.4, 0.6, 0.8$, and 1 . Open and filled circles are the slow-cooled and quenched data, respectively. In the panel of $x = 0.2$, the slow-cooled data in three samples are displayed (#1, 2, and #3).

value, because the actual value x of each crystal has not been investigated experimentally. Typical dimensions of the samples obtained were $1 \times 1 \times 0.2 \text{ mm}^3$ (0.4 mg). For each single crystal, static magnetization measurements were performed with a SQUID magnetometer (Quantum Design, MPMS-5). The magnetic field of 3.0 Oe was applied perpendicular to the conduction plane. The data were taken with warming up after zero-field-cooling from above T_c (ZFC: shielding curve) and then with cooling under the magnetic field (FC: Meissner curve). The samples were cooled with a rate of 100 K/m in from room temperature to 15 K , giving "quenched" state. After a series of the measurements, the systems were warmed up to 100 K , and the other cooling of 0.2 K/m in (slow-cooled) was then carried out.

Figure 1 shows the temperature dependence of the static susceptibility (4χ) for selected several concentrations. The demagnetization factor was corrected using an ellipsoidal approximation. The SC transition temperatures were defined as the intercept of the extrapolated lines of the normal and SC states. The results for $x = 0$ and 1 , corresponding to the pure h8- and d8-ET salts, respectively, are consistent with the literatures.^{14,18,21)} In $x = 0$, T_c is $11.83 \pm 0.03 \text{ K}$ (slow-cooled) and $10.93 \pm 0.05 \text{ K}$ (quenched) with a sharp transition width. The shielding curves indicate almost the full-volume fraction of superconductivity for both cooling-rates. On the other hand, the broad SC transition emerges in $x = 1$ with $T_c = 11.61 \pm 0.06 \text{ K}$ (slow-cooled) and $9.94 \pm 0.15 \text{ K}$ (quenched). The incomplete shielding volume even in the slow-cooled state reflects the coexistence with a non-SC phase (AFI state^{7,8)}). The SC state is further suppressed by quenching. In the panel of $x = 0.2$, the slow-cooled data in three samples are displayed (#1, 2, and #3; taken from the same batch). The ZFC curve and T_c are well reproduced, while the FC curves show the sample-dependent behavior. The similar variation appears even in the pure h8-ET salt (not shown in Figure). Thus it is not the problem on the substitution, but may reflect the inevitable sample-dependence of the vortex-pinning force²¹⁾ in the low magnetic-field region, such as surface

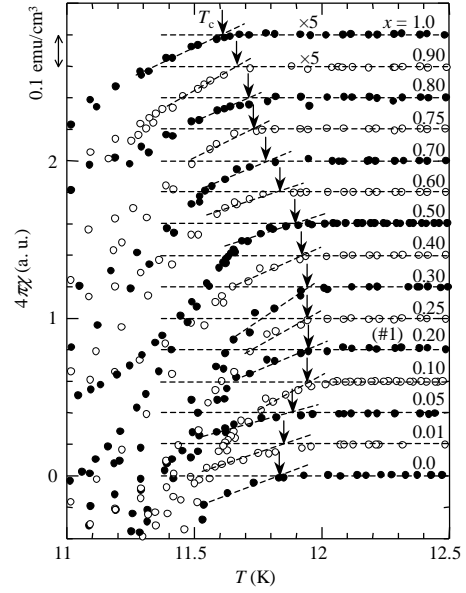


Fig. 2. Temperature dependence of the magnetic susceptibility in $-(\text{h8-ET})_{1-x}(\text{d8-ET})_x\text{Cu}[\text{N}(\text{CN})_2]\text{Br}$ around T_c in the slow-cooled state. Arrows indicate T_c , defined as the intercept of the extrapolated broken lines of the normal and SC states.

pinning. In the following, we focus on the ZFC data of the slow-cooled state in $x = 0.4 \text{--} 0.8$. The ZFC curve in $x = 0.4$ shows the full-volume fraction within the accuracy of the measurements. Almost the same sharpness of the transition width with $x = 0$ can provide evidence of the complete SC state without any non-SC phase. In contrast to the data in $x = 0.4$, the transition width becomes slightly broad in $x = 0.6$ and meanwhile the temperature dependent behavior of the ZFC curve remains even at 5.0 K . In $x = 0.8$ the SC volume fraction is rather suppressed and T_c decreases as well as the case in $x = 1$.

Figure 2 shows the slow-cooled data of $4\chi(T)$ around T_c . As indicated by arrows, T_c obviously increases from $x = 0$ to 0.1 . Between $x = 0.2$ and 0.4 , T_c reaches a maximum value, and then gradually starts to decrease above $x = 0.5$ toward the value of the pure d8-ET salt. To exhibit the convex curvature of T_c as a function of x , the x -dependence of T_c in the slow-cooled state is shown in Fig. 3(a). In addition, the values of 4χ at 5.0 K as the SC volume fraction is displayed in Fig. 3(b). One can see the bulk SC state in $x = 0.5$. Above $x = 0.5$, both T_c and volume fraction seem to decrease, reflecting the existence of non-SC phases, although the large ambiguity in the demagnetization factor to estimate the SC volume fraction obscures the maximum x of the bulk SC state. On the other hand, in the quenched state, both T_c and SC volume fraction, shown in Figs. 4(a) and (b), monotonically decrease with x , in which the SC volume fraction is steeply suppressed in the small x region.

In the present deuterium substitution, the characteristic increase of T_c observed up to $x = 0.1$ in the slow-cooled state is evidently caused by the chemical pressure effect, as well as the case of the $-(\text{d8-ET})_2\text{Cu}[\text{NCS}]_2$. Note that the perfect SC volume fraction of the slow-cooled state appears in these concentrations [Fig. 3(a)].

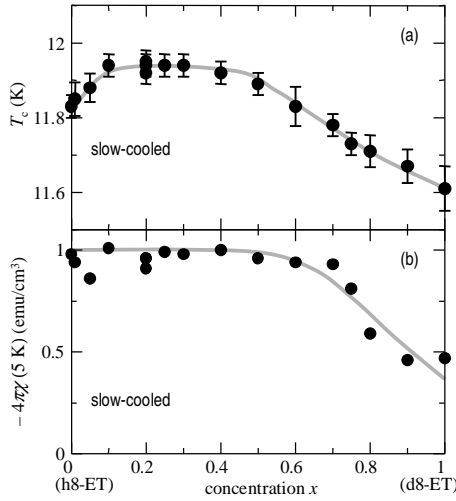


Fig. 3. (a) Superconducting transition temperature and (b) values of $-4\pi\chi$ at 5.0 K as a function of concentration x in the slow-cooled state of $-(\text{h8-ET})_{1-x}(\text{d8-ET})_x\text{Cu}[\text{N}(\text{CN})_2]\text{Br}$. The bold curves are guides to the eye.

Conversely, T_c can be reduced by the following mechanisms: (1) the normal (BCS) isotope effect, (2) a disorder effect introduced by molecular substitution, and (3) a magnetic impurity effect coming from the coexisting non-SC phase, which will be in the AFI state. We propose that the third one is attributed to the origin on the decrease of T_c with x in the present system. As shown in Figs. 3 and 4, the decrease of T_c is accompanied with the suppression of the SC volume fraction in both cooling conditions. This indicates that the non-SC phase develops with increasing x , leading to the reduction of T_c . An assumption that these non-SC phases are in the AFI states will be reasonable, as it is proved in the d8-ET salt ($x = 1$).^{7,8)} Since magnetic impurities reduce T_c in singlet-pairing superconductors,²²⁾ T_c therefore decreases with developing the non-SC phases. The former two mechanisms can be excluded because the first one has not been observed in deuterium substitution for the ET-based salts,⁹⁽¹¹⁾ and thus the present system will be also not the case. Although the second one is widely seen in anion substitution, such as $-(\text{h8-ET})_2(\text{I}_3)_{1-x}(\text{IBr}_2)_x$ ²³⁾ and $-(\text{h8-ET})_2\text{Cu}[\text{N}(\text{CN})_2]\text{Br}_{1-x}\text{I}_x$,²⁴⁾ this will be also ruled out because of the less difference between H and D atoms than that between the anions. This point is discussed in the following, taking account of the partially-deuterated system.

The effect on the superconductivity by disorder in the present substitution is negligible, whereas they may exist on a scale of the molecular size. In the partially-deuterated ET system,¹⁸⁾ after slow cooling, T_c starts to decrease between d-[2,2] and d-[3,3] salts with increasing degree of deuteration, which contain 50% and 75% deuterium atoms in a ET molecule, respectively. In both the d-[2,2] and d-[3,3] salts, almost the full-volume fraction after slow cooling is observed, while the bulk superconductivity is suppressed by fast cooling. These trends are very similar to the present substitution system. Thus

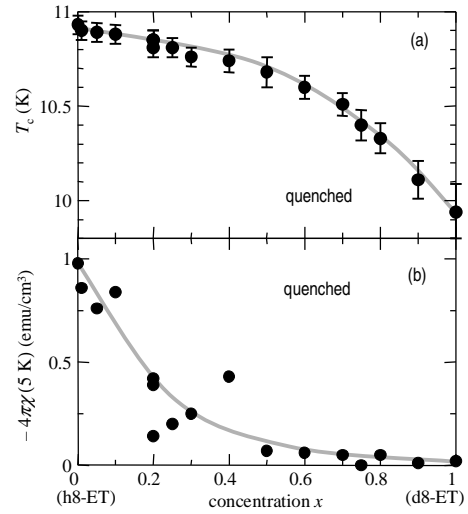


Fig. 4. (a) Superconducting transition temperature and (b) values of $-4\pi\chi$ at 5.0 K as a function of concentration x in the quenched state of $-(\text{h8-ET})_{1-x}(\text{d8-ET})_x\text{Cu}[\text{N}(\text{CN})_2]\text{Br}$. The bold curves are guides to the eye.

our experimental data guarantee the minimum effect by disorder, which is almost comparable to the partially-deuterated system.

A schematic phase diagram on the present deuterium substitution system is depicted in Fig. 5. The horizontal axis indicates the degree of chemical pressure. To compare with the present results, the data of the $\text{Cu}(\text{NCS})_2$ salt taken from ref. 10 are also plotted. The same scale unit is used in both $\text{Cu}[\text{N}(\text{CN})_2]\text{Br}$ and $\text{Cu}(\text{NCS})_2$ salts, in which the present data are plotted between the h8-ET ($x = 0$) and d8-ET salts ($x = 1$). The most feature in this phase diagram is the boundary between the bulk SC and non-bulk SC (with AFI) phases at around $x = 0.5$. This boundary is expected to be the Mott transition induced by chemical pressure, in which both T_c and SC volume fraction start to decrease. In the $\text{Cu}(\text{NCS})_2$ salt, T_c 's are 9.20 ± 0.05 K and 9.50 ± 0.05 K for the hydrogenated and deuterated salts, respectively.¹⁰⁾ Thus deuterium substitution in this salt increases T_c by 0.3

0.1 K. The degree of chemical pressure giving such an increase of T_c is estimated to be about 40 bar as uniaxial-pressure toward inter-plane direction.⁹⁾ We note that the variation of T_c in the $\text{Cu}[\text{N}(\text{CN})_2]\text{Br}$ salt is on the same order with the $\text{Cu}(\text{NCS})_2$ salt: the increase by about 0.1 K up to $x = 0.1$ and decrease by about 0.3 K from $x = 0.5$ to 1. This demonstrates that deuterium substitution in the -ET system gives the same degree of chemical pressure, as suggested by Schluter et al.¹⁰⁾ Moreover, further decrease of T_c is observed in the quenched state: about 1 K from $x = 0$ to 1 [see Fig. 4(a)]. This can be interpreted as the influence of the much more non-SC phase as shown in Fig. 4(b), giving rise to further magnetic-impurity scattering than that in the slow-cooled state.

In summary, we have investigated the superconductivity in the d8-ET molecular substitution system by means of the magnetic susceptibility measurements. The measurements were performed in the two cooling conditions of the slow-cooled (0.2 K/min) and quenched (>100 K)

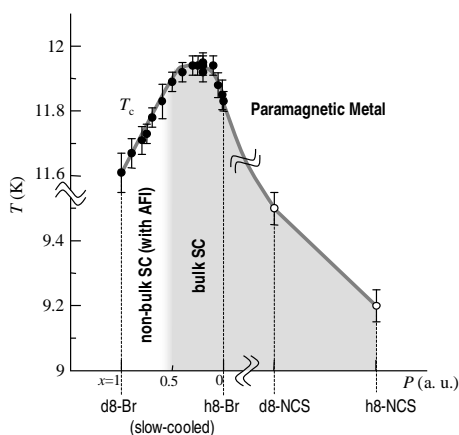


Fig. 5. Schematic phase diagram in $-(\text{h8-ET})_{1-x}(\text{d8-ET})_x\text{Cu}[\text{N}(\text{CN})_2]\text{Br}$. The horizontal axis indicates the degree of chemical pressure. The same scale unit is used in both the salts. The present results are plotted between the h8-ET ($x = 0$) and d8-ET salts ($x = 1$). The data of $-(\text{ET})_2\text{Cu}(\text{NCS})_2$ are taken from ref. 9. The bold line is a guide to the eye.

states. On the one hand, in the slow-cooled state, the chemical pressure effect leads to an increase of T_c by about 0.1 K. Neither reduction of T_c nor suppression of the SC volume fraction is observed below $x = 0.5$. This demonstrates that the effect of disorder by substitution is sufficiently negligible in the present system. With further increase of x , both T_c and SC volume fraction start to decrease toward the values in $x = 1$. On the other hand, the data of the quenched state between $x = 0$ and 1 qualitatively resemble the behavior of the slow-cooled state in $x = 0.5$; both T_c and SC volume fraction monotonically decrease, while the degrees of the T_c 's reduction or the SC volume suppression are much larger than that in the slow-cooled state. The reduction of T_c is interpreted as a magnetic impurity effect coming from the coexisting non-SC (AFI) phase. As a result, this simple substitution method makes it possible to control chemical pressure with minimal disorder. It is a useful technique to approach the Mott boundary at ambient pressure because the samples of any concentration x can be easily prepared.

Acknowledgment

This research was partly supported by the Ministry of Education, Science, Sports and Culture, Grant-in-Aid

for Encouragement of Young Scientists (NY, Grant No. 14740373), and for Scientific Research (C) (TS, Grant No. 15540329).

- 1) T. Ishiguro, K. Yamaji and G. Saito: Organic Superconductors, 2nd ed. (Springer, Berlin, 1998).
- 2) H. Ito, T. Ishiguro, M. Kubota and G. Saito: J. Phys. Soc. Jpn. 65 (1996) 2987.
- 3) S. Lefebvre, P. Wzietek, S. Brown, C. Bourbonnais, D. Jerome, C. Meziere, M. Fournier and P. Batail: Phys. Rev. Lett. 85 (2000) 5420.
- 4) D. Fournier, M. Poirier, M. Castonguay and K. D. Truong: Phys. Rev. Lett. 90 (2003) 127002.
- 5) P. Leliette, P. Wzietek, S. Florens, A. Georges, T. A. Costi, C. Pasquier, D. Jerome, C. Meziere and P. Batail: Phys. Rev. Lett. 91 (2003) 016401.
- 6) H. Kano and H. Fukuyama: J. Phys. Soc. Jpn. 65 (1996) 2158.
- 7) A. Kawamoto, K. Miyagawa and K. Kanoda: Phys. Rev. B 55 (1997) 14140.
- 8) K. Miyagawa, A. Kawamoto and K. Kanoda: Phys. Rev. Lett. 89 (2002) 017003.
- 9) A. M. Kini, K. D. Carlson, H. H. Wang, J. A. Schlueter, J. D. Dudek, S. A. Sirchio, U. Geiser, K. R. Lykke and J. M. Williams: Physica C 264 (1996) 81.
- 10) J. A. Schlueter, A. M. Kini, B. H. Ward, U. Geiser, H. H. Wang, J. M. Ohtsuka, R. W. Winter and G. L. Gard: Physica C 351 (2001) 261.
- 11) Other isotopic substitutions (^{13}C and ^{34}S) in $-(\text{BEDT-TTF})_2\text{Cu}(\text{NCS})_2$ has been investigated, resulting in the normal isotope effect on T_c .
- 12) K. Kanoda: Physica C 282-287 (1997) 299.
- 13) R. H. McKenzie: Science 278 (1997) 820.
- 14) T. Sasaki, N. Yoneyama, A. Matsuyama and N. Kobayashi: Phys. Rev. B 65 (2002) 060505.
- 15) M. Tokumoto, N. Kishimoto, Y. Tanaka and H. Anzai: J. Phys. Soc. Jpn. 60 (1991) 1426.
- 16) H. Ito, M. Watanabe, Y. Nogami, T. Ishiguro, T. Komatsu, G. Saito and N. Hosito: J. Phys. Soc. Jpn. 60 (1991) 3230.
- 17) A. Kawamoto, H. Taniguchi and K. Kanoda: J. Am. Chem. Soc. 120 (1998) 10984.
- 18) H. Taniguchi, A. Kawamoto and K. Kanoda: Phys. Rev. B 59 (1999) 8424.
- 19) Y. Nakazawa, H. Taniguchi, A. Kawamoto and K. Kanoda: Phys. Rev. B 61 (2000) R16295.
- 20) H. Taniguchi, K. Kanoda and A. Kawamoto: Phys. Rev. B 67 (2003) 014510.
- 21) N. Yoneyama, T. Sasaki, T. Nishizaki and N. Kobayashi: J. Phys. Soc. Jpn. 73 (2004) 184.
- 22) B. J. Powell and R. H. McKenzie: Phys. Rev. B 69 024519.
- 23) M. Tokumoto, H. Anzai, K. Murata, K. Kajimura and T. Ishiguro: J. Jpn. Appl. Phys. 26 (1987) 1977.
- 24) N. D. Kushch, L. I. Buravov, A. G. Khomenko, S. I. Pesotskii, V. N. Laukhin, E. B. Yagubskii, R. P. Shibaeva, V. E. Zavodnik and L. P. Rozenberg: Synth. Metals 72 (1995) 181.