

Excess current in point contacts on two-band superconductor MgB_2 in magnetic field

Yu. G. Naidyuk,* O. E. Kvitnitskaya, I. K. Yanson

*B. Verkin Institute for Low Temperature Physics and Engineering,
National Academy of Sciences of Ukraine, 47 Lenin Ave., 61103, Kharkiv, Ukraine*

S. Lee, and S. Tajima

Superconductivity Research Laboratory, ISTEK, 1-10-13 Shinonome, Koto-ku, Tokyo 135-0062, Japan

(Dated: January 27, 2022)

A series of $I(V)$ characteristics and bias-dependent differential resistances $dV/dI(V)$ of the point contacts made of the single crystal of two-band superconductor MgB_2 were measured in magnetic fields up to 9 T. The magnetic field dependences of the excess current in the $I(V)$ curves were obtained and analyzed using Koshelev and Golubov's [Phys. Rev. Lett. **90**, 177002 (2003)] theoretical results for the mixed state of a dirty two-band superconductor. Introducing a simple model for the excess current in the point contact in the mixed state, our data can be qualitatively described using the theoretical magnetic field dependence of the superconducting order parameter of the σ and π -bands and the averaged electronic density of states in MgB_2 .

PACS numbers: 74.45.+c, 74.70.Ad, 73.40.Jn

I. INTRODUCTION

MgB_2 has attracted considerable attention due to its high T_c (≈ 40 K) which is due to specific multi-band electronic structure (see Ref.¹ and Refs. therein). Here superconductivity develops in two-dimensional cylindrical sheets of the Fermi surface constituted from the σ -band and three-dimensional tubular Fermi surface from the π -band. The commonly accepted explanation for high- T_c superconductivity in MgB_2 is connected with the strong interaction between the charge carriers and the E_{2g} phonon mode,² caused by the antiparallel vibrations of the atoms in the honeycomb-like boron planes. The superconducting order parameter is distributed over the Fermi surface of MgB_2 , being $\Delta_\sigma \approx 7$ meV for the σ -band and $\Delta_\pi \approx 2$ meV for the π -band.³ The different properties of the σ and π bands with different anisotropies result in very peculiar and interesting physical characteristics of MgB_2 both in the normal and especially in the superconducting state.^{1,3,4}

Point-contact (PC) spectroscopy is one of the straightforward methods which has proved the existence the double-gap superconductivity in MgB_2 (see, e.g., Refs.^{5,6,7,8}). Although much was done to understand the remarkable superconducting state in this diboride, some issues should be clarified, such as the behavior of the superconducting gaps in the magnetic field and the rapid depression of the superconducting features of the π -band in the PC conductivity by a moderate field of about 1 T. In this study we carried out PC measurements both of the order parameter and the excess current versus the magnetic field in MgB_2 and analyzed them using the theory⁹ for the mixed state of a dirty two-band superconductor.

II. SAMPLES AND MEASUREMENTS

Our experiments were carried out on the MgB_2 single-crystal samples investigated earlier in Ref.¹⁰. Their properties are described elsewhere.¹¹ The crystals were small thin plates (flakes) of a sub-millimeter size. They were glued with silver epoxy to the sample holder at one of their side faces. The noble metal counter electrode was brought into a gentle touch with the opposite side face of the crystal in liquid helium. Thus we tried to make a contact mainly along the ab plane, for which both the σ and π -band superconducting features should be present in the PC characteristics. The magnetic field was applied along the c -axis.

The $I(V)$ characteristic and the differential resistance $dV/dI(V)$ were recorded through sweeping DC current I on which small AC current i was superimposed and through measuring the alternating voltage $V_1 \propto dV/dI(V)$ using the standard lock-in technique.

III. EXPERIMENTAL RESULTS

First we evaluated the characteristic length scales important for this study. The contact size for the typical resistance of $10\ \Omega$ is estimated by the Sharvin formula $d \simeq \sqrt{\rho l/R}$ ($d \simeq 7$ nm in Ref.¹²) irrespectively of the crystallographic directions. For a dirty constriction (with a very short mean free path) the use of the Maxwell formula $d \sim \rho/R$ results in d about 0.7 nm and 2.6 nm (see Ref.¹²) for the ab plane and c direction, respectively. Thus, the contact size can be of the order of magnitude or smaller than the elastic electron mean free path ($l_{ab} = 24$ nm, $l_c = 6$ nm, according to Ref.¹³), which means that theoretically we can approach the ballistic (spectroscopic) regime. In practice the spectroscopic regime is confirmed by observation of the characteristic Andreev-reflection features in dV/dI in the su-

*e-mail: naidyuk@ilt.kharkov.ua

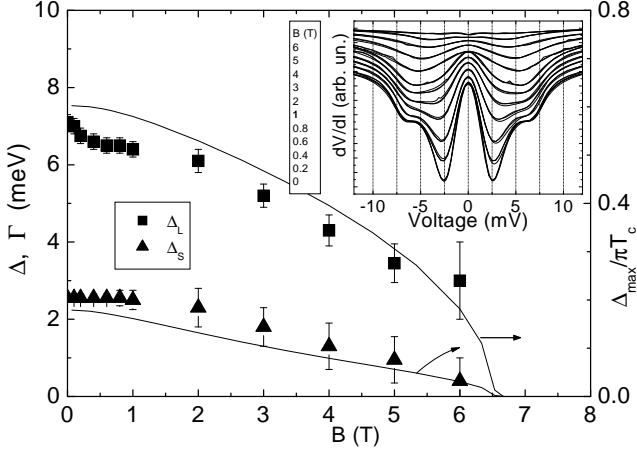


FIG. 1: Magnetic field dependence of large and small superconducting energy gaps at 4.2 K (solid squares and triangles, left y-axis) obtained by a BTK fitting of the curves shown in the inset. Solid curves show magnetic field dependence of the maximal pair potential (right y-axis) for MgB_2 for $D_1 = D_2$ (see Fig. 2). Inset: symmetrized experimental dV/dI curves in magnetic field (solid lines) for the single crystal $\text{MgB}_2\text{-Cu}$ 2.2 Ω junction along the ab plane with BTK fit (thin lines) from Ref. ¹². Two separate sets of the gap minima around ± 2.5 and ± 7 mV are clearly seen in the low fields.

perconducting state.

The measurements of the superconducting energy gap in MgB_2 by means of the Andreev reflection demonstrate two sets of the energy-gap minima in the differential resistance dV/dI at $\pm 2.4 \pm 0.1$ and $\pm 7.1 \pm 0.4$ meV, respectively; their distribution⁸ corresponds to the theoretical prediction.³ The dV/dI curves can be well fitted by the known BTK¹⁴ equations (with the suitable Γ parameter) for two conducting channels with the appropriate weight factors w .^{5,6,7,8} The contribution of the large gap to the double-gap spectra w_L is the largest along the ab plane and amounts theoretically to 0.34, while it is negligible in the perpendicular direction (along the c axis).¹⁵

A series of dV/dI measured in magnetic field is shown in Fig. 1 (inset) with clearly seen two sets of the gap minima (double-gap features). The main panel in Fig. 1 displays the magnetic field dependence of the large and small gaps obtained by the routine BTK fitting of the curves from the inset. In spite of the rapid decrease in the intensity of the small gap minima with the field (a factor of two at 1 T, see the inset in Fig. 1), the small gap is not suppressed by low fields ($\lesssim 1$ T), and the estimated critical field 6-7 T (see Fig. 1) is much higher than that stated²⁰ in Refs. ^{6,16}. Moreover this field corresponds to B_{c2} determined from the onset temperature in the broadened resistive transition in single crystals.¹⁷ Similar behavior of the small gap persisting up to 5 T was found in Ref. ¹⁸, where visual disappearance of the π -gap features in the PC characteristics was attributed to broadening of the spectra in the magnetic field.

Experimental data for Δ in Fig. 1 are in good agree-

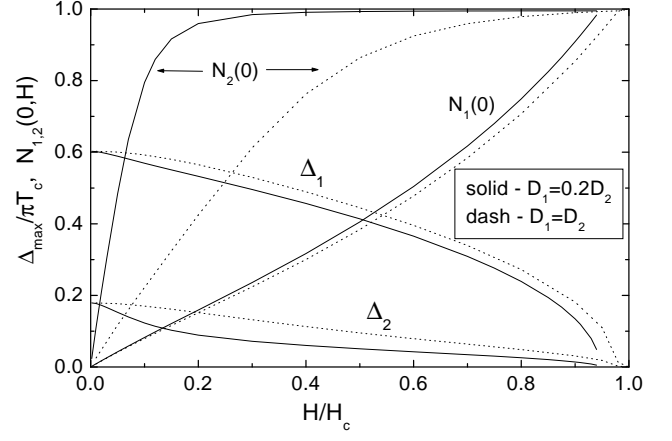


FIG. 2: Magnetic field dependences of the maximal pair potential Δ and averaged electron DOS $N(0, H)$ at zero energy for two ratios of the diffusion constants $D_i = 2\pi T_c \xi_i^2$ for the σ (1) and π (2) bands. By courtesy of Koshelev and Golubov.⁹

ment with the magnetic field dependence of the maximal pair potential Δ for MgB_2 according to Ref. ⁹ with $D_1 = D_2$ relation. Under this condition, the smaller Δ_2 (see Fig. 2, dashed curve) has a negative curvature in low and near to the critical fields, which is similar to the experimental Δ_S (see Fig. 1).

The Andreev reflection of electrons from the $N - S$ boundary in a $N - c - S$ point contact (N stands for the normal metal, c is the constriction, and S is the superconductor) produces an excess current I_{exc} in the superconducting state. As a result, $I(V)$ can be written¹⁴ at $eV \gg \Delta$ as $I(V) = V/R_N + I_{exc}$, where

$$I_{exc} \approx \Delta/eR_N \quad (1)$$

with Δ being the superconducting energy gap and R_N being the PC resistance in the normal state.

We determined the reduced $I_{exc}(B)/I_{exc}(B=0)$ either from the raw $I(V)$ or mostly by integrating the reduced $R^{-1}dV/dI(V)$ or $RdI/dV(V)$ after subtracting the normal state background. The use of the $I(V)$ curves provides less accurate results because of the resistance instability for some contacts during the field sweep.

For all investigated contacts the excess current depends on the magnetic field with the overall positive curvature (Fig. 3). At first, $I_{exc}(B)$ decreases abruptly and then more slowly above 1 T. This corresponds to the aforementioned drastic suppression of the $dV/dI(V)$ small-gap minima intensity by a magnetic field about 1 T and to the persistence of the residual superconducting minima on a further increase in the magnetic field. This is quite different from what is expected for I_{exc} according to (1), taking into account that $\Delta(B)$ has, as a rule, a negative curvature (see Fig. 2).

Generally, the excess current, just like the net current through the contact, is proportional to the contact area A (see, e. g., Eqs. (18), (19) in Ref. ¹⁴), i. e. $I_{exc} \sim A \times \Delta$.

Assuming that I_{exc} is caused by the superconducting component of the current, which in the mixed state is determined by the superconducting volume (part) in the PC area, the coefficient A in the above-mentioned formula should be effectively reduced by the contribution of the nonsuperconducting volume. Koshelev and Golubov⁹ calculated the magnetic field dependence of the electron density of states (DOS) $N(E)$ at $E=0$ averaged over the vortex unit cell. We assume that in the first approximation the *averaged* $N(0, B)$ can be regarded as a measure of the nonsuperconducting region in the mixed state, and, vice versa, $(1 - N(0, B))$ characterizes the superconducting phase portion. Thus, according to above reasoning, we suppose that

$$I_{exc} \propto w_L(1 - N_L(0, B))\Delta_L + w_S(1 - N_S(0, B))\Delta_S \quad (2)$$

with the weight factors w_L and w_S for large and small gaps, respectively ($w_L + w_S = 1$), $N_{L,S}(0, B)$ and $\Delta_{L,S}$ are taken from Fig. 2, where $L \equiv 1$, $S \equiv 2$. Here, I_{exc} is presented²¹ by (2) as a sum of two contribution from the σ and π bands weighted by $w_{L,S}$ factors, which along with Δ were derived from the fitting of the Andreev-reflection features in dV/dI at zero field.

Figure 3 shows the magnetic field dependence of I_{exc} for three different types of dV/dI with visually distinct small, large and double gap structures. Here, we also plotted I_{exc} calculated by (2). The most unexpected result is the observation of dV/dI (see Fig. 3(b)) with large-gap minima only, which is discussed in Ref. ¹⁰. The large-gap minima are only slightly affected by magnetic fields of a few tesla. This is in contrast to the small-gap minima, which according to Refs. ^{5,6} should vanish above 1 T. The curve in the bottom panel was calculated taking w_L from the fitting of the double-gap structure (see Fig. 1), while in panel (a) and (b), where only the small- or large-gap structures are seen, w_L can vary from zero to its highest value 0.34.¹⁵ The latter w_L value was used for the spectra in the middle panel in which only large-gap minima are seen. Evaluation of w_L for the spectrum in panel (a) inset is not straightforward because the spikes present at higher energies mask the large gap features. However, selected $w_L = 0.15$ and $w_L = 0.34$ fit reasonably both zero-field dV/dI and $I_{exc}(B)$ curves in panels (a) and (b), respectively.

In general, the experimental and calculated curves agree well in spite of the simple empiric model adopted for I_{exc} . The calculated curves describe qualitatively the experimental data, especially the abrupt initial decrease in I_{exc} , pronounced in the curves with the dominant small-gap features (Fig. 3(a)). In Fig. 3(c), showing two curves with different D_1/D_2 ratios, it is seen that better correspondence can be reached with an intermediate ratio between D_i values. The same occurs for the data in Fig. 3(b) for the large-gap spectrum, though the experimental data for large-gap and small-gap spectra are closer to the cases with $D_1 = D_2$. This fact testifies that in this case the σ band is closer to the clean limit, also mentioned in Ref. ¹⁸.

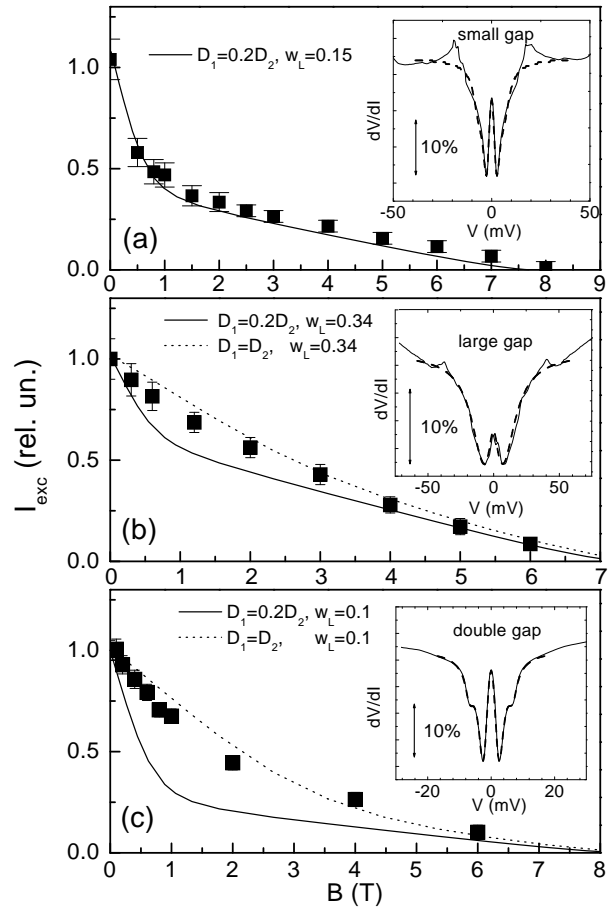


FIG. 3: I_{exc} vs magnetic field behavior for 3 PCs between the MgB₂ single crystal and Cu at 4.2 K: (a) junction with small-gap minima and normal state resistance $R=1.5 \Omega$, (b) junction with large-gap minima from Ref. ¹⁰, $R=6.7 \Omega$, (c) junction with double-gap structure from Fig. 1, $R=2.2 \Omega$. The lines present calculated $I_{exc}(B)$ according to (2) with w_L , D_1 and D_2 shown in each panel. The error bars show difference between $I_{exc}(B)$ calculated from the experimental (insets, solid curves) and BTK (insets, dashed curves) dV/dI . Insets: zero-field experimental (solid curves) and BTK (dashed) dV/dI curves for each contact with $\Delta_S=2.55$ meV and $\Delta_L=7.8$ meV (a), $\Delta_S=2$ meV and $\Delta_L=7.5$ meV (b), and $\Delta_S=2.55$ meV and $\Delta_L=7.1$ meV (c). Vertical bars are drawn to show relative dV/dI value with respect to the contact resistance R .

IV. CONCLUSIONS

We have investigated the excess current in PCs based on single crystals of MgB₂ in the magnetic field and proposed an empiric model for the excess current behavior in the mixed state. Using this model, a magnetic field dependence of the excess current was obtained, which is in qualitative agreement with experimental data. The anomalous magnetic field dependence of the excess current in PCs reflects the specific two-band structure of the superconducting order parameter and the spatial DOS

behavior in MgB_2 . Thus, $I_{exc}(B)$ can be used for evaluation of the diffusivity in both bands on the base of Koshelev and Golubov's theory.⁹

Acknowledgements

We are indebted to A. E. Koshelev for providing theoretical data and L. V. Tyutrina for the help in the $dV/dI(V)$ fitting. The fruitful discussion with S. I. Be-

loborod'ko, S.-L. Drechsler and A. N. Omelyanchouk and their comments are highly acknowledged. The work was partially supported by the National Academy of Sciences of Ukraine under Project Φ 1-19, by the State Foundation of Fundamental Research of Ukraine under Grant Φ 7/528 - 2001 and by the New Energy and Industrial Technology Development Organization (NEDO) in Japan. The investigations were carried out in part using the equipment donated by the Alexander von Humboldt Foundation (Germany).

-
- ¹ I. I. Mazin, V. P. Antropov, *Physica C* **385**, 49 (2003).
 - ² J. M. Ann, W. E. Pickett, *Phys. Rev. Lett.* **86**, 4366 (2001).
 - ³ Hyoung Joon Choi, David Roundy, Hong Sun, Marvin L. Cohen, Steven G. Louie, *Nature* **418**, 758 (2002).
 - ⁴ C. Buzea and T. Yamashita, *Supercond. Sci. Technol.* **14**, R115 (2001).
 - ⁵ P. Szabó, P. Samuely, J. Kačmarčík, T. Klein, J. Marcus, D. Fruchart, S. Miraglia, C. Marcenat, A. G. M. Jansen, *Phys. Rev. Lett.* **87** 137005 (2001).
 - ⁶ R. S. Gonnelli, D. Daghero, A. Calzolari, G. A. Ummarino, V. A. Stepanov, J. Jun, S. M. Kazakov and J. Karpinski, *Phys. Rev. Lett.* **89** 247004 (2002).
 - ⁷ N. L. Bobrov, P. N. Chubov, Yu. G. Naidyuk, L. V. Tyutrina, I. K. Yanson, W. N. Kang, Hyeong-Jin Kim, Eun-Mi Choi, C. U. Jung, and Sung-Ik Lee, in book *New Trends in Superconductivity*, Vol.67 of NATO Science Series II: Math. Phys. and Chem., ed. by J. F. Annett and S. Kruchinin, (Kluwer Acad. Publ., 2002), p.225.
 - ⁸ Yu. G. Naidyuk, I. K. Yanson, L. V. Tyutrina, N. L. Bobrov, P. N. Chubov, W. N. Kang, Hyeong-Jin Kim, Eun-Mi Choi, and Sung-Ik Lee, *JETP Lett.* **75**, 283 (2002).
 - ⁹ A. E. Koshelev, A. A. Golubov, *Phys. Rev. Lett.* **90**, 177002 (2003).
 - ¹⁰ Yu. G. Naidyuk, I. K. Yanson, O. E. Kvitnitskaya, S. Lee, and S. Tajima, *Phys. Rev. Lett.*, **90**, 197001 (2003).
 - ¹¹ Sergey Lee, *Physica C* **385**, 31 41 (2003); S. Lee, H. Mori, T. Masui, Yu. Eltsev, A. Yamamoto and S. Tajima, *J. Phys. Soc. of Japan*, **70**, 2255 (2001).
 - ¹² I. K. Yanson, Yu. G. Naidyuk, *Fiz. Nizk. Temp.* **30**, 355 (2004) [*Low Temp. Phys.* **30**, 261 (2004)](see also: cond-mat/0309693).
 - ¹³ Yu. Eltsev, S. Lee, K. Nakao, N. Chikumoto, S. Tajima, N. Koshizuka, and M. Murakami, *Phys. Rev. B*, **65**, 140501(R) (2002).
 - ¹⁴ G. E. Blonder, M. Tinkham and T. M. Klapwijk, *Phys. Rev. B* **25**, 4515 (1982).
 - ¹⁵ A. Brinkman, A. A. Golubov, H. Rogalla, O. V. Dolgov, J. Kortus, Y. Kong, O. Jepsen, and O. K. Andersen, *Phys. Rev. B* **65**, 180517 (2002).
 - ¹⁶ P. Samuely, P. Szabo, J. Kacmarcik, T. Klein, A. G. M. Jansen, *Physica C* **385** 244 (2003).
 - ¹⁷ Yu. Eltsev, *Physica C* **385**, 162 (2003); T. Masui, S. Lee and S. Tajima, *Physica C* **383**, 299 (2003).
 - ¹⁸ Y. Bugoslavsky, Y. Miyoshi, G. K. Perkins, A. D. Caplin, L. F. Cohen, A. V. Pogrebnayakov, X. X. Xi, *Phys. Rev. B* **69**, 132508 (2004).
 - ¹⁹ R. S. Gonnelli, D. Daghero, G. A. Ummarino, V. Delarocca, V. A. Stepanov, J. Jun, S. M. Kazakov and J. Karpinski, *Phys. Rev. B* **69**, 100504(R) (2004).
 - ²⁰ In Ref.¹⁹, Gonnelli *et al.* have corrected their previous claims and they mentioned that identification of the magnetic field (at which the π -band features in dV/dI disappear visually) with the critical field for the π band might not be correct.
 - ²¹ According to S. I. Beloborod'ko's private communication, I_{exc} is proportional to $(1 - N(0))^{1/2}\Delta$ in the gapless state for a S-c-N junction with magnetic impurities (see, e.g., S. I. Beloborod'ko, *Low Temp. Phys.*, **29**, 650 (2003) and corresponding Refs. therein). Therefore, our assumption about the I_{exc} dependence on the averaged zero-energy density of states has some physical grounds.