## Ab initio results for the electronic structure of $C_{50}Cl_{10}$ .

Steven W.D. Bailey<sup>1</sup> and Colin J. Lambert<sup>1</sup>

<sup>1</sup> Department of Physics, Lancaster University, Lancaster, LA1 4YB, UK

In this paper we use ab initio density functional theory (DFT) to calculate the electronic properties of  $C_{50}Cl_{10}$ . In comparison with the unstable  $C_{50}$  which has a small  $t_{lu}(LUMO) - h_u(HOMO)$ energy gap and a high total free energy compared with  $C_{60}$ , the belt of chlorines atoms stabilize the  $C_{50}Cl_{10}$  fullerene by increasing the energy gap to approximately that of  $C_{60}$  and lowering the total free energy. We also examine the effects of inter-cage separation on the band structure for infinite periodic  $C_{50}Cl_{10}$  chains where a high degree of dispersion is found to persist for separations beyond the predicted  $C_{60} - C_{60}$  distance of closest approach.

A new example of the fullerene family,  $C_{50}Cl_{10}$  has recently been produced as a stable solid [1]. The fullerenes smaller than the  $C_{60}$  buckyball are very difficult to produce in a stable form as the structure breaks the isolated pentagon rule (IPR) [2]. In  $C_{50}$  there are five sets of adjacent pentagons and this together with the high curvature of the molecular surface means it is highly unstable [3–5]. Xie et al have overcome this instability by attaching chlorine atoms around the  $C_{50}$  equator as seen in Fig. 1(a). In what follows, we examine the electronic properties and stability of  $C_{50}Cl_{10}$ , along with the electronic properties of chains of  $C_{50}Cl_{10}$  molecules. To model  $C_{50}Cl_{10}$  we use a double zeta basis set with a cutoff radius of 150 Ry to describe the carbon and Chlorine atoms within the SIESTA [6] implementation of DFT, where nonlocal norm-conserving pseudopotentials describe the core electrons and a linear combination of atomic orbitals the valence electrons. The relaxed, isolated molecule is shown in Fig. 1(a). In the case of a chain we concider molecules aligned along the z axis as shown in Fig. 1(b).

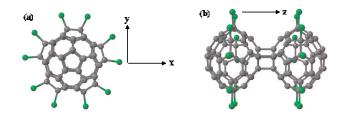


FIG. 1. Relaxed atomic coordinates of  $C_{50}Cl_{10}$ . The chlorine atoms form a fan around the equator of the  $C_{50}$  molecule (**a**). The proposed chain of  $C_{50}Cl_{10}$  in the z direction (**b**)

**TABLE 1.** compares the Fermi energy  $E_F(eV)$ , the total free energy  $E_{tot}(eV)$  and the  $t_{lu}(LUMO)$  -  $h_u(HOMO)$  energy gap  $E_{\Delta}(eV)$  between the  $C_{60}$ ,  $C_{50}$  molecules and  $C_{50}Cl_{10}$  as a linear chain with varying inter-cage separations in  $(\dot{A})$ , up to the isolated molecule. **TABLE 1** 

| IADLE I.                  |              |              |                           |                           |                           |                     |  |
|---------------------------|--------------|--------------|---------------------------|---------------------------|---------------------------|---------------------|--|
| Case                      | a            | b            | с                         | d                         | е                         | f                   |  |
|                           | $C_{60}$ mol | $C_{50}$ mol | $C_{50}Cl_{10}2.5\dot{A}$ | $C_{50}Cl_{10}2.9\dot{A}$ | $C_{50}Cl_{10}3.4\dot{A}$ | $C_{50}Cl_{10}$ mol |  |
| $E_F(eV)$                 | -4.61        | -7.04        | -5.41                     | -5.41                     | -5.47                     | -5.67               |  |
| $E_{tot}(eV)$             | -9201        | -7670        | -11751                    | -11751                    | -11751                    | -11750              |  |
| $E_{\Delta}(\mathrm{eV})$ | 1.80         | 0.16         |                           |                           |                           | 1.80                |  |

The table shows that the unstable  $C_{50}$  has a high  $E_{tot}$  of -7670eV in comparison to that of -9201eV for the  $C_{60}$  molecule but that the belt of ten Cl atoms stabilizes the  $C_{50}Cl_{10}$  to produce a lower  $E_{tot}$  of -11751eV. This is reflected in the result for the  $t_{lu}(LUMO)$  -  $h_u(HOMO)$  energy gap,  $(E_{\Delta})$ , where the energy gap of 0.16eV for  $C_{50}$  opens to 1.80eV, matching that of  $C_{60}$ , for the  $C_{50}Cl_{10}$  molecule. It is noted that the value of  $E_{\Delta} = 1.80$ eV for  $C_{60}$  is in very good agreement with the experimental values of  $E_{\Delta}$  between (1.6 - 1.8)eV [7]

Fig. 2 shows the energy levels of the isolated molecules in cases (a,b and f) and the electronic band structures of  $C_{50}Cl_{10}$  chains with the different inter-molecule separations in cases (c - e), of Table 1. In each case the energy is measured from the  $E_F$  for each relaxed structure studied. In cases(c - e) the band structure is shown for a wavevector kz in the z direction as defined in Fig. 1. The  $C_{60} - C_{60}$  distance of closest approach is predicted to be approximately

 $3.0\dot{A}$  [8] therefore the range of cage separations for cases (c - e) were selected to cover this interval and beyond. The band structures for the infinite periodic chains of  $C_{50}Cl_{10}$  for cases (c - e) show the dispersion of the  $t_{lu}(LUMO)$  and  $h_u(HOMO)$  bands persists up to and beyond a  $3.4\dot{A}$  separation and that the  $C_{50}Cl_{10}$  chain is an insulator.

In conclusion we have used DFT calculations to investigate the electronic properties of the newly produced, solid  $C_{50}Cl_{10}$  fullerene. We find that the belt of chlorine atoms around the equator of the  $C_{50}$  stabilize the structure by dramatically lowering the total free energy of  $C_{50}Cl_{10}$  and increasing the  $h_u(HOMO) - t_{lu}(LUMO)$  gap to match that of  $C_{60}$ . The  $t_{lu}(LUMO)$  and  $h_u(HOMO)$  bands show a marked dispersion even for separations of the  $C_{50}Cl_{10}$  cages in excess of the predicted closest  $C_{60} - C_{60}$  approach of 3.0Å. This points to some interesting properties arising from carbon nanotube peapods such as  $(12, 12)@C_{50}Cl_{10}$ .

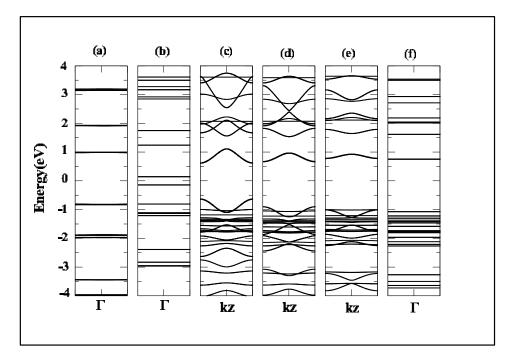


FIG. 2. For the structures (a - f) defined in Table 1, the energy levels of the isolated molecules are seen in cases (a,b and f) and the electronic band structures for wavevectors kz in the z direction as defined in Fig. 1, in cases (c - e).

- [1] Su Yuan Xie et al, Science. **304**, 5671 (2004).
- [2] K. M. Kadish and R. S. Ruoff, Fullerene: Chemistry, Physics and Technology (Wiley, new York, 2002).
- [3] T. Guo et al., Science **257**, 1661 (1992).
- [4] H. W. Kroto, Nature **329**, 529 (1987).
- [5] J. R. Heath, Nature **393**, 730 (1998).
- [6] S. D. S-Portal, P. Ordejon, E. Artacho, J. Soler Int. J. Quantum Chem. 65, 453 (1997).
- [7] M.S. Dresselhaus, G. Dresselhaus and P. C. Eklund, Science of Fullerenes and Carbon Nanotubes (Academic, San Diego, 1996).
- [8] A. Rochefort, Phys. rev. B, 67, 115401, (2003).