A novel route to phase formation of cobalt oxyhydrates using KMnO₄ as an oxidizing agent

C.-J. Liu, a,* C.-Y. Liao, L.-C. Huang, C.-H. Su, S. Neeleshwar, and Y.-Y. Chen

^aDepartment of Physics, National Changhua University of Education, Changhua, 500 Taiwan, R. O. C.

^bInstitute of Physics, Academia Sinica, Taipei, Taiwan, R. O.C.

*To whom correspondence should be addressed. Phone: +886-4-723-2105 ext-3337. E-mail: liucj@cc.ncue.edu.tw.

ABSTRACT

We have first successfully synthesized the sodium cobalt oxyhydrate superconductors using KMnO₄ as a de-intercalating and oxidizing agent. It is a novel route to form the superconductive phase of $Na_xCoO_2\cdot yH_2O$ without resort to the commonly used Br_2/CH_3CN solution. The role of KMnO₄ is to de-intercalate the Na^+ from the parent compound $Na_{0.7}CoO_2$ and oxidize the Co ion as a result. The higher molar ratio of KMnO₄ relative to the sodium content tends to remove more Na^+ from the parent compound and results in a slight expansion of the c-axis in the unit cell. The superconducting transition temperature is 4.6 - 3.8 K for samples treated by aqueous KMnO₄ solution with the molar ratio of KMnO₄ relative to the sodium content in the range of 0.03 and 2.29.

1. Introduction

The recent discovery of superconductivity [1] in hexagonal cobalt oxyhydrates $Na_xCoO_2 \cdot yH_2O$ with $T_c = 4-5$ K has attracted great attention [2-7] because it is unique to have the water molecule intercalated into the parent structure of $Na_{0.7}CoO_2$ which is crucial for the occurrence of superconductivity. It is also a particularly interesting system for comparison with the high- T_c cuprates in terms of the structure-electronic state correlations in view of the fact that both have 2D layers (triangular CoO_2 layers and square CuO_2 layers) in structure and have spin 1/2 ions $(t_{2g}^{-5}$ for Co^{4+} in low spin state and $t_{2g}^{-6}e_g^{-3}$ for Cu^{2+}) in electron configuration. Besides, this family of materials is of particular interest because of their magnetic and thermoelectric properties. The parent compound Na_xCoO_2 is a potential candidate for thermoelectric applications due to its high electrical conductivity, large thermopower and low thermal conductivity [8]. There exists four phases [9.10] in the related cobalt oxides: (1) α - Na_xCoO_2 (0.9 \leq x \leq 1, O3 phase); (2) α '- $Na_{0.75}CoO_2$ (O'3 phase); (3) β - Na_xCoO_2 (0.55 \leq x \leq 0.6, P3 phase); and (4) γ - $Na_xCo_yO_2$ (0.55 \leq x/y \leq 0.74, P2 phase). The O3 phase represents 3 CoO_2 layers in the unit cell with the Na^+ in the octahedral surroundings, while P2 phase represents 2 CoO_2 layers in the unit cell with the Na^+ in the trigonal prismatic surroundings. The O'3 phase is the monoclinic distortion of O3 phase.

Takada et al. obtained the superconducting phase of $Na_xCoO_2\cdot yH_2O$ by immersing $Na_{0.7}CoO_2$ powders in Br_2/CH_3CN solution followed by filtering and rinsing [1]. Park et al. [11] reported the alternative route to make the superconductive $Na_xCoO_2\cdot yH_2O$. This process is generally considered as a chemical oxidation by removing Na partially before the H_2O is intercalated between the CoO_2 layers and Na layers. The purpose of this paper is to report a novel route of preparing the superconducting $Na_xCoO_2\cdot yH_2O$ phase using aqueous $KMnO_4$ solution as a de-intercalating and oxidizing agent. It is an alternative route to use oxidant rather than Br_2/CH_3CN solution to form the superconducting phase of $Na_xCoO_2\cdot yH_2O$.

2. Experimental

The superconducting cobalt oxyhydrates Na_xCoO₂·yH₂O were prepared following the procedures below: (1) Preparation of parent material Na_{0.7}CoO₂. Polycrystalline powders of Na_{0.7}CoO₂ were synthesized by quantitatively mixing high-purity powders of Na₂CO₃ and CoO. The mixed powders were ground thoroughly using a Retch MM2000 laboratory mixer mill, followed by a rapid heat-up procedure [12] at 700°C in order to avoid the loss of Na in the heating process. (2) De-intercalation of Na and Oxidation. The resulting powders (0.5 -1 g) were immersed and stirred in 50 ml of water solution with different molar ratios of $KMnO_4/Na$ labeled as 0.05X-2.29X at room temperature for 5 days. (3) Formation of superconductive phase. The products were carefully filtered and washed thoroughly with deionized water, followed by drying at ambient conditions for 10 - 20 hrs in order to remove the powders from the filter paper. The dried powders were then stored in a wet chamber with sufficient humidity for further structural and magnetic characterization. Powder x-ray diffraction (XRD) patterns were obtained using a. Shimadzu XRD-6000 diffractometer equipped with Fe Kα radiation. The sodium content was determined by using a Perkin Elmer Optima 3000 DC inductively coupled plasma - atomic emission spectrometer (ICP-AES). Before the chemical analysis, samples are dehydrated by heating at 300°C in air for 12 h. Thermogravimetric analysis (TGA) was carried out by using a Perkin Elmer Pyris 1 thermogravimetric analyzer. A commercial SQUID magnetometer (Quantum Design) was used to characterize the superconducting transition temperature of the samples.

3. Results and discussion

Fig. 1 shows the powder x-ray diffraction patterns (XRD) of the products obtained by different molar ratios of KMnO₄ relative to Na content. The XRD patterns for $\leq 0.1X$ samples are a mixture of a fully-hydrated superconducting phase and a non-superconducting dehydrated phase, which is similar to bromine-treated samples with substoichiometric or stoichiometric Br₂/CH₃CN solutions [2]. Single phase of fully hydrated Na_xCoO₂·yH₂O occurs for KMnO₄/Na = 0.3. For $0.5 \leq$ KMnO₄/Na ≤ 2.29 , there is a very tiny peak appearing at $2\theta \approx 16^{\circ}$, the characteristic (002) peak of so-called y = 0.6 intermediate

hydrated phase [5], in addition to the diffraction peaks of the fully hydrated phase. The sodium contents are determined by using inductively coupled plasma atomic emission spectroscopy (ICP-AES) and shown in Table I. Chemical analyses show that the sodium contents in Na_xCoO₂·yH₂O systematically decreases with increasing molar ratio of KMnO₄/Na. The values of x are 0.38, 0.32, 0.28 for 0.3X, 0.5X, and 2.29X samples, respectively. These results confirm that the role of KMnO₄ is acting as an oxidizing agent to partially de-intercalate the Na from the structure and hence oxidize the electronically active CoO₂ layers. The *c*-axis of the unit cell in Na_xCoO₂·yH₂O tends to increase with increasing molar ratio of KMnO₄/Na from19.669 A for the 0.3X sample to 19.735 A for the 2.29X sample but with little changes in the *a*-axis

The thermal stability and water content of 0.3X sample are checked and determined by heating the sample in flowing O_2 at the slowest rate of 0.1°C/min available to the Perkin Elmer Pyris 1 thermogravimetric analyzer (TGA). Fig. 2 indicates a multi-stage loss of water with relatively unstable intermediates [13], being consistent with the thermally unstable nature of the fully hydrated phase [5,14]. The water content of fully hydrated phase is estimated to contain 1.45 and 1.55 H₂O pre formula unit by taking the weight loss at 320 $^{\circ}\text{C}$ and 600 $^{\circ}\text{C}$, respectively, as the fully dehydrated phase (y = 0), assuming no oxygen deficiency in the sample for the present estimations.

Fig. 3 shows the zero-field cooled and field cooled magnetization data of 0.3X, 0.5X, and 2.29X samples measured in a dc field of 10 Oe. The onset superconducting transition is observed at about 4.6 K, 4.5 K, and 3.8 K for 0.3X, 0.5X, and 2.29X, respectively. The mass magnetization at 1.8 K is - 1.28×10⁻² emu/g in the zero-field cooling measurements, which is approximately 31 % of the theoretical value for perfect diamagnetism.

4. Conclusions

We have first synthesized the superconductive cobalt oxyhydrates Na_xCoO₂·yH₂O using KMnO₄ as an oxidizing agent instead of using Br₂/CH₃CN solutions. The role of KMnO₄ is to de-intercalate the

Na from the structure and hence oxidize the Co ion based on the electron neutrality. The higher molar ratio of KMnO₄ relative to Na content used to treat the samples leads to more removal of Na. The superconductive phase of Na_xCoO₂·yH₂O is commonly obtained by Br₂/CH₃CN solutions, which is highly toxic by ingestion and inhalation. This new route might also indicate that KMnO₄ has the potential to treat other layered oxide materials with similar function of de-intercalation and oxidation and to have mass production of superconducting samples.

Acknowledgment. This work is supported by National Science Council of ROC under the grant No. NSC 92-2112-M-018-005.

References

- (1) K. Takada, H., Sakurai, E. Takayama-Muromachi, F. Izumi, R.A. Dilanian, T. Sasaki, Nature 422 (2003) 53.
- (2) R. E. Schaak, T. Klimczuk, M. L. Foo, R. J. Cava, Nature 424 (2003) 527.
- (3) J. Cmaidalka, A. Baikalov, Y. Y. Xue, R. L. Meng, C. W. Chu, Physica C 403 (2004) 125.
- (4) B. G. Ueland, P. Schiffer, R.E. Schaak, M. L. Foo, V. L. Miller, R. J. Cava, Physica C 402 (2004) 27.
- (5) M. L. Foo, R.E. Schaak, V. L. Miller, T. Klimczuk, N. S. Rogado, Y. Wang, G. C. Lau, C. Craley, H. W. Zandbergen, N. P. Ong, R. J. Cava, Solid State Commun. 127 (2003) 33.
- (6) J. D. Jorgensen, M. Avdeev, D.G. Hinks, J. C. Burley, S. Short, cond-mat/0307627 (2003).
- (7) H. D.Yang, J.-Y Lin, C. P. Sun, Y. C. Kang, K. Takada, T. Sasaki, H. Sakurai, E. Takayama-Muromachi, cond-mat/0308031 (2003).
- (8) I. Terasaki, Y. Sasago, K. Uchinokura, Phys. Rev. B 56 (1997) R12685.
- (9) C. Fouassier, G. Matejka, J.-M. Reau, P. Hagenmuller, J. Solid State Chem. 6 (1973) 532.
- (10) M. Mikami, M. Yoshimura, Y. Mori, T. Sasaki, Jpn. J. Appl. Phys. 41 (2002) L777.
- (11) S. Par, Y. Lee, A. Moodenbaugh, Vogt, T. Phys. Rev. B 68 (2003) 180505.
- (12) T. Motohashi, E. Naujalis, R. Ueda, K. Isawa, M. Karppinen, H. Yamauchi, Appl. Phys. Lett. 79 (2001) 1480.
- (13) M. E.Brown, Introduction to Thermal Analysis, Chapman and Hall, New York, 1988.
- (14) D. P. Chen, H. C. Chen, A. Maljuk, A. Kulakov, H. Zhang, C. T. Lin, cond-mat/0401636 (2004).

Table I. Sodium content and lattice constants of $Na_xCoO_2 \cdot yH_2O$ prepared using $KMnO_4$ as oxidant

Molar ratio of KMnO ₄ /Na	Sodium content x ^a	a axis ^b A	c axis ^b
0.3X	0.38	2.8249(1)	19.669(1)
0.5X	0.32	2.8248(1)	19.679(1)
2.29X	0.28	2.8250(2)	19.735(2)

^aThe error in weight % of each element in ICP-AES analysis is ± 3 %, which corresponds to an estimated error of ± 0.02 per formula unit. ^bLattic constants are determined by least squares refinement using the XRD data between 2θ of 5° and 90° based on a hexagonal lattice with space group P6₃/mmc.

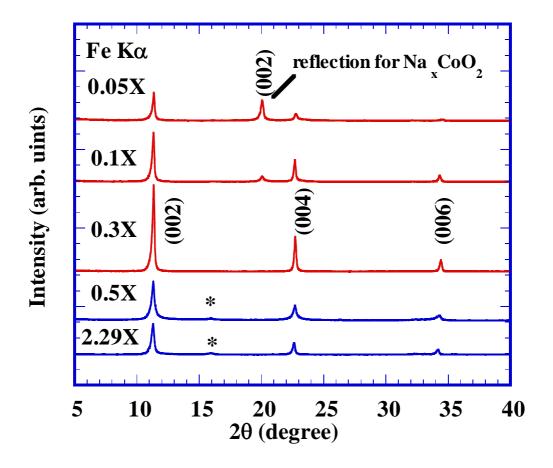


Fig. 1. Powder x-ray diffraction (XRD) patterns for $Na_xCoO_2 \cdot yH_2O$ prepared using different molar ratios of KMnO₄ relative to Na content. The 0.3 X and 2.29 X represent the molar ratios of KMnO₄ relative to Na content are 0.3 and 2.29, respectively. The asterisk indicates the tiny peak for the (002) diffraction peak for the so-called y = 0.6 intermediate hydrated phase.

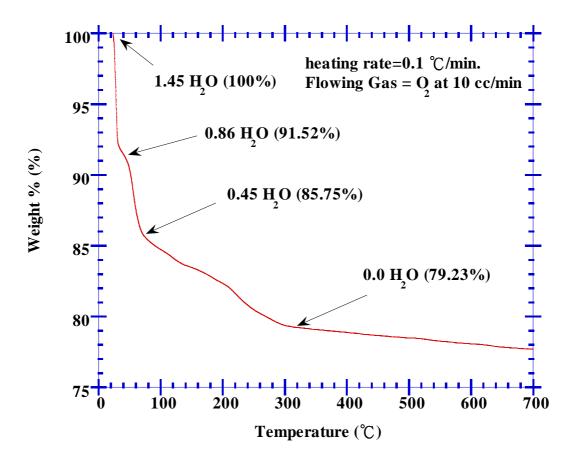


Fig. 2. Thermogravimetric analysis of $Na_xCoO_2\cdot yH_2O$ (0.3X) with a heating rate of 0.1°C/min in flowing oxygen. The water content is determined by assuming a complete loss of water at 320°C.

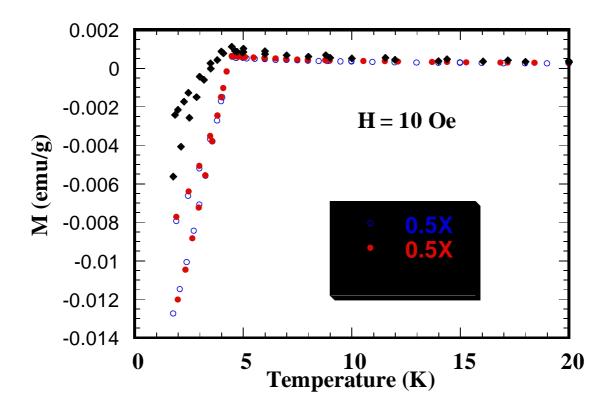


Fig. 3. Zero-field cooled and field cooled d.c. magnetization for $Na_xCoO_2 \cdot yH_2O$ (solid circle: 0.3X; open circle: 0.5X; solid diamond: 2.29X).