

Networks of self-avoiding chains and Ogden-type constitutive equations for elastomers

A.D. Drozdov and M. Gottlieb
Department of Chemical Engineering
Ben-Gurion University of the Negev
P.O. Box 653
Beer-Sheva 84105, Israel

Abstract

An expression is derived for the strain energy of a polymer chain under an arbitrary three-dimensional deformation with finite strains. For a Gaussian chain, this expression is reduced to the conventional Mooney–Rivlin constitutive law, while for non-Gaussian chains it implies novel constitutive relations. Based on the three-chain approximation, explicit formulas are developed for the strain energy of a chain modeled as a self-avoiding random walk. In the case of self-avoiding chains with stretched-exponential distribution function of end-to-end vectors, the strain energy density of a network is described by the Ogden law with only two material constants. For the des Cloizeaux distribution function, the constitutive equation involves three adjustable parameters. The governing equations are verified by fitting observations on uniaxial tension, uniaxial compression and biaxial tension of elastomers. Good agreement is demonstrated between the experimental data and the results of numerical analysis. An analytical formula is derived for the ratio of the Young's modulus of a self-avoiding chain to that of a Gaussian chain. It is found that the elastic modulus per chain in the Ogden network exceeds that in a Gaussian network by a factor of three, whereas the elastic modulus of a chain with the generalized stretched exponential distribution function equals about half of the modulus of a Gaussian chain.

Key-words: Constitutive equations, Elastomers, Affine networks, Non-Gaussian chains, Self-avoiding random walks

1 Introduction

This paper is concerned with the so-called “physically motivated” constitutive equations for the elastic response of elastomers at finite strains. Although this subject has attracted substantial attention in the past half a century, it remains a focus of attention both in the communities of mechanical engineers, [1, 2, 3, 4, 5, 6, 7, 8, 9, 10] and polymer physicists [11, 12, 13, 14, 15, 16, 17, 18, 19, 20, 21]. This interest may be explained by two reasons: (i) from the standpoint of applications, it is induced by the necessity to have a reliable tool for the analysis of the mechanical behavior of polymer materials, whose response is inadequately described by conventional stress–strain equations, and (ii) from the point of view of fundamental research, it is driven by the lack of constitutive laws based on the solid ground of statistical physics that provide rather simple formulas for the strain energy of rubber-like materials.

Surprisingly, the concept of Gaussian chains in an affine network introduced about a century ago [22] may serve as the only example of a physically-based theory that can be employed in the analysis of stresses in elastomer structures (in this assertion, we exclude from the consideration (i) slip-link models [23] that deal with chains in non-affine networks, (ii) numerous variants, see [24] the the references therein, of the Kratky–Porod¹ model [25], where the stress–strain relations contain the inverse Langevin function and can be resolved only numerically, and (iii) the Gent [27], see also [28], and FENE dumbbell [29] constitutive equations, which correctly mimic a limiting chain extensibility, but can be deduced from an appropriate statistical theory within the Peterlin approximation only). The model of a Gaussian chain is, however, overly simplified for engineering applications, because it implies the neo–Hookean expression for the strain energy per chain

$$W = \frac{1}{2}k_{\text{B}}T(J_1 - 3), \quad (1)$$

which rather poorly describes observations. Here k_{B} is Boltzmann’s constant, T is the absolute temperature, and J_m stands for the m th principal invariant of the right Cauchy–Green deformation tensor \mathbf{C} . From the physical standpoint, other shortcomings of the model of a freely jointed chain are that it (i) disregards short- and long-range interactions between segments, and (ii) implies that the end-to-end distance exceeds the contour length of a chain with a non-zero probability.

To avoid these disadvantages, more sophisticated models of non-Gaussian linear chains are introduced. The starting point in their derivation is the treatment of a chain as a random curve in a three-dimensional space [30]. The randomness of the curve reflects random fluctuations of the chain driven by thermal excitations. Each realization of the curve is described by the vector equation $\tilde{\mathbf{Q}}(s)$, where s is the arc-length. For definiteness, we suppose that $s \in [0, L]$, where L stands for the contour length, and assume the end $s = 0$ to be fixed at the origin, and the end $s = L$ to be free. In these notation, the end-to-end vector of a chain reads $\mathbf{Q} = \tilde{\mathbf{Q}}(L)$.

As the description of random curves is extremely complicated from the mathematical standpoint, it is convenient to replace any curve by a set of N rigid segments with length l connected with each other. These segments are thought of as random vectors, which are independent for Gaussian chains or mutually dependent for more advanced models. The segment length l and the number of segments N are connected by the formula $L = Nl$. Conventionally, N is treated as a given integer number. The parameter l may be fixed (for the Gaussian and Kratky–Porod chains), or it may be considered as a random variable (for the Lévy flights [31]). For a fixed l ,

¹We employ the terminology widely used in statistical mechanics of macromolecules. In the studies on mechanics of polymers, this model is conventionally referred to as the James–Guth theory[26] or the theory of Langevin chains [10].

the discrete model of a chain is equivalent to a random walk with N steps that starts at the origin.

Formally, a random walk is entirely described by the probability density $f(\tilde{\mathbf{Q}}_1, \dots, \tilde{\mathbf{Q}}_N)$, where the vector $\tilde{\mathbf{Q}}_n$ characterizes the n th step of the walk. For a large N , this description becomes, however, inconvenient, and only the distribution $p_0(\mathbf{Q})$ of the corresponding end-to-end vector \mathbf{Q} is studied. For a spherically symmetric walk (no preferable direction in space), the average value of \mathbf{Q} vanishes, $\overline{\mathbf{Q}} = \mathbf{0}$, whereas the mean-square end-to-end distance $b^2 = \overline{Q^2}$ characterizes the spatial dimension of a chain. The scaling analysis [32] implies that

$$b = lN^\nu, \quad (2)$$

where ν is a scaling exponent. For a Gaussian chain without interaction between segments, $\nu = \frac{1}{2}$, but for a chain that is sensitive to such interactions, ν becomes higher.

All theories of polymer chains may be divided into two groups: (i) phantom chains, for which two segments of a chain may be located at the same point, and (ii) self-avoiding chains, for which excluded volume interactions are taken into account. The first group of models is relatively simple, and a number of mathematically strong results have been derived for phantom chains. The most famous models of this group are the Kratky–Porod concept [25] that accounts for interactions between nearest neighbors only, and its continuous analog, the model of worm-like chains [33].

Unlike most previous studies concerned with phantom chains, the present work concentrates on constitutive equations for linear macromolecules modeled as self-avoiding random walks (SARW) [34]. Although an exact expression for the distribution function of end-to-end vectors of a SARW is unknown, two convenient approximations are widely used [35, 36]. According to the first, the distribution function of end-to-end vectors is described by the stretched exponential expression

$$p_0(\mathbf{Q}) = p^0 \exp\left[-\beta\left(\frac{Q}{R}\right)^{2\delta}\right], \quad (3)$$

where $Q = |\mathbf{Q}|$, and β , δ , R are positive constants. The pre-factor p^0 is found from the normalization condition

$$\int p_0(\mathbf{Q})d\mathbf{Q} = 1, \quad (4)$$

which implies that

$$p^0 = \frac{1}{4\pi} \left[\int_0^\infty \exp\left(-\beta\left(\frac{Q}{R}\right)^{2\delta}\right) Q^2 dQ \right]^{-1}. \quad (5)$$

The other approximation of the distribution function was developed in [37, 38]

$$p_0(\mathbf{Q}) = p^0 \left(\frac{Q}{R}\right)^{2\alpha} \exp\left[-\beta\left(\frac{Q}{R}\right)^{2\delta}\right]. \quad (6)$$

In the literature on random walks [35, 36], Eq. (6) is conventionally referred to as the des Cloizeaux law. In the field of mathematical statistics, this formula is known [39] as a symmetrical Kotz-type distribution. Equation (6) involves four adjustable constants, α , β , δ and R . The pre-factor p^0 is determined from the normalization condition (4),

$$p^0 = \frac{R^{2\alpha}}{4\pi} \left[\int_0^\infty \exp\left(-\left(\frac{Q}{R}\right)^{2\delta}\right) Q^{2(1+\alpha)} dQ \right]^{-1}. \quad (7)$$

There is a substantial difference between the parameters α , β and R , on the one hand, and the exponent δ in Eqs. (3) and (6), on the other. While the quantities α , β and R can adopt

practically arbitrary values, the parameter δ is strongly connected [35] with the scaling exponent ν in Eq. (2),

$$\delta = \frac{1}{1 - \nu}. \quad (8)$$

Due to some technical peculiarities of the renormalization-group method [40] employed for the evaluation of the scaling exponent, it is convenient to assess ν for a SARW in a d -dimensional space. Flory [41] was the first who conjectured that

$$\nu = \frac{d}{d + 2}. \quad (9)$$

For a three-dimensional space, Eqs. (8) and (9) imply that $\nu = \frac{3}{5}$ and

$$\delta = \frac{5}{2}. \quad (10)$$

Although Eq. (9) has not been either proved or disproved up to now, the estimate (10) is used in the present study for two reasons: (i) formula (9) is widely employed in the field of statistical physics of polymers, and (ii) Eq. (10) allows necessary calculations to be performed explicitly.

The objective of this study is three-fold:

1. To derive an analytical expression for the strain energy W of a polymer chain with an arbitrary distribution function of end-to-end vectors $p_0(\mathbf{Q})$.
2. To apply this formula in order to develop explicit expressions for the strain energy of chains with distribution functions (3) and (6).
3. To calculate the strain energy density of a network of self-avoiding chains, and to find adjustable parameters in the governing equations by fitting experimental data.

To derive constitutive equations, we employ the Boltzmann formula, according to which the probability $p_0(\mathbf{Q})$ that a chain has an end-to-end vector \mathbf{Q} is expressed in terms of the configurational free energy $U_0(\mathbf{Q})$ as

$$p_0(\mathbf{Q}) = \exp\left(-\frac{U_0(\mathbf{Q})}{k_B T}\right). \quad (11)$$

The function $U_0(\mathbf{Q})$ determines the energy of a chain in the reference (stress-free) state. When macro-deformation is applied to a polymer network, the initial end-to-end vector \mathbf{Q} of the chain is transformed into some vector \mathbf{q} at an instant $t \geq 0$ (time $t = 0$ corresponds to the application of external loads). For an affine network of chains, the distribution function $p(t, \mathbf{q})$ of the vector \mathbf{q} obeys an appropriate Smoluchowski equation [30] that is solved explicitly.

Given $p(t, \mathbf{q})$, the configurational free energy of a chain in the actual (deformed) state $U(t, \mathbf{q})$ is described by the equation similar to Eq. (11),

$$p(t, \mathbf{q}) = \exp\left(-\frac{U(t, \mathbf{q})}{k_B T}\right). \quad (12)$$

When the functions $U_0(\mathbf{Q})$ and $U(t, \mathbf{q})$ are found, the increment of the configurational free energy is given by

$$\Delta U = U - U_0. \quad (13)$$

The strain energy per chain $W(t)$ is determined by averaging the increment ΔU with respect to an appropriate distribution function (p_0 or p). A general expression for W will be developed in Section 3. At volume-preserving deformation of a Gaussian chain with the distribution function

$$p_0(\mathbf{Q}) = \left(\frac{3}{2\pi b^2}\right)^{\frac{3}{2}} \exp\left(-\frac{3Q^2}{2b^2}\right), \quad (14)$$

where $Q = |\mathbf{Q}|$, this formula is transformed into Eq. (1), when the averaging is performed with respect to the current distribution of end-to-end vectors, and it implies the Mooney–Rivlin constitutive law

$$W = \frac{1}{2}k_{\text{B}}T \left[a(J_1 - 3) + (1 - a)(J_2 - 3) \right], \quad (15)$$

when the averaging is performed with respect to the functions p and p_0 with the weights a and $1 - a$, respectively.

Regrettably, the strain energy of a chain cannot be expressed as an elementary function of principal stretches for an arbitrary three-dimensional deformation. To develop such an analytical expression, we apply an approximation procedure similar to the three-chain hypothesis [26], according to which “the network of chains. . . is mathematically equivalent to three independent sets of chains respectively parallel to the axes of a three-dimensional Cartesian coordinate system” [42].

By using the three-chain approximation, explicit formulas are derived for the strain energy of self-avoiding chains with distribution functions (3) and (6). An important conclusion of our analysis is that for an incompressible network, the strain energy of a chain with the stretched exponential distribution function (3) is described (up to a small correction term) by the three-term Ogden law [43]

$$W = \frac{1}{2}k_{\text{B}}T \sum_{n=1}^3 \kappa_n \sum_{m=1}^3 \left[a(\lambda_m^{\frac{\alpha_n}{2}} - 3) + (1 - a)(\lambda_m^{-\frac{\alpha_n}{2}} - 3) \right]. \quad (16)$$

Unlike the original Ogden formula [43], where a , α_n and κ_n ($n = 1, 2, 3$) are treated as adjustable parameters, our expression contains only 2 material constants, while the exponents α_n equal 1, 3 and 5, respectively. This result provides a micro-mechanical basis for the Ogden model, on the one hand, and allows the number of experimental constants in Eq. (16) to be reduced noticeably, on the other.

For the des Cloizeaux law (6), an expression for the strain energy per chain W is developed for an arbitrary (positive and negative) exponent α . The function W differs from that described by Eq. (16) by an additional term that depends on α . Surprisingly, approximation of experimental data reveals that the best fit of observations is reached at negative values of α . As these values have no physical meaning within the model of self-avoiding random walks (although they are not forbidden from the physical standpoint), we conclude that the Ogden constitutive law (16) describes the elastic response of all chains that can be modeled as self-avoiding random walks.

Finally, the mechanical response of self-avoiding chains is analyzed at small deformations. At uniaxial tension (compression) with small strains, the elastic behavior of a chain is entirely described by the only parameter, an analog of the Young’s modulus. The elastic modulus is proportional to $k_{\text{B}}T$, but the coefficient of proportionality depends on the distribution function $p_0(\mathbf{Q})$. It is found that self-avoiding chains with the stretched exponential distribution function (3) are “stronger” than Gaussian chains with the distribution function (14) by a factor of three, whereas the ratio of the Young’s modulus of a self-avoiding chain with the des Cloizeaux distribution function to that of a Gaussian chain linearly increases with exponent α .

The exposition is organized as follows. The Smoluchowski equation for the distribution function $p(t, \mathbf{q})$ is resolved in Section 2 for an arbitrary time-dependent deformation of an affine network. A formula for the strain-energy of a chain is developed in Section 3. The strain energy of a Gaussian chain is calculated in Section 4. A three-chain approximation procedure is introduced in Section 5. The mechanical energy of a self-avoiding chain with the stretched-exponential distribution function is found in Section 6. This expression is applied in Section 7 to fit experimental data on several elastomers. The strain energy of a chain whose statistics is governed by the des Cloizeaux law (6) is determined in Section 8, and the corresponding constitutive law is validated in Section 9. The elastic moduli of self-avoiding chains are calculated in Section 10. Some concluding remarks are formulated in Section 11. To avoid technical details in the main text, necessary calculations are given in Appendices.

2 Transformation of the distribution function

We begin with the solution of the Smoluchowski equation for the distribution function of end-to-end vectors p . Consider a chain with an end-to-end vector \mathbf{Q} in the reference state and an end-to-end vector \mathbf{q} in the actual state at time $t \geq 0$. In an affine network, transformation of the reference state of the chain into its deformed state is described by the formula

$$\mathbf{q} = \mathbf{F}(t) \cdot \mathbf{Q}, \quad (17)$$

where \mathbf{F} stands for the deformation gradient for macro-deformation (at this stage of the analysis, we do not impose the incompressibility condition on the tensor \mathbf{F}). The function $\mathbf{F}(t)$ obeys the differential equation

$$\frac{d\mathbf{F}}{dt} = \mathbf{L} \cdot \mathbf{F}, \quad \mathbf{F}(0) = \mathbf{I}, \quad (18)$$

where $\mathbf{L}(t)$ is the velocity gradient, \mathbf{I} is the unit tensor.

The distribution function $p(t, \mathbf{q})$ of the end-to-end vector \mathbf{q} satisfies the equation [30]

$$\frac{\partial p}{\partial t} = -\frac{\partial}{\partial \mathbf{q}} \cdot (\mathbf{L} \cdot \mathbf{q} p) = -\mathcal{I}_1(\mathbf{D})p - \frac{\partial p}{\partial \mathbf{q}} \cdot \mathbf{L} \cdot \mathbf{q}, \quad (19)$$

with the initial condition

$$p(0, \mathbf{q}) = p_0(\mathbf{q}). \quad (20)$$

Here

$$\mathbf{D} = \frac{1}{2}(\mathbf{L} + \mathbf{L}^\top)$$

is the rate-of-strain tensor, \top denotes transpose, and \mathcal{I}_m stands for the m th principal invariant of a tensor ($m = 1, 2, 3$). Simple algebra implies that the solution of Eqs. (19) and (20) reads

$$p(t, \mathbf{q}) = p_0(\mathbf{F}^{-1}(t) \cdot \mathbf{q}) \exp\left[-\int_0^t \mathcal{I}_1(\mathbf{D}(s)) ds\right]. \quad (21)$$

It follows from Eq. (18) that the third principal invariant of the deformation gradient obeys the equation

$$\frac{d\mathcal{I}_3(\mathbf{F})}{dt} = \mathcal{I}_1(\mathbf{D})\mathcal{I}_3(\mathbf{F}). \quad (22)$$

The solution of Eq. (22) with the initial condition $\mathcal{I}_3(\mathbf{F}(0)) = 1$ reads

$$\mathcal{I}_3(\mathbf{F}(t)) = \exp\left[\int_0^t \mathcal{I}_1(\mathbf{D}(s)) ds\right]. \quad (23)$$

Equations (21) and (23) imply that

$$p(t, \mathbf{q}) = \frac{p_0(\mathbf{F}^{-1}(t) \cdot \mathbf{q})}{\mathcal{I}_3(\mathbf{F}(t))}. \quad (24)$$

To demonstrate that function (24) satisfies the normalization condition

$$\int p(t, \mathbf{q}) d\mathbf{q} = 1, \quad (25)$$

we substitute expression (24) into the left-hand side of Eq. (25) and find that

$$\int p(t, \mathbf{q}) d\mathbf{q} = \frac{1}{\mathcal{I}_3(\mathbf{F}(t))} \int p_0(\mathbf{F}^{-1}(t) \cdot \mathbf{q}) d\mathbf{q}.$$

Introducing the new variable \mathbf{Q} by Eq. (17) and bearing in mind that

$$d\mathbf{q} = \mathcal{I}_3(\mathbf{F}) d\mathbf{Q}, \quad (26)$$

we arrive at the formula

$$\int p(t, \mathbf{q}) d\mathbf{q} = \int p_0(\mathbf{Q}) d\mathbf{Q}.$$

Equation (25) follows from this equality and Eq. (4).

3 Strain energy of a chain

Our aim now is to calculate the strain energy of a chain in an affine network by using Eq. (24). The configurational free energies of a chain in the reference and actual states are connected with appropriate distribution functions by Eqs. (11) and (12),

$$U_0(\mathbf{Q}) = -k_B T \ln p_0(\mathbf{Q}), \quad U(t, \mathbf{q}) = -k_B T \ln p(t, \mathbf{q}). \quad (27)$$

There are two ways to determine the strain energy per strand W . According to the first, the increment ΔU of the configurational free energy caused by transition from the reference state to the actual state,

$$\Delta U(t, \mathbf{Q}) = U(t, \mathbf{Q}) - U_0(\mathbf{Q}) = -k_B T [\ln p(t, \mathbf{Q}) - \ln p_0(\mathbf{Q})]$$

is averaged with the help of the distribution function in the reference state,

$$W_1(t) = -k_B T \int [\ln p(t, \mathbf{Q}) - \ln p_0(\mathbf{Q})] p_0(\mathbf{Q}) d\mathbf{Q}. \quad (28)$$

According to the other approach, we calculate the increment of the configurational free energy with respect to the actual state,

$$\Delta U(t, \mathbf{q}) = U_0(\mathbf{q}) - U(t, \mathbf{q}) = -k_B T [\ln p_0(\mathbf{q}) - \ln p(t, \mathbf{q})],$$

and average it by using the distribution function in the deformed state,

$$W_2(t) = -k_B T \int [\ln p_0(\mathbf{q}) - \ln p(t, \mathbf{q})] p(t, \mathbf{q}) d\mathbf{q}. \quad (29)$$

We begin with transformation of Eq. (28). Substituting expression (24) into this equality and using Eq. (26), we obtain

$$W_1(t) = -k_B T \left\{ \int \left[\ln p_0(\mathbf{F}^{-1}(t) \cdot \mathbf{Q}) - \ln p_0(\mathbf{Q}) \right] p_0(\mathbf{Q}) d\mathbf{Q} - \ln \mathcal{I}_3(\mathbf{F}(t)) \right\}. \quad (30)$$

We now proceed with Eq. (29), combine this equality with Eq. (24), we find that

$$W_2(t) = \frac{k_B T}{\mathcal{I}_3(\mathbf{F}(t))} \int \left[\ln p_0(\mathbf{F}^{-1}(t) \cdot \mathbf{q}) - \ln p_0(\mathbf{q}) - \ln \mathcal{I}_3(\mathbf{F}(t)) \right] p_0(\mathbf{F}^{-1}(t) \cdot \mathbf{q}) d\mathbf{q}.$$

Introducing the new variable \mathbf{Q} by Eq. (17) and using Eqs. (25) and (26), we find that

$$W_2(t) = k_B T \left\{ \int \left[\ln p_0(\mathbf{Q}) - \ln p_0(\mathbf{F}(t) \cdot \mathbf{Q}) \right] p_0(\mathbf{Q}) d\mathbf{Q} - \ln \mathcal{I}_3(\mathbf{F}(t)) \right\}. \quad (31)$$

It seems natural to define the strain energy per strand W as the weighted sum of the strain energies W_1 and W_2 that are determined by employing different ways of averaging of the configurational free energy,

$$W = (1 - a)W_1 + aW_2, \quad (32)$$

where $a \in [0, 1]$ is a material parameter. Combining Eqs. (30)–(32), we arrive at the formula

$$\begin{aligned} W(t) = & k_B T \left\{ -(2a - 1) \ln \mathcal{I}_3(\mathbf{F}(t)) + \int \left[a \left(\ln p_0(\mathbf{Q}) - \ln p_0(\mathbf{F}(t) \cdot \mathbf{Q}) \right) \right. \right. \\ & \left. \left. + (1 - a) \left(\ln p_0(\mathbf{Q}) - \ln p_0(\mathbf{F}^{-1}(t) \cdot \mathbf{Q}) \right) \right] p_0(\mathbf{Q}) d\mathbf{Q} \right\}. \end{aligned} \quad (33)$$

To proceed with transformations of Eq. (33), an additional hypothesis is needed regarding the function $p_0(\mathbf{Q})$. Assuming the end-to-end vectors to be distributed uniformly in the reference state, we set

$$p_0(\mathbf{Q}) = P(Q^2), \quad (34)$$

where $Q^2 = \mathbf{Q} \cdot \mathbf{Q}$, and $P(r)$ is a given function of a scalar argument r . Substituting expression (34) into Eq. (33) and taking into account that

$$\begin{aligned} (\mathbf{F} \cdot \mathbf{Q}) \cdot (\mathbf{F} \cdot \mathbf{Q}) &= \mathbf{Q} \cdot \mathbf{F}^\top \cdot \mathbf{F} \cdot \mathbf{Q} = \mathbf{Q} \cdot \mathbf{C} \cdot \mathbf{Q}, \\ &= \mathbf{Q} \cdot \mathbf{B}^{-1} \cdot \mathbf{Q}, \\ \mathcal{I}_3^2(\mathbf{F}) &= J_3, \end{aligned}$$

where the left and right Cauchy–Green deformation tensors are determined by the conventional formulas

$$\mathbf{B} = \mathbf{F} \cdot \mathbf{F}^\top, \quad \mathbf{C} = \mathbf{F}^\top \cdot \mathbf{F}, \quad (35)$$

we find that

$$\begin{aligned} W = & k_B T \left\{ -\frac{1}{2}(2a - 1) \ln J_3 + \int \left[a \left(\ln P(Q^2) - \ln P(\mathbf{Q} \cdot \mathbf{C} \cdot \mathbf{Q}) \right) \right. \right. \\ & \left. \left. + (1 - a) \left(\ln P(Q^2) - \ln P(\mathbf{Q} \cdot \mathbf{B}^{-1} \cdot \mathbf{Q}) \right) \right] P(Q^2) d\mathbf{Q} \right\}. \end{aligned} \quad (36)$$

It is easy to show (Appendix A) that

$$\int \ln P(\mathbf{Q} \cdot \mathbf{B}^{-1} \cdot \mathbf{Q}) P(Q^2) d\mathbf{Q} = \int \ln P(\mathbf{Q} \cdot \mathbf{C}^{-1} \cdot \mathbf{Q}) P(Q^2) d\mathbf{Q}. \quad (37)$$

It follows from Eqs. (36) and (37) that the strain energy per strand reads

$$W = k_{\text{B}}T \left\{ -\frac{1}{2}(2a-1) \ln J_3 + \int \left[a \left(\ln P(Q^2) - \ln P(\mathbf{Q} \cdot \mathbf{C} \cdot \mathbf{Q}) \right) + (1-a) \left(\ln P(Q^2) - \ln P(\mathbf{Q} \cdot \mathbf{C}^{-1} \cdot \mathbf{Q}) \right) \right] P(Q^2) d\mathbf{Q} \right\}. \quad (38)$$

Our aim now is to apply Eq. (38) in order to determine the strain energy of a Gaussian chain with distribution function (14).

4 Strain energy of a Gaussian chain

According to Eqs. (14) and (34), the function $P(r)$ reads

$$P(r) = \left(\frac{3}{2\pi b^2} \right)^{\frac{3}{2}} \exp\left(-\frac{3r}{2b^2}\right).$$

Simple algebra (Appendix B) implies that

$$\begin{aligned} \int \left(\ln P(Q^2) - \ln P(\mathbf{Q} \cdot \mathbf{C} \cdot \mathbf{Q}) \right) P(Q^2) d\mathbf{Q} &= \frac{1}{2}(J_1 - 3), \\ \int \left(\ln P(Q^2) - \ln P(\mathbf{Q} \cdot \mathbf{C}^{-1} \cdot \mathbf{Q}) \right) P(Q^2) d\mathbf{Q} &= \frac{1}{2}(J_{-1} - 3), \end{aligned} \quad (39)$$

where $J_{-m} = \mathcal{I}_m(\mathbf{C}^{-1})$ ($m = 1, 2, 3$). Substitution of expressions (39) into Eq. (38) implies that

$$W = \frac{1}{2} k_{\text{B}}T \left[a(J_1 - 3) + (1-a)(J_{-1} - 3) - (2a-1) \ln J_3 \right]. \quad (40)$$

Bearing in mind that $J_{-1} = J_2/J_3$, we present Eq. (40) in the form

$$W = \frac{1}{2} k_{\text{B}}T \left[a(J_1 - 3) + (1-a) \left(\frac{J_2}{J_3} - 3 \right) - (2a-1) \ln J_3 \right]. \quad (41)$$

Equation (41) implies that for an incompressible polymer network with $J_3 = 1$, the strain energy of a chain is given by the Mooney–Rivlin law (15). Equation (41) is reduced to the constitutive relation (1) for an incompressible neo–Hookean medium (which is traditionally associated with the response of Gaussian chains) at $a = 1$ only (when the averaging of the increment of configurational free energy ΔU is performed with respect to the distribution function p in the actual state). It is worth noting that our results are in accord with those developed in [2, 44] by using another approach (a tube model for rubbery polymers).

5 Three-chain approximation

Our aim now is to introduce a three-chain approximation for the strain energy per chain based on expression (40) for the mechanical energy of a Gaussian chain. Bearing in mind that

$$J_1 = \lambda_1 + \lambda_2 + \lambda_3, \quad J_{-1} = \frac{1}{\lambda_1} + \frac{1}{\lambda_2} + \frac{1}{\lambda_3}, \quad J_3 = \lambda_1 \lambda_2 \lambda_3,$$

where λ_m ($m = 1, 2, 3$) are eigenvalues of the Cauchy–Green tensor \mathbf{C} , we find from Eq. (40) that

$$W = \frac{1}{2} k_{\text{B}}T \left[a(\lambda_1 + \lambda_2 + \lambda_3 - 3) + (1-a) \left(\frac{1}{\lambda_1} + \frac{1}{\lambda_2} + \frac{1}{\lambda_3} - 3 \right) - (2a-1) \ln(\lambda_1 \lambda_2 \lambda_3) \right]. \quad (42)$$

Let us consider now three networks of chains. The principal axes of the Cauchy–Green deformation tensor $\mathbf{C}^{(m)}$ for the m th network ($m = 1, 2, 3$) coincide with the eigenvectors of the tensor \mathbf{C} , whereas the corresponding eigenvalues $\{\lambda_1^{(m)}, \lambda_2^{(m)}, \lambda_3^{(m)}\}$ are given by

$$\begin{aligned}\lambda_1^{(1)} &= \lambda_1, & \lambda_2^{(1)} &= 1, & \lambda_3^{(1)} &= 1, \\ \lambda_1^{(2)} &= 1, & \lambda_2^{(2)} &= \lambda_2, & \lambda_3^{(2)} &= 1, \\ \lambda_1^{(3)} &= 1, & \lambda_2^{(3)} &= 1, & \lambda_3^{(3)} &= \lambda_3.\end{aligned}\tag{43}$$

It follows from Eqs. (42) and (43) that the strain energy per chain in the m th network reads

$$W^{(m)} = \frac{1}{2}k_{\text{B}}T \left[a(\lambda_m - 1) + (1 - a) \left(\frac{1}{\lambda_m} - 1 \right) - (2a - 1) \ln \lambda_m \right].\tag{44}$$

Equations (42) and (44) imply that

$$W = \sum_{m=1}^3 W^{(m)}.\tag{45}$$

Formula (45) may be referred to as the three-chain approximation of the strain energy W (it slightly differs from the three-chain approach proposed in [26]). Equation (45) provides an exact expression for the strain energy of a Gaussian chain. For non-Gaussian chains, this formula may serve as a convenient approximation for the strain energy.

Returning to general expression (38) and applying the three-chain approximation, we find that the strain energy W is given by Eq. (45), where $W^{(m)}$ read

$$\begin{aligned}W^{(m)} &= k_{\text{B}}T \left\{ -\frac{1}{2}(2a - 1) \ln \lambda_m + \int \left[a \left(\ln P(Q^2) - \ln P(\mathbf{Q} \cdot \mathbf{C}^{(m)} \cdot \mathbf{Q}) \right) \right. \right. \\ &\quad \left. \left. + (1 - a) \left(\ln P(Q^2) - \ln P(\mathbf{Q} \cdot (\mathbf{C}^{(m)})^{-1} \cdot \mathbf{Q}) \right) \right] P(Q^2) d\mathbf{Q} \right\}.\end{aligned}\tag{46}$$

We now choose a spherical coordinate frame $\{Q, \theta, \phi\}$, whose axes coincide with the eigenvectors of the tensor $\mathbf{C}^{(m)}$ and the z -axis is directed along the eigenvector with the eigenvalue that differs from unity. The quadratic forms $\mathbf{Q} \cdot \mathbf{C}^{(m)} \cdot \mathbf{Q}$ and $\mathbf{Q} \cdot (\mathbf{C}^{(m)})^{-1} \cdot \mathbf{Q}$ are calculated as follows:

$$\mathbf{Q} \cdot \mathbf{C}^{(m)} \cdot \mathbf{Q} = Q^2(\sin^2 \theta + \lambda_m \cos^2 \theta), \quad \mathbf{Q} \cdot (\mathbf{C}^{(m)})^{-1} \cdot \mathbf{Q} = Q^2(\sin^2 \theta + \frac{1}{\lambda_m} \cos^2 \theta).$$

Substituting these expressions into Eq. (46) and performing integration over ϕ , we find that

$$\begin{aligned}W^{(m)} &= k_{\text{B}}T \left\{ -\frac{1}{2}(2a - 1) \ln \lambda_m + 2\pi \int_0^\infty P(Q^2) Q^2 dQ \int_0^\pi \sin \theta d\theta \right. \\ &\quad \times \left[a \left(\ln P(Q^2) - \ln P(Q^2(\sin^2 \theta + \lambda_m \cos^2 \theta)) \right) \right. \\ &\quad \left. \left. + (1 - a) \left(\ln P(Q^2) - \ln P(Q^2(\sin^2 \theta + \lambda_m^{-1} \cos^2 \theta)) \right) \right] \right\}.\end{aligned}$$

Introducing the new variable $z = \cos \theta$, we obtain

$$\begin{aligned}W^{(m)} &= k_{\text{B}}T \left\{ -\frac{1}{2}(2a - 1) \ln \lambda_m + 4\pi \int_0^\infty P(Q^2) Q^2 dQ \right. \\ &\quad \times \int_0^1 \left[a \left(\ln P(Q^2) - \ln P(Q^2(1 + (\lambda_m - 1)z^2)) \right) \right. \\ &\quad \left. \left. + (1 - a) \left(\ln P(Q^2) - \ln P(Q^2(1 + (\lambda_m^{-1} - 1)z^2)) \right) \right] dz \right\}.\end{aligned}\tag{47}$$

Our aim now is to calculate the strain energy W of a self-avoiding chain with distribution function (3) by using Eqs. (45) and (47).

6 The stretched exponential distribution function

Equations Eqs. (3) and (34) imply that

$$P(r) = p^0 \exp\left[-\beta\left(\frac{r}{R^2}\right)^\delta\right], \quad (48)$$

where the pre-factor p^0 is given by Eq. (5). Substitution of Eq. (48) into Eqs. (45) and (47) results in (see Appendix C for detail)

$$\begin{aligned} W = & k_{\text{B}}T \left\{ -\frac{1}{2}(2a-1) \ln(\lambda_1 \lambda_2 \lambda_3) + \left[a \sum_{m=1}^3 \left(\frac{1}{6} \lambda_m^{\frac{5}{2}} + \frac{5}{24} \lambda_m^{\frac{3}{2}} + \frac{5}{16} \lambda_m^{\frac{1}{2}} \right) \right. \right. \\ & \left. \left. + (1-a) \sum_{m=1}^3 \left(\frac{1}{6} \lambda_m^{-\frac{5}{2}} + \frac{5}{24} \lambda_m^{-\frac{3}{2}} + \frac{5}{16} \lambda_m^{-\frac{1}{2}} \right) - \frac{33}{16} \right] + \tilde{W} \right\}, \quad (49) \end{aligned}$$

where

$$\tilde{W} = \frac{5}{16} \left[\sum_{m=1}^3 \left(aG(\lambda_m) + (1-a)G(\lambda_m^{-1}) \right) - 3 \right]. \quad (50)$$

The function $G(z)$ in Eq. (50) reads

$$G(z) = \begin{cases} (1-z)^{-\frac{1}{2}} \arcsin(1-z)^{\frac{1}{2}}, & z < 1, \\ 1, & z = 1, \\ (z-1)^{-\frac{1}{2}} \ln(z^{\frac{1}{2}} + (z-1)^{\frac{1}{2}}), & z > 1. \end{cases} \quad (51)$$

This function does not exceed $\frac{\pi}{2}$ for any $z \geq 0$, and it monotonically decreases (however, rather weakly) with z and vanishes as $z \rightarrow \infty$.

At finite strains, when the norm of the Cauchy–Green tensor \mathbf{C} is large compared with unity, the last term in Eq. (49) may be disregarded. Under this assumption, Eq. (49) is reduced to the constitutive equation of the Ogden medium with a special choice of material parameters.

$$\begin{aligned} W_0 = & k_{\text{B}}T \left[-\frac{1}{2}(2a-1) \ln J_3 + a \sum_{m=1}^3 \left(\frac{1}{6} \lambda_m^{\frac{5}{2}} + \frac{5}{24} \lambda_m^{\frac{3}{2}} + \frac{5}{16} \lambda_m^{\frac{1}{2}} - \frac{11}{16} \right) \right. \\ & \left. + (1-a) \sum_{m=1}^3 \left(\frac{1}{6} \lambda_m^{-\frac{5}{2}} + \frac{5}{24} \lambda_m^{-\frac{3}{2}} + \frac{5}{16} \lambda_m^{-\frac{1}{2}} - \frac{11}{16} \right) \right]. \end{aligned}$$

For an incompressible network, the first term in this equality vanishes, and we obtain, in accord with Eq. (16),

$$\begin{aligned} W_0 = & k_{\text{B}}T \left[a \sum_{m=1}^3 \left(\frac{1}{6} \lambda_m^{\frac{5}{2}} + \frac{5}{24} \lambda_m^{\frac{3}{2}} + \frac{5}{16} \lambda_m^{\frac{1}{2}} - \frac{11}{16} \right) \right. \\ & \left. + (1-a) \sum_{m=1}^3 \left(\frac{1}{6} \lambda_m^{-\frac{5}{2}} + \frac{5}{24} \lambda_m^{-\frac{3}{2}} + \frac{5}{16} \lambda_m^{-\frac{1}{2}} - \frac{11}{16} \right) \right]. \quad (52) \end{aligned}$$

To demonstrate that Eq. (52) provides quite an acceptable approximation of the strain energy W for conventional loading programs, we calculate the strain energies determined by Eqs. (49) and (52) for uniaxial extension of an incompressible network,

$$\lambda_1 = k^2, \quad \lambda_2 = k^{-1}, \quad \lambda_3 = k^{-1}, \quad (53)$$

where k stands for elongation ratio, and for simple shear with

$$\lambda_1 = 1, \quad \lambda_2 = \left(1 + \frac{k^2}{2}\right) + \sqrt{\left(1 + \frac{k^2}{2}\right)^2 - 1}, \quad \lambda_3 = \left(1 + \frac{k^2}{2}\right) - \sqrt{\left(1 + \frac{k^2}{2}\right)^2 - 1},$$

where k denotes shear. For definiteness, we set $a = 0.5$. The quantities W and W_0 are plotted versus k in Figures 1 and 2. These figures show that the dimensionless strain energies $\bar{W} = W/(k_B T)$ practically coincide when they are calculated with and without the correction term \tilde{W} .

Formula (52) determines the strain energy of an individual chain. Neglecting the energy of interaction between chains (this energy is conventionally accounted for by the incompressibility condition [30]), we calculate the strain energy per unit volume of a network as the sum of strain energies of chains,

$$w_0 = \mu_1 \sum_{m=1}^3 \left(\frac{1}{6} \lambda_m^{\frac{5}{2}} + \frac{5}{24} \lambda_m^{\frac{3}{2}} + \frac{5}{16} \lambda_m^{\frac{1}{2}} - \frac{11}{16} \right) + \mu_2 \sum_{m=1}^3 \left(\frac{1}{6} \lambda_m^{-\frac{5}{2}} + \frac{5}{24} \lambda_m^{-\frac{3}{2}} + \frac{5}{16} \lambda_m^{-\frac{1}{2}} - \frac{11}{16} \right), \quad (54)$$

where

$$\mu_1 = k_B a M T, \quad \mu_2 = k_B (1 - a) M T, \quad (55)$$

and M is the number of chains per unit volume. Equation (54) involves only two coefficients, μ_1 and μ_2 , to be found by fitting observations. Our aim now is to show that constitutive law (54) correctly describes experimental data at uniaxial tension, uniaxial compression and equi-biaxial tension of elastomers.

7 Results of numerical simulation

At three-dimensional deformation of an incompressible medium without rotations, the principal Cauchy stresses σ_m are expressed in terms of the principal stretches λ_m by the formulas

$$\sigma_m = \lambda_m \frac{\partial w}{\partial \lambda_m} - \tilde{p}, \quad (56)$$

where \tilde{p} is an unknown pressure, and w is a strain energy per unit volume. Substitution of expression (54) into Eq. (56) results in

$$\sigma_m = \lambda_m \left[\mu_1 F_0(\lambda_m) - \frac{\mu_2}{\lambda_m^2} F_0\left(\frac{1}{\lambda_m}\right) \right] - \tilde{p}, \quad (57)$$

where

$$F_0(\lambda) = \frac{5}{4} \left(\frac{1}{3} \lambda^{\frac{3}{2}} + \frac{1}{4} \lambda^{\frac{1}{2}} + \frac{1}{8} \lambda^{-\frac{1}{2}} \right). \quad (58)$$

For uniaxial extension with an elongation ratio k , the principal stretches are given by Eq. (53). Excluding the pressure \tilde{p} from the condition $\sigma_2 = \sigma_3 = 0$, we find from Eq. (57) that the engineering stress $\sigma_e = \sigma_1/k$ is given by

$$\sigma_e = \frac{1}{k} \left[\mu_1 \left(k^2 F_0(k^2) - \frac{1}{k} F_0\left(\frac{1}{k}\right) \right) + \mu_2 \left(k F_0(k) - \frac{1}{k^2} F_0\left(\frac{1}{k^2}\right) \right) \right]. \quad (59)$$

For equi-biaxial deformation of an incompressible material, the principal stretches λ_m read

$$\lambda_1 = k^2, \quad \lambda_2 = k^2, \quad \lambda_3 = k^{-4}, \quad (60)$$

where k stands for elongation ratio. We substitute Eq. (60) into Eq. (57), exclude the unknown pressure \tilde{p} from the condition $\sigma_3 = 0$, and find the Cauchy stresses $\sigma_1 = \sigma_2 = \sigma$. The engineering stress $\sigma_e = \sigma/k$ is determined as

$$\sigma_e = \frac{1}{k} \left[\mu_1 \left(k^2 F_0(k^2) - \frac{1}{k^4} F_0\left(\frac{1}{k^4}\right) \right) + \mu_2 \left(k^4 F_0(k^4) - \frac{1}{k^2} F_0\left(\frac{1}{k^2}\right) \right) \right]. \quad (61)$$

Given an experimental dependence $\sigma_e(k)$, the coefficients μ_1 and μ_2 in Eqs. (59) and (61) are found by the least-squares technique from the condition of minimum of the function

$$R = \sum_{k_n} \left[\sigma_e^{\text{exp}}(k_n) - \sigma_e^{\text{num}}(k_n) \right]^2,$$

where the sum is calculated over all elongation ratios k_n at which measurements are reported, σ_e^{exp} is the stress measured in a test, and σ_e^{num} is given by Eqs. (59) and (61).

We begin with fitting the observations on uniaxial extension of natural rubber with various amounts of cross-linker tetramethylthiuram disulfide (TMTD) reported by Klüppel and Schramm [2]. The experimental data together with their approximation by Eqs. (58) and (59) are depicted in Figure 3 (where phr means parts per hundred parts of rubber). This figure shows that Eq. (59) with the only parameter μ_1 (we set $\mu_2 = 0$ to reduce the number of material constants) provides good agreement between the observations and the results of numerical simulation. The elastic modulus μ_1 is plotted versus concentration of cross-linker ϕ in Figure 4, where the experimental data are approximated by the linear dependence

$$\mu_1 = \mu_1^{(1)} \phi. \quad (62)$$

The coefficient $\mu_1^{(1)}$ in Eq. (62) is determined by the least-squares technique. Formula (62) confirms our assumption that the energy of interaction between chains in a network may be taken into account with the help of the incompressibility condition. It implies that the modulus μ_1 is proportional to the amount of cross-linker, which, in turn, is proportional to the number of chains per unit volume M , in accord with Eq. (55).

We proceed with matching the experimental data on uniaxial compression of carbon black-filled chloroprene rubber reported by Bergström and Boyce [1]. The experimental dependencies $\sigma_e(k)$ measured at various amounts of filler are depicted in Figure 5 together with their approximations by Eq. (59) with $\mu_2 = 0$. The modulus μ_1 is plotted versus concentration of filler ϕ in Figure 6. The experimental data for $\mu_1(\phi)$ are approximated by the linear dependence

$$\mu_1 = \mu_1^{(0)} + \mu_1^{(1)} \phi, \quad (63)$$

where the coefficients $\mu_1^{(0)}$ and $\mu_1^{(1)}$ are found by the least-squares method. Figure 6 demonstrates that Eq. (63), which is conventionally employed in the mechanics of composites to describe the effect of filler on the shear modulus, correctly predicts the experimental data.

Figures 3 and 5 show that the observations on natural and chloroprene rubbers at uniaxial tension and compression can be approximated by the model with $a = 1$, i.e. when averaging of the configurational free energy is performed by using the distribution function of end-to-end vectors in the deformed state. To demonstrate that this is not the rule in the general case, we fit experimental data on uniaxial tension-compression of carbon black-reinforced natural rubber reported by Hartmann et al. [9] and of polybutadiene rubber presented by Roland et al. [45]. The observations and the results of numerical analysis are depicted in Figures 7 and 8, which reveal good agreement between the experimental data and the results of simulation.

To validate the governing equations, we approximate the observations on uniaxial extension of a synthetic rubber reported by Chevalier et al. [3], find adjustable parameters μ_1 and μ_2 , calculate the engineering stress σ_e at equi-biaxial tension by Eq. (61), and compare the results of numerical simulation with the experimental data. Figure 9 demonstrates that the model provides quite an acceptable prediction of the elastic response at equi-biaxial deformation with moderate finite strains, $1.0 \leq k < 1.4$.

Figures 3 to 9 reveal that Eq. (54) with two adjustable parameters can correctly describe the mechanical response of elastomers at large deformations. It is worth noting that this assertion is not trivial (the fact that the Ogden model adequately describes observations has been confirmed by numerous experimental data in the past three decades), because the number of material constants in Eq. (54) is noticeably smaller than that in the original expression (16) for the strain energy density.

Another result to be mentioned is that the description of some experimental data by Eq. (54) is not perfect. As examples, we refer to the observations depicted in Figures 7 and 9. This conclusion may be attributed to the fact that Eq. (3) for the stretched-exponential distribution function of a self-avoiding random walk is overly simplified, and more sophisticated formula (6) should be used. Our aim now is to develop governing equations for a network of self-avoiding chains with the des Cloizeaux distribution function of end-to-end vectors.

8 The des Cloizeaux distribution function

For a SARW with the distribution function (6), the function $P(r)$ reads

$$P(r) = p^0 \left(\frac{r}{R^2} \right)^\alpha \exp \left[-\beta \left(\frac{r}{R^2} \right)^\delta \right], \quad (64)$$

where δ is given by Eq. (10), and p^0 is determined by Eq. (7). Substitution of expression (64) into Eqs. (45) and (47) implies that (see Appendix D for detail)

$$\begin{aligned} W = & k_B T \left\{ -(2a - 1) \left(\alpha + \frac{1}{2} \right) \ln(\lambda_1 \lambda_2 \lambda_3) \right. \\ & + \left(1 + \frac{2}{3} \alpha \right) \left[a \sum_{m=1}^3 \left(\frac{1}{6} \lambda_m^{\frac{5}{2}} + \frac{5}{24} \lambda_m^{\frac{3}{2}} + \frac{5}{16} \lambda_m^{\frac{1}{2}} - \frac{11}{16} \right) \right. \\ & + (1 - a) \sum_{m=1}^3 \left(\frac{1}{6} \lambda_m^{-\frac{5}{2}} + \frac{5}{24} \lambda_m^{-\frac{3}{2}} + \frac{5}{16} \lambda_m^{-\frac{1}{2}} - \frac{11}{16} \right) \left. \right] + \tilde{W} \\ & \left. - 2\alpha \sum_{m=1}^3 \left(a H(\lambda_m) + (1 - a) H(\lambda_m^{-1}) \right) \right\}, \quad (65) \end{aligned}$$

where

$$\begin{aligned} H(z) &= \frac{\arctan \sqrt{z-1}}{\sqrt{z-1}} - 1, & z > 1, \\ H(z) &= 0, & z = 1, \\ H(z) &= \frac{1}{2\sqrt{1-z}} \ln \frac{1+\sqrt{1-z}}{1-\sqrt{1-z}} - 1, & z < 1. \end{aligned} \quad (66)$$

The function $H(z)$ monotonically decreases in $(0, \infty)$ and tends to -1 when $z \rightarrow \infty$. The graph of this function is presented in Figure 10.

Using notation (52) and neglecting the small term \tilde{W} compared with W_0 , we find from Eq. (65) that

$$W = \left(1 + \frac{2}{3} \alpha \right) W_0 - k_B T \left[(2a - 1) \left(\alpha + \frac{1}{2} \right) \ln J_3 + 2\alpha \sum_{m=1}^3 \left(a H(\lambda_m) + (1 - a) H(\lambda_m^{-1}) \right) \right]. \quad (67)$$

In the tensor form, Eq. (67) reads (see Appendix E)

$$\begin{aligned} \frac{W}{k_B T} &= -(2a-1)\left(\alpha + \frac{1}{2}\right) \ln J_3 + \left(1 + \frac{2}{3}\alpha\right) \left[a \left(\frac{1}{6} \mathcal{I}_1(\mathbf{C}_e^{\frac{5}{2}}) + \frac{5}{24} \mathcal{I}_1(\mathbf{C}_e^{\frac{3}{2}}) + \frac{5}{16} \mathcal{I}_1(\mathbf{C}_e^{\frac{1}{2}}) \right) \right. \\ &\quad \left. + (1-a) \left(\frac{1}{6} \mathcal{I}_1(\mathbf{C}_e^{-\frac{5}{2}}) + \frac{5}{24} \mathcal{I}_1(\mathbf{C}_e^{-\frac{3}{2}}) + \frac{5}{16} \mathcal{I}_1(\mathbf{C}_e^{-\frac{1}{2}}) \right) - \frac{33}{16} \right] - \alpha \sum_{k=1}^{\infty} \frac{2^{k+1}}{2k+1} \\ &\quad \times \left[a(-1)^k \mathcal{I}_1(\mathbf{E}_C^k) + (1-a) \mathcal{I}_1(\mathbf{E}_A^k) \right], \end{aligned} \quad (68)$$

where

$$\mathbf{E}_C = \frac{1}{2}(\mathbf{C} - \mathbf{I}), \quad \mathbf{E}_A = \frac{1}{2}(\mathbf{I} - \mathbf{C}^{-1}) \quad (69)$$

are the Cauchy and Almansi strain tensors, respectively.

At volume-preserving deformations, Eqs. (52) and (67) imply that

$$\begin{aligned} W &= k_B T \left\{ a \sum_{m=1}^3 \left[\left(1 + \frac{2}{3}\alpha\right) \left(\frac{1}{6} \lambda_m^{\frac{5}{2}} + \frac{5}{24} \lambda_m^{\frac{3}{2}} + \frac{5}{16} \lambda_m^{\frac{1}{2}} - \frac{11}{16} \right) - 2\alpha H(\lambda_m) \right] \right. \\ &\quad \left. + (1-a) \sum_{m=1}^3 \left[\left(1 + \frac{2}{3}\alpha\right) \left(\frac{1}{6} \lambda_m^{-\frac{5}{2}} + \frac{5}{24} \lambda_m^{-\frac{3}{2}} + \frac{5}{16} \lambda_m^{-\frac{1}{2}} - \frac{11}{16} \right) - 2\alpha H(\lambda_m^{-1}) \right] \right\}. \end{aligned}$$

Applying the same approach that has been employed in Section 6, that is neglecting the energy of interaction between chains and assuming the strain energy of a network to coincide with the sum of strain energies of individual chains, we arrive at the formula for the strain energy density per unit volume of an incompressible network

$$\begin{aligned} w &= a \sum_{m=1}^3 \left[\mu_1 \left(\frac{1}{6} \lambda_m^{\frac{5}{2}} + \frac{5}{24} \lambda_m^{\frac{3}{2}} + \frac{5}{16} \lambda_m^{\frac{1}{2}} - \frac{11}{16} \right) - \mu_2 H(\lambda_m) \right] \\ &\quad + (1-a) \sum_{m=1}^3 \left[\mu_1 \left(\frac{1}{6} \lambda_m^{-\frac{5}{2}} + \frac{5}{24} \lambda_m^{-\frac{3}{2}} + \frac{5}{16} \lambda_m^{-\frac{1}{2}} - \frac{11}{16} \right) - \mu_2 H(\lambda_m^{-1}) \right], \end{aligned} \quad (70)$$

where we set

$$\mu_1 = k_B T \left(1 + \frac{2}{3}\alpha\right) M, \quad \mu_2 = 2k_B T \alpha M. \quad (71)$$

In the general case, constitutive law (70) involves 3 adjustable parameters, a , μ_1 and μ_2 . It is worth noting a substantial difference between the parameter μ_2 in Eqs. (55) and (70). According to the physical meaning of the quantity μ_2 in Eq. (55), this parameter should always be positive. On the contrary, the parameter μ_2 in Eq. (70) may be positive [this corresponds to the case $\alpha > 0$ in Eq. (6)], as well as negative [when $\alpha \in (-\frac{3}{2}, 0)$]. The latter condition ensures that the integral of the function $P(Q^2)$ over the entire space converges.

Our aim now is to develop stress-strain relations for finite deformations of an incompressible network, to derive explicit expressions for the principal Cauchy stresses, and to compare experimental data on elastomers with results of numerical analysis.

9 Fitting of observations

It follows from Eq. (70) that

$$\frac{\partial w}{\partial \lambda_m} = a \left[\mu_1 F_0(\lambda_m) + \mu_2 F(\lambda_m) \right] - \frac{1-a}{\lambda_m^2} \left[\mu_1 F_0\left(\frac{1}{\lambda_m}\right) + \mu_2 F\left(\frac{1}{\lambda_m}\right) \right], \quad (72)$$

where $F_0(z)$ is given by Eq. (58), and

$$F(z) = -\frac{dH}{dz}(z) = \begin{cases} \frac{1}{2(z-1)} \left(\frac{\arctan \sqrt{z-1}}{\sqrt{z-1}} - \frac{1}{z} \right), & z > 1, \\ \frac{1}{3}, & z = 1, \\ \frac{1}{2(1-z)} \left(\frac{1}{z} - \frac{1}{2\sqrt{1-z}} \ln \frac{1+\sqrt{1-z}}{1-\sqrt{1-z}} \right), & z < 1. \end{cases} \quad (73)$$

The function $F(z)$ is positive and continuous at any $z > 0$, it monotonically decreases with z and vanishes when $z \rightarrow \infty$. The graph of the function $F(z)$ is depicted in Figure 10.

Substitution of expression (72) into Eq. (57) results in the formula

$$\sigma_m = -p + \mu_1 \lambda_m \left[a F_0(\lambda_m) - \frac{1-a}{\lambda_m^2} F_0\left(\frac{1}{\lambda_m}\right) \right] + \mu_2 \lambda_m \left[a F(\lambda_m) - \frac{1-a}{\lambda_m^2} F\left(\frac{1}{\lambda_m}\right) \right]. \quad (74)$$

According to Eq. (74), at uniaxial extension with an elongation ratio k , see Eq. (53), the engineering stress σ_e is given by

$$\begin{aligned} \sigma_e = & \frac{1}{k} \left\{ \mu_1 \left[a \left(k^2 F_0(k^2) - \frac{1}{k} F_0\left(\frac{1}{k}\right) \right) + (1-a) \left(k F_0(k) - \frac{1}{k^2} F_0\left(\frac{1}{k^2}\right) \right) \right] \right. \\ & \left. + \mu_2 \left[a \left(k^2 F(k^2) - \frac{1}{k} F\left(\frac{1}{k}\right) \right) + (1-a) \left(k F(k) - \frac{1}{k^2} F\left(\frac{1}{k^2}\right) \right) \right] \right\}. \end{aligned} \quad (75)$$

At equi-biaxial extension with an elongation ratio k , see Eq. (60), the engineering stress reads

$$\begin{aligned} \sigma_e = & \frac{1}{k} \left\{ \mu_1 \left[a \left(k^2 F_0(k^2) - \frac{1}{k^4} F_0\left(\frac{1}{k^4}\right) \right) + (1-a) \left(k^4 F_0(k^4) - \frac{1}{k^2} F_0\left(\frac{1}{k^2}\right) \right) \right] \right. \\ & \left. + \mu_2 \left[a \left(k^2 F(k^2) - \frac{1}{k^4} F\left(\frac{1}{k^4}\right) \right) + (1-a) \left(k^4 F(k^4) - \frac{1}{k^2} F\left(\frac{1}{k^2}\right) \right) \right] \right\}. \end{aligned} \quad (76)$$

At biaxial extension with elongation ratios k_1 and k_2 ,

$$\lambda_1 = k_1^2, \quad \lambda_2 = k_2^2, \quad \lambda_3 = (k_1 k_2)^{-2}, \quad (77)$$

the engineering stresses $\sigma_{e,1} = \sigma_1/k_1$ and $\sigma_{e,2} = \sigma_2/k_2$ are determined by

$$\begin{aligned} \sigma_{e,1} = & \frac{1}{k_1} \left\{ \mu_1 \left[a \left(k_1^2 F_0(k_1^2) - \frac{1}{k_1^2 k_2^2} F_0\left(\frac{1}{k_1^2 k_2^2}\right) \right) + (1-a) \left(k_1^2 k_2^2 F_0(k_1^2 k_2^2) - \frac{1}{k_1^2} F_0\left(\frac{1}{k_1^2}\right) \right) \right] \right. \\ & \left. + \mu_2 \left[a \left(k_1^2 F(k_1^2) - \frac{1}{k_1^2 k_2^2} F\left(\frac{1}{k_1^2 k_2^2}\right) \right) + (1-a) \left(k_1^2 k_2^2 F(k_1^2 k_2^2) - \frac{1}{k_1^2} F\left(\frac{1}{k_1^2}\right) \right) \right] \right\}, \\ \sigma_{e,2} = & \frac{1}{k_2} \left\{ \mu_1 \left[a \left(k_2^2 F_0(k_2^2) - \frac{1}{k_1^2 k_2^2} F_0\left(\frac{1}{k_1^2 k_2^2}\right) \right) + (1-a) \left(k_1^2 k_2^2 F_0(k_1^2 k_2^2) - \frac{1}{k_2^2} F_0\left(\frac{1}{k_2^2}\right) \right) \right] \right. \\ & \left. + \mu_2 \left[a \left(k_2^2 F(k_2^2) - \frac{1}{k_1^2 k_2^2} F\left(\frac{1}{k_1^2 k_2^2}\right) \right) + (1-a) \left(k_1^2 k_2^2 F(k_1^2 k_2^2) - \frac{1}{k_2^2} F\left(\frac{1}{k_2^2}\right) \right) \right] \right\}. \end{aligned} \quad (78)$$

Our purpose now is to apply Eqs. (75), (76) and (78) in order to approximate observations at uniaxial, equi-biaxial and biaxial extension of elastomers. To find the constants a , μ_1 and μ_2 , we divide the interval $[0, 1]$, where the parameter a is located, into I subintervals by the points $a^{(i)} = i\Delta a$ ($i = 1, \dots, I-1$) with $\Delta a = 1/I$. Given $a^{(i)}$, the coefficients μ_1 and μ_2 are found by the least-squares method from the condition of minimum of the function R . The ‘‘best-fit’’ parameter a is determined from the condition of minimum of this function on the set $\{a^{(i)}\}$.

We begin with the experimental data on uniaxial tension–compression of two types of carbon black-filled natural rubber. The experimental stress–strain curves reported by Roland et al. [45]

are depicted in Figure 11 together with their approximations by Eq. (75). This figure shows that Eq. (75) with $a = 1$ (averaging with respect to the distribution function in the actual state) and $\mu_2 < 0$ (a weakly-singular at $Q = 0$ des Cloizeaux distribution function) ensures good agreement with the observations.

The latter peculiarity of the model appear to be rather typical. To confirm this assertion, we approximate the experimental data on equi-biaxial extension of natural rubber reported by James et al. [46]. The observations together with their fit are plotted in Figure 12. It is worth noting some similarity between the material constants determined by matching the experimental data for three different types of natural rubber: the modulus μ_1 is of order of $(2 \div 4) \cdot 10^{-2}$ MPa, and the modulus $|\mu_2|$ is of order of $3 \div 7$ MPa.

To validate the model, we analyze observations on biaxial extension of poly(dimethylsiloxane) network (volume fraction of PDMS $\phi = 0.463$) reported by Kawamura et al. [47]. The adjustable parameters are found by matching the dependence $\sigma_{e,2}(k_2)$ at $k_1 = 1.9$. Afterwards, the functions $\sigma_{e,2}(k_2)$ at $k_1 = 1.1, 1.3, 1.5$ and 1.7 are predicted numerically, and the results of simulation are compared with the experimental data. Figure 13 shows excellent agreement between the observations and the model predictions.

10 The elastic modulus of self-avoiding chains

We return now to expressions (52) and (70) for the strain energy of an incompressible network of self-avoiding chains in order to assess the effect of excluded volume on the elastic modulus per chain at small deformations.

For a network of Gaussian chains under uniaxial tension with an elongation ratio k , the engineering stress σ_e is given by the conventional formula [22]

$$\sigma_e = (\mu_1 + \mu_2 k^{-1})(k - k^{-2}),$$

where

$$\mu_1 = \frac{1}{2} k_B a T M, \quad \mu_2 = \frac{1}{2} k_B (1 - a) T M. \quad (79)$$

At small strains, when $k = 1 + \epsilon$ with $\epsilon \ll 1$, we obtain $\sigma_e = 3(\mu_1 + \mu_2)\epsilon$. The Young's modulus of a network E is given by

$$E = \frac{\sigma_e}{\epsilon}. \quad (80)$$

Substituting expressions (79) into Eq. (80) and introducing the Young's modulus per chain as

$$E_c = \frac{E}{M}, \quad (81)$$

we arrive at the formula

$$E_c = \frac{3}{2} k_B T. \quad (82)$$

For a network with strain energy density (52), the engineering stress at uniaxial extension is given by Eqs. (58) and (59). Omitting simple algebra, we find that at small strains,

$$\sigma_e = \frac{305}{64} (\mu_1 + \mu_2) \epsilon.$$

It follows from this equality and Eqs. (55), (80), and (81) that

$$E_c = \frac{305}{64} k_B T.$$

Combining Eq. (82) and this equation, we arrive at the formula

$$\frac{E_c^{\text{Ogden}}}{E_c^{\text{Gauss}}} = \frac{305}{96} \approx 3.1771, \quad (83)$$

which means that the “rigidity” of a self-avoiding chain exceeds that of a Gaussian chain by a factor of three (approximately). A reason for the anesthetic ratio in Eq. (83) is that the contribution of \tilde{W} into the strain energy density W is neglected.

We proceed with the evaluation of the Young’s modulus for a chain whose distribution function is described by des Cloizeaux law (6). It follows from Eq. (73) that

$$\frac{dF}{dz}(1) = -\frac{2}{5}.$$

Using this expression, we find from Eqs. (58) and (75) that at uniaxial extension with small strains,

$$E = \frac{305}{64}\mu_1 - \frac{1}{5}\mu_2.$$

Substitution of expressions (71) into this formula results in

$$E_c = \left(\frac{305}{64} + \frac{1333}{480}\alpha \right) k_B T.$$

It follows from this equality and Eqs. (82) and (83) that

$$\frac{E_c^{\text{desCloizeaux}}}{E_c^{\text{Gauss}}} = \frac{E_c^{\text{Ogden}}}{E_c^{\text{Gauss}}} + \frac{1333}{720}\alpha \approx 3.1771 + 1.8514\alpha. \quad (84)$$

Equations (83) and (84) imply that the Young’s modulus per chain E_c is independent of the characteristic length R and the exponent β in Eqs. (3) and (6), and it increases with α in Eq. (6) being proportional to 2α (approximately).

Qualitatively, the latter conclusion is not surprising. The growth of α is tantamount to the fact that the tail of distribution function (6) becomes thicker, while the latter implies (within the conventional “force–stretch” approach in the statistical mechanics of polymers) an enhancement of the rigidity of chains.

To assess the Young’s modulus found in our approximation of the observations, we use Eq. (71), which implies that

$$\alpha = -\frac{1}{2} \left(\frac{1}{3} - \frac{\mu_1}{\mu_2} \right)^{-1}.$$

Using the results presented in Figures 11 to 13, we find that $\alpha = -1.46$ (Figure 11) and -1.48 (Figure 12) for natural rubber, and -1.49 (Figure 13) for PDMS. For these parameters, Eq. (84) implies that the ratio $E_c^{\text{desCloizeaux}}/E_c^{\text{Gauss}}$ is close to 0.43 for PDMS and is located between 0.47 and 0.49 for natural rubber. The difference between these quantities and the ratio of elastic moduli predicted by Eq. (83) may provide an explanation, why constitutive law (52) does not provide an adequate approximation of the observations depicted in Figures 11 to 13.

11 Concluding remarks

A general expression has been derived for the strain energy of a polymer chain with an arbitrary distribution function of end-to-end vectors. This formula has been applied to determine the

strain energy of a chain that is modeled as a self-avoiding random walk. By using three-chain approximation method, we have found that the strain energy of a network of chains with the stretched exponential distribution function coincides with the Ogden law with a special choice of adjustable parameters. In this case, the stress–strain relations involve only two material constants that are found by matching experimental data at uniaxial tension, uniaxial compression and equi-biaxial tension of elastomers. Good agreement is demonstrated between the observations and the results of numerical simulation.

For the generalized stretched-exponential distribution function (the des Cloizeaux law), a new expression is developed for the strain energy density of a network. In this case, the governing equations contain three material constants to be found by matching observations. It is shown that the stress–strain relations provide quite an acceptable fit of observations at uniaxial and bi-axial extension of filled elastomers even when the Ogden relations poorly approximate the experimental data. It is demonstrated that the latter case corresponds to rubber-like materials, whose elastic modulus at uniaxial extension is lower than that for Gaussian chains.

Appendix A

To derive Eq. (37), we, first, choose a spherical coordinate frame $\{Q, \theta, \phi\}$, whose axes coincide with the eigenvectors of the symmetric tensor \mathbf{B}^{-1} . In the spherical coordinates, the quadratic form $\mathbf{Q} \cdot \mathbf{B}^{-1} \cdot \mathbf{Q}$ is given by

$$\mathbf{Q} \cdot \mathbf{B}^{-1} \cdot \mathbf{Q} = Q^2 \left[(B^{-1})_1 \sin^2 \theta \cos^2 \phi + (B^{-1})_2 \sin^2 \theta \sin^2 \phi + (B^{-1})_3 \cos^2 \theta \right],$$

where $(B^{-1})_m$ ($m = 1, 2, 3$) are eigenvalues of the tensor \mathbf{B}^{-1} . The integral on the left-hand side of Eq. (37) reads

$$\int \ln P(\mathbf{Q} \cdot \mathbf{B}^{-1} \cdot \mathbf{Q}) P(Q^2) d\mathbf{Q} = \int_0^\infty P(Q^2) Q^2 dQ \int_0^\pi \sin \theta d\theta \int_0^{2\pi} \left[(B^{-1})_1 \sin^2 \theta \cos^2 \phi + (B^{-1})_2 \sin^2 \theta \sin^2 \phi + (B^{-1})_3 \cos^2 \theta \right] d\phi.$$

We now choose the spherical coordinate frame $\{Q', \theta', \phi'\}$, whose axes coincide with the eigenvectors of the symmetric tensor \mathbf{C}^{-1} . Repeating the above calculations, we find the integral on the right-hand side of Eq. (37),

$$\int \ln P(\mathbf{Q} \cdot \mathbf{C}^{-1} \cdot \mathbf{Q}) P(Q^2) d\mathbf{Q} = \int_0^\infty P(Q'^2) Q'^2 dQ' \int_0^\pi \sin \theta' d\theta' \int_0^{2\pi} \left[(C^{-1})_1 \sin^2 \theta' \cos^2 \phi' + (C^{-1})_2 \sin^2 \theta' \sin^2 \phi' + (C^{-1})_3 \cos^2 \theta' \right] d\phi',$$

where $(C^{-1})_m$ ($m = 1, 2, 3$) are eigenvalues of the tensor \mathbf{C}^{-1} . Bearing in mind that the eigenvalues of the Cauchy-Green tensors \mathbf{B}^{-1} and \mathbf{C}^{-1} coincide, we conclude from these relations that Eq. (37) is satisfied.

Appendix B

We begin with transformation of the term

$$\int \ln P(\mathbf{Q} \cdot \mathbf{C} \cdot \mathbf{Q}) P(Q^2) d\mathbf{Q} = \frac{3}{2} \ln \frac{3}{2\pi b^2} - \frac{3}{2b^2} \left(\frac{3}{2\pi b^2} \right)^{\frac{3}{2}} \int (\mathbf{Q} \cdot \mathbf{C} \cdot \mathbf{Q}) \exp\left(-\frac{3Q^2}{2b^2}\right) d\mathbf{Q}. \quad (\text{B-1})$$

In spherical coordinates $\{Q, \theta, \phi\}$ directed along the eigenvectors of the symmetrical tensor \mathbf{C} , the integral in Eq. (B-1) is presented as

$$\int (\mathbf{Q} \cdot \mathbf{C} \cdot \mathbf{Q}) \exp\left(-\frac{3Q^2}{2b^2}\right) d\mathbf{Q} = \int_0^\infty Q^4 \exp\left(-\frac{3Q^2}{2b^2}\right) dQ \int_0^\pi \sin \theta d\theta \int_0^{2\pi} \left[\lambda_1 \sin^2 \theta \cos^2 \phi + \lambda_2 \sin^2 \theta \sin^2 \phi + \lambda_3 \cos^2 \theta \right] d\phi,$$

where λ_m ($m = 1, 2, 3$) are eigenvalues of the tensor \mathbf{C} . The integrals on the right-hand side of this equality are calculated explicitly,

$$\int_0^\infty Q^4 \exp\left(-\frac{3Q^2}{2b^2}\right) dQ = 3 \left(\frac{\pi}{2} \right)^{\frac{1}{2}} \left(\frac{b^2}{3} \right)^{\frac{5}{2}},$$

$$\int_0^\pi \sin \theta d\theta \int_0^{2\pi} \left[\lambda_1 \sin^2 \theta \cos^2 \phi + \lambda_2 \sin^2 \theta \sin^2 \phi + \lambda_3 \cos^2 \theta \right] d\phi = \frac{4\pi}{3} J_1.$$

Substitution of these expressions into Eq. (B-1) results in

$$\int \ln P(\mathbf{Q} \cdot \mathbf{C} \cdot \mathbf{Q}) P(Q^2) d\mathbf{Q} = \frac{3}{2} \ln \frac{3}{2\pi b^2} - \frac{1}{2} J_1. \quad (\text{B-2})$$

Bearing in mind that $P(Q^2) = P(\mathbf{Q} \cdot \mathbf{I} \cdot \mathbf{Q})$, we find from this equality that

$$\int \ln P(Q^2) P(Q^2) d\mathbf{Q} = \frac{3}{2} \ln \frac{3}{2\pi b^2} - \frac{3}{2}. \quad (\text{B-3})$$

Equation (39) follows from Eqs. (B-2) and (B-3).

Appendix C

Substitution of Eq. (48) into Eq. (47) implies that

$$\begin{aligned} W^{(m)} = & k_{\text{B}} T \left\{ -\frac{1}{2} (2a-1) \ln \lambda_m + K \left[\int_0^1 \left(a(1 + (\lambda_m - 1)z^2)^\delta \right. \right. \right. \\ & \left. \left. \left. + (1-a)(1 + (\lambda_m^{-1} - 1)z^2)^\delta \right) dz - 1 \right] \right\}, \end{aligned} \quad (\text{C-1})$$

where

$$K = 4\pi\beta P_0 \int_0^\infty \exp\left[-\beta\left(\frac{Q}{R}\right)^{2\delta}\right] \left(\frac{Q}{R}\right)^{2\delta} Q^2 dQ.$$

Combining this equality with Eq. (5) and introducing the new variable $r = Q/R$, we find that

$$K = \beta \frac{\int_0^\infty \exp(-\beta r^3) r^5 dr}{\int_0^\infty \exp(-\beta r^3) r^2 dr}.$$

We set $z = \beta^{\frac{1}{3}} r$ in this equality and obtain

$$K = \frac{\int_0^\infty \exp(-z^3) z^5 dz}{\int_0^\infty \exp(-z^3) z^2 dz}.$$

The ratio of the integrals is easily calculated by integration by parts,

$$K = 1. \quad (\text{C-2})$$

Substitution of expression (C-2) into Eq. (C-1) results in

$$\begin{aligned} W^{(m)} = & k_{\text{B}} T \left\{ -\frac{1}{2} (2a-1) \ln \lambda_m + \left[\int_0^1 \left(a(1 + (\lambda_m - 1)z^2)^\delta \right. \right. \right. \\ & \left. \left. \left. + (1-a)(1 + (\lambda_m^{-1} - 1)z^2)^\delta \right) dz - 1 \right] \right\}. \end{aligned} \quad (\text{C-3})$$

To find an analytical expression for the function $W^{(m)}$, it is necessary to calculate the integral

$$L(\mu, \delta) = \int_0^1 (1 + \mu z^2)^\delta dz \quad (\text{C-4})$$

for $\mu = \lambda_m - 1$ and $\mu = \lambda_m^{-1} - 1$, and for δ given by Eq. (10). We begin with the case $\mu > 0$. Integration by parts implies that

$$\int (1 + \mu z^2)^{\frac{5}{2}} dz = \frac{1}{6} \left[z(1 + \mu z^2)^{\frac{5}{2}} + 5 \int (1 + \mu z^2)^{\frac{3}{2}} dz \right].$$

It follows from this formula that

$$L(\mu, \frac{5}{2}) = \frac{1}{6} \left[(1 + \mu)^{\frac{5}{2}} + 5L(\mu, \frac{3}{2}) \right], \quad (\text{C-5})$$

where the function L is given by Eq. (C-4). Applying integration by parts to the new integral, we obtain

$$\int (1 + \mu z^2)^{\frac{3}{2}} dz = \frac{1}{4} \left[z(1 + \mu z^2)^{\frac{3}{2}} + 3 \int (1 + \mu z^2)^{\frac{1}{2}} dz \right],$$

which results in

$$L(\mu, \frac{3}{2}) = \frac{1}{4} \left[(1 + \mu)^{\frac{3}{2}} + 3L(\mu, \frac{1}{2}) \right]. \quad (\text{C-6})$$

It is easy to check that

$$\int (1 + \mu z^2)^{\frac{1}{2}} dz = \frac{1}{2} \left[z\sqrt{1 + \mu z^2} + \frac{1}{\sqrt{\mu}} \ln(\sqrt{\mu}z + \sqrt{1 + \mu z^2}) \right].$$

It follows from this equality that

$$L(\mu, \frac{1}{2}) = \frac{1}{2} \left[\sqrt{1 + \mu} + \frac{1}{\sqrt{\mu}} \ln(\sqrt{\mu} + \sqrt{1 + \mu}) \right]. \quad (\text{C-7})$$

Combination of Eqs. (C-5) to (C-7) yields

$$L(\mu, \frac{5}{2}) = \frac{1}{6}(1 + \mu)^{\frac{5}{2}} + \frac{5}{24}(1 + \mu)^{\frac{3}{2}} + \frac{5}{16}(1 + \mu)^{\frac{1}{2}} + \frac{5}{16\sqrt{\mu}} \ln(\sqrt{\mu} + \sqrt{1 + \mu}). \quad (\text{C-8})$$

Returning to the initial notation, we find from Eqs. (C-4) and (C-8) that

$$\begin{aligned} \int_0^1 (1 + (\lambda_m - 1)z^2)^{\frac{5}{2}} dz &= \frac{1}{6}\lambda_m^{\frac{5}{2}} + \frac{5}{24}\lambda_m^{\frac{3}{2}} + \frac{5}{16}\lambda_m^{\frac{1}{2}} + \frac{5}{16}(\lambda_m - 1)^{-\frac{1}{2}} \\ &\quad \times \ln\left(\lambda_m^{\frac{1}{2}} + (\lambda_m - 1)^{\frac{1}{2}}\right) \quad (\lambda_m > 1). \end{aligned} \quad (\text{C-9})$$

We now consider the case $\mu < 0$, set $\mu_1 = -\mu$, and calculate the integral

$$L_1(\mu_1, \frac{5}{2}) = \int_0^1 (1 - \mu_1 z^2)^{\frac{5}{2}} dz \quad (\mu_1 > 0).$$

Repeating the above transformations, we find that

$$\begin{aligned} L_1(\mu_1, \frac{5}{2}) &= \frac{1}{6} \left[(1 - \mu_1)^{\frac{5}{2}} + 5L_1(\mu_1, \frac{3}{2}) \right], \\ L_1(\mu_1, \frac{3}{2}) &= \frac{1}{4} \left[(1 - \mu_1)^{\frac{3}{2}} + 3L_1(\mu_1, \frac{1}{2}) \right], \\ L_1(\mu_1, \frac{1}{2}) &= \frac{1}{2} \left[(1 - \mu_1)^{\frac{1}{2}} + \frac{1}{\sqrt{\mu_1}} \arcsin \sqrt{\mu_1} z \right]. \end{aligned} \quad (\text{C-10})$$

To develop the latter equality, we use the formula

$$\int (1 - \mu_1 z^2)^{\frac{1}{2}} dz = \frac{1}{2} \left[z\sqrt{1 - \mu_1 z^2} + \frac{1}{\mu_1} \arcsin \sqrt{\mu_1} z \right].$$

It follows from Eq. (C-10) that

$$L_1(\mu_1, \frac{5}{2}) = \frac{1}{6}(1 - \mu_1)^{\frac{5}{2}} + \frac{5}{24}(1 - \mu_1)^{\frac{3}{2}} + \frac{5}{16}(1 - \mu_1)^{\frac{1}{2}} + \frac{5}{16\sqrt{\mu_1}} \arcsin \sqrt{\mu_1}. \quad (\text{C-11})$$

Bearing in mind that $\mu_1 = 1 - \lambda_m$, we find from Eq. (C-11) that

$$\int_0^1 (1 + (\lambda_m - 1)z^2)^{\frac{5}{2}} dz = \frac{1}{6}\lambda_m^{\frac{5}{2}} + \frac{5}{24}\lambda_m^{\frac{3}{2}} + \frac{5}{16}\lambda_m^{\frac{1}{2}} + \frac{5}{16}(1 - \lambda_m)^{-\frac{1}{2}} \\ \times \arcsin(1 - \lambda_m)^{\frac{1}{2}} \quad (\lambda_m < 1). \quad (\text{C-12})$$

It is obvious that

$$\int_0^1 (1 + (\lambda_m - 1)z^2)^{\frac{5}{2}} dz = \frac{1}{6}\lambda_m^{\frac{5}{2}} + \frac{5}{24}\lambda_m^{\frac{3}{2}} + \frac{5}{16}\lambda_m^{\frac{1}{2}} + \frac{5}{16} \quad (\lambda_m = 1). \quad (\text{C-13})$$

Substituting expressions (C-9), (C-12) and (C-13) into Eq. (C-3) and using Eq. (45), we arrive at Eqs. (49) to (51).

Appendix D

It follows from Eq. (64) that for any $m = 1, 2, 3$,

$$\begin{aligned} \ln P(Q^2) - \ln P(Q^2(1 + (\lambda_m - 1)z^2)) &= \beta \left(\frac{Q}{R}\right)^{2\delta} \left[(1 + (\lambda_m - 1)z^2)^\delta - 1 \right] \\ &\quad - \alpha \ln(1 + (\lambda_m - 1)z^2), \\ \ln P(Q^2) - \ln P(Q^2(1 + (\lambda_m^{-1} - 1)z^2)) &= \beta \left(\frac{Q}{R}\right)^{2\delta} \left[(1 + (\lambda_m^{-1} - 1)z^2)^\delta - 1 \right] \\ &\quad - \alpha \ln(1 + (\lambda_m^{-1} - 1)z^2). \end{aligned}$$

Substitution of these expressions into Eq. (47) implies that

$$W^{(m)} = \Psi_1^{(m)} - \Psi_2^{(m)} \quad (\text{D-1})$$

with

$$\begin{aligned} \Psi_1^{(m)} &= k_B T \left\{ -\frac{1}{2}(2a - 1) \ln \lambda_m + K \left[\int_0^1 \left(a(1 + (\lambda_m - 1)z^2)^\delta \right. \right. \right. \\ &\quad \left. \left. \left. + (1 - a)(1 + (\lambda_m^{-1} - 1)z^2)^\delta \right) dz - 1 \right] \right\}, \\ \Psi_2^{(m)} &= k_B T K_1 \int_0^1 \left[a \ln(1 + (\lambda_m - 1)z^2) + (1 - a) \ln(1 + (\lambda_m^{-1} - 1)z^2) \right] dz, \end{aligned} \quad (\text{D-2})$$

where we set

$$K = \frac{4\pi\beta}{R^{2\delta}} \int_0^\infty P(Q^2) Q^{2(1+\delta)} dQ, \quad K_1 = 4\pi\alpha \int_0^\infty P(Q^2) Q^2 dQ. \quad (\text{D-3})$$

Introducing the new variable $z = Q/R$ in the first equality in Eq. (D-3) and using Eq. (7) to evaluate the other equality, we find that

$$K = \beta \frac{\int_0^\infty \exp(-\beta z^3) z^{2\alpha+5} dz}{\int_0^\infty \exp(-\beta z^3) z^{2\alpha+2} dz}, \quad K_1 = \alpha. \quad (\text{D-4})$$

To determine the coefficient K , we set $y = \beta^{\frac{1}{3}} z$, which results in

$$K = \frac{\int_0^\infty \exp(-y^3) y^{2\alpha+5} dy}{\int_0^\infty \exp(-y^3) y^{2\alpha+2} dy}.$$

Calculating the integral in the nominator by parts, we arrive at the formula

$$K = 1 + \frac{2}{3}\alpha. \quad (\text{D-5})$$

The function $\Psi_1^{(m)}$ has already been found in Appendix C,

$$\begin{aligned} \Psi_1^{(m)} &= k_{\text{B}}T \left\{ -\frac{1}{2}(2a-1) \ln \lambda_m + K \left[a \left(\frac{1}{6} \lambda_m^{\frac{5}{2}} + \frac{5}{24} \lambda_m^{\frac{3}{2}} + \frac{5}{16} \lambda_m^{\frac{1}{2}} \right) + (1-a) \right. \right. \\ &\times \left. \left. \left(\frac{1}{6} \lambda_m^{-\frac{5}{2}} + \frac{5}{24} \lambda_m^{-\frac{3}{2}} + \frac{5}{16} \lambda_m^{-\frac{1}{2}} \right) + \frac{5}{16} \left(aG(\lambda_m) + (1-a)G(\lambda_m^{-1}) \right) - 1 \right] \right\}. \end{aligned} \quad (\text{D-6})$$

To determine the function $\Psi_2^{(m)}$, we introduce the notation

$$M(\mu) = \int_0^1 \ln(1 + \mu z^2) dz \quad (\text{D-7})$$

and calculate the function $M(\mu)$ for $\mu = \lambda_m - 1$ and $\lambda_m^{-1} - 1$, respectively. Performing integration by parts in Eq. (D-7), we obtain

$$M(\mu) = z \left[\ln(1 + \mu z^2) - 2 \right]_{z=0}^{z=1} + 2 \int_0^1 \frac{dz}{1 + \mu z^2} = \ln(1 + \mu) + 2 \left[\int_0^1 \frac{dz}{1 + \mu z^2} - 1 \right]. \quad (\text{D-8})$$

Calculating the integral, we find that

$$\begin{aligned} M(\mu) &= \ln(1 + \mu) + 2 \left(\frac{\arctan \sqrt{\mu}}{\sqrt{\mu}} - 1 \right), & \mu > 0, \\ M(\mu) &= 0, & \mu = 0, \\ M(\mu) &= \ln(1 + \mu) + 2 \left(\frac{1}{2\sqrt{\mu}} \ln \frac{1 + \sqrt{\mu}}{1 - \sqrt{\mu}} - 1 \right), & \mu < 0. \end{aligned}$$

This implies that

$$\int_0^1 \ln(1 + (\lambda_m - 1)z^2) dz = \ln \lambda_m + 2H(\lambda_m), \quad (\text{D-9})$$

where the function $H(z)$ is given by Eq. (66). Substitution of expression (D-9) into the second equality in Eq. (D-2) results in

$$\Psi_2^{(m)} = k_{\text{B}}TK_1 \left[(2a-1) \ln \lambda_m + 2 \left(aH(\lambda_m) + (1-a)H(\lambda_m^{-1}) \right) \right]. \quad (\text{D-10})$$

It follows from Eqs. (D-1), (D-4), (D-5), (D-6) and (D-10) that

$$\begin{aligned} W^{(m)} &= k_{\text{B}}T \left\{ -\frac{1}{2}(2a-1) \ln \lambda_m + \left(1 + \frac{2}{3}\alpha \right) \left[a \left(\frac{1}{6} \lambda_m^{\frac{5}{2}} + \frac{5}{24} \lambda_m^{\frac{3}{2}} + \frac{5}{16} \lambda_m^{\frac{1}{2}} \right) + (1-a) \right. \right. \\ &\times \left. \left. \left(\frac{1}{6} \lambda_m^{-\frac{5}{2}} + \frac{5}{24} \lambda_m^{-\frac{3}{2}} + \frac{5}{16} \lambda_m^{-\frac{1}{2}} \right) + \frac{5}{16} \left(aG(\lambda_m) + (1-a)G(\lambda_m^{-1}) \right) - 1 \right] \right\} \\ &\quad - k_{\text{B}}T\alpha \left[(2a-1) \ln \lambda_m + 2 \left(aH(\lambda_m) + (1-a)H(\lambda_m^{-1}) \right) \right]. \end{aligned} \quad (\text{D-11})$$

Equation (65) follows from Eqs. (45) and (D-11).

Appendix E

According to Eq. (52), the function W_0 is given by

$$W_0 = k_B T \left[a \left(\frac{1}{6} \mathcal{I}_1(\mathbf{C}^{\frac{5}{2}}) + \frac{5}{24} \mathcal{I}_1(\mathbf{C}^{\frac{3}{2}}) + \frac{5}{16} \mathcal{I}_1(\mathbf{C}^{\frac{1}{2}}) \right) \right. \\ \left. + (1-a) \left(\frac{1}{6} \mathcal{I}_1(\mathbf{C}^{-\frac{5}{2}}) + \frac{5}{24} \mathcal{I}_1(\mathbf{C}^{-\frac{3}{2}}) + \frac{5}{16} \mathcal{I}_1(\mathbf{C}^{-\frac{1}{2}}) \right) - \frac{33}{16} \right]. \quad (\text{E-1})$$

Expanding the function $H(z)$ in Eq. (66) into a Taylor series in the vicinity of the point $z = 1$, we find that

$$H(z) = \sum_{k=1}^{\infty} \frac{(-1)^k (z-1)^k}{2k+1} \quad (z > 1), \quad H(z) = \sum_{k=1}^{\infty} \frac{(1-z)^k}{2k+1} \quad (z < 1),$$

which means that for any z belonging to the region where the series converges,

$$H(z) = \sum_{k=1}^{\infty} \frac{(1-z)^k}{2k+1}. \quad (\text{E-2})$$

It follows from Eq. (E-2) that

$$\sum_{m=1}^3 H(\lambda_m) = \sum_{k=1}^{\infty} \frac{1}{2k+1} \sum_{m=1}^3 (1-\lambda_m)^k = \sum_{k=1}^{\infty} \frac{1}{2k+1} \mathcal{I}_1((\mathbf{I} - \mathbf{C})^k).$$

Similarly,

$$\sum_{m=1}^3 H(\lambda_m^{-1}) = \sum_{k=1}^{\infty} \frac{1}{2k+1} \mathcal{I}_1((\mathbf{I} - \mathbf{C}^{-1})^k).$$

Substitution of these expressions into Eq. (67) results in

$$W = \left(1 + \frac{2}{3} \alpha \right) W_0 - k_B T \left[(2a-1) \left(\alpha + \frac{1}{2} \right) \ln J_3 \right. \\ \left. + 2\alpha \sum_{k=1}^{\infty} \frac{1}{2k+1} \left(a \mathcal{I}_1((\mathbf{I} - \mathbf{C})^k) + (1-a) \mathcal{I}_1((\mathbf{I} - \mathbf{C}^{-1})^k) \right) \right]. \quad (\text{E-3})$$

Equation (68) follows from Eqs. (E-1) and Eq. (E-3) and definition (69) of the strain tensors.

As the series in Eq. (E-3) converges rather slowly, it is tempting to truncate it up to terms of an order k_0 with respect to the norms of the strain tensors. Taking into account one term only ($k_0 = 1$), we find that

$$\sum_{k=1}^{k_0} \frac{1}{2k+1} \left[a \mathcal{I}_1((\mathbf{I} - \mathbf{C})^k) + (1-a) \mathcal{I}_1((\mathbf{I} - \mathbf{C}^{-1})^k) \right] \\ = -\frac{1}{3} \left[a \left(\mathcal{I}_1(\mathbf{C}) - 3 \right) + (1-a) \left(\mathcal{I}_1(\mathbf{C}^{-1}) - 3 \right) \right]. \quad (\text{E-4})$$

It follows from Eq. (E-4) that in the first-order approximation, the account for the pre-exponential term in the distribution function (6) is equivalent to the introduction of additional Gaussian chains into the network.

Taking into account two terms ($k_0 = 2$) in Eq. (E-3), we find, after simple algebra, that

$$\begin{aligned}
& \sum_{k=1}^{k_0} \frac{1}{2k+1} \left[a \mathcal{I}_1((\mathbf{I} - \mathbf{C})^k) + (1-a) \mathcal{I}_1((\mathbf{I} - \mathbf{C}^{-1})^k) \right] \\
&= \frac{1}{15} \left\{ a \left[3(J_1 - 3)^2 + 7(J_1 - 3) - 6(J_2 - 3) \right] \right. \\
& \quad \left. + (1-a) \left[3(J_{-1} - 3)^2 + 7(J_{-1} - 3) - 6(J_{-2} - 3) \right] \right\}. \tag{E-5}
\end{aligned}$$

According to Eq. (E-5), in the second-order approximation, the account for the pre-exponential term in Eq. (6) results in a decrease in the strain energy of a self-avoiding chain.

References

- [1] Bergström, J.S.; Boyce, M.C.: Constitutive modeling of the large strain time-dependent behavior of elastomers. *J. Mech. Phys. Solids* 46 (1998) 931–954.
- [2] Klüppel, M.; Schramm, J.: A generalized tube model of rubber elasticity and stress softening of filled reinforced elastomer systems. *Macromol. Theory Simul.* 9 (2000) 742–754.
- [3] Chevalier, L.; Calloch, S.; Hild, F.; Marco, Y.: Digital image correlation used to analyze the multiaxial behavior of rubber-like materials. *Eur. J. Mech. A/Solids* 20 (2001) 169–187.
- [4] Amin, A.F.M.S.; Alam, M.S.; Okui, Y.: An improved hyperelasticity relation in modeling viscoelasticity response of natural and high damping rubbers in compression: experiments, parameter identification and numerical verification. *Mech. Mater.* 34 (2002) 75–95.
- [5] Bischoff, J.E.; Arruda, E.A.; Grosh, K.: A microstructurally based orthotropic hyperelastic constitutive law. *J. Appl. Mech.* 69 (2002) 570–579.
- [6] Elias-Zuniga, A.; Beatty, M.F.: Constitutive equations for amended non-Gaussian network models of rubber elasticity. *Int. J. Engng. Sci.* 40 (2002) 2265–2294.
- [7] Beatty, M.F.: An average-stretch full-network model for rubber elasticity. *J. Elasticity* 70 (2003) 65–86.
- [8] Cheng, M.; Chen, W.: Experimental investigation of the stress–stretch behavior of EPDM rubber with loading rate effects. *Int. J. Solids Structures* 40 (2003) 4749–4768.
- [9] Hartmann, S.; Tschöpe, T.; Schreiber, L.; Haupt, P.: Finite deformations of a carbon black-filled rubber. Experiment, optical measurement and material parameter identification using finite elements. *Eur. J. Mech. A/Solids* 22 (2003) 309–324.
- [10] Meissner, B.; Matejka, L.: A Langevin-elasticity-theory-based constitutive equation for rubberlike networks and its comparison with biaxial stress-strain data. I. *Polymer* 44 (2003) 4599–4610.
- [11] Bouchiat, C.; Mezard, M.: Elasticity model of a supercoiled DNA molecule. *Phys. Rev. Lett.* 80 (1998) 1556–1559.
- [12] Stigter, D.; Bustamante, C.: Theory for the hydrodynamic and electrophoretic stretch of tethered B-DNA. *Biophys. J.* 75 (1998) 1197–1210.
- [13] Bouchiat, B.; Wang, M.D.; Allemand, J.-F.; Strick, T.; Bloch, S.M.; Croquette, V.: Estimating the persistence length of a worm-like chain molecule from force-extension measurements. *Biophys. J.* 76 (1999) 409–413.
- [14] Bouchiat, C.; Mezard, M.: Elastic rod model of a supercoiled DNA molecule. *Eur. Phys. J. E* 2 (2000) 377–402.
- [15] Golestanian, R.; Liverpool, T.B.: Statistical mechanics of semiflexible ribbon polymers. *Phys. Rev. E* 62 (2000) 5488–5499.
- [16] Schiessel, H.; Gelbart, W.M.; Bruinsma, R.: DNA folding: structural and mechanical properties of the two-angle model for chromatin. *Biophys. J.* 80 (2001) 1940–1956.

- [17] Cocco, S.; Marko, J.F.; Monasson, R.: Theoretical models for single-molecule DNA and RNA experiments: from elasticity to unzipping. *C.R. Physique* 3 (2002) 569–584.
- [18] Samuel, J.; Sinha, S.: Elasticity of semiflexible polymers. *Phys. Rev. E* 66 (2002) 050801.
- [19] Storm, C.; Nelson, P.C.: Theory of high-force DNA stretching and overstretching. *Phys. Rev. E* 67 (2003) 051906.
- [20] Winkler, R.G.: Deformation of semiflexible chains. *J. Chem. Phys.* 118 (2003) 2919–2928.
- [21] Lee, N.-K.; Thirumalai, D.: Pulling-speed-dependent force-extension profiles for semiflexible chains. *Biophys. J.* 86 (2004) 2641–2649.
- [22] Treloar, L.R.G.: *The Physics of Rubber Elasticity*. Clarendon Press, Oxford, 1975.
- [23] Edwards, S.F.; Vilgis, T.A.: The tube model theory of rubber elasticity. *Rep. Prog. Phys.* 51 (1988) 243–297.
- [24] Boyce, M.C.; Arruda, E.M.: Constitutive models of rubber elasticity: A review. *Rubber Chem. Technol.* 73 (2000) 504–523.
- [25] Kratky, O.; Porod, G.: Röntgenuntersuchung gelöster Faden-moleküle. *Rec. Trav. Chim. Pays-Bas.* 68 (1949) 1106–1122.
- [26] James, H.M.; Guth, E.: Theory of elastic properties of rubber. *J. Chem. Phys.* 10 (1943) 455–481.
- [27] Gent, A.N.: A new constitutive model for rubber. *Rubber. Chem. Technol.* 69 (1996) 59–61.
- [28] Horgan, C.O.; Saccomandi, G.: A molecular-statistical basis for the Gent constitutive model of rubber elasticity. *J. Elasticity* 68 (2002) 167–176.
- [29] Herrchen, M.; Öttinger, H.C.: A detailed comparison of various FENE dumbbell models. *J. Non-Newtonian Fluid Mech.* 68 (1997) 17–42.
- [30] Doi, M.; Edwards, S.F.: *The Theory of Polymer Dynamics*. Clarendon Press, Oxford, 1986.
- [31] Lévy, P.: *Theorie de l'Addition des Variables Aleatoires*. Gauthier-Villars, Paris, 1954.
- [32] de Gennes, P.G.: *Scaling Concepts in Polymer Physics*. Cornell Univ. Press, Ithaca, NY, 1979.
- [33] Kovac, J.; Crabb, C.C.: Modified Gaussian model for rubber elasticity. 2. The wormlike chain. *Macromolecules* 15 (1982) 537–541.
- [34] Vanderzande, C.: *Lattice Models of Polymers*. Cambridge Univ. Press, Cambridge, 1998.
- [35] Bishop, M.; Clarke, J.H.P.: Investigation of the end-to-end distance distribution function for random and self-avoiding walks in two and three dimensions. *J. Chem. Phys.* 94 (1991) 3936–3942.
- [36] Dayantis, J.; Paliarne, J.-P.: Monte Carlo precise determination of the end-to-end distribution function of self-avoiding walks on the simple-cubic lattice. *J. Chem. Phys.* 95 (1991) 6088–6099.

- [37] McKenzie, D.S.; Moore, M.A.: Shape of a self-avoiding walker or polymer chain. *J. Phys. A* 4 (1971) L82–L86.
- [38] des Cloizeaux, J.: Lagrangian theory for a self-avoiding random chain. *Phys. Rev. A* 10 (1974) 1665–1669.
- [39] Liang, J.-J.; Bentler, P.M.; Characterizations of some subclasses of spherical distributions. *Statistics Prob. Lett.* 40 (1998) 155–164.
- [40] Freed, K.F.: *Renormalization Group Theory of Macromolecules*. Wiley, New York, 1987.
- [41] Flory, P.J.: The configuration of real polymer chains. *J. Chem. Phys.* 17 (1949) 303–310.
- [42] Treloar, L.R.G.; Riding, G.: A non-Gaussian theory for rubber in biaxial strain. I. Mechanical properties. *Proc. R. Soc. Lond. A* 369 (1979) 261–280.
- [43] Ogden, R.W.: *Nonlinear Elastic Deformations*. Chichester, Ellis Horwood, 1984.
- [44] Heinrich, G.; Kaliske, M.: Theoretical and numerical formulation of a molecular based constitutive tube-model of rubber elasticity. *Comput. Theor. Polym. Sci.* 7 (1997) 227–241.
- [45] Roland, C.M.; Mott, P.H.; Heinrich, G.: Elasticity of polydiene networks in tension and compression. *Comput. Theor. Polym. Sci.* 9 (1999) 197–202.
- [46] James, A.G.; Green, A.; Simpson, G.M.: Strain energy functions of rubber. I. Characterization of gum vulcanizates. *J. Appl. Polym. Sci.* 19 (1975) 2033–2258.
- [47] Kawamura, T.; Urayama, K.; Kohjiya, S.: Multiaxial deformations of end-linked poly-(dimethylsiloxane) networks. 3. Effect of entanglement density on strain-energy function. *J. Polym. Sci. B: Polym. Phys.* 40 (2002) 2780–2790.

List of figures

Figure 1: The dimensionless strain energy \overline{W} versus elongation ratio k at uniaxial extension of an incompressible network. Solid line: the Ogden model (52). Circles: the Ogden model with account for the correction term (50).

Figure 2: The dimensionless strain energy \overline{W} versus shear k at simple shear of an incompressible network. Solid line: the Ogden model (52). Circles: the Ogden model with account for the correction term (50).

Figure 3: The engineering stress σ_e versus elongation ratio k at uniaxial extension of natural rubber with the concentration of cross-linker $\phi = 1.0, 1.5, 2.0, 2.5, 3.0, 3.5$ and 4.0 phr, from bottom to top, respectively. Circles: experimental data [2]. Solid lines: results of numerical simulation.

Figure 4: The elastic modulus μ_1 versus concentration of cross-linker ϕ . Circles: treatment of observations [2]. Solid line: approximation of the experimental data by Eq. (63) with $\mu_1^{(1)} = 0.12$ MPa/phr.

Figure 5: The engineering stress σ_e versus elongation ratio k at uniaxial compression of chloroprene rubber reinforced with carbon black (CB). Symbols: experimental data [1]. Unfilled circles: 15 phr CB. Filled circles: 40 phr CB. Diamonds: 65 phr CB. Solid lines: results of numerical simulation.

Figure 6: The elastic modulus μ_1 versus concentration of carbon black ϕ for chloroprene rubber. Circles: treatment of observations [1]. Solid line: approximation of the experimental data by Eq. (63) with $\mu_1^{(0)} = 0.16$ MPa and $\mu_1^{(1)} = 0.02$ MPa/phr.

Figure 7: The engineering stress σ_e versus elongation ratio k at uniaxial tension–compression of carbon black-filled natural rubber. Circles: experimental data [9]. Solid line: results of numerical simulation with $\mu_1 = 0.39$ and $\mu_2 = 0.27$ MPa.

Figure 8: The engineering stress σ_e versus elongation ratio k at uniaxial tension–compression of polybutadiene rubber. Circles: experimental data [45]. Solid line: results of numerical simulation with $\mu_1 = 0.285$ and $\mu_2 = 0.056$ MPa.

Figure 9: The engineering stress σ_e versus elongation ratio k at uniaxial (unfilled circles) and equi-biaxial (filled circles) extension of synthetic rubber Smactane. Symbols: experimental data [3]. Solid lines: results of numerical simulation with $\mu_1 = 0.075$ and $\mu_2 = 0.704$ MPa.

Figure 10: The functions $H(z)$ (thin curve) and $F(z)$ (thick curve).

Figure 11: The engineering stress σ_e versus elongation ratio k at uniaxial tension–compression of carbon black-filled natural rubbers NR–1 (unfilled circles) and NR–2 (filled circles). Symbols: experimental data [45]. Solid lines: results of numerical simulation with $a = 1.0$. Curve 1: $\mu_1 = 0.0296$, $\mu_2 = -2.72$ MPa. Curve 2: $\mu_1 = 0.0449$, $\mu_2 = -4.94$ MPa.

Figure 12: The engineering stress σ_e versus elongation ratio k at equi-biaxial extension of natural rubber. Circles: experimental data [46]. Solid line: results of numerical simulation with $a = 1.0$, $\mu_1 = 0.023$ and $\mu_2 = -6.96$ MPa.

Figure 13: The engineering stress $\sigma_{e,2}$ versus elongation ratio k_2 at biaxial tension of PDMS network with the elongation ratios $k_1 = 1.1, 1.3, 1.5, 1.7$ and 1.9 , from bottom to top, respectively. Circles: experimental data [47]. Solid lines: results of numerical simulation with $a = 1.0$, $\mu_1 = 0.0027$ and $\mu_2 = -0.291$ MPa.

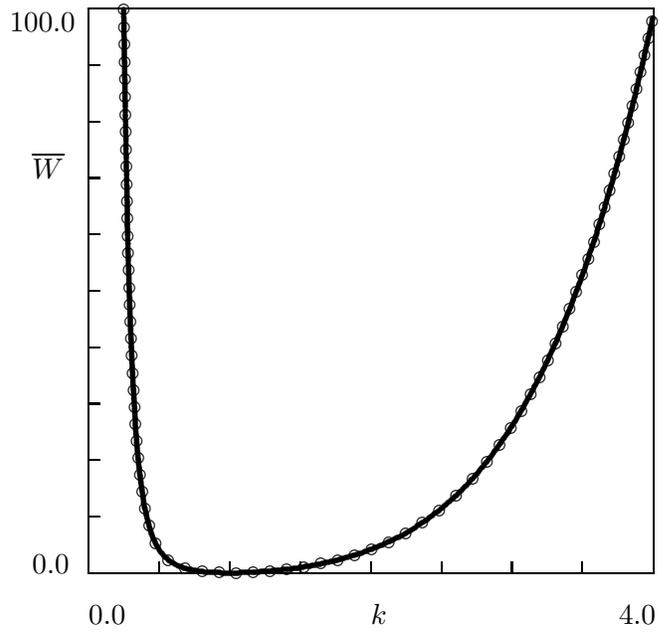


Figure 1:

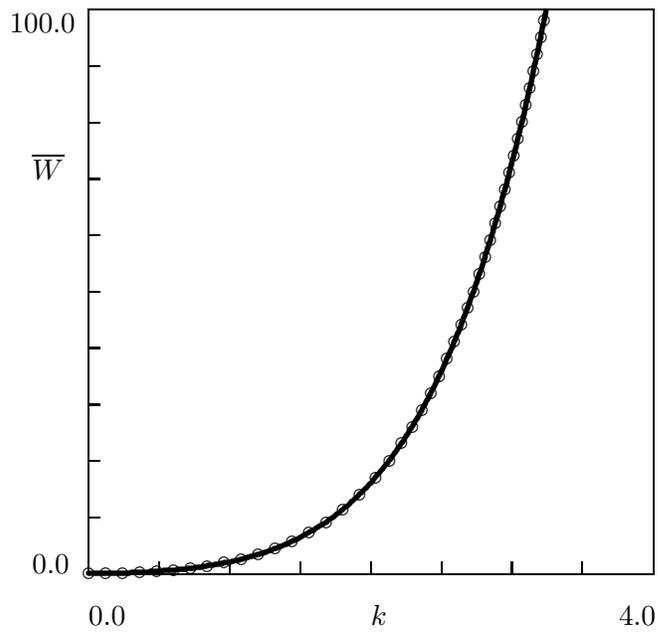


Figure 2:

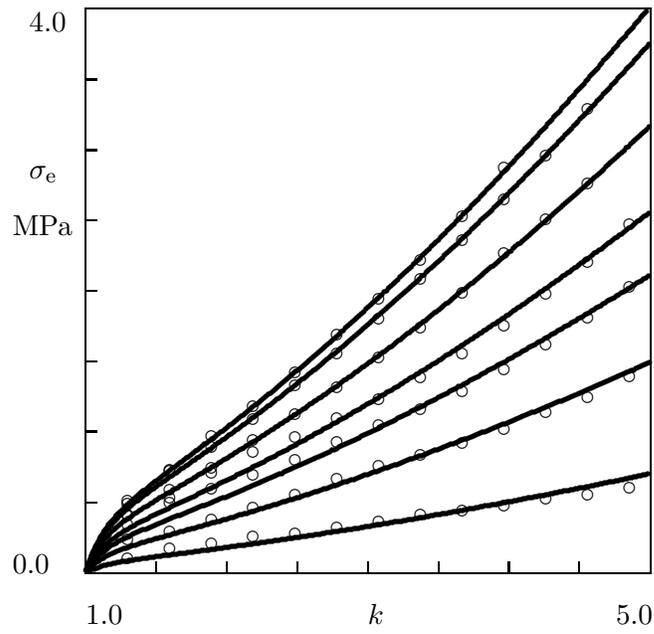


Figure 3:

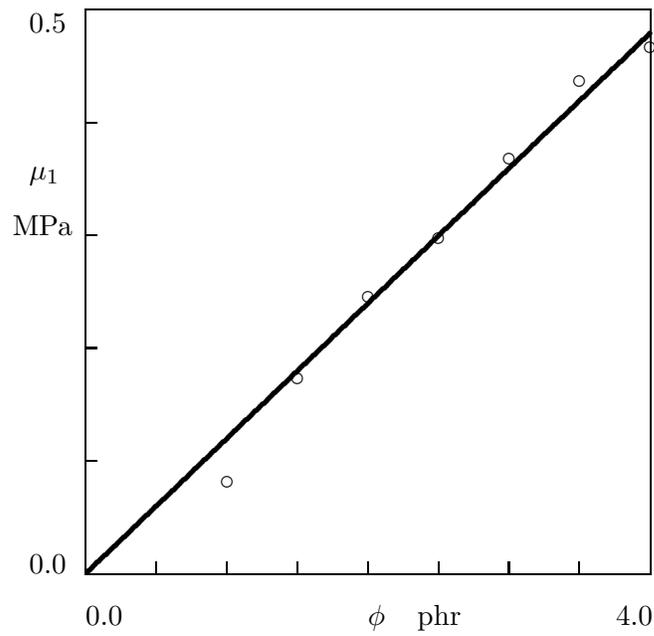


Figure 4:

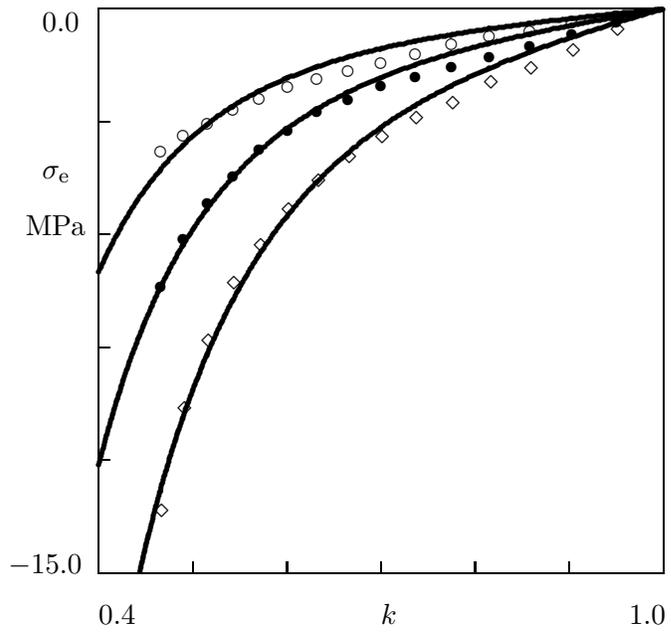


Figure 5:

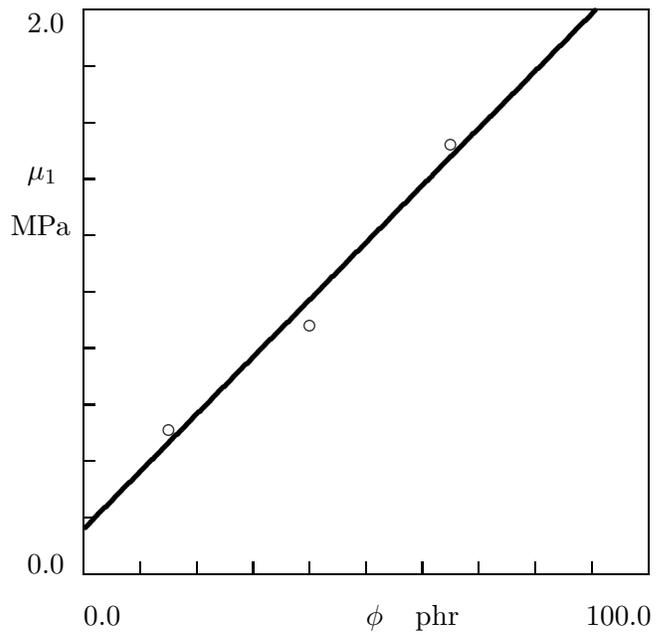


Figure 6:

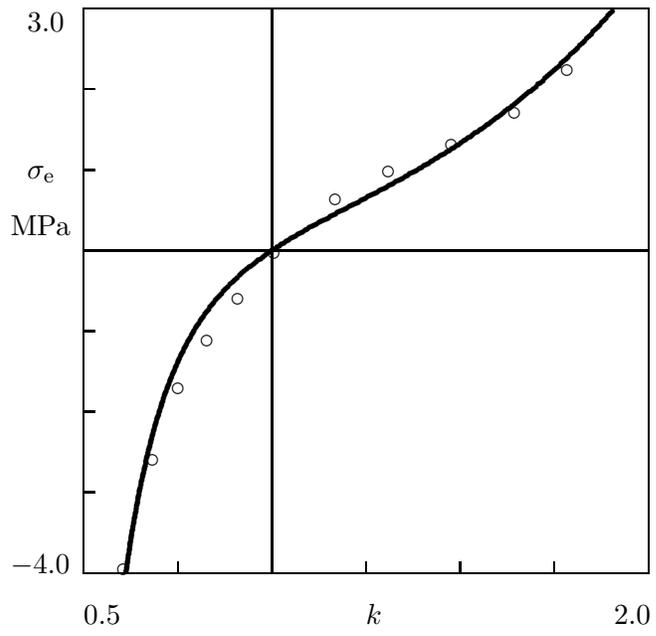


Figure 7:

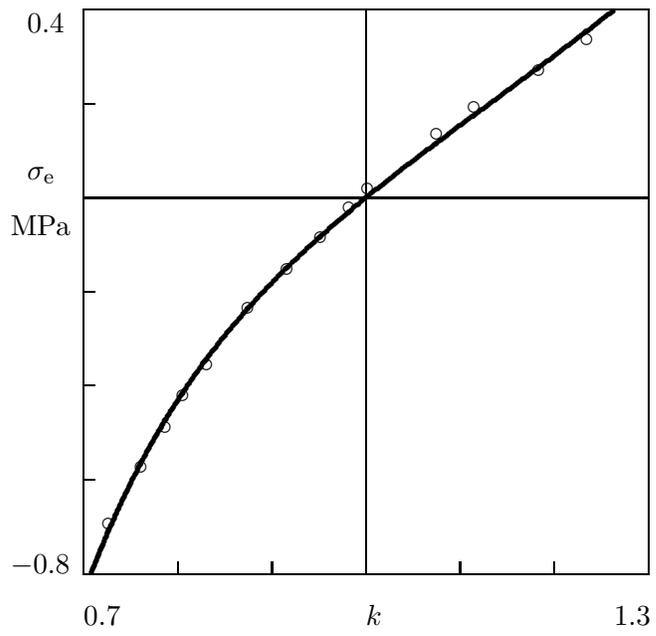


Figure 8:

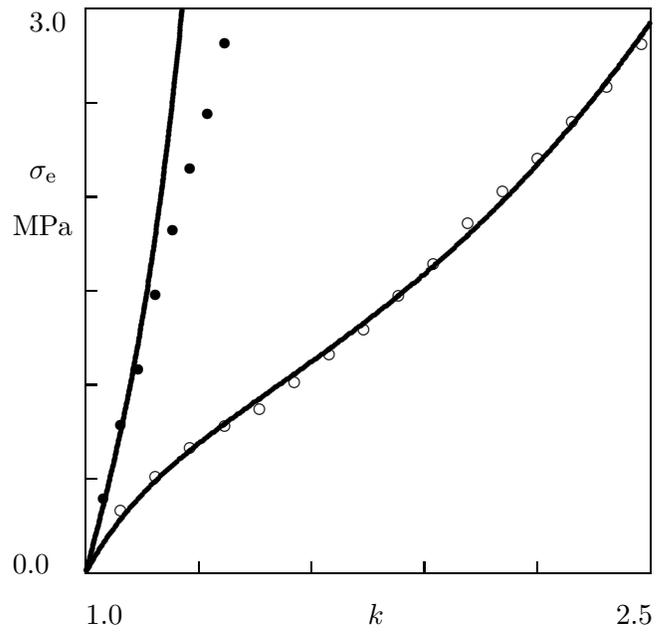


Figure 9:

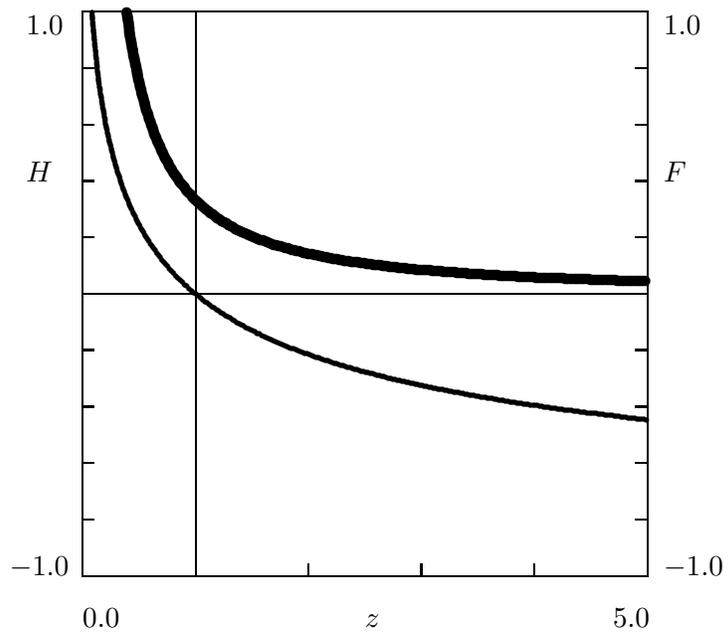


Figure 10:

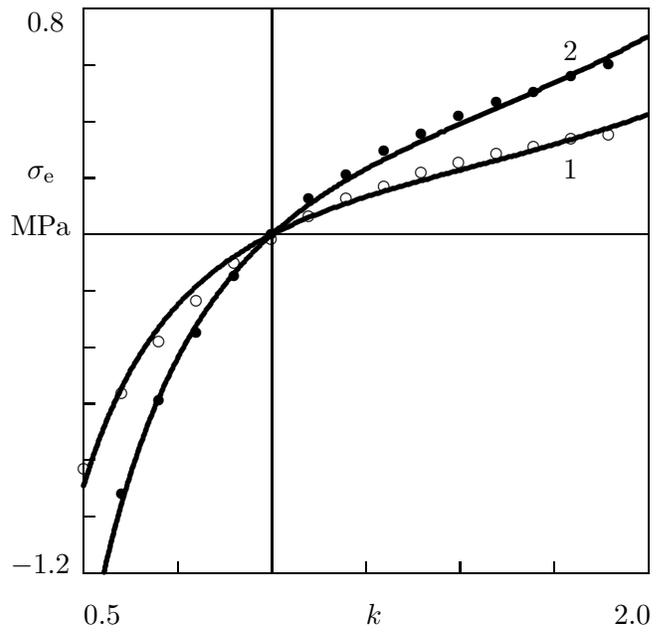


Figure 11:

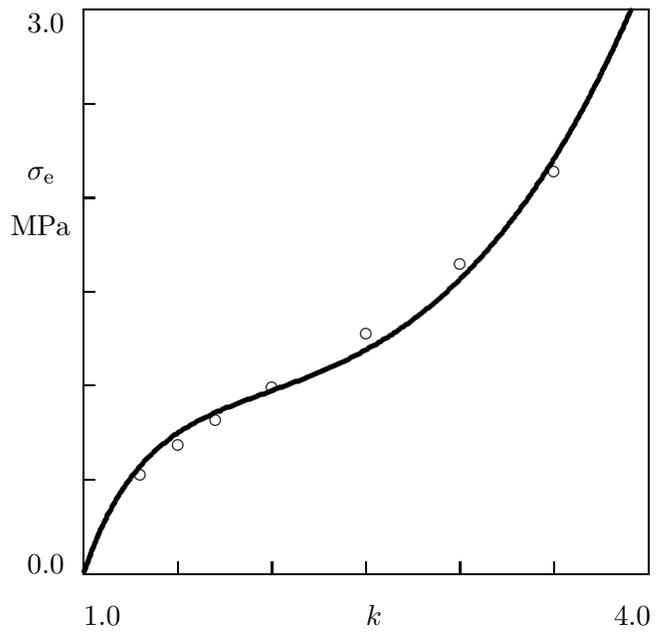


Figure 12:

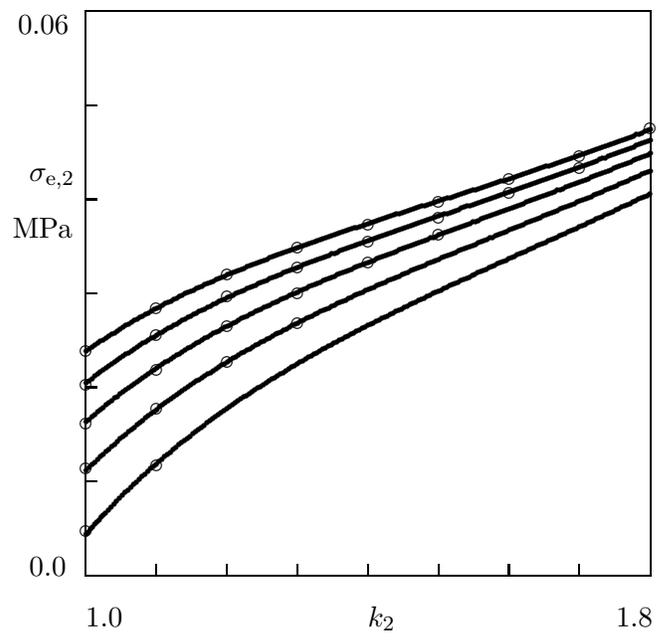


Figure 13: