

# Low dimensional ordering and fluctuations in methanol-hydroquinone-clathrate studied by X-ray and neutron diffraction

Maikel C. Rheinstädter

Institut Laue-Langevin, 6 rue Jules Horowitz, BP 156,38042 Grenoble Cedex 9, France and  
Technische Physik, Universität des Saarlandes, PSF 1551150, 66041 Saarbrücken, Germany

Mechthild Enderle

Institut Laue-Langevin, 6 rue Jules Horowitz, BP 156,38042 Grenoble Cedex 9, France

Axel Klöpperpieper and Klaus Knorr

Technische Physik, Universität des Saarlandes, PSF 1551150, 66041 Saarbrücken, Germany  
(dated: January 20, 2022)

Methanol-hydroquinone-clathrate has been established as a model system for dielectric ordering and fluctuations and is conceptually close to magnetic spin systems. In X-ray and neutron diffraction experiments, we investigated the ordered structure, the one-dimensional (1D) and the three-dimensional (3D) critical scattering in the paraelectric phase, and the temperature dependence of the lattice constants. Our results can be explained by microscopic models of the methanol pseudospin in the hydroquinone cage network, in consistency with previous dielectric investigations.

PACS numbers: 64.60, 61.10.Nz, 61.12.Ld, 77.22.Ch

Reducing the dimensionality has a drastic influence on order-disorder phenomena, as it generally enhances fluctuations. Phase transitions are shifted to lower temperatures, or may be suppressed entirely. In the one-dimensional Ising model with nearest-neighbor interaction, thermal fluctuations suppress ordering at any finite temperature, independent of the strength of the interaction. Theoretical models for low-dimensional ordering and fluctuations are mostly tested on magnetically interacting materials, where the magnetic moment is well decoupled from the surrounding chemical lattice, and the interaction is short-ranged. Materials with low-dimensional, but long-ranged interactions like the dipole-dipole interaction are rare. Due to its small energy scale, the magnetic dipole-dipole interaction is often negligible compared to exchange-type interactions, magneto-elastic interactions and anisotropies induced by spin-orbit coupling and crystal field. The electric dipole-dipole interaction (EDD) is several orders of magnitude larger than its magnetic pendant. The electric dipole moment is connected to polar molecules or to displacements of groups of atoms against each other. Usually, the interaction with the surrounding lattice is far from being negligible. Materials, which allow to test theoretical predictions for fluctuations and ordering of "pseudospins" interacting exclusively via the EDD interaction, are extremely rare. In this context, clathrates with polar guest molecules provide a happy exception. They may undergo structural phase transitions driven by the interactions between the dipole moments of the guest molecules, with practically no coupling of the orientational degrees of freedom to the host lattice.

The present article deals with methanol-hydroquinone clathrate, where well defined methanol electric dipoles occupy the almost spherical hydroquinone cavities. The electric dipoles arrange in chains

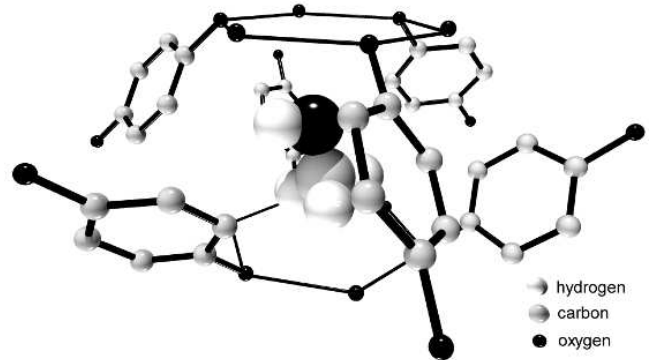


FIG. 1: The methanol molecule ( $\text{CH}_3\text{OH}$ ) in the quinone cage network. The atoms of the guest molecules are shown with their Van-der-Waals diameters whereas for the hydroquinone host lattice the stick-and-ball presentation is used.

and are well decoupled from the surrounding host lattice. Thus the methanol clathrate can be understood in terms of interacting point-dipoles and has been established as a model system for dipolar ordering processes<sup>1,2,3,4,5</sup>.


Figure 1 shows the methanol molecule, which carries a dipole moment of 1.69 Debye<sup>6</sup>, in the hydroquinone cage. The shortest distance between the guest molecules is along the hexagonal c-axis. The geometry of the lattice combined with EDD interaction is responsible for the formation of ferroelectric chains along the c-axis, reflected in the dielectric properties: Woll et al. have studied the dielectric response as a function of temperature and frequency<sup>1,2</sup>. The static dielectric constant along the hexagonal c-axis,  $\epsilon_{\text{cs}}$ , shows a strong deviation from the Curie-Weiss behavior already at 250 K. The temperature dependence of  $\epsilon_{\text{cs}}$  at higher temperatures is well described by a quasi-one-dimensional (1D) Ising model with

a ferroelectric coupling  $J_c$  to nearest neighbors within the chain and a mean-field antiferroelectric inter-chain interaction with coupling constant  $J_z$ <sup>7</sup>. At lower  $T$ ,  $\chi_{cs}(T)$  deviates from this mean-field-Ising-behavior and finally decreases with decreasing  $T$ , indicating the onset of three-dimensional (3D) antiferroelectric inter-chain correlations. At  $T_c = 65$  K the methanol-clathrate undergoes a transition into an antiferroelectrically ordered structure.


While the dielectric experiments probe the macroscopic response at  $Q = 0$ , at the center of the Brillouin zone, diffraction experiments give access to the corresponding underlying microscopic processes and allow to study the structural susceptibility at arbitrary points in reciprocal space. In this article, we first present X-ray diffraction results obtained in the ordered phase, which allow to develop the dipolar structure model. Then we turn to the paraelectric regime, where we studied the 1D and 3D critical scattering by X-ray and neutron diffraction experiments, as well as the temperature dependence of the lattice parameters. We compare our results to theoretical predictions and discuss them in the context of the preceding dielectric experiments.

## Experimental

Single crystals of methanol-hydroquinone clathrate have been grown from a saturated solution of quinol and methanol at 313 K. Completely deuterated samples were used for neutron experiments to minimize the incoherent background. Typical sample crystals were  $2 \times 2 \times 2$  mm<sup>3</sup>. At room temperature, the methanol-clathrate has a rhombohedral  $R\bar{3}$  structure<sup>8</sup>. Throughout this article, we use the hexagonal notation, which is better adapted to the dielectric properties of the clathrate than the rhombohedral. Exceptions are marked explicitly by  $(:::)_{rh}$ . The hexagonal lattice parameters at 300 K are  $a = 16.62$  Å,  $c = 5.56$  Å. For the X-ray investigations, we used monochromatic CuK $\alpha$  radiation and a two-circle diffractometer, equipped with a closed cycle refrigerator. The single crystalline samples were oriented with  $c$  perpendicular to the scattering plane. This allows scans within the  $(hk0)$  plane. Scans within planes  $(hkl)$ ,  $l$  constant,  $l \neq 0$  are possible by moving the detector out of the diffractometer plane. Rotating crystal exposures have also been taken. Here the crystal was rotated about  $c$  and the incoming beam was perpendicular to the  $c$ -axis. Diffuse 1D critical scattering has been measured at the two-circle neutron diffractometer D23 (CEA-CRG) at the high flux reactor of the ILL in Grenoble, France. Here the 1D axis,  $c$ , was mounted in the scattering plane.

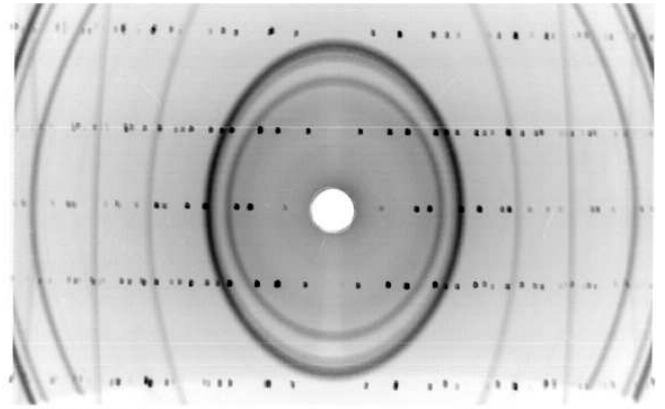

a)  $T = 100$  K

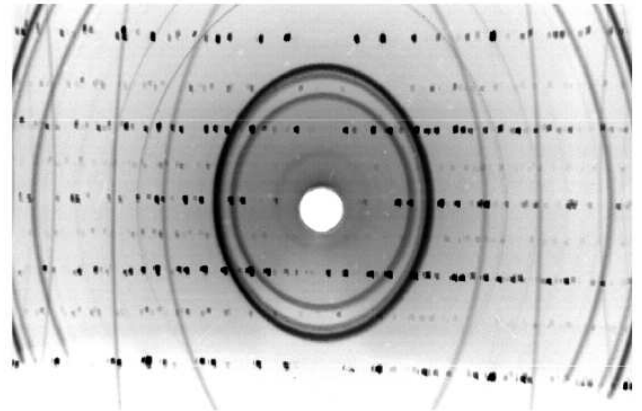

b)  $T = 39$  K

FIG. 2: Rotating crystal photographs taken at  $T = 100$  K (a) and 39 K (b). The elliptical lines are due to scattering from the Al windows of the cryo-refrigerator.

## Results

### Ordered phase

Rotating-crystal X-ray photographs of methanol-clathrate were taken above and below the phase transition ( $T_c = 65$  K). Figure 2a) displays the photograph taken in the paraelectric phase at  $T = 100$  K, gure 2b) in the ordered phase, at 39 K. At high temperatures, horizontal layers of reflections  $(hkl)$  with  $l = 0; 1; 2; :::$  are visible. Below  $T_c$ , additional reflections in layers with integer and half-integer values of  $l$ ,  $l = \frac{1}{2}; \frac{3}{2}; :::$  appear. The  $(hkl)$  values of the superlattice reflections can be determined from their position on the photograph. Careful analysis shows that modes with wave vectors  $k_1 = (00\frac{1}{2})_{rh}$  and  $k_2 = (\frac{1}{2}\frac{1}{2}\frac{1}{2})_{rh}$  condense at the phase transition on the boundary of the rhombohedral Brillouin zone at the Lifshitz points F ( $k_1$ ) and L ( $k_2$ ). To generate all superlattice reflections as linear combinations of  $k_1$  and  $k_2$ , L and two arms of the F-star are required. This means, two of the rhombohedral lattice vectors double at  $T_c$ . Additionally, the unit cell doubles in the hexagonal  $c$  direction (as indicated by the L-type

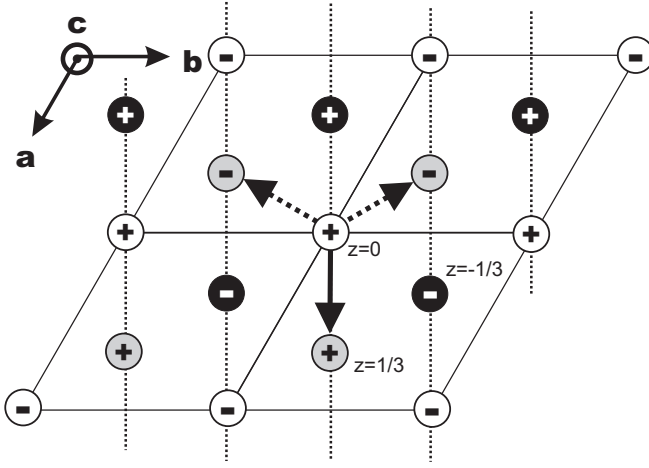


FIG. 3: Projection of the 3D ordered antiferroelectric structure onto the hexagonal basal plane: white circles: dipoles at  $z = 0$ , grey circles:  $z = \frac{1}{3}$ , black circles:  $z = \frac{2}{3}$ . +/− indicates the orientation of the electric dipole. Below  $T_c$ , two of the rhombohedral lattice vectors double (indicated by the dotted arrows). Along  $c$ , the dipoles order ferroelectrically. The ferroelectric chains arrange in ferro-ordered (100) layers with alternating sign from layer to layer. These layers are visualized by dotted lines. Solid lines indicate the hexagonal unit cells.

vector  $k_2 = (\frac{1}{2} \frac{1}{2} \frac{1}{2})_{rh}$ .

The occurrence of  $k_1$  indicates the freezing of the methanol molecules into one of the six symmetry directions of the  $R3$  space group. The resulting structure of the dipole system in the dielectrically ordered phase is shown in Fig. 3. The dipoles are arranged in ferroelectrically ordered chains running along the hexagonal  $c$ -axis, which are arranged in sheets of alternating sign. As a property of the EDD interaction and the lattice symmetry, the dipoles prefer an antiferroelectric arrangement perpendicular to the chains, which can not be satisfied for all chains, because of the triangular lattice symmetry. As a consequence, every dipole chain is surrounded by 4 chains, which are oriented antiparallel, and by 2 parallel oriented dipole chains. The antiferroelectric interaction is thus satisfied by the majority. The  $4:2$  pattern fills the hexagonal basal plane in a regular fashion: Every dipole has the same environment of ferro- and antiferroelectrically oriented pseudospins. This  $2-k_1$  ground state is also obtained from Monte Carlo calculations<sup>9</sup> and simple lattice sum calculations, considering the EDD interaction of the guest molecules, only (see Ref. [10] for the case of acetonitrile).

The doubling of the unit cell along  $c$ , evidenced by the occurrence of  $L$ -type  $k_2$  reflections, indicates an antiphase arrangement in neighboring cells along  $c$ .  $k_2$  indicates a dimerization of the dipoles in the 1D chain, i.e. the appearance of pairs of strongly coupled pseudospins. Considering the EDD interaction in combination with a static potential in the cage center, the latter dimerization is energetically favorable, as we will discuss below. The

ordering of the dipole system at  $T_c$  is connected with a structural phase transition into the triclinic space group  $P1$ , connected with a small triclinic distortion of the host lattice below  $T_c$ .

#### Paraelectric regime

The 1D fluctuations in the dipole chains give rise to diffuse scattering which is distributed in planes perpendicular to the 1D axis (and weighted by the methanol molecular form factor). The onset of 3D ordering close to the phase transition is indicated in diffuse scattering at the positions of the superlattice reflections (of the low- $T$  phase). The correlation length along the dipole chains,  $\xi_c$ , and perpendicular,  $\xi_\perp$ , follows from the quasi1D Ising model, which has also been applied to the dielectric data, to<sup>7</sup>:

$$\frac{\xi_c}{a} = \frac{T_c}{2J_c} \frac{e^{2J_c/T_c}}{2J_c^{(1=2)}} \quad (1)$$

and

$$\frac{\xi_\perp}{a} = \frac{T_c}{4J_c} \frac{1}{J_c^{(1=2)}} \quad (2)$$

( $t = (T - T_c)/T_c$  is the reduced critical temperature). Figure 4 shows diffuse 1D and 3D scattering as measured with X-ray and neutron diffraction at different temperatures in the paraelectric regime. We investigated the weak 1D scattering on a neutron diffractometer because the contribution of the methanol molecules to the total scattering is higher in neutron scattering with deuterated samples than in the X-ray experiments. The correlation lengths  $\xi_c$  and  $\xi_\perp$  follow from the width of Lorentzian peak profiles and are shown in Figure 5. The solid lines in the figure are fits after Eq. (1) and (2). The fitting parameter  $J_c$  is determined to  $J_c = 202$  K, in excellent agreement with the dielectric results ( $195$  K<sup>1</sup>). The structural data are well described by the quasi1D Ising model. The onset of the 3D correlations close to  $T_c$  finally leads to the phase transition into a 3D antiferroelectrically ordered structure.

There is no indication of a static dimerization of the dipole chains in the paraelectric phase, i.e. no intensity at the superlattice positions of  $k_2$ . But as a true 1D feature, the dimerization could already appear in the dynamically ordered chain segments in the paraelectric regime, where the 1D fluctuations already reach some hundreds of unit cells. We found no sign of diffuse scattering in planes with half-integer values of  $l$ , as caused by fluctuations of the dimerization above  $T_c$ . From calculations of the methanol structure factor<sup>13</sup> where we allowed a displacement of the dipoles along the 1D axis of  $\delta = 0.25$  Å, the intensity of the diffuse scattering due to the dimerization can be estimated as being at least two orders of magnitude smaller than that of the 1D critical scattering. The corresponding correlation length  $\xi_{sp}$  should be smaller

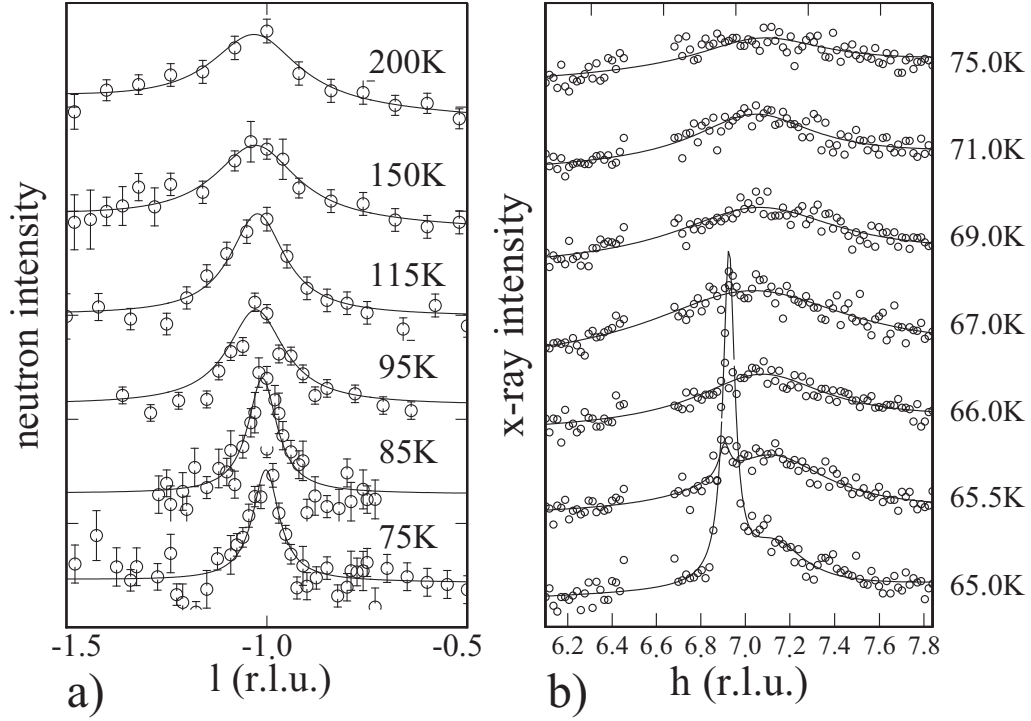


FIG. 4: (a): Diffuse 1D-scattering at  $Q = (3\frac{4}{5}\frac{1}{5}+)$  (neutron measurement) and (b) diffuse 3D-scattering at  $Q = (7 + \frac{3}{5} 0.43\ 0.5)$  (measured with X-rays). At 65 K the superlattice reflection of the ordered low-T phase is already visible as a sharp peak. (An Al-powder line has been cut around  $h = 6.55$ .)

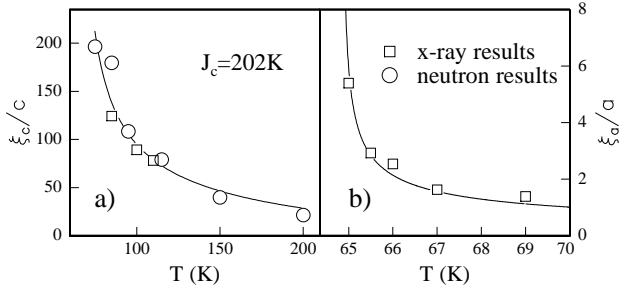


FIG. 5: Correlation length  $\xi_c$  (a) and  $\xi_a$  (b), parallel and perpendicular to the dipole chains as it was determined from Fig. 4. Solid lines are fits after Eq. (1) and (2). Results from neutron diffraction are marked by  $\circ$ , X-ray results by  $\square$ .

than  $\xi_c$ , the corresponding critical scattering as a consequence broader. If the dimerization of the dipole chains already occurs in the paraelectric phase, this effect presumably is too small to be seen in standard diffraction experiments.

Figure 6 shows the temperature dependence of the hexagonal lattice parameters  $a$  and  $c$ , as derived from the Bragg positions. Whilst the  $a$ -axis decreases linearly with temperature,  $c$  shows a distinct anomaly below about 170 K.

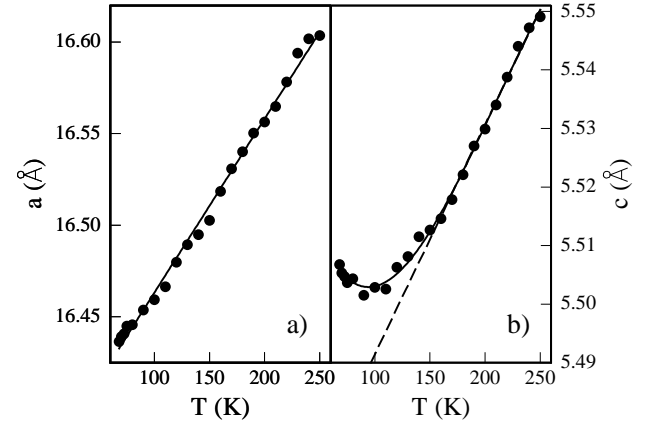


FIG. 6: Temperature dependence of the hexagonal lattice parameters  $a$  (a) and  $c$  (b) of the hexagonal cell. The dotted line in part (b) is a linear extrapolation of the high temperature linear behavior to lower  $T$ .

## Discussion

The structure of the dipole system in the dielectrically ordered phase in methanol-hydroquinone-clathrate, as determined from the analysis of the superlattice reflections below  $T_c$ , agrees well with the ground state calculated by Monte Carlo simulations<sup>9</sup> and lattice sum cal-

culations. The temperature behavior of the correlation length  $\xi_c$  and  $\xi_{\text{an}}$  is well described by the corresponding quasi 1D model by Scalapino et al.<sup>7</sup>. The structural investigations therefore confirm the microscopic picture for low dimensional ordering and fluctuations of the methanol pseudospins in the  $\alpha$ -hydroquinone cagework, as it was deduced from the dielectric experiments.

An interesting point is the appearance of superlattice reflections of type " $k_2$ ", because they indicate a doubling of the unit cell in the 1D direction. The most probable explanation of this doubling is a dimerization of the dipoles in the 1D chains. Considering a 1D chain of electric dipoles on a deformable lattice (with distance  $d$ ), interacting solely by the electric dipole-dipole interaction, a dimerization of the chain with respect to an alternating distance  $d+$  and  $d-$  of the dipoles is energetically favorable. Because of the rather steep  $r^{-3}$  potential, a dipole can lower its energy much more by approaching its neighbor by a distance  $d-$  than it at the same time loses potential energy by removing from the second neighbor in the 1D chain. The small lattice distortion at  $T_c$  (a first order structural transition) finally leads to a coupling of the two otherwise independent wave vectors  $k_1$  and  $k_2$ . The freezing of the methanol molecule and the static dimerization of the pseudospins along the chains therefore fall together at  $T_c$ . In a system with smaller coupling of the pseudospins to the surrounding host lattice, two successive transitions should occur. In 1D  $S = \frac{1}{2}$  magnetic chain compounds,  $\text{CuGeO}_3$  is a prominent example<sup>11</sup>, a structural phase transition into a statically dimerized structure is observed well above the magnetic ordering temperature. The nature of this spin-Peierls-transition is purely quantum mechanical. The pairing of neighboring antiferromagnetic  $S = \frac{1}{2}$  spins to a  $S = 0$  singlet leads to an energy gap thereby suppressing thermal spin fluctuations and lowering the ground state energy.

What is the reason for the unusual temperature behavior of the 1D lattice parameter  $c$ ? Fig. 7 shows the anomalous part of the temperature dependence of the lattice parameter, i.e. the difference of the lattice parameter  $c$  from Fig. 6 b) to an extrapolated linear decrease with temperature and the measured and calculated correlation length  $\xi_c$  from Fig. 5 in the same plot. When choosing the right scaling factor, the anomalous part of  $c$ ,  $c_{\text{an}}$ , and the correlation length  $\xi_c$  fall on the same curve and both are well described by the quasi 1D Ising model in Eq. (1). That suggests a coupling of the 1D fluctuations in the paraelectric regime to local strains. Such a coupling, however, is forbidden in the centrosymmetric space group  $R\bar{3}$ ; the coefficients of the (direct) piezoelectric effect all vanish<sup>12</sup>. The peculiarity of the present system is the unusual large amplitude of the paraelectric fluctuations. Because of the reduced dimensionality of the interactions, the ferroelectric fluctuations are strongly enhanced. The anomaly of  $c$  occurs below about 170 K, where the correlation length already reaches about 40 lattice units,  $\xi_c(170 \text{ K}) = c' \cdot 40$  (see Fig. 5). Coupling via higher order terms in susceptibility and strain, which

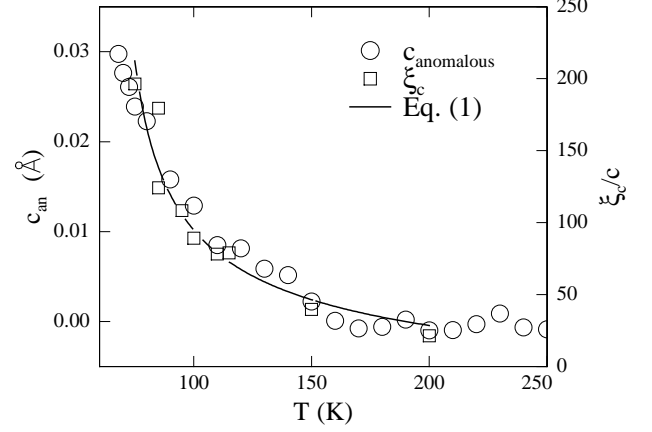


FIG. 7: Temperature dependence of the anomalous part of the lattice constant  $c_{\text{an}}$  (, see text for explanation) and the 1D correlation length  $\xi_c$  ( ). The solid line is the fit from Fig 5 after Eq. (1).

become important due to the long ranged correlations, then presumably leads to the observed electrostriction. This effect is likely to occur in other low-dimensional systems, but has not been reported before. We do not know, why the electrostriction leads to a dilatation of the  $\alpha$ -hydroquinone host lattice ( $c_{\text{an}} > 0$ ) and a larger distance of the pseudospins in the 1D direction. Intuitively, a contraction along  $c$  should be energetically more favorable.

We investigated methanol-clathrates with methanol-occupancies less than 100 % to prove that the anomaly of  $c$  is a true property of the EDD interaction. By lowering the fractional occupancy of the cavities, the interaction between the pseudospins is diluted and the transition into a dielectrically ordered state shifts to lower temperatures. Samples with a larger percentage  $x$  of filled cavities ( $x > x_c \approx 0.76$ ) show conventional ordering via a first order phase transition into an antiferroelectrically ordered structure, whereas the others ( $x < x_c$ ) freeze into dipolar glasses<sup>1,2,3,4</sup>. The temperature dependence of the 1D lattice parameter  $c$  for several filling degrees down to 50 % is shown in Figure 8. Comparing the structural data with the static dielectric constant for different degrees of occupation, see e.g. Fig. 13 from Ref. [2], there is an analogous behavior: The anomaly is most pronounced for the completely filled methanol-clathrate. When reducing the filling, the anomaly shifts to lower temperatures and broadens.

## Conclusion

The methanol clathrate can serve as a model system for dielectric ordering and fluctuations and is conceptually close to magnetic spin systems. Because of the lattice symmetry and the peculiar property of the EDD interac-

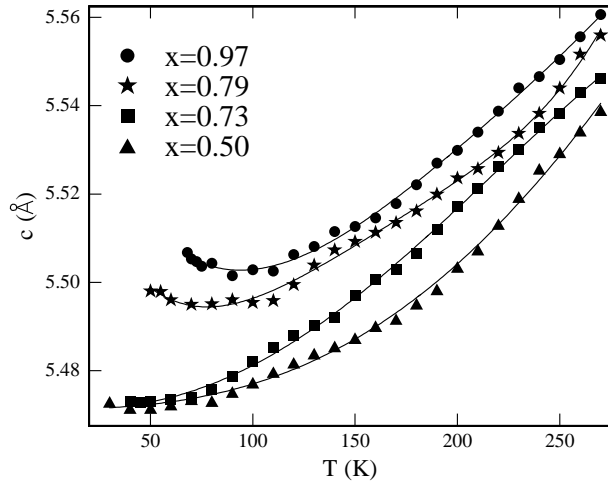


FIG. 8: Hexagonal lattice parameter  $c$  for the concentrations  $x = 0.97$ ,  $x = 0.79$ ,  $x = 0.73$  and  $x = 0.50$ . The curves are shifted vertically, for clarity. At 270 K, the lattice parameters for all concentrations coincide.

tion, the latter clathrate has quasi 1D dielectric properties. From analysis of the superlattice reflections in the dielectrically ordered phase, we can confirm the theoretically predicted 4:2 structure. The latter ground state can be calculated from Monte Carlo simulations and first principles, considering the EDD interactions between the

guest molecules, only. We observe 1D and 3D critical scattering in the paraelectric regime in neutron and X-ray diffraction experiments. The temperature dependence of the correlation lengths  $\xi_c$  and  $\xi_a$  is well described by the corresponding quasi-1D Ising theory and agrees perfectly with results from dielectric investigations, thereby confirming the microscopic picture of low dimensional ordering and fluctuations of the methanol pseudospins in the hydroquinone cage work. The EDD interaction on a deformable lattice should be unstable against a dimerization of the dipoles in the 1D chains. At the dielectric ordering temperature  $T_c$  we find superlattice reflections that indicate a doubling of the unit cell in the 1D direction, i.e. a static dimerization of the dipole chains. We find no sign of diffuse scattering in half-integer layers of  $l$  due to fluctuations of the dimerization. Below  $T = 170$  K an anomaly in the temperature dependence of the 1D lattice parameter  $c$  occurs. The large amplitude of the 1D fluctuations in the paraelectric regime leads to a coupling of the susceptibility to local strains and a piezoelectric effect in the otherwise centrosymmetric space group  $R\bar{3}$ . This effect is likely to be observed in low dimensional interacting systems because fluctuations are strongly enhanced and long ranged.

Acknowledgments

We thank B. Grenier and F. Bourdarot for support at the D23 diffractometer.

Present address: Institut Laue-Langevin, 6 rue Jules Horowitz, BP 156, 38042 Grenoble Cedex 9, France; Electronic address: rheinstadter@ill.fr

- <sup>1</sup> H. Woll, M. Enderle, A. Kloppepiper, M. Rheinstadter, K. Kiefer, K. Ruchten, and K. Knorr, *Europhys. Lett.* 51, 407 (2000).
- <sup>2</sup> H. Woll, M. Rheinstadter, F. Kuchten, K. Kiefer, M. Enderle, A. Kloppepiper, J. Albers, and K. Knorr, *Phys. Rev. B* 63, 224202 (2001).
- <sup>3</sup> A. Kityk, M. Rheinstadter, K. Knorr, and H. Rieger, *Phys. Rev. B* 65, 144415 (2002).
- <sup>4</sup> M. Rheinstadter, A. Kityk, H. Rieger, and K. Knorr, *Eur. Phys. J. E* 12, S47 (2003).
- <sup>5</sup> M. C. Rheinstadter, H. Rieger, and K. Knorr, *Phys. Rev. B* 69, 144427 (2004).
- <sup>6</sup> D. Burkhard and D. Dennison, *Phys. Rev.* 84, 408 (1951).

- <sup>7</sup> D. Scalapino, Y. Imry, and P. Pincus, *Phys. Rev. B* 11, 2042 (1975).
- <sup>8</sup> D. Palin and H. Powell, *J. Chem. Soc.* p. 815 (1948).
- <sup>9</sup> P. Sixou and P. Dansas, *Ber. Bunsen-Ges. Phys. Chem.* 80, 364 (1976).
- <sup>10</sup> M. Rheinstadter, A. Kityk, A. Kloppepiper, and K. Knorr, *Phys. Rev. B* 66, 064105 (2002).
- <sup>11</sup> M. Hase, I. Terasaki, and K. Uchinokura, *Phys. Rev. Lett.* 70, 3651 (1993).
- <sup>12</sup> J. Nye, *Physical properties of crystals* (Oxford University Press, Oxford, 1979).
- <sup>13</sup> To calculate the form factor we assumed a tilt of the elementary dipole of 22 degs to the hexagonal  $c$ -axis, as determined from the dielectric experiments in Refs. [1,2].