

Scaling of Entropic Shear Rigidity

Xiangjun Xing, Swagatam Mukhopadhyay, Paul M. Goldbart
 Department of Physics, University of Illinois at Urbana-Champaign,
 1110 West Green Street, Urbana, Illinois 61801-3080, U.S.A.
 (Dated: October 13, 2004)

The scaling of shear modulus near the gelation/vulcanization transition is explored heuristically and analytically. It is found that in a dense melt the effective chains of the infinite cluster have sizes that scale sub-linearly with their contour length. Consequently, each chain contributes $k_B T$ to the rigidity, which leads to a shear modulus exponent d . In contrast, in phantom elastic networks the scaling is linear in the contour length, yielding an exponent identical to that of the random resistor network conductivity, as predicted by de Gennes. For non-dense systems, the exponent should cross over to d when the percolation correlation length is much larger than the density-fluctuation length.

PACS numbers: 62.20.Dc, 61.41.+e, 64.60.Ak, 64.60.Fr, 64.70.Dv

Introduction | Gelation and vulcanization are continuous phase transitions from liquids to random solids, caused by the introduction of chemical (i.e. permanent) crosslinks; see, e.g., Ref. [1]. It is by now well established that the geometrical aspects of these transitions are correctly described by percolation theory [1, 2, 3]. Qualitatively speaking, both transitions | gelation/vulcanization and percolation | are controlled by the emergence and structure of an infinite cluster at the critical point.

The elastic and thermodynamic properties of gels near the critical point are not as well established. Of these, the most controversial is the scaling behavior of the static shear modulus, which is defined in the following way. Consider a spatially homogeneous, volume-preserving shear deformation [4], with $\det = 1$. Under such a deformation, the increase in the free energy of a gel is, to leading order, given by [5]

$$F = V (T \text{Tr} g - d); \quad g = T^{-1}; \quad (1)$$

where g is the metric tensor and d is the spatial dimensionality. The shear modulus is expected, on general grounds, to obey a scaling law near the critical point,

$$G = G_0 (r)^{-f}; \quad (2)$$

where the control parameter r measures (minus the) deviation of the cross-link density from criticality (i.e. $r < 0$ in the solid phase), and θ is the unit step function.

Values reported for the exponent f , either from experiments or computer simulations, are rather scattered, and seem to suggest four different universality classes [6]. For systems with entropic elasticity, which is the focus of this Letter, values of f usually fall into one of two classes. Firstly, most numerical simulations [7] involving phantom networks, as well as many gelation experiments, suggest that f has the same value as the conductivity exponent t (1.9 in three dimensions) of random resistor networks (RRN), supporting a conjecture of de Gennes' [1]. A second class of experiments, as well as some simulations, support the scaling result $f = d$ (2.6 for three dimensions), where ξ_{perc} is the percolation

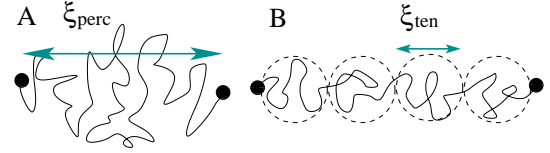


FIG. 1: The infinite cluster is a network of effective chains: (A) In a dense melt each effective chain is one single thermal blob with typical size ξ_{perc} , and contributes $k_B T$ to the shear rigidity. (B) In a phantom network each chain is sequence of "tension blobs" (dashed circles), each of size ξ_{ten} . Each tension blob contributes $k_B T$ to the shear rigidity.

correlation-length exponent, as proposed in Ref. [8]. The argument for the latter exponent is in the spirit of the classical theory of rubber elasticity (see, e.g., Ref. [5]), in which the elastic modulus acquires a contribution of $k_B T$ per effective chain. The purpose of this Letter is to use heuristic and analytical methods to outline a resolution of the long-standing apparent contradiction between the two plausible arguments, mentioned above, as well as the inconsistency across experimental and simulation data. **Heuristic reasoning** | Let us first consider gelation in a dense system with strong inter-particle repulsions, and let the system be near the critical point. Then the characteristic length-scale for density fluctuations ξ_{den} is much smaller than the percolation correlation length ξ_{perc} (beyond which the infinite cluster is effectively homogeneous). Now let us invoke the "nodes-links-blobs" picture [9, 10], in which the incipient infinite cluster is a network of effective chains, connected to one another at effective vertices, called nodes. For our purposes, it is adequate to treat the effective chains as quasi-one-dimensional objects having some average thickness. The end-to-end displacement of these effective chains has a certain distribution with a characteristic length-scale, which is presumably identical to the percolation correlation length ξ_{perc} . In the absence of external stress, we expect these chains to exhibit a type of random walk [11], owing to thermal fluctuations. Therefore, the end-to-end displacements should scale sub-linearly with the contour

length. In the language of polymer physics, every effective chain constitutes a single "thermal blob"; see Fig. 1 and Ref. [13]. Under a small shear deformation, each chain will be slightly stretched or compressed, thus contributing $k_B T$ to the shear modulus. As there are roughly ξ_{perc}^d effective chains per unit volume, the shear modulus should scale as $k_B T \xi_{\text{perc}}^d |\dot{\gamma}|$, near the critical point. We note that the shear modulus has dimensions of energy per unit volume; hence, this scaling is also mandated by dimensional analysis, provided that ξ_{perc} is the only important length-scale near the transition.

Let us now consider typical numerical simulations of phantom networks, i.e., systems without inter-particle repulsions. The crucial observation, made above, that the equilibrium conformations of the effective chains are un-stretched random walks (i.e. "thermal blobs") with typical size ξ_{perc} now breaks down, for the following reason. In such simulations, the sol fraction (i.e. the finite clusters) are usually removed completely, as they do not interact with the gel fraction. The resulting gel is very sparse, and would tend to collapse so as to maximize the entropy. To prevent this, the system size is usually fixed during shear deformation. Consequently, long effective chains are strongly stretched. The conformation of the infinite cluster is such that the net entropic force at each node vanishes, i.e., the cluster is statistically in mechanical equilibrium. Therefore, the mean tension S carried by each chain has the same order of magnitude. As shown Fig. 1B, S defines a length-scale, $\xi_{\text{ten}} = k_B T / S$, beyond which chain conformations are dominated by tension, and are thus effectively straight. By contrast, within ξ_{ten} thermal fluctuations dominate, so that chain conformations are random walks. ξ_{ten} is, by definition, the typical size of a "tension blob" [12] for a polymer under tension S . Near the critical point, ξ_{ten} is much smaller than ξ_{perc} , which diverges as $|\dot{\gamma}|$. It follows that the number of tension blobs on each chain, as well as the chain's end-to-end displacement, scales linearly with its contour length in a phantom network. Under a shear deformation, every tension blob contributes $k_B T$ to the overall shear rigidity [12]. Therefore, a typical chain, comprising many tension blobs, contributes a term to the total shear rigidity that is proportional to its contour length. This should be contrasted with the case of melt, in which every chain contributes $k_B T$, independent of its contour length. In a coarse-grained description, we may replace every tension blob by a mechanical spring of natural length zero and force constant $k_B T = \frac{2}{\xi_{\text{ten}}}$, without changing the elasticity. The resulting model is a randomly diluted network of mechanical springs of zero natural length at zero temperature, which can be mapped into the randomly diluted resistance network model [14]. In this mapping, the coordinates of nodes are mapped into voltages, and the shear modulus into the conductivity. Therefore the shear modulus of a randomly diluted entropic phantom network is equivalent

to the conductivity of a random resistor network, as de Gennes conjectured and many numerical simulations have supported.

Analytical reasoning | We have extended the Landau theory for the elasticity of vulcanized matter [2] to the case of tunable repulsive interactions [15]. The relevant order parameter is the $(1+n)$ -fold replicated particle density distribution, less its expectation value in the liquid phase:

$$\langle \hat{\rho} \rangle = \frac{1}{N} \int \prod_{j=1}^N \delta(\mathbf{x}^0 - \mathbf{x}^j) \prod_{j=1}^N \delta(\mathbf{x}^j - \mathbf{x}^0) d\mathbf{x}^j = \frac{1}{N} \int \prod_{j=1}^N \delta(\mathbf{x}^0 - \mathbf{x}^j) d\mathbf{x}^j \quad (3)$$

Here, $\hat{\rho}$ is short-hand for $(1+n)$ -dimensional vectors $(\mathbf{x}^0; \mathbf{x}^1; \dots; \mathbf{x}^n)$; \mathbf{c}_j labels the position of the j^{th} particle in the system, $\langle \cdot \rangle$ denotes a thermal average over the measurement ensemble [16], and $[\cdot]$ denotes the average over the cross-linking realization (i.e. the quenched disorder) as well as the thermal fluctuations of the preparation ensemble. $\langle \hat{\rho} \rangle$ can be interpreted as giving the joint probability density function (p.d.f.) that a particle is located at \mathbf{x}^0 in the preparation state and is later found at positions $\mathbf{x}^1; \dots; \mathbf{x}^n$ in n independent measurements in the measurement state. $\langle \hat{\rho} \rangle$ encodes a great deal of information about random solid state. In particular, the particle density fluctuations of the preparation and measurement states are respectively given by

$$\delta \rho(\mathbf{x}) = \frac{1}{N} \sum_{j=1}^N (\mathbf{x} - \mathbf{c}_j) \quad N=V; \quad (4a)$$

$$\delta \rho(\mathbf{x}) = \frac{1}{N} \sum_{j=1}^N (\mathbf{x} - \mathbf{c}_j) \quad N=V; \quad (4b)$$

$$\delta \rho(\mathbf{x}) = \frac{1}{N} \sum_{j=1}^N \int \delta(\mathbf{x} - \mathbf{c}_j) d\mathbf{c}_j \quad (4c)$$

In the liquid phase, all particles are delocalized, i.e., $\langle \delta \rho(\mathbf{x} - \mathbf{c}_j) \rangle = 0$ for all j . This ensures that the order parameter $\langle \hat{\rho} \rangle$ vanishes identically. In the gel phase, however, a certain fraction of particles belong to an infinite cluster and are localized. If such a particle were at position \mathbf{x}^0 in the preparation state, it would fluctuate around the same point in the measurement state (modulo a global translation and rotation that are common to the system as a whole). This is captured by a nonzero expectation value of the joint p.d.f. (3) in the gel phase.

The Landau free energy functional comprises one part concerning localization, and another describing density fluctuations. The localization part accounts for the effects of cross-links, and is given by

$$H_x = \int d\mathbf{x} \left[\frac{r}{2} \left(\frac{\partial \rho}{\partial \mathbf{x}} \right)^2 + \frac{K_0}{2} (\rho^0)^2 + \frac{K}{2} \sum_{n=1}^n (\rho^n)^2 \right] \quad (5)$$

where ρ^0 and ρ^n are, respectively, derivatives with respect to \mathbf{x}^0 and \mathbf{x}^n . The parameter r controls the cross-link density and drives the transition to the random solid state, whereas K_0 and K respectively measure the

stretchability of polymer chains in the preparation and measurement states (the larger the K 's, the softer the chains). The free energy cost for density fluctuations depends only on one-replica quantities, $\langle x^0 \rangle$, and is

$$H_D = \frac{B_0}{2} \int dx^0 \int d\mathbf{x}^0 (\mathbf{x}^0)^2 + \frac{B}{2} \int d\mathbf{x} (\mathbf{x})^2; \quad (6)$$

where the non-negative parameters B_0 and B are, respectively, the compressibility of the system in the preparation and measurement states. A large value of B_0 would ensure that the system is cross-linked in a state with almost uniform density profile, i.e., vanishingly small fluctuations in ρ^0 . On the other hand, B characterizes the repulsive interactions between particles in the measurement state. In a typical vulcanization experiment on a concentrated solution or melt, both B_0 and B are large, so that the density remains essentially uniform across the transition. It is important, however, to realize that B_0 and B are separately adjustable (as are K_0 and K), e.g., via tuning the solvent quality before and after crosslinking. For gelation, the network formation process commences only lasts for an extended period. As a result, B may differ from B_0 , even by a large factor (e.g. due to correlations built up during the course of the chemical reaction), even if all external physical conditions remain unchanged.

In strong contrast, in typical numerical simulations of phantom systems, all polymers (or particles) are ascribed to lattice sites, and then cross-links are randomly introduced, connecting some neighboring particles. After removing the solvent, the system is allowed to relax at nonzero temperature, with intra-cluster repulsion completely ignored. This corresponds to a large positive value for B_0 but a vanishing value of B . As we shall soon see, it is this qualitative difference between B_0 and B that is responsible for conductivity-like scaling of the shear modulus in phantom networks.

To study the elastic properties, we consider deforming the system after cross-links have been introduced. As shown in Fig. 2, this amounts to making an affine change of the boundaries for measurement replicas (1 through n), leaving the preparation replica intact. It is convenient to then make the linear coordinate transformation

$$\mathbf{c} \rightarrow \mathbf{c}; \quad \mathbf{x} \rightarrow \mathbf{x}; \quad \text{for } 1 \leq n; \quad (7)$$

which restores the original boundary conditions for the n measurement replicas. Under this transformation, H_D of Eq. (6), is unchanged, provided we redefine B appropriately. As for H_X , Eq. (5), we find that all terms are invariant under the transformation (in the $n \rightarrow 0$ limit), except for the term with coefficient K , which becomes

$$\frac{K}{2} \int d\mathbf{x} (\mathbf{x})^2 \rightarrow \frac{K}{2} \int d\mathbf{x}^a g_{ab}^{-1} \mathbf{x}^a \mathbf{x}^b; \quad (8)$$

where g is the metric tensor defined in Eq. (1).

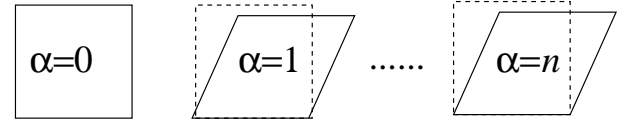


FIG. 2: Shear deformation (full vs. dotted lines) is applied to measurement but not preparation replicas. After the coordinate transformation, the original boundaries are recovered at the cost of introducing a nontrivial metric tensor.

The effects of fluctuations, both thermal and quenched, are studied by averaging over all order-parameter configurations. Then the disordered-averaged physical free energy $[F]$ is related to the $(1+n)$ -fold replicated partition function Z_{1+n} by

$$[F] = \lim_{n \rightarrow 0} \frac{1}{n} \ln Z_{1+n} = \lim_{n \rightarrow 0} \frac{1}{n} \ln \int D\mathbf{x} e^{-H_{1+n}};$$

where $H_{1+n} = H_D + H_X$ is the full effective [18] Hamiltonian; see Ref. [19].

A renormalization-group (RG) analysis of the full model, described by H_{1+n} , will be presented in a future publication [15]. Here, we shall only present results for two limiting cases: (a) $B_0 = B = +1$, i.e., vulcanization in an incompressible polymer melt; and (b) $B_0 = +1$ but $B = 0$, i.e., phantom networks. We apply a momentum-shell RG transformation, thus integrating out short length-scale fluctuations recursively, whilst rescaling the order-parameter field and spatial coordinates such that K_0 and K remain unity. The renormalizations of r and v turn out to be independent of B and g , i.e., the parameters describing the measurement ensemble. To one-loop order we find:

$$\frac{dr}{dl} = r^2 + \frac{1}{6}v^2 + \frac{v^2}{2}; \quad \frac{dv}{dl} = \frac{1}{2}v - \frac{7}{4}v^3; \quad (9)$$

where for $d < 6$ there is a nontrivial fixed point at $(r^*, v^*) = (14/27, 2/7)$. Correspondingly, the critical exponents $(\nu; \gamma)$ are given by $(\frac{1}{21}; \frac{1}{2} + \frac{5}{84})$, which agree with results from the ϵ -expansion for the percolation transition [20].

The flow of g determines the elastic properties. Expressing g as gg^* , where g^* has unit determinant [so that $g^d = \det(g)$] we find that, regardless of the value of B , g^* does not flow. Therefore, renormalization of the metric g is completely controlled by its determinant. For $B = B_0 = +1$, we find the flow equation

$$dg/dl = (2-d)v^2 - \frac{1}{3}g^3/g; \quad (10)$$

For $d < 6$, $v^2 \rightarrow v^2 = 2/7 > 0$, hence g flows to unity. Qualitatively, this implies a symmetry between the preparation and measurement ensembles. It also suggests that the correlation length ξ_{perc} is the only relevant length-scale, in agreement with the preceding heuristic argument, that, in a dense melt, each effective chain

constitutes a single thermal blob of typical size ξ_{perc} . Near the fixed point, the singular part of the free energy (i.e. the elastic free energy) has the scaling form

$$f_s = \xi^{-d} f_1(g) = \xi^{-d} f_1(g): \quad (11)$$

As the shear modulus is given by an appropriate derivative of f_s with respect to g [cf. Eq. (1)], we immediately see that it scales as ξ^{-d} .

For the second case, viz., $(B_0; B) = (1; 0)$ we find

$$dg/dl = (2/3)v^2 g^{-1/4} \quad g=21 \quad (12)$$

Now g , and also the metric tensor g , are relevant near the percolation fixed point, with a positive crossover exponent ν_g of $4/21$, echoing our heuristic argument that effective chains are strongly stretched in a phantom network. In general, the singular part of free energy should then have the scaling form

$$f_s = \xi^{-d} f_2(g) = \xi^{-d} f_2(g): \quad (13)$$

For a pure shear with $\det(g) = 1$, this f_s must agree with Eq. (1), up to a constant independent of g . Therefore the shear modulus exponent is given by $d_{\nu_g} = 3 \frac{5}{21}$, which, to the same order in ϵ , is identical to the conductivity exponent of a random resistor network [20].

This equivalence between critical exponents of phantom elastic networks and random resistor networks should in fact hold to all orders in ϵ . To see this analytically, we note that setting $(B_0; B) = (1; 0)$ in H_D is equivalent to setting $B_0 = B = 0$, together with the hard constraint $\phi(x) = 0$, which explicitly excludes configurations having nonzero density fluctuations in the preparation ensemble. The resulting model then becomes formally identical to the Harris-Lubensky formulation of the random resistor network problem [20], with the $d(1/0)$ coordinates associated with the measurement ensembles $(x^1; \dots; x^n)$ mapped onto the $D(1/0)$ replicated voltages $\#$, provided the stated limits are taken. Thus, the pair of systems are governed by identical RG equations and, hence, critical exponents.

Having established the two limiting cases, $B = 1$ and $B = 0$, it is natural to ask which one is the more stable. As B , like r , has naive dimension 2, it is always relevant near 6 dimensions. Therefore, if we keep B_0 large and tune B to be small, the shear modulus exponent should cross over from the conductivity one, ν , to the incompressible system one, ν_{ν_g} when ξ becomes smaller than B . This can be readily realized in a numerical simulation, if one were to retain the soft part of the system and turn on a small repulsion. In principle, this cross-over might also be observed in gelation experiments on non-dense solutions, provided ξ is sufficiently small.

Acknowledgments | We thank E. Fradkin and O. Stenull for helpful discussions. We acknowledge support from NSF DMR 02-05858 and DOE DEFG 02-91ER 45439.

- [1] P. G. de Gennes, *Scaling Concepts in Polymer Physics* (Cornell University Press, Ithaca, NY, 1979).
- [2] W. Peng, et al, Phys. Rev. B 57, 839 (1998); Phys. Rev. E 61, 3339 (2000).
- [3] H.-K. Janssen, O. Stenull, Phys. Rev. E 64, 026119 (2001); W. Peng, P. M. Goldbart, A. J. McKane, Phys. Rev. E 64, 031105 (2001).
- [4] A homogeneous deformation is described by a constant matrix, such that $x^0 = x$, where x and x^0 are the positions of mass points before and after deformation.
- [5] L. R. G. Treloar, *The Physics of Rubber Elasticity* (Clarendon Press, Oxford, 1975).
- [6] For a brief overview, see E. Delgado et al., Phys. Rev. E 65, 041803 (2002) and reference therein.
- [7] Recent numerical studies include: M. Plischke et al., Phys. Rev. Lett. 80, 4907 (1998), Phys. Rev. E 60, 3129 (1999); O. Farago and Y. Kantor, Phys. Rev. Lett. 85, 2533 (2000), Phys. Rev. E 62, 6094 (2000).
- [8] M. Daoud, A. Coniglio, J. Phys. A 14, L-30 (1981).
- [9] See, e.g., T. Nakayama et al., Rev. Mod. Phys. 66, 381 (1994), and references therein.
- [10] Our arguments are not dependent on the details of the "nodes-links-blobs" picture. In particular, the internal structure of the effective chains will not feature.
- [11] Owing to the complicated internal structure of these chains and repulsive interactions, this random walk is not expected to be ideal.
- [12] For a discussion of thermal blobs, tension blobs and force-extension curves for polymers, see, e.g., Ref. [13].
- [13] M. Rubinstein, R. H. Colby, *Polymer Physics* (Oxford University Press, 2003).
- [14] W. Tang, M. F. Thorpe, Phys. Rev. B 36, 3798 (1987).
- [15] S. Mukhopadhyay, X. Xing, P. M. Goldbart, manuscript in preparation
- [16] The properties of gels and rubbers depend on both the state in which properties are measured and the state in which the system is prepared. A statistical mechanical study of these materials necessarily involves two ensembles: a preparation one and a measurement one. The effect of cross-links is to couple these two ensembles. The quenched nature of the cross-links requires that the measurement ensemble be replicated n -times (with the $n \rightarrow 0$ limit ultimately taken). Early discussions of these issues can be found in Refs. [1] and [17]. A full account will be presented in a forthcoming manuscript [15].
- [17] R. T. Deam, S. F. Edwards, Phil. Trans. R. Soc. A, 280, 317 (1976).
- [18] Recall that H_{1+n} is an effective Hamiltonian obtained by integrating out the polymer degree of freedom of the original vulcanization model. As a result, the parameters in H_{1+n} depend on the temperatures T_0 (before crosslinking) and T (after crosslinking) in different ways. A temperature is not the driving factor of the transition, we do not show it explicitly in the formalism. The only essential T dependence comes from a factor of T in the shear modulus, which is easily handled.
- [19] P. M. Goldbart et al., Adv. Phys. 45, 393 (1996).
- [20] A. B. Harris, T. C. Lubensky, Phys. Rev. Lett. 35, 327 (1975); Phys. Rev. B 35, 6964 (1987).