## E lectronic structure properties and BCS superconductivity in -pyrochlore oxides: KO \$20 6

R. Saniz, J. E. Medvedeva, Lin-Hui Ye, T. Shishidou, and A. J. Freem an

Department of Physics and Astronomy, Northwestern University, Evanston, Illinois 60208-3112, USA

(D ated: M arch 22, 2022)

We report a rst-principles density-functional calculation of the electronic structure and properties of the recently discovered superconducting -pyrochlore oxide K O s<sub>2</sub>O <sub>6</sub>. We indicate the electronic structure near the Ferm i energy  $E_F$  is dominated by strongly hybridized O s-5d and O -2p states. A van H ove singularity very close to  $E_F$  leads to a relatively large density of states at  $E_F$ , and the Ferm i surface exhibits strong nesting along several directions. These features could provide the scattering processes leading to the observed anom alous tem perature dependence of the resistivity and to the rather large speci c heat m ass enhancement we obtain from the calculated density of states and the observed speci c heat coe cient. An estimate of T <sub>c</sub> within the framework of the BCS theory of superconductivity taking into account the possible elects of spin uctuations arising from nesting yields the experimental value.

PACS num bers: 71.20 Be, 74.25 Jb, 74.70 Dd

Transition m etal (TM) oxides are of intrinsic interest in physics because of the very rich phenom enology they exhibit due to electron correlations, ranging from m etalinsulator transitions to colossal m agnetoresistance and high critical temperature superconductivity. TM oxide com pounds with the pyrochlore structure have long been studied and have found m any applications thanks to their diverse electronic properties,<sup>1</sup> but it is not until recently that superconductivity was found in one such a material, nam ely C d<sub>2</sub>R e<sub>2</sub>O  $_7$ .<sup>2,3</sup> A lihough its superconducting critical temperature turned out to be low (T<sub>c</sub> ' 1 K), it was an in portant discovery because it opened research in this area to a new class of materials. Very recently, superconductivity was reported in KO s<sub>2</sub>O  $_6$ ,<sup>4,5</sup> a so-called -pyrochlore, with a T<sub>c</sub> of 9.6 K. M ore reports of su-

perconductivity in the same family of compounds have followed at a rapid pace, with superconductivity being observed in RbO  $s_2O_6$  ( $T_c = 6:3 \text{ K}$ )<sup>6,8</sup> and in C sO  $s_2O_6$ ( $T_c = 3:3 \text{ K}$ ),<sup>10</sup> adding to the interest in these materials.

The discovery of superconductivity in the pyrochlores raises, of course, the question of the underlying mechanism. W hile the mechanism in  $Cd_2Re_2O_7$ , an -pyrochlore,<sup>10</sup> can be understood within the weakcoupling Bardeen, Cooper, and Schrie er (BCS) theory of superconductivity,<sup>11</sup> Hiroi and co-workers have suggested<sup>5</sup> from the outset that  $KOs_2O_6$  is an unconventional superconductor, with the pairing mediated by spin uctuations.<sup>7</sup> On the other hand, Batlogg and coworkers suggested<sup>8</sup> that RbOs<sub>2</sub>O<sub>6</sub> could be a conventionalBCS-type superconductor, and recent pressure effects m easurem ents appear to bring further support to their conclusions.9 Given the close similarity between these two compounds, it seems unlikely that their superconductivity has a di erent origin. C learly, a careful study of the electronic structure of these m aterials m ay shed light on the superconductivity mechanism.

In this work, we focus on  $KO s_2O_6$  and carry out a self-consistent rst-principles density-functional calculation of its electronic structure, using a newly paral-

lelized in plan entation<sup>12</sup> of the full-potential linearized augmented plane wave (FLAPW) method.<sup>13</sup> Our calculations are m ade within the Perdew, Burke, and Emzerhof generalized gradient approximation  $(G G A)^{14}$  to the exchange-correlation potential and include the spin-orbit coupling (SOC) term in the Hamiltonian. Our results show that the electronic structure near the Ferm i energy (E  $_{\rm F}$  ) is dom inated by strongly hybridized 0 s-5d and 0 -2p states. There is a van Hove singularity (vHS) very close to  $E_{\rm F}$  , leading to a relatively large density of states (DOS) at  $E_F$  , and the Ferm isurface shows strong nesting along several directions. These features could provide the scattering processes leading to the reported<sup>4,5</sup> anom alous tem perature dependence of the resistivity above T<sub>c</sub>, and to the rather large specic heat mass enhancement we obtain from the calculated DOS and the measured low tem perature speci c heat coe cient.<sup>5</sup> W e estim ate the  $T_c$  within the BCS fram ework and are able to obtain the experimental value if we take into account the possible e ects of spin uctuations arising from nesting.

 $KOs_2O_6$  crystallizes in a cubic structure with space group F d3m, and has 18 atom sper unit cell: two K (8b), four 0 s (16c), and twelve 0 (48f).<sup>4</sup> The structure has an internal parameters, that xes the position of the oxygen atom s. The experim ental lattice constant recently given by Yonezawa and  $\infty$ -workers is a = 10:101 A, <sup>5</sup> but no value for the x param eter has yet been reported. W e have optim ized variationally both the lattice constant and the internalparam eter, obtaining a = 10:298 A, which di ers by 1.95% from the experimental value, and x = 0.316. The latter can be compared with the value of x = 0.315recently reported for the related superconducting pyroch lore R bO  $s_2 O_6$  by B ruhw iler and collaborators.<sup>8</sup> E ach Os atom is octahedrally coordinated by six O atoms, with 0-0s-0 angles of 88.66 and 91.34 (com pare with 88.85 and 91.15, respectively, for RbO s<sub>2</sub>O<sub>6</sub>, reported in Ref. 8). Unlike the perovskite superconductors, in the pyrochlore oxides the transition m etal-oxygen octahedra are not distorted. The Os-O distance we nd is 1.94 A

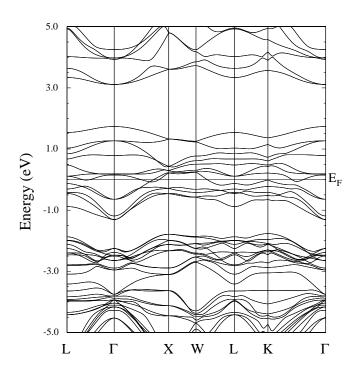


FIG.1: Band structure of KOs<sub>2</sub>O<sub>6</sub>, calculated within the GGA for exchange and correlation and taking into account spin-orbit coupling self-consistently. The twelve bands around  $E_F$  arise from 0 s 5d and 0 2p states. A saddle point near the center of the L line causes a vHS very close to  $E_F$ .

(com pare with, for example, the calculated  $^{15,16}$  Ru-O distances of 1.93 A and 2.061 A in Sr<sub>2</sub>RuO<sub>4</sub>). In KO s<sub>2</sub>O<sub>6</sub>, the pyrochlore lattice is formed by highly interconnected 0 s-O staggered chains, resulting in corner sharing tetrahedra, with the O s ions occupying the vertices. In Ref. 8, it is suggested that in the -pyrochlore oxides, the transition TM -O -TM angle plays a role in de ning the superconducting properties, <sup>8</sup> with smaller angles favoring higher critical temperatures. For KO s<sub>2</sub>O<sub>6</sub>, we nd an O s-O s angle of 139.16, which is indeed smaller than the reported angle of 139.4 for RbO s<sub>2</sub>O<sub>6</sub>.<sup>8</sup> There is currently not enough experimental information regarding C sO s<sub>2</sub>O<sub>6</sub> for com parison with this material.

The calculated energy bands along high symmetry directions in k-space, within 5 eV from  $E_F$ , are shown in Fig.1. There is a manifold of twelve states in the vicinity ofE<sub>F</sub>, with a bandwidth of 3 eV, separated by relatively large energy gaps above and below . Two bands cross the Ferm ienergy: the lower band cuts the X and W L lines and gives rise to a hole-like Ferm i surface sheet in the form of a tubular network; the upper band crosses  $E_F$ twice within the rst Brillouin zone (cf. the L, X, and K lines), giving rise to two Ferm i surface sheets. As will be illustrated below, this results in an electronlike closed shell centered at the point. Of importance is the existence of a vHS very close to  $E_F$  , caused by a saddle point between the two sheets at 0:015 eV below the Ferm i level, near the middle of the L line.

The character of the bands near  $E_{\,F}\,$  is further ana-

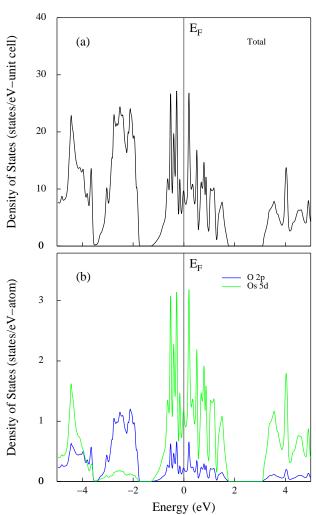


FIG.2: Density of states within the GGA and taking into account spin-orbit coupling self-consistently. (a) TotalDOS, showing a sharp peak very close to  $E_F$ . (b) ProjectedDOS of the O 2p and Os 5d states, on a per atom basis.

lyzed by exam ining the density of states (DOS). The totalDOS, shown in Fig. 2(a), exhibits a peak very close to  $\mathrm{E}_{\,\mathrm{F}}$  , due to the vHS m entioned above. W e point out that a precursor of the peak is already present, at a slightly lower energy, in a calculation without including spin-orbit coupling; the inclusion of the latter splits this peak, causes the saddle point, and pushes the higher peak  $cbserto E_{F}$ . In Fig.2 (b) we show the partial DOS of the 0 2p and 0s 5d states, which are by far the dom inant states in the energy range shown. As in previously studied oxide superconductors,  $^{15,16,17}$  the TM and O states are strongly hybridized near  $E_F$ . The orbital character of the states near E  $_{\rm F}$  is 0 sd (xy; yz; zx) and 0 p . This is clearly shown in Fig. 3, which presents a contour plot of the charge density in the (110) plane for states lying within 0.027 eV below  $E_F$ .<sup>18</sup>

An important nding is that the Ferm i surface shows strong nesting, in particular the shell-like sheets. Contourplots of the eigenenergies for the corresponding band along two di erent planes centered at the point are

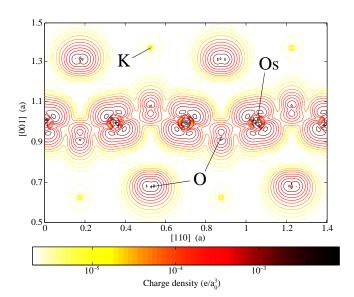


FIG.3: Contour plot of the charge density in the (110) plane for states lying within 0.027 eV below  $E_F$ . A staggered 0 s-0 chain is clearly seen. The other oxygen ions in the plot belong to chains traversing the (110) plane. A s expected, the charge around the potassium ions is extrem ely weak.

given in Fig. 4. Figure 4(a) shows the contour plot for k in the X X plane, with strong nesting occurring for k ' 0.44 =a and k ' 0.624 =a along the K directions. Similarly, Fig. 4(b) shows a contour plot for k in the X K plane, also showing strong nesting, in particular for k ' 0.644 =a along L directions.

Consider further som e of the properties deduced from the electronic structure in relation to experim ent. Firstly, the DOS at the Ferm i level is relatively high, N ( $E_{\rm F}$ ) = 9:8 states/eV -unit cell, yielding a Som m erfeld electronic =  $5:78 \text{ mJ/K}^2 \text{ mol}\Theta \text{ s. This}$ specic heat coe cient is much lower than the experimental value of 19 m J/K $^2$ m ol-O s found by H iroi and collaborators,<sup>5</sup> based on their estimation of the specic heat jump at  $T_{\rm c}$  and the BCS weak-coupling relation  $C = T_c = 1:43$ . Thus, we nd a very large specic heat mass enhancement  $_{exp} = _{band}$ 3:3, though it is still sm aller than that of, e.g., Sr<sub>2</sub>RuO<sub>4</sub>, found to be 3.8 or m ore.<sup>15,16</sup> The above m ass enhancem ent represents a rather high coupling constant, = 2:3:Given the relatively low  $T_c$  of KO  $s_2O_6$ , it appears that, besides electron-phonon, there is a very important electronic m any-body contribution to the speci c heat m ass enhancem ent. Interestingly, H iroi and co-w orkers noted in particular the unusual behavior of the m easured resistivity as a function of tem perature.4,5 D at a corresponding to single crystals are greatly desirable to advance further in this direction. Let us just point out here that, under appropriate conditions, deviations from conventional Ferm i liquid behavior in two-dimensional system s can be caused by both vHS's near the Ferm i energy<sup>19</sup> and by Ferm i surface nesting,<sup>20</sup> due to the increased phase space available for electron-electron scattering.<sup>21</sup>

From the measured  $T_{\rm c}$  = 9:6 K, and using ~=

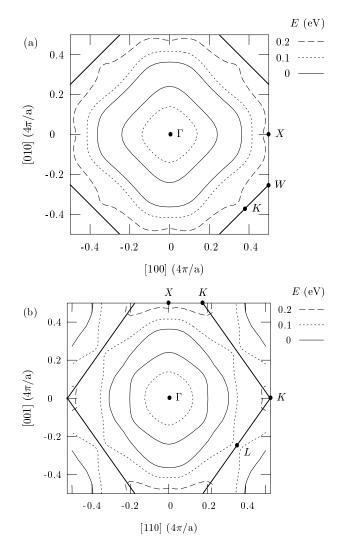


FIG. 4: Contour plots of the upper band crossing  $E_F$  (cf. Fig. 1) along two high symmetry planes. E = 0 corresponds to  $E_F$ . The thick lines indicate the rst Brillouin zone boundaries. (a) Plot for k in the X X plane. Extensive nesting occurs for k along K, with k' 0:4 and 0.62 4 =a. (b) Plot for k in the X K plane. Strong nesting occurs, e.g., for k along L, with k' 0:64 4 =a.

1:76 $k_B T_c$ , the superconducting gap is calculated to be

= 1:456 meV. A calculation of the average Ferm i velocity then allows us to readily estimate the BCS-P ippard coherence length  $_0$  = hhv<sub>F</sub> i= . We nd hv<sub>F</sub> i = 1:47  $10^7$  cm/s, which yields  $_0$  = 212 A. This is an order of magnitude larger than the reported G inzburg-Landau coherence length = 30 A, obtained from the estimated upper critical eld H  $_{c2}$ .<sup>5,22</sup> Thus, the so-called dirty limit would apply. Indeed, writing  $^1 = _0^1 + 1^1$ , with 1 the mean free path, yields an estimated value of l= 35 A. This relatively short value suggests again that strong scattering processes play an important role in the electronic properties of this material.

We estimate the McM illan-H op  $eld^{23,24}$  electronphonon coupling constant  $e_p$ , for which the constituept-weighted average can be written  $_{ep} = _{i}w_{i} = M_{i}h!^{2}i!^{2}$  Here, the spherically averaged Hop eld parameters, , were calculated in the crude rigid-mun-tin approximation, with <sup>26</sup>

$$= 2N (E_{\rm F})^{\rm X} (1+1)M_{1;1+1}^{2} \frac{f_{1}f_{1+1}}{(21+1)(21+3)}; \qquad (1)$$

where  $f_1 = N_1(E_F) = N(E_F)$  is a relative partial DOS and M <sub>l;l+1</sub> =  $_{1 l+1}$  [(D<sub>1</sub> l) (D<sub>l+1</sub> + l + 2) + (E<sub>F</sub> V)R<sup>2</sup>] is an electron-phonon matrix element. The quantities entering the latter are the logarithm ic derivatives (D  $_1$ ) and the partial wave amplitudes  $(_1)$ , both evaluated at  $E_F$  and at the mun-tin radius (R); V is the oneelectron potential at R. The average phonon frequency can be estimated by h!  $2i^{1=2} = 0.69$  <sub>D</sub>. There is currently no reported  $_{\rm D}$  for KOs<sub>2</sub>O<sub>6</sub>, but B ruhw iler and  $\infty$ -workers did such measurem ents for R b0 s<sub>2</sub>0<sub>6</sub>.<sup>8</sup> Under the assumption that the values of  $_{\rm D}$  fall in the same range for both m aterials, we take  $_{\rm D}$  = 240 K, and obtain  $_{ep} = 1:4$ . As expected, this value is well below the total obtained from the speci cheatmass enhancement discussed above.<sup>27</sup>

To estim ate  $T_c$ <sup>28</sup> we use the A llen and D ynesm odi cation of the M cM illan equation,<sup>23,29</sup> including an elective

Now at the Department of Quantum M atter, ADSM , H irroshim a University, H igashihiroshim a 739-8530, Japan.

- <sup>1</sup> M.A. Subram anian, G.Aravam udan, and G.V.S.Rao, Prog.Solid St.Chem.15, 55 (1983).
- <sup>2</sup> M. Hanawa, Y. Muraoka, T. Tayama, T. Sakakibara, J. Yamaura, and Z. Hiroi, Phys. Rev. Lett. 87 187001 (2001).
- <sup>3</sup> H.Sakai, K.Yoshimura, H.Ohno, H.Kato, S.Kambe, R. E.Walsted, T.D.Matsuda, Y.Haga, and Y.Onuki, J. Phys.: Condens.Matter 13, L785 (2001).
- <sup>4</sup> S.Yonezawa, Y.M uraoka, Y.M atsushita, and Z.H iroi, J. Phys.: Condens.M atter 16, L9 (2004).
- <sup>5</sup> Z. Hiroi, S. Yonezawa, and Y. Muraoka, cond-m at/0402006v1.
- <sup>6</sup> S.Yonezawa, Y.M uraoka, Y.M atsushita, and Z.H iroi, J. Phys. Soc. Jpn. 73, 819 (2004).
- <sup>7</sup> A. Koda, W. Higemoto, K. Ohishi, S. R. Saha, R. Kadono, S. Yonezawa, Y. Muraoka, and Z. Hiroi, cond-m at/0402400.
- <sup>8</sup> M.Bruhwiler, S.M.Kazakov, N.D.Zhigadb, J.Kaminksi, and B.Batlogg, cond-mat/0403526; S.M.Kazakov, N.D. Zhigadb, M.Bruhwiler, B.Batlogg, and J.Kaminksi, cond-mat/0403588.
- <sup>9</sup> R.Khasanov, D.G.Eshchenko, J.Karpinski, S.M.Kazakov, N.D.Zhigadlo, R.Brutsch, D.Gavillet, and H.Keller, cond-m at 0404542.
- <sup>10</sup> S.Yonezawa, Y M uraoka, Z.H iroi, cond-m at/0404220.
- <sup>11</sup> Z.H iroi and M.Hanawa, J.Phys.Chem.Solids 63, 1021 (2002).
- <sup>12</sup> T. Shishidou, L.H. Ye, M. W einert, and A. J. Freem an (unpublished).
- <sup>13</sup> E.W immer, H.K rakauer, M.W einert, and A.J.Freeman, Phys.Rev.B 24,864 (1981); M.W einert, E.W immer, and

electron-spin interaction coupling constant  $_{sp}$ ,<sup>30</sup> i.e.,

$$T_{c} = \frac{h!^{2} \dot{1}^{1=2}}{1\cdot 2} \exp \left( \frac{1\cdot 04 \left(1 + \frac{1}{ep} + \frac{1}{sp}\right)}{\frac{1}{ep} \left(1 + \frac{1}{sp}\right) \left(1 + \frac{1}{0} \cdot 62 \frac{1}{ep}\right)} \right)$$
(2)

The so-called Coulomb pseudopotential can be estimated from the DOS at  $E_F$ ,<sup>30</sup> and in our case is = 0.09. On the other hand, there is no simple expression for  $_{\rm sp}$ . If  $_{\rm sp} = 0$  we nd  $T_c = 18$  K. Strong spin uctuations,<sup>31</sup> with a coupling constant  $_{\rm sp} = 0.13$  would yield the experimental value  $T_c = 9.6$  K. As an estimate, from our DOS we have calculated the Pauli param agnetic susceptibility, nding  $_{\rm band} = 1.58 \, 10^{-4}$  cm  $^3$ /m ol. From Ref. 5, we estimate the experimental value at T = 0 to be  $_{\rm exp}$  ' 4 10 4 cm  $^3$ /m ol, which yields an enhancement ratio  $_{\rm exp} = _{\rm band} = 2.53$ . Thus, strong spin uctuations may indeed play an important role due to the signi cant nesting of the Ferm i surface.

W e are grateful to 0.K ontsevoi, M.W einert, T.Jarlborg, and J.B.K etterson for helpful discussions. This work was supported by the D epartm ent of Energy (under grant No. D E-FG 02-88ER 45372/A 021 and a computer time grant at the National Energy Research Scientic C om puting C enter).

A.J.Freem an, ibid. 26, 4571 (1982).

- <sup>14</sup> J. P. Perdew, K. Burke, and M. Emzerhof, Phys. Rev. Lett. 77, 3865 (1996).
- <sup>15</sup> T.Oguchi, Phys. Rev. B 51, 1385 (1995).
- <sup>16</sup> D.J.Singh, Phys. Rev. B 52, 1358 (1995).
- <sup>17</sup> D. J. Singh, P. B laha, K. Schwarz, and J. O. Sofo, Phys. Rev. B 65 155109 (2002).
- $^{18}$  T his energy corresponds to 313 K , which is of the order of a typical  $_{\rm D}$  in metallic pyrochlores; see Ref. 8.
- <sup>19</sup> D.M.Newns, C.C.Tsuei, R.P.Huebener, P.J.M. van Bentum, P.C.Pattnaik, and C.C.Chi, Phys.Rev.Lett. 73, 1695 (1994).
- <sup>20</sup> A .V irosztek and J.R uvalds, Phys. Rev. B 42, 4064 (1990).
- <sup>21</sup> M oreover, disorder and/or impurities can play a critical role in this respect, as shown by A.Rosch, Phys.Rev. Lett. 82, 4280 (1999).
- <sup>22</sup> W e point out that although the estim ated H <sub>c2</sub> for K O s<sub>2</sub>O <sub>6</sub> is high (38.3 T) and m ore than twice its C handrasekhar-C logston lim it H <sub>p</sub>, the values found are not without precedent am ong B C S-superconductors, being close to those of several ternary molybdenum chalcogenides; see M. D ecroux and . Fischer, in Superconductivity in Ternary C om pounds, edited by M. B. Maple and . Fischer (Springer-Verlag, Berlin, 1982). On the other hand, our results indicate that K O s<sub>2</sub>O <sub>6</sub> m ay be a strong-coupling superconductor, so that som e of the values reported in R ef. 5 m ay require revision; see D. R ainer and G. Bergm ann, J. Low Tem p. Phys. 14, 501 (1974).
- <sup>23</sup> W .L.M cM illan, Phys. Rev. 167, 331 (1968).
- <sup>24</sup> J.J.Hop eld, Phys.Rev. 186, 443 (1969).
- <sup>25</sup> H.G. Salunke, R.M ittal, G.P.D as, and S.L.Chaplot, J. Phys.: Condens. M atter 9, 10137 (1997).

- <sup>26</sup> H.L.Skriver and I.M ertig, Phys. Rev. B 32, 4431 (1985).
- $^{27}$  Since depends directly on the l-projected DOS at  $E_{\rm F}$  for the di erent atom s, the role of potassium in this regard is only indirect, mainly through its participation in the determ ination of the structural parameters of the compound.
- <sup>28</sup> A more rigorous estimation of and of  $T_c$  may require a more elaborate approach than the one adopted here, due to the peak in the DOS very close to  $E_F$ . See, e.g., E.

Cappellutiand L.Pietronero, Phys.Rev.B 53,932 (1996).

- <sup>29</sup> P.B.Allen and R.C.Dynes, Phys. Rev.B 12, 905 (1975).
- <sup>30</sup> K.Bennem ann and J.Garland, AIP Conf. Proc. 4, 103 (1972).
- <sup>31</sup> In transition m etals  $_{\rm sp}$  is generally around 0:05. H ow ever, for Sc one has  $_{\rm sp}$  = 0:15; see R ef. 30.