

Intermediate valence behavior in CeCo_9Si_4

M. El-Hagary^a H. Michor^a E. Bauer^a R. Grossinger^a P. Kersch^b D. Eckert^b
K. H. Müller^b P. Rogl^c G. G. Jester^d G. Hilscher^a

^aInstitut für Festkörperphysik, T.U. Wien, A-1040 Wien, Austria

^bLeibniz-Institut für Festkörper- und Werkstofforschung, IFW Dresden, D-01171 Dresden, Germany

^cInstitut für Physikalische Chemie, Universität Wien, A-1090 Wien, Austria

^dInstitut für Mineralogie und Kristallographie, Universität Wien, A-1090 Wien, Austria

Abstract

The novel ternary compound CeCo_9Si_4 has been studied by means of specific heat, magnetisation, and transport measurements. Single crystal X-ray Rietveld refinements reveal a fully ordered distribution of Ce, Co and Si atoms with the tetragonal space group $I4/m\bar{c}$ isostructural with other RCo_9Si_4 . The smaller lattice constants of CeCo_9Si_4 in comparison with the trend established by other RCo_9Si_4 is indicative for intermediate valence of cerium. While RCo_9Si_4 with $R = \text{Pr}, \dots, \text{Tb}$, and Y show ferromagnetism and LaCo_9Si_4 is nearly ferromagnetic, CeCo_9Si_4 remains paramagnetic even in external fields as large as 40 T, though its electronic specific heat coefficient ($\sim 190 \text{ mJ/molK}^2$) is of similar magnitude as that of ferromagnetic LaCo_9Si_4 and weakly ferromagnetic YCo_9Si_4 .

Key words:

CeCo_9Si_4 , Intermediate Valence, High Field Measurement

The ordered ternary rare-earth cobalt silicon phase with composition 1:9:4 attracted our attention mainly because of the extraordinary magnetic properties of LaCo_9Si_4 which is a strongly exchange enhanced Pauli paramagnet and exhibits an itinerant metamagnetic phase transition at about 3.5 T for H_{jjc} and 6 T for H_{||c}, which is the lowest value ever found for rare earth intermetallic compounds [1]. Related isostructural RCo_9Si_4 with $R = \text{Pr}, \text{Nd}, \text{Gd}, \text{Dy}$ and also Y are ferromagnetic (see Refs. [2,3]) with relatively low $T_c \sim 20-50 \text{ K}$. This report is on the exceptional behavior of CeCo_9Si_4 among the ferromagnetic (FM) or almost FM RCo_9Si_4 compounds.

Polycrystalline samples of CeCo_9Si_4 and related RCo_9Si_4 were synthesized by induction melting of

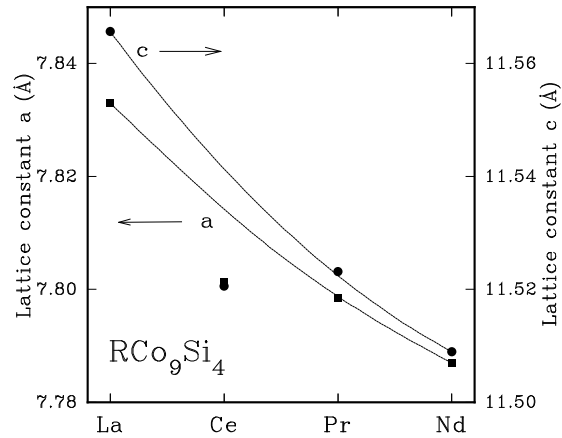


Fig. 1. Comparison of lattice parameters a (squares) and c (circles) of some RCo_9Si_4 compounds; dashed lines guides to the eye.

pure elements ($R: 3\text{N}, \text{Co}: 4.5\text{N}, \text{Si}: 6\text{N}$) under protective argon atmosphere and subsequent annealing at

Corresponding Author: Phone: (+431) 58801-13130 Fax: (+431) 58801-13199, Email: hilscher@ifp.tuwien.ac.at

¹ The work was supported by the Austrian Science Foundation Fonds under project P-15066-Phy; PK is supported by the BM BF project No. 03SC 5D RE. M. El-H. is on leave of Helwan University, Cairo, Egypt.

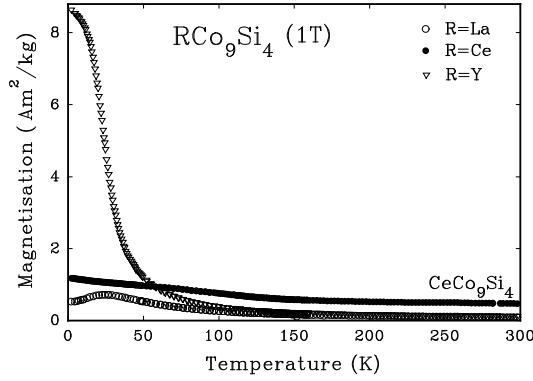


Fig. 2. Temperature dependent magnetisation $M(T)$ measured at 1T of CeCo_9Si_4 and for comparison LaCo_9Si_4 and YCo_9Si_4 .

1050 C for one week. The crystal structure was determined by means of single crystal X-ray diffraction ($R_F = 2.3\%$) revealing, analogous to CeNi_9Si_4 [4], a fully ordered distribution of Ce, Co and Si atoms with the LaFe_9Si_4 -type [5] (space group $I4/m$). The lattice parameters are $a = 7.801(1)$ Å and $c = 11.521(2)$ Å at room temperature.

The comparison of the lattice parameters of RCo_9Si_4 with $R = \text{La, Ce, Pr, Nd}$ shown in Fig. 1 reveals a significant negative deviation of the CeCo_9Si_4 data from the common trend. The smaller lattice constants of CeCo_9Si_4 indicates an intermediate valence state between the magnetic trivalent $4f^1$ and the non-magnetic tetravalent $4f^0$ state due to hybridization of 4f and conduction band states. Intermediate valence close to tetravalence is corroborated by the magnetisation data shown in Fig. 2 where the Curie-Weiss component expected for Ce^{3+} ions is not observed. The dc susceptibility measurement in fact reveals an almost temperature independent paramagnetic susceptibility for CeCo_9Si_4 , while LaCo_9Si_4 exhibits a more pronounced temperature dependence, typical for a spin fluctuation system, and all other RCo_9Si_4 are ferromagnetic below 20(50 K) (see the YCo_9Si_4 data shown in Fig. 2 as one example). The small offset of the room temperature magnetic moment of CeCo_9Si_4 as compared with LaCo_9Si_4 and YCo_9Si_4 in Fig. 2 is due to a contribution from traces of unreacted free Co which is also visible in the $M(H)$ data (see Fig. 3). The Pauli-susceptibility χ_0 estimated from $M = H$ at 40 T is about $5 \cdot 10^{-7} \text{ m}^3/\text{kg}$, slightly smaller than $8.2 \cdot 10^{-7} \text{ m}^3/\text{kg}$ given in Ref. [1] for LaCo_9Si_4 .

Motivated by the metamagnetism observed for LaCo_9Si_4 high-field magnetisation $M(H)$ measurements have been carried out up to 40 T in pulsed fields (see Ref. [6] for details of the setup) on CeCo_9Si_4 and LaCo_9Si_4 for comparison. Apart from a small hysteresis at low fields due to the above mentioned Co impurities, CeCo_9Si_4 shows a rather perfectly linear

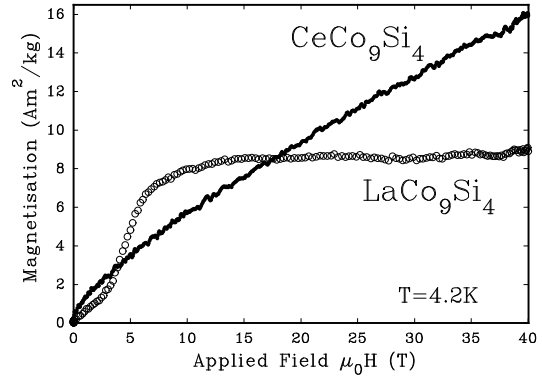


Fig. 3. High-field magnetisation measurements $M(H)$ on CeCo_9Si_4 and LaCo_9Si_4 performed at 4.2 K.

paramagnetic field dependence reaching 2 B/f.u. at $B_{\text{max}} = 40 \text{ T}$, whereas the magnetic moment of the field induced FM state of LaCo_9Si_4 saturates already above about 8 T at approximately 1.1 B/f.u.

The obviously more stable paramagnetic state of CeCo_9Si_4 with respect to the appearance of metamagnetism is most likely due to d-band filling caused by hybridized 4f states of cerium being close to tetravalence. Thus, one expects a reduction of spin-fluctuation mass enhancement which however may be partly compensated by contributions due to Ce valence fluctuations. The latter is supported by the specific heat data (not shown) where the linear electronic specific heat coefficient of CeCo_9Si_4 , the Sommerfeld value $\gamma' = 190 \text{ mJ/mole K}^2$, is slightly lower than that of nearly magnetic LaCo_9Si_4 , where $\gamma' = 200 \text{ mJ/mole K}^2$. The comparison of the temperature dependent resistivities $\rho(T)$, on the other hand (not shown), indicates for both a Fermi liquid behavior with $\rho(T) = \rho_0 + AT^2$, however, with a significantly lower A -coefficient for CeCo_9Si_4 as compared to LaCo_9Si_4 [7].

We conclude that CeCo_9Si_4 exhibits intermediate valence with Ce being close to a non-magnetic tetravalent state where 4f states hybridize with the conduction bands and thereby weaken the magnetic correlations among d-electrons as compared to other RCo_9Si_4 .

References

- [1] H. M. Ichor et al., Phys. Rev. B 69 (2004) 081404(R).
- [2] M. Q. Huang et al., J. Appl. Phys. 79 (1996) 5949.
- [3] H. M. Ichor et al., SCES04 (this conference).
- [4] H. M. Ichor et al., Phys. Rev. B 67 (2003) 224428.
- [5] W. H. Tang et al., J. Appl. Phys. 76 (1994) 4095.
- [6] D. Eckert et al., Physica B 294-295 (2001) 705.
- [7] M. El-Hagary et al., to be published.